

Acta Crystallographica Section E

Structure Reports

Online

ISSN 1600-5368

 Poly[(μ_2 -4,4'-bipyridine)(μ_2 -3,5-dicarboxybenzenesulfonato)silver(I)]

 Dan Lin,^{a*} Ping Lian^b and Yong-Rong Xie^b
^aDepartment of Adult Education, Xinyu College, Xinyu, Jiangxi 338000, People's Republic of China, and ^bCollege of Chemistry and Life Science, Gannan Normal University, Ganzhou, Jiangxi 341000, People's Republic of China

Correspondence e-mail: gohappyxu@yahoo.com.cn


Received 26 December 2009; accepted 2 February 2010

 Key indicators: single-crystal X-ray study; $T = 295$ K; mean $\sigma(\text{C}-\text{C}) = 0.011$ Å; R factor = 0.044; wR factor = 0.189; data-to-parameter ratio = 12.0.

In the title compound, $[\text{Ag}(\text{C}_8\text{H}_5\text{O}_7\text{S})(\text{C}_{10}\text{H}_8\text{N}_2)]_n$, the Ag atom is tetracoordinated by two 4,4'-bipyridine (4,4'-bipy) N atoms and two monodentate sulfonate O atoms of the 5-sulfoisophthalic acid (H_3sip) ligands. Adjacent Ag atoms are bonded through four sulfonate O atoms, forming a dinuclear unit with an $\text{Ag}\cdots\text{Ag}$ separation of 3.384 (5) Å; they are further linked together by the 4,4'-bipy ligands into a chain. Classical intermolecular $\text{O}-\text{H}\cdots\text{O}$ and non-classical intramolecular $\text{C}-\text{H}\cdots\text{O}$ hydrogen bonds are also observed in the two-dimensional supramolecular structure.

Related literature

For general background to the design and construction of coordination polymers using multifunctional ligands, see: James (2003); Kawando & Fujita (2007); Liu *et al.* (2007, 2008). For related structures, see: Liu & Xu (2005, 2006); Lu *et al.* (2007). For the synthesis of related compounds, see: Wang *et al.* (2008).

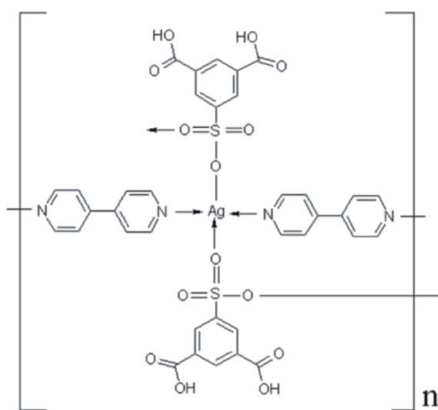

Experimental

Crystal data

$[\text{Ag}(\text{C}_8\text{H}_5\text{O}_7\text{S})(\text{C}_{10}\text{H}_8\text{N}_2)]$
 $M_r = 509.24$
 Triclinic, $P\bar{1}$
 $a = 7.9424$ (16) Å
 $b = 9.970$ (2) Å
 $c = 11.650$ (2) Å
 $\alpha = 83.38$ (3)°
 $\beta = 87.36$ (3)°

$\gamma = 78.67$ (3)°
 $V = 898.3$ (3) Å³
 $Z = 2$
 Mo $K\alpha$ radiation
 $\mu = 1.29$ mm⁻¹
 $T = 295$ K
 $0.52 \times 0.34 \times 0.13$ mm

Data collection

Siemens SMART CCD area-detector diffractometer
 Absorption correction: multi-scan (*SADABS*; Sheldrick, 1996)
 $T_{\min} = 0.615$, $T_{\max} = 0.831$

7152 measured reflections
 3156 independent reflections
 2350 reflections with $I > 2\sigma(I)$
 $R_{\text{int}} = 0.030$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.044$
 $wR(F^2) = 0.189$
 $S = 1.06$
 3156 reflections

263 parameters
 H-atom parameters constrained
 $\Delta\rho_{\max} = 0.97$ e Å⁻³
 $\Delta\rho_{\min} = -1.43$ e Å⁻³

Table 1

Hydrogen-bond geometry (Å, °).

$D-\text{H}\cdots A$	$D-\text{H}$	$\text{H}\cdots A$	$D\cdots A$	$D-\text{H}\cdots A$
$\text{O4}-\text{H4B}\cdots\text{O5}^{\text{i}}$	0.82	1.81	2.627 (8)	173
$\text{O6}-\text{H6B}\cdots\text{O2}^{\text{ii}}$	0.82	1.86	2.630 (8)	155
$\text{C1}-\text{H1A}\cdots\text{O1}^{\text{iii}}$	0.93	2.56	3.299 (10)	136
$\text{C6}-\text{H6A}\cdots\text{O1}^{\text{iv}}$	0.93	2.49	3.212 (9)	135
$\text{C12}-\text{H12A}\cdots\text{O3}$	0.93	2.59	2.926 (9)	102
$\text{C16}-\text{H16A}\cdots\text{O6}$	0.93	2.39	2.703 (10)	100
$\text{C16}-\text{H16A}\cdots\text{O6}^{\text{ii}}$	0.93	2.48	3.376 (9)	162

Symmetry codes: (i) $-x + 2, -y + 2, -z + 1$; (ii) $-x, -y + 3, -z + 1$; (iii) $-x, -y + 4, -z + 2$; (iv) $-x + 1, -y + 3, -z + 2$.

Data collection: *SMART* (Siemens, 1994); cell refinement: *SAINTE* (Siemens, 1994); data reduction: *SAINTE*; program(s) used to solve structure: *SHELXS97* (Sheldrick, 2008); program(s) used to refine structure: *SHELXL97* (Sheldrick, 2008); molecular graphics: *SHELXTL* (Sheldrick, 2008); software used to prepare material for publication: *SHELXTL*.

This work was supported by the Jiangxi Provincial Educational Foundation (No. 20060237), the Natural Science Foundation of Fujian Province (No. 2008 J0172) and the Key Laboratory of Jiangxi University for Functional Materials Chemistry

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: RK2187).

References

- James, S. L. (2003). *Chem. Soc. Rev.* **32**, 276–288.
 Kawando, M. & Fujita, M. (2007). *Coord. Chem. Rev.* **251**, 2592–2605.
 Liu, Q. Y., Wang, Y. L., Zhao, J. & Xu, L. (2008). *Eur. J. Inorg. Chem.* pp. 1157–1163.
 Liu, Q. Y. & Xu, L. (2005). *CrystEngComm*, **7**, 87–89.
 Liu, Q. Y. & Xu, L. (2006). *Eur. J. Inorg. Chem.* pp. 1620–1628.

Liu, Q. Y., Yuan, D. Q. & Xu, L. (2007). *Cryst. Growth Des.* **7**, 1832–1843.
Lu, J., Li, F., Yuan, D. Q. & Cao, R. (2007). *Polyhedron*, **26**, 2979–2986.
Sheldrick, G. M. (1996). *SADABS*. University of Göttingen, Germany.
Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.

Siemens (1994). *SMART* and *SAINT*. Siemens Analytical X-ray Instruments Inc., Madison, Wisconsin, USA.
Wang, Y. L., Liu, Q. Y. & Xu, L. (2008). *CrystEngComm*, **10**, 1667–1673.

supporting information

Acta Cryst. (2010). E66, m259–m260 [doi:10.1107/S160053681000406X]

Poly[(μ_2 -4,4'-bipyridine)(μ_2 -3,5-dicarboxybenzenesulfonato)silver(I)]**Dan Lin, Ping Lian and Yong-Rong Xie****S1. Comment**

The design and construction of coordination polymers from multifunctional ligands with metal ions is one of the most active areas of materials research. The increasing interest in these materials is stimulated by their intriguing structural diversities and potential applications such as catalysis, molecular magnets and adsorption (James, 2003; Kawando *et al.*, 2007; Liu *et al.*, 2007 and 2008).

As a multidentate *O*-donor organic aromatic polycarboxylate ligand, 5-sulfoisophthalic acid monosodium salt (NaH_2sip) has been used a good organic ligand 'spacer' to obtain many metal-organic complexes (Liu & Xu, 2005 and 2006; Lu *et al.*, 2007; Wang *et al.*, 2008). In this work, with the introduction of a rigid linear ligand, 4,4'-bipy, a novel 1-*D* organic-inorganic hybrid, $\text{Ag}(\text{H}_2\text{sip})(\text{bipy})(\text{I})$ (H_2sip = 5-sulfoisophthalic acid and bipy = 4,4'-bipyridine), has been obtained through hydrothermal self-assembly.

As depicted in Fig. 1, each asymmetric unit in compound **I** contains one Ag ion, one H_2sip and one 4,4'-bipy ligands. The Ag1 ion is tetra-coordinated by two 4,4'-bipy nitrogen atoms with Ag—N distances being 2.194 (39) and 2.184 (40) Å, and two monodentate sulfonate oxygen atom with Ag—O bond lengths of 2.653 (27) and 2.621 (9) Å. The adjacent two Ag atoms are bonded through two oxygen atoms (O1 and O3) from one sulfonate group and its symmetry-related atoms to form a dinuclear unit with the Ag1...Ag1 separation of 3.384 (5) Å. Such dinuclear units are further linked together by the linkage of 4,4'-bipy to construct 1-*D* chain-like, as shown in Fig. 2.

In compound **I**, each 4,4'-bipy ligand bridges two Ag1 ions to yield a 1-*D* chain along the *a* axis. While each H_2sip ligand acts as mono-armed ligand using its bidentate sulfonate group, with remaining two carboxylate group uncoordinated.

In the crystal structure of the compound **I**, classical inter-molecular O—H...O and non-classical intra-molecular C—H...O hydrogen bonds are observed, which link the H_2sip and 4,4'-bipy molecules into a two-dimensional H-bonded network and stabilize the crystal packing.

S2. Experimental

AgNO_3 (0.086 g, 0.50 mmol) and NaH_2sip (0.133 g, 0.50 mmol) were dissolved in 10 mL of distilled water by vigorous stirring. 4,4'-bipy (0.078 g, 0.50 mmol) was added to the mixture and stirred for 30 min. The resulting solution was sealed in a teflon-lined stainless autoclave and heated at 433 K for 4 days under autogenous pressure and then cooled to room temperature during 18 h. Yellow block crystals of **I** suitable for X-ray analysis were collected in 59% yield (based on silver).

S3. Refinement

All H atoms bound to carbon were refined using a riding model with C—H = 0.93 Å and $U_{\text{iso}}(\text{H}) = 1.2U_{\text{eq}}(\text{C})$. Two hydroxy H atoms were located in a difference map and refined with O—H distance restraints of 0.82 Å and with $U_{\text{iso}}(\text{H}) =$

$1.5U_{eq}(O)$.

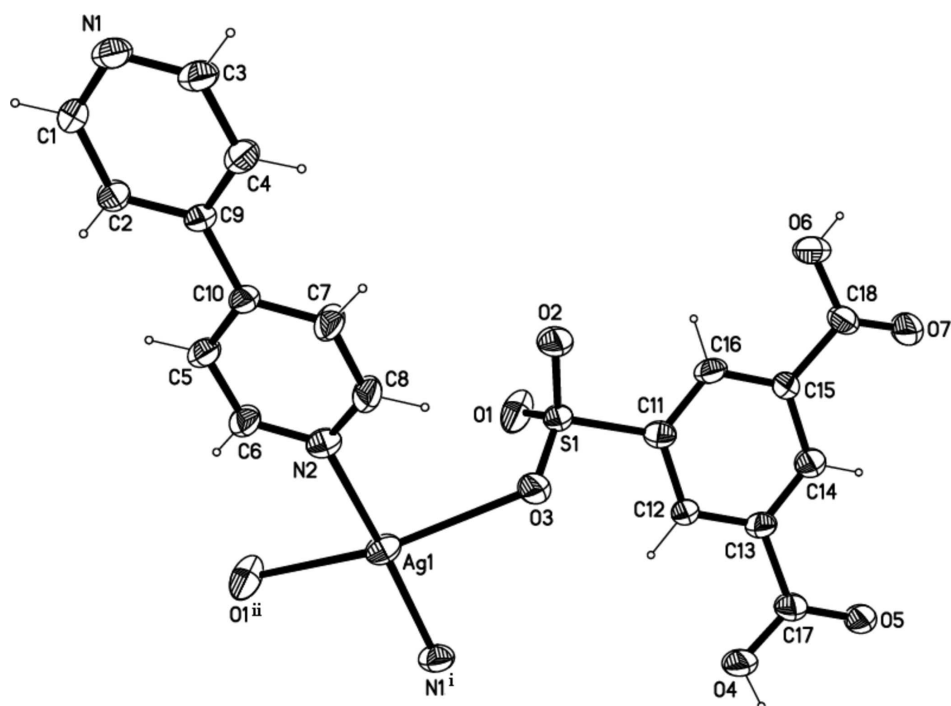


Figure 1

View of the structure of title compound, showing the atom-labelling scheme. Displacement ellipsoids are drawn at the 35% probability level. H atoms are shown as small spheres of arbitrary radius.

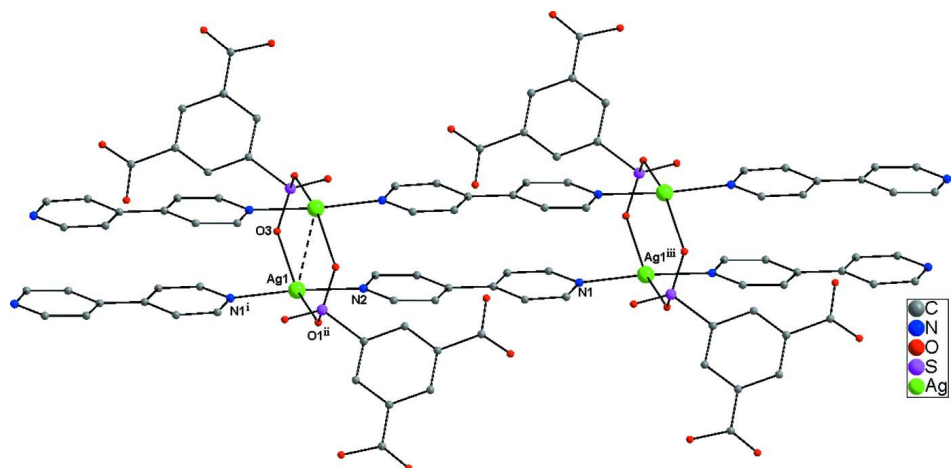


Figure 2

View of the 1-*D* chain in the crystal structure of title compound.

Poly[$(\mu_2$ -4,4'-bipyridine)(μ_2 -3,5-dicarboxybenzenesulfonato)silver(I)]

Crystal data

[Ag(C₈H₅O₇S)(C₁₀H₈N₂)]

$M_r = 509.24$

Triclinic, $P\bar{1}$

Hall symbol: $-P\ 1$

$a = 7.9424(16)\ \text{\AA}$

$b = 9.970(2)\ \text{\AA}$

$c = 11.650(2)\ \text{\AA}$

$\alpha = 83.38(3)^\circ$

$\beta = 87.36 (3)^\circ$
 $\gamma = 78.67 (3)^\circ$
 $V = 898.3 (3) \text{ \AA}^3$
 $Z = 2$
 $F(000) = 508$
 $D_x = 1.883 \text{ Mg m}^{-3}$
 Mo $K\alpha$ radiation, $\lambda = 0.71073 \text{ \AA}$

Cell parameters from 7152 reflections
 $\theta = 3.0\text{--}25.0^\circ$
 $\mu = 1.29 \text{ mm}^{-1}$
 $T = 295 \text{ K}$
 Block, yellow
 $0.52 \times 0.34 \times 0.13 \text{ mm}$

Data collection

Siemens SMART CCD area-detector
 diffractometer
 Radiation source: fine-focus sealed tube
 Graphite monochromator
 ω scans
 Absorption correction: multi-scan
 (SADABS; Sheldrick, 1996)
 $T_{\min} = 0.615$, $T_{\max} = 0.831$

7152 measured reflections
 3156 independent reflections
 2350 reflections with $I > 2\sigma(I)$
 $R_{\text{int}} = 0.030$
 $\theta_{\max} = 25.0^\circ$, $\theta_{\min} = 3.0^\circ$
 $h = -9 \rightarrow 9$
 $k = -11 \rightarrow 11$
 $l = -13 \rightarrow 13$

Refinement

Refinement on F^2
 Least-squares matrix: full
 $R[F^2 > 2\sigma(F^2)] = 0.044$
 $wR(F^2) = 0.189$
 $S = 1.06$
 3156 reflections
 263 parameters
 0 restraints
 Primary atom site location: structure-invariant
 direct methods
 Secondary atom site location: difference Fourier
 map

Hydrogen site location: inferred from
 neighbouring sites
 H-atom parameters constrained
 $w = 1/[\sigma^2(F_o^2) + (0.0986P)^2 + 4.7322P]$
 where $P = (F_o^2 + 2F_c^2)/3$
 $(\Delta/\sigma)_{\max} < 0.001$
 $\Delta\rho_{\max} = 0.97 \text{ e \AA}^{-3}$
 $\Delta\rho_{\min} = -1.43 \text{ e \AA}^{-3}$
 Extinction correction: SHELXS97 (Sheldrick,
 2008), $F_c^* = kF_c[1 + 0.001x F_c^2 \lambda^3 / \sin(2\theta)]^{-1/4}$
 Extinction coefficient: 0.009 (2)

Special details

Geometry. All s.u.'s (except the s.u. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell s.u.'s are taken into account individually in the estimation of s.u.'s in distances, angles and torsion angles; correlations between s.u.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell s.u.'s is used for estimating s.u.'s involving l.s. planes.

Refinement. Refinement of F^2 against ALL reflections. The weighted R -factor wR and goodness of fit S are based on F^2 , conventional R -factors R are based on F , with F set to zero for negative F^2 . The threshold expression of $F^2 > \sigma(F^2)$ is used only for calculating R -factors(gt) etc. and is not relevant to the choice of reflections for refinement. R -factors based on F^2 are statistically about twice as large as those based on F , and R -factors based on ALL data will be even larger.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	<i>x</i>	<i>y</i>	<i>z</i>	$U_{\text{iso}}^*/U_{\text{eq}}$
Ag1	0.65733 (8)	1.58243 (6)	0.94443 (6)	0.0538 (3)
S1	0.3909 (2)	1.50090 (19)	0.72770 (16)	0.0418 (5)
N1	-0.1357 (8)	2.4038 (6)	0.9399 (6)	0.0446 (15)
N2	0.4706 (8)	1.7746 (6)	0.9457 (6)	0.0467 (15)
C1	-0.0690 (10)	2.3342 (8)	1.0376 (7)	0.050 (2)
H1A	-0.1067	2.3686	1.1072	0.060*
C2	0.0521 (10)	2.2150 (7)	1.0411 (7)	0.0442 (18)
H2A	0.0957	2.1723	1.1116	0.053*

C3	-0.0763 (10)	2.3507 (8)	0.8420 (7)	0.0492 (19)
H3A	-0.1186	2.3969	0.7722	0.059*
C4	0.0425 (10)	2.2327 (8)	0.8396 (7)	0.0433 (17)
H4A	0.0794	2.2015	0.7688	0.052*
C5	0.2986 (9)	1.9505 (8)	1.0438 (7)	0.0432 (17)
H5A	0.2617	1.9832	1.1141	0.052*
C6	0.4124 (10)	1.8288 (7)	1.0428 (7)	0.0423 (17)
H6A	0.4513	1.7813	1.1131	0.051*
C7	0.2962 (11)	1.9698 (8)	0.8416 (7)	0.051 (2)
H7A	0.2599	2.0159	0.7704	0.061*
C8	0.4094 (12)	1.8445 (8)	0.8457 (7)	0.054 (2)
H8A	0.4445	1.8074	0.7769	0.065*
C9	0.1099 (9)	2.1579 (7)	0.9401 (6)	0.0366 (15)
C10	0.2368 (8)	2.0268 (7)	0.9412 (6)	0.0343 (15)
C11	0.4218 (9)	1.3809 (7)	0.6227 (6)	0.0406 (16)
C12	0.5797 (9)	1.2933 (7)	0.6153 (6)	0.0409 (17)
H12A	0.6681	1.2990	0.6630	0.049*
C13	0.6045 (9)	1.1976 (8)	0.5365 (6)	0.0415 (17)
C14	0.4729 (10)	1.1858 (8)	0.4675 (7)	0.0443 (17)
H14A	0.4894	1.1182	0.4171	0.053*
C15	0.3146 (9)	1.2759 (8)	0.4736 (6)	0.0420 (17)
C16	0.2894 (9)	1.3741 (8)	0.5512 (6)	0.0446 (18)
H16A	0.1847	1.4348	0.5553	0.054*
C17	0.7761 (10)	1.1076 (8)	0.5217 (7)	0.0471 (19)
C18	0.1776 (10)	1.2684 (8)	0.3903 (7)	0.0461 (18)
O1	0.3287 (9)	1.4280 (6)	0.8299 (5)	0.0643 (17)
O2	0.2644 (7)	1.6189 (5)	0.6839 (5)	0.0522 (14)
O3	0.5564 (7)	1.5339 (7)	0.7414 (6)	0.0626 (17)
O4	0.8908 (7)	1.1182 (7)	0.5940 (6)	0.071 (2)
H4B	0.9825	1.0691	0.5782	0.106*
O5	0.8050 (7)	1.0323 (6)	0.4427 (5)	0.0567 (15)
O6	0.0381 (8)	1.3629 (8)	0.4059 (7)	0.083 (2)
H6B	-0.0409	1.3479	0.3695	0.125*
O7	0.1923 (8)	1.1889 (7)	0.3209 (6)	0.0678 (18)

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Ag1	0.0480 (4)	0.0396 (4)	0.0663 (5)	0.0174 (3)	-0.0110 (3)	-0.0155 (3)
S1	0.0382 (10)	0.0395 (10)	0.0434 (10)	0.0099 (8)	-0.0101 (8)	-0.0122 (8)
N1	0.033 (3)	0.039 (3)	0.058 (4)	0.002 (3)	-0.004 (3)	-0.005 (3)
N2	0.041 (3)	0.040 (3)	0.054 (4)	0.008 (3)	-0.007 (3)	-0.009 (3)
C1	0.046 (4)	0.048 (4)	0.054 (5)	0.008 (4)	-0.010 (4)	-0.025 (4)
C2	0.049 (4)	0.028 (3)	0.053 (4)	0.007 (3)	-0.017 (4)	-0.009 (3)
C3	0.041 (4)	0.048 (4)	0.049 (5)	0.013 (4)	-0.006 (3)	-0.004 (4)
C4	0.041 (4)	0.043 (4)	0.042 (4)	0.004 (3)	0.002 (3)	-0.009 (3)
C5	0.038 (4)	0.044 (4)	0.042 (4)	0.009 (3)	-0.001 (3)	-0.009 (3)
C6	0.045 (4)	0.035 (4)	0.042 (4)	0.006 (3)	-0.004 (3)	-0.008 (3)

C7	0.067 (5)	0.038 (4)	0.037 (4)	0.019 (4)	-0.009 (4)	-0.011 (3)
C8	0.064 (5)	0.046 (4)	0.049 (5)	0.014 (4)	-0.012 (4)	-0.023 (4)
C9	0.031 (3)	0.032 (3)	0.044 (4)	0.005 (3)	-0.006 (3)	-0.009 (3)
C10	0.030 (3)	0.029 (3)	0.043 (4)	0.000 (3)	-0.004 (3)	-0.009 (3)
C11	0.037 (4)	0.038 (4)	0.042 (4)	0.003 (3)	-0.007 (3)	0.000 (3)
C12	0.034 (4)	0.044 (4)	0.042 (4)	0.008 (3)	-0.008 (3)	-0.015 (3)
C13	0.032 (4)	0.045 (4)	0.041 (4)	0.007 (3)	-0.003 (3)	-0.003 (3)
C14	0.043 (4)	0.040 (4)	0.048 (4)	0.003 (3)	-0.006 (3)	-0.010 (3)
C15	0.038 (4)	0.047 (4)	0.038 (4)	0.005 (3)	-0.009 (3)	-0.013 (3)
C16	0.032 (4)	0.051 (4)	0.043 (4)	0.011 (3)	0.000 (3)	-0.002 (3)
C17	0.040 (4)	0.045 (4)	0.051 (4)	0.008 (3)	-0.012 (3)	-0.008 (4)
C18	0.043 (4)	0.045 (4)	0.050 (4)	0.000 (3)	-0.017 (3)	-0.012 (4)
O1	0.090 (5)	0.049 (3)	0.046 (3)	0.005 (3)	0.011 (3)	-0.009 (3)
O2	0.049 (3)	0.042 (3)	0.061 (3)	0.011 (2)	-0.017 (3)	-0.010 (3)
O3	0.044 (3)	0.070 (4)	0.077 (4)	0.006 (3)	-0.019 (3)	-0.041 (3)
O4	0.039 (3)	0.083 (5)	0.087 (5)	0.021 (3)	-0.019 (3)	-0.047 (4)
O5	0.044 (3)	0.060 (3)	0.064 (4)	0.012 (3)	-0.014 (3)	-0.030 (3)
O6	0.048 (4)	0.101 (5)	0.099 (5)	0.027 (4)	-0.031 (4)	-0.056 (4)
O7	0.059 (4)	0.075 (4)	0.068 (4)	0.011 (3)	-0.023 (3)	-0.038 (4)

Geometric parameters (Å, °)

Ag1—N1 ⁱ	2.178 (6)	C6—H6A	0.9300
Ag1—N2	2.181 (6)	C7—C10	1.374 (10)
Ag1—O3	2.658 (7)	C7—C8	1.385 (10)
Ag1—O1 ⁱⁱ	2.626 (6)	C7—H7A	0.9300
S1—O3	1.436 (6)	C8—H8A	0.9300
S1—O1	1.441 (6)	C9—C10	1.485 (9)
S1—O2	1.449 (5)	C11—C12	1.386 (10)
S1—C11	1.784 (8)	C11—C16	1.387 (10)
N1—C1	1.336 (10)	C12—C13	1.379 (10)
N1—C3	1.340 (10)	C12—H12A	0.9300
N1—Ag1 ⁱⁱⁱ	2.178 (6)	C13—C14	1.379 (10)
N2—C6	1.334 (10)	C13—C17	1.492 (10)
N2—C8	1.346 (10)	C14—C15	1.399 (10)
C1—C2	1.372 (10)	C14—H14A	0.9300
C1—H1A	0.9300	C15—C16	1.389 (10)
C2—C9	1.385 (10)	C15—C18	1.508 (10)
C2—H2A	0.9300	C16—H16A	0.9300
C3—C4	1.358 (10)	C17—O5	1.239 (9)
C3—H3A	0.9300	C17—O4	1.295 (9)
C4—C9	1.383 (10)	C18—O7	1.183 (9)
C4—H4A	0.9300	C18—O6	1.326 (10)
C5—C6	1.364 (10)	O4—H4B	0.8200
C5—C10	1.396 (10)	O6—H6B	0.8200
C5—H5A	0.9300		
O3—Ag1—N2	92.9 (2)	C8—C7—H7A	119.5

O3—Ag1—N1 ⁱ	89.0 (2)	N2—C8—C7	122.4 (7)
O3—Ag1—O1 ⁱⁱ	158.2 (3)	N2—C8—H8A	118.8
N2—Ag1—N1 ⁱ	174.0 (2)	C7—C8—H8A	118.8
N2—Ag1—O1 ⁱⁱ	88.5 (2)	C4—C9—C2	115.1 (6)
O3—S1—O1	113.3 (4)	C4—C9—C10	123.1 (7)
O3—S1—O2	113.0 (4)	C2—C9—C10	121.8 (6)
O1—S1—O2	111.8 (4)	C7—C10—C5	115.5 (6)
O3—S1—C11	105.9 (3)	C7—C10—C9	122.3 (6)
O1—S1—C11	104.6 (4)	C5—C10—C9	122.1 (6)
O2—S1—C11	107.6 (3)	C12—C11—C16	120.8 (7)
C1—N1—C3	115.9 (6)	C12—C11—S1	118.6 (5)
C1—N1—Ag1 ⁱⁱⁱ	120.9 (5)	C16—C11—S1	120.6 (5)
C3—N1—Ag1 ⁱⁱⁱ	123.1 (5)	C13—C12—C11	119.4 (7)
C6—N2—C8	117.0 (6)	C13—C12—H12A	120.3
C6—N2—Ag1	122.8 (5)	C11—C12—H12A	120.3
C8—N2—Ag1	120.2 (5)	C14—C13—C12	120.8 (7)
N1—C1—C2	123.7 (7)	C14—C13—C17	118.6 (7)
N1—C1—H1A	118.2	C12—C13—C17	120.6 (7)
C2—C1—H1A	118.2	C13—C14—C15	119.7 (7)
C1—C2—C9	120.4 (7)	C13—C14—H14A	120.1
C1—C2—H2A	119.8	C15—C14—H14A	120.1
C9—C2—H2A	119.8	C16—C15—C14	119.8 (7)
N1—C3—C4	123.3 (7)	C16—C15—C18	121.5 (7)
N1—C3—H3A	118.4	C14—C15—C18	118.6 (7)
C4—C3—H3A	118.4	C11—C16—C15	119.4 (7)
C3—C4—C9	121.5 (7)	C11—C16—H16A	120.3
C3—C4—H4A	119.3	C15—C16—H16A	120.3
C9—C4—H4A	119.3	O5—C17—O4	123.6 (7)
C6—C5—C10	121.1 (7)	O5—C17—C13	121.1 (7)
C6—C5—H5A	119.5	O4—C17—C13	115.3 (7)
C10—C5—H5A	119.5	O7—C18—O6	124.6 (7)
N2—C6—C5	123.0 (7)	O7—C18—C15	124.7 (7)
N2—C6—H6A	118.5	O6—C18—C15	110.7 (6)
C5—C6—H6A	118.5	C17—O4—H4B	109.5
C10—C7—C8	120.9 (7)	C18—O6—H6B	109.5
C10—C7—H7A	119.5		

Symmetry codes: (i) $x+1, y-1, z$; (ii) $-x+1, -y+3, -z+2$; (iii) $x-1, y+1, z$.

Hydrogen-bond geometry (\AA , $^\circ$)

$D-H\cdots A$	$D-H$	$H\cdots A$	$D\cdots A$	$D-H\cdots A$
O4—H4B \cdots O5 ^{iv}	0.82	1.81	2.627 (8)	173
O6—H6B \cdots O2 ^v	0.82	1.86	2.630 (8)	155
C1—H1A \cdots O1 ^{vi}	0.93	2.56	3.299 (10)	136
C6—H6A \cdots O1 ⁱⁱ	0.93	2.49	3.212 (9)	135
C12—H12A \cdots O3	0.93	2.59	2.926 (9)	102

C16—H16A···O6	0.93	2.39	2.703 (10)	100
C16—H16A···O6 ^v	0.93	2.48	3.376 (9)	162

Symmetry codes: (ii) $-x+1, -y+3, -z+2$; (iv) $-x+2, -y+2, -z+1$; (v) $-x, -y+3, -z+1$; (vi) $-x, -y+4, -z+2$.