

Acta Crystallographica Section E

Structure Reports

Online

ISSN 1600-5368

Poly[bis(acetonitrile- κN)bis[μ_3 -bis(trifluoromethanesulfonyl)imido- $\kappa^4 O, O': O'': O''']$ dilithium]

Daniel M. Seo,^a Paul D. Boyle^b and Wesley A. Henderson^{a*}

^aDepartment of Chemical and Biomolecular Engineering, North Carolina State University, Raleigh, NC 27695, USA, and ^bDepartment of Chemistry, North Carolina State University, Raleigh, NC 27695, USA
Correspondence e-mail: wesley_henderson@ncsu.edu


Received 4 March 2011; accepted 28 March 2011

Key indicators: single-crystal X-ray study; $T = 110$ K; mean $\sigma(\text{C}-\text{C}) = 0.004$ Å; R factor = 0.041; wR factor = 0.108; data-to-parameter ratio = 11.4.

In the title compound, $[\text{Li}_2(\text{CF}_3\text{SO}_2\text{NSO}_2\text{CF}_3)_2(\text{CH}_3\text{CN})_2]_n$, two Li^+ cations reside on crystallographic inversion centers, each coordinated by six O atoms from bis(trifluoromethanesulfonyl)imide (TFSI⁻) anions. The third Li^+ cation on a general position is four-coordinated by two anion O atoms and two N atoms from acetonitrile molecules in a tetrahedral geometry.

Related literature

For the structure of $\text{LiN}(\text{SO}_2\text{CF}_3)_2$, see: Nowinski *et al.* (1994). For a related structure of $\text{LiN}(\text{SO}_2\text{CF}_3)_2$, see: Henderson *et al.* (2005); Davidson *et al.* (2003); Brouillette *et al.* (2002); Dillon *et al.* (2001). For the structure of CH_3CN with lithium salts, see: Klapötke *et al.* (2006); Brooks *et al.* (2002); Yokota *et al.* (1999); Raston *et al.* (1989).

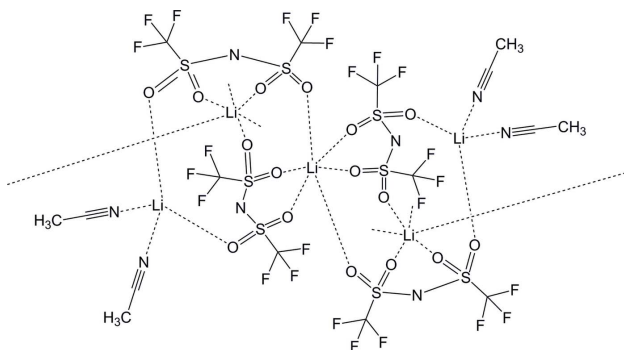

Experimental

Crystal data

 $[\text{Li}_2(\text{C}_2\text{F}_6\text{NO}_4\text{S}_2)_2(\text{C}_2\text{H}_3\text{N})_2]$ $M_r = 656.29$

Monoclinic, $P2_1/n$
 $a = 10.8654$ (2) Å
 $b = 11.0610$ (2) Å
 $c = 19.1778$ (3) Å
 $\beta = 90.8483$ (10)°
 $V = 2304.58$ (7) Å³

$Z = 4$
Cu $K\alpha$ radiation
 $\mu = 5.16$ mm⁻¹
 $T = 110$ K
 $0.40 \times 0.20 \times 0.15$ mm

Data collection

Bruker–Nonius X8 APEXII diffractometer
Absorption correction: multi-scan (SADABS; Bruker, 2009)
 $T_{\min} = 0.232$, $T_{\max} = 0.512$

937 measured reflections
3950 independent reflections
3482 reflections with $I > 2\sigma(I)$
 $R_{\text{int}} = 0.041$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.041$
 $wR(F^2) = 0.108$
 $S = 1.07$
3950 reflections

348 parameters
H-atom parameters constrained
 $\Delta\rho_{\text{max}} = 0.66$ e Å⁻³
 $\Delta\rho_{\text{min}} = -0.49$ e Å⁻³

Data collection: APEX2 (Bruker, 2009); cell refinement: SAINT (Bruker, 2009); data reduction: SAINT; program(s) used to solve structure: SIR92 (Altomare *et al.*, 1994); program(s) used to refine structure: SHELXTL (Sheldrick, 2008); molecular graphics: ORTEP-3 (Farrugia, 1997); software used to prepare material for publication: cif2tables.py (Boyle, 2008).

The authors wish to thank Dr Peter S. White and the Department of Chemistry at the University of North Carolina at Chapel Hill for use of their diffractometer. They also wish to express their gratitude to the US Department of Energy, Office of Basic Energy Sciences, Division of Materials Sciences and Engineering, which fully supported this research (Award DE-SC0002169).

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: SI2342).

References

- Altomare, A., Casciarano, G., Giacovazzo, C., Guagliardi, A., Burla, M. C., Polidori, G. & Camalli, M. (1994). *J. Appl. Cryst.* **27**, 435–436.
Boyle, P. D. (2008). <http://www.xray.ncsu.edu/PyCIFUtils/>.
Brooks, N. R., Henderson, W. A. & Smyrl, W. H. (2002). *Acta Cryst.* **E58**, m176–m177.
Brouillette, D., Irish, D. E., Taylor, N. J., Perron, G., Odziemkowski, M. & Desnoyers, J. E. (2002). *Phys. Chem. Chem. Phys.* **4**, 6063–6071.
Bruker (2009). APEX2, SAINT and SADABS. Bruker AXS Inc., Madison, Wisconsin, USA.
Davidson, M. G., Raithby, P. R., Johnson, A. L. & Bolton, P. D. (2003). *Eur. J. Inorg. Chem.* **18**, 3445–3452.
Dillon, R. E. A., Stern, C. L. & Shriver, D. F. (2001). *Chem. Mater.* **13**, 2516–2522.
Farrugia, L. J. (1997). *J. Appl. Cryst.* **30**, 565.
Henderson, W. A., McKenna, F., Khan, M. A., Brooks, N. R., Young, V. G. Jr & Frech, R. (2005). *Chem. Mater.* **17**, 2284–2289.
Klapötke, T. M., Krumm, B., Mayer, P., Scherr, M. & Schwab, I. (2006). *Acta Cryst.* **E62**, m2666–m2667.
Nowinski, J. L., Lightfoot, P. & Bruce, P. G. (1994). *J. Mater. Chem.* **4**, 1579–1580.
Raston, C. L., Whitaker, C. R. & White, A. H. (1989). *Aust. J. Chem.* **42**, 201–207.
Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.
Yokota, Y., Young, V. G. & Verkade, J. G. (1999). *Acta Cryst.* **C55**, 196–198.

supporting information

Acta Cryst. (2011). E67, m534 [doi:10.1107/S1600536811011561]

Poly[bis(acetonitrile- κ N)bis[μ_3 -bis(trifluoromethanesulfonyl)imido- κ^4 O,O':O'':O''']dilithium]

Daniel M. Seo, Paul D. Boyle and Wesley A. Henderson

S1. Comment

The structure contains three symmetry independent Li⁺ cations. Two of these, Li1 and Li2, reside on crystallographic inversion centers and are each coordinated by six O atoms from TFSI⁻ anions in a pseudo-octahedral coordination geometry. The third Li⁺ cation, Li3, sits at a general position and is four coordinate: two O atoms and two N atoms from acetonitrile molecules form a pseudo-tetragonal coordination geometry. There are two different TFSI⁻ anions which ligate the Li⁺ cations Li1 and Li2 by chelating a single lithium as well as bridging the Li1...Li2 sites. These two lithium sites are joined by two TFSI⁻ anions to form eight membered rings. The rings are formed using atoms {O1, O2} and {O5, O6}, while the axial coordination sites for Li1 and Li2 are occupied by O3 and O7, respectively. These rings form a polymeric chain which propagates along the [0 1 0] direction. Two of the coordination sites for the four coordinate Li3 atom are occupied by O4 and O8, thus providing a link between two TFSI⁻ ligands. The other two coordination sites are occupied by the N atoms from two different acetonitrile molecules. The methyl tails as well as the CF₃ groups from the TFSI⁻ anions form the exterior of the polymeric chains.

S2. Experimental

LiTFSI was purchased from 3M and dried under high-vacuum at 393 K. Anhydrous acetonitrile (Sigma Aldrich, 99.8%) was used as-received. In a vacuum atmospheres (N₂) glove box (< 5 p.p.m. H₂O), LiTFSI (5 mmol) and acetonitrile (6 mmol) were sealed in a vial and the mixture heated on a hot plate to form a homogeneous solution. 2 ml of toluene was then added to the vial to dilute the mixture. Upon standing at 278 K in a refrigerator, colorless plate single crystals formed suitable for analysis.

S3. Refinement

The structure was solved by direct methods using the *SIR92* program. All non-hydrogen atoms were obtained from the initial solution. The structural model was fit to the data using full matrix least-squares based on F^2 . The calculated structure factors included corrections for anomalous dispersion from the usual tabulation. The structure was refined using the XL program from *SHELXTL*, and graphic plots were produced using the *ORTEP-3* program. Methyl hydrogens were introduced at idealized positions and were allowed to ride on the parent carbon atom with C—H = 0.98 Å and $U_{\text{iso}}(\text{H}) = 1.5$ times $U_{\text{eq}}(\text{C})$.

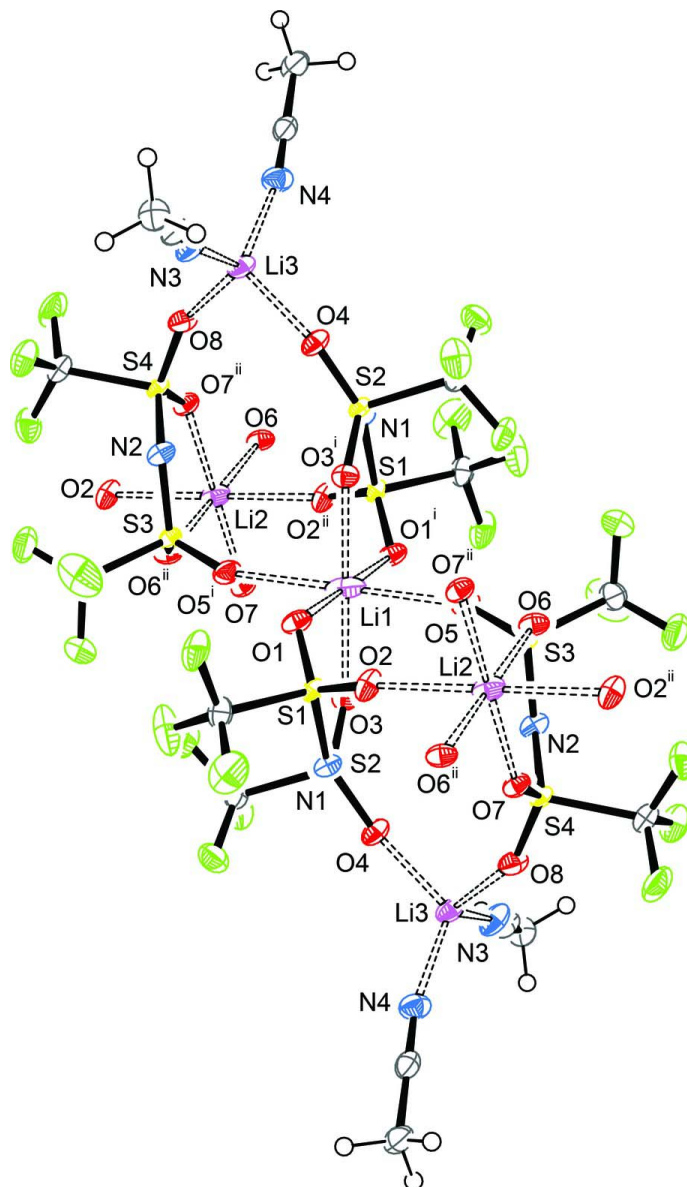


Figure 1

Molecular structure of the title compound. The thermal ellipsoids are shown at a 50% probability level. (Symmetric codes: (i) $-x + 2, -y - 1, -z + 1$; (ii) $-x + 2, -y, -z + 1$)

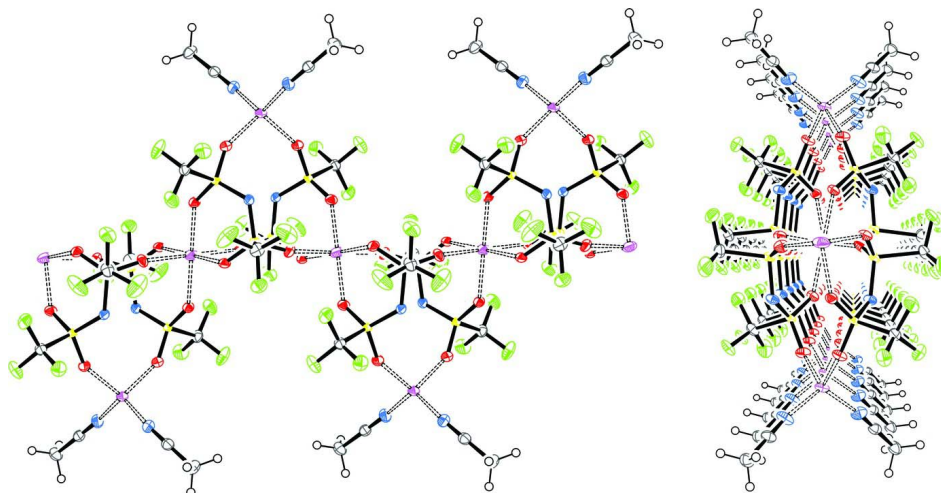


Figure 2

Schematic illustration of ion and solvent coordination for the title compound.

Poly[bis(acetonitrile- κ N)bis[μ_3 - bis(trifluoromethanesulfonyl)imido- κ^4 O,O':O'': O''']dilithium]

Crystal data

[Li₂(C₂F₆NO₄S₂)₂(C₂H₃N)₂]

$M_r = 656.29$

Monoclinic, $P2_1/n$

Hall symbol: -P 2yn

$a = 10.8654$ (2) Å

$b = 11.0610$ (2) Å

$c = 19.1778$ (3) Å

$\beta = 90.8483$ (10)°

$V = 2304.58$ (7) Å³

$Z = 4$

$F(000) = 1296$

$D_x = 1.892$ Mg m⁻³

Melting point: 315.68 K

Cu $K\alpha$ radiation, $\lambda = 1.54178$ Å

Cell parameters from 4162 reflections

$\theta = 4.6$ – 65.8 °

$\mu = 5.16$ mm⁻¹

$T = 110$ K

Plate, colourless

0.40 × 0.20 × 0.15 mm

Data collection

Bruker–Nonius X8 APEXII

diffractometer

Radiation source: fine-focus sealed tube

Graphite monochromator

ω and ϕ scans

Absorption correction: multi-scan

(SADABS; Bruker, 2009)

$T_{\min} = 0.232$, $T_{\max} = 0.512$

9937 measured reflections

3950 independent reflections

3482 reflections with $I > 2\sigma(I)$

$R_{\text{int}} = 0.041$

$\theta_{\max} = 66.2$ °, $\theta_{\min} = 4.6$ °

$h = -12$ → 12

$k = -13$ → 9

$l = -22$ → 22

Refinement

Refinement on F^2

Least-squares matrix: full

$R[F^2 > 2\sigma(F^2)] = 0.041$

$wR(F^2) = 0.108$

$S = 1.07$

3950 reflections

348 parameters

0 restraints

Primary atom site location: structure-invariant

direct methods

Secondary atom site location: difference Fourier map

Hydrogen site location: inferred from neighbouring sites

H-atom parameters constrained

$w = 1/[\sigma^2(F_o^2) + (0.0689P)^2 + 0.1796P]$

where $P = (F_o^2 + 2F_c^2)/3$

$(\Delta/\sigma)_{\max} = 0.001$

$\Delta\rho_{\max} = 0.66$ e Å⁻³

$\Delta\rho_{\min} = -0.49$ e Å⁻³

Special details

Geometry. All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

Refinement. Refinement of F^2 against ALL reflections. The weighted R -factor wR and goodness of fit S are based on F^2 , conventional R -factors R are based on F , with F set to zero for negative F^2 . The threshold expression of $F^2 > \sigma(F^2)$ is used only for calculating R -factors(gt) *etc.* and is not relevant to the choice of reflections for refinement. R -factors based on F^2 are statistically about twice as large as those based on F , and R -factors based on ALL data will be even larger.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	x	y	z	$U_{\text{iso}}^*/U_{\text{eq}}$
Li1	1.0000	-0.5000	0.5000	0.0241 (13)
Li2	1.0000	0.0000	0.5000	0.0319 (15)
Li3	1.2401 (4)	-0.2523 (4)	0.7428 (2)	0.0212 (8)
S1	0.86669 (5)	-0.27813 (5)	0.57295 (3)	0.01533 (16)
S2	1.02904 (5)	-0.40779 (5)	0.65910 (3)	0.01465 (16)
O1	0.86025 (16)	-0.38148 (16)	0.52784 (9)	0.0198 (4)
O2	0.88818 (17)	-0.16218 (16)	0.54296 (10)	0.0242 (4)
O3	1.05935 (15)	-0.48372 (15)	0.60138 (9)	0.0189 (4)
O4	1.12685 (17)	-0.37177 (16)	0.70505 (10)	0.0235 (4)
N1	0.9472 (2)	-0.29426 (18)	0.64117 (11)	0.0189 (4)
C1	0.7103 (2)	-0.2650 (3)	0.60816 (15)	0.0259 (6)
F1	0.63021 (15)	-0.26086 (15)	0.55589 (10)	0.0322 (4)
F2	0.70074 (18)	-0.1660 (2)	0.64600 (12)	0.0514 (6)
F3	0.68438 (17)	-0.3600 (2)	0.64704 (11)	0.0514 (6)
C2	0.9349 (3)	-0.5030 (2)	0.71598 (14)	0.0223 (5)
F4	0.83885 (15)	-0.54657 (15)	0.68038 (9)	0.0322 (4)
F5	0.89314 (17)	-0.43864 (16)	0.76878 (8)	0.0338 (4)
F6	1.00206 (18)	-0.59308 (15)	0.74022 (10)	0.0387 (4)
S3	1.17709 (5)	-0.22534 (5)	0.47597 (3)	0.01494 (16)
S4	1.22060 (5)	-0.09504 (5)	0.59873 (3)	0.01427 (16)
O5	1.11998 (18)	-0.34116 (16)	0.46985 (9)	0.0227 (4)
O6	1.11351 (17)	-0.12146 (16)	0.44846 (9)	0.0211 (4)
O7	1.11864 (15)	-0.01780 (16)	0.58177 (9)	0.0194 (4)
O8	1.23617 (17)	-0.13043 (16)	0.66994 (9)	0.0223 (4)
N2	1.23502 (19)	-0.21021 (18)	0.55127 (11)	0.0182 (4)
C3	1.3146 (3)	-0.2392 (2)	0.42186 (15)	0.0237 (5)
F7	1.28089 (18)	-0.24474 (16)	0.35552 (9)	0.0344 (4)
F8	1.38759 (17)	-0.1450 (2)	0.43007 (10)	0.0463 (5)
F9	1.3759 (2)	-0.3386 (2)	0.43789 (11)	0.0532 (6)
C4	1.3576 (2)	-0.0027 (2)	0.58387 (14)	0.0202 (5)
F10	1.36085 (16)	0.08703 (15)	0.62945 (10)	0.0336 (4)
F11	1.35530 (15)	0.04254 (15)	0.52012 (9)	0.0305 (4)
F12	1.45820 (14)	-0.06888 (15)	0.59205 (10)	0.0310 (4)
N3	1.3951 (2)	-0.3487 (2)	0.75516 (13)	0.0278 (5)
C5	1.4711 (2)	-0.4159 (2)	0.76885 (14)	0.0234 (6)

C6	1.5678 (3)	-0.5024 (3)	0.78594 (15)	0.0285 (6)
H61	1.6388	-0.4879	0.7562	0.043*
H62	1.5371	-0.5847	0.7782	0.043*
H63	1.5927	-0.4929	0.8350	0.043*
N4	1.1814 (2)	-0.1550 (2)	0.82413 (12)	0.0289 (5)
C7	1.1632 (3)	-0.0855 (2)	0.86648 (14)	0.0240 (6)
C8	1.1392 (3)	0.0036 (3)	0.92008 (15)	0.0274 (6)
H81	1.1588	0.0844	0.9025	0.041*
H82	1.1904	-0.0138	0.9614	0.041*
H83	1.0521	0.0004	0.9326	0.041*

Atomic displacement parameters (Å²)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Li1	0.031 (3)	0.027 (3)	0.014 (3)	0.008 (2)	-0.001 (2)	-0.004 (2)
Li2	0.038 (4)	0.036 (4)	0.021 (3)	0.019 (3)	-0.010 (3)	-0.005 (3)
Li3	0.030 (2)	0.0212 (19)	0.0124 (19)	-0.0019 (16)	-0.0045 (17)	0.0002 (16)
S1	0.0196 (3)	0.0144 (3)	0.0120 (3)	0.00129 (19)	0.0004 (2)	-0.0002 (2)
S2	0.0209 (3)	0.0143 (3)	0.0088 (3)	-0.0003 (2)	-0.0007 (2)	0.0000 (2)
O1	0.0244 (9)	0.0204 (8)	0.0145 (8)	0.0041 (7)	-0.0042 (7)	-0.0033 (7)
O2	0.0284 (9)	0.0179 (9)	0.0261 (10)	-0.0009 (7)	-0.0054 (7)	0.0072 (7)
O3	0.0248 (9)	0.0192 (8)	0.0126 (8)	0.0044 (6)	0.0010 (7)	-0.0002 (7)
O4	0.0298 (9)	0.0212 (9)	0.0195 (9)	-0.0012 (7)	-0.0070 (7)	0.0025 (7)
N1	0.0288 (11)	0.0145 (9)	0.0133 (10)	0.0030 (8)	-0.0010 (8)	-0.0031 (8)
C1	0.0219 (13)	0.0309 (14)	0.0249 (14)	0.0058 (10)	0.0050 (11)	0.0002 (11)
F1	0.0226 (8)	0.0376 (9)	0.0362 (10)	0.0036 (6)	-0.0033 (7)	0.0029 (7)
F2	0.0379 (10)	0.0616 (13)	0.0549 (12)	0.0145 (9)	0.0075 (9)	-0.0308 (11)
F3	0.0339 (9)	0.0677 (14)	0.0532 (12)	0.0096 (9)	0.0184 (9)	0.0374 (11)
C2	0.0310 (13)	0.0187 (12)	0.0173 (12)	0.0000 (10)	0.0041 (11)	0.0028 (10)
F4	0.0324 (8)	0.0305 (8)	0.0337 (9)	-0.0125 (7)	0.0053 (7)	-0.0030 (7)
F5	0.0455 (10)	0.0399 (9)	0.0165 (8)	-0.0008 (7)	0.0135 (7)	-0.0035 (7)
F6	0.0452 (10)	0.0294 (9)	0.0418 (10)	0.0070 (7)	0.0111 (8)	0.0208 (8)
S3	0.0207 (3)	0.0140 (3)	0.0102 (3)	-0.0003 (2)	0.0020 (2)	-0.0006 (2)
S4	0.0196 (3)	0.0143 (3)	0.0090 (3)	-0.00059 (19)	-0.0006 (2)	0.0010 (2)
O5	0.0367 (10)	0.0172 (8)	0.0141 (8)	-0.0066 (7)	0.0034 (7)	-0.0030 (7)
O6	0.0297 (9)	0.0206 (9)	0.0129 (8)	0.0053 (7)	-0.0016 (7)	-0.0008 (7)
O7	0.0216 (8)	0.0219 (8)	0.0148 (8)	0.0032 (7)	-0.0004 (7)	-0.0040 (7)
O8	0.0336 (9)	0.0208 (8)	0.0123 (8)	-0.0018 (7)	-0.0010 (7)	0.0009 (7)
N2	0.0249 (10)	0.0152 (9)	0.0143 (10)	0.0029 (7)	-0.0021 (8)	0.0006 (8)
C3	0.0274 (13)	0.0244 (12)	0.0195 (13)	-0.0011 (10)	0.0074 (10)	-0.0037 (10)
F7	0.0470 (10)	0.0403 (9)	0.0162 (8)	-0.0102 (7)	0.0124 (7)	-0.0057 (7)
F8	0.0400 (10)	0.0579 (12)	0.0417 (11)	-0.0271 (9)	0.0201 (8)	-0.0218 (9)
F9	0.0543 (12)	0.0562 (13)	0.0499 (12)	0.0327 (10)	0.0257 (10)	0.0126 (10)
C4	0.0225 (12)	0.0198 (12)	0.0182 (12)	-0.0019 (9)	0.0020 (10)	-0.0005 (10)
F10	0.0370 (9)	0.0275 (8)	0.0366 (10)	-0.0109 (7)	0.0078 (7)	-0.0144 (7)
F11	0.0374 (9)	0.0285 (8)	0.0258 (8)	-0.0067 (7)	0.0066 (7)	0.0096 (7)
F12	0.0205 (7)	0.0323 (8)	0.0402 (10)	0.0021 (6)	-0.0004 (7)	0.0014 (7)
N3	0.0307 (12)	0.0214 (11)	0.0311 (13)	-0.0008 (10)	-0.0080 (10)	0.0037 (10)

C5	0.0284 (13)	0.0240 (13)	0.0177 (13)	-0.0068 (11)	-0.0007 (10)	0.0017 (10)
C6	0.0331 (14)	0.0303 (14)	0.0223 (14)	0.0057 (11)	0.0032 (11)	0.0059 (11)
N4	0.0486 (14)	0.0224 (11)	0.0157 (11)	-0.0041 (10)	0.0017 (10)	-0.0001 (10)
C7	0.0328 (14)	0.0217 (13)	0.0174 (13)	-0.0022 (10)	-0.0018 (11)	0.0041 (11)
C8	0.0313 (14)	0.0273 (14)	0.0236 (14)	-0.0007 (10)	0.0019 (11)	-0.0061 (11)

Geometric parameters (Å, °)

Li1—O3	2.0473 (17)	S3—O5	1.4275 (18)
Li1—O1	2.0817 (17)	S3—O6	1.4370 (18)
Li1—O5	2.2678 (17)	S3—N2	1.576 (2)
Li2—O7	2.0247 (17)	S3—C3	1.838 (3)
Li2—O6	2.0831 (17)	S4—O8	1.4284 (18)
Li2—O2	2.3243 (18)	S4—O7	1.4326 (18)
Li3—O4	1.940 (5)	S4—N2	1.575 (2)
Li3—O8	1.942 (5)	S4—C4	1.831 (3)
Li3—N3	2.004 (5)	C3—F8	1.317 (3)
Li3—N4	2.006 (5)	C3—F9	1.319 (3)
S1—O2	1.4263 (18)	C3—F7	1.320 (3)
S1—O1	1.4347 (18)	C4—F11	1.321 (3)
S1—N1	1.573 (2)	C4—F10	1.323 (3)
S1—C1	1.844 (3)	C4—F12	1.323 (3)
S2—O4	1.4272 (19)	N3—C5	1.139 (4)
S2—O3	1.4317 (18)	C5—C6	1.455 (4)
S2—N1	1.574 (2)	C6—H61	0.9800
S2—C2	1.838 (3)	C6—H62	0.9800
C1—F1	1.318 (4)	C6—H63	0.9800
C1—F2	1.318 (4)	N4—C7	1.138 (4)
C1—F3	1.322 (3)	C7—C8	1.450 (4)
C2—F6	1.316 (3)	C8—H81	0.9800
C2—F5	1.323 (3)	C8—H82	0.9800
C2—F4	1.329 (3)	C8—H83	0.9800
O3 ⁱ —Li1—O3	180.00 (3)	F2—C1—F3	109.3 (3)
O3 ⁱ —Li1—O1	94.49 (7)	F1—C1—S1	109.02 (19)
O3—Li1—O1	85.51 (7)	F2—C1—S1	110.3 (2)
O3 ⁱ —Li1—O1 ⁱ	85.51 (7)	F3—C1—S1	110.43 (18)
O3—Li1—O1 ⁱ	94.49 (7)	F6—C2—F5	109.4 (2)
O1—Li1—O1 ⁱ	180.00 (9)	F6—C2—F4	109.5 (2)
O3 ⁱ —Li1—O5 ⁱ	89.99 (7)	F5—C2—F4	108.2 (2)
O3—Li1—O5 ⁱ	90.01 (7)	F6—C2—S2	109.43 (18)
O1—Li1—O5 ⁱ	89.90 (7)	F5—C2—S2	110.27 (18)
O1 ⁱ —Li1—O5 ⁱ	90.10 (7)	F4—C2—S2	110.04 (18)
O3 ⁱ —Li1—O5	90.01 (7)	O5—S3—O6	118.77 (12)
O3—Li1—O5	89.99 (7)	O5—S3—N2	109.75 (11)
O1—Li1—O5	90.10 (7)	O6—S3—N2	115.79 (11)
O1 ⁱ —Li1—O5	89.90 (7)	O5—S3—C3	103.57 (11)
O5 ⁱ —Li1—O5	180.00 (8)	O6—S3—C3	104.46 (12)

O7 ⁱⁱ —Li2—O7	180.00 (6)	N2—S3—C3	102.08 (12)
O7 ⁱⁱ —Li2—O6 ⁱⁱ	86.00 (7)	O8—S4—O7	117.44 (11)
O7—Li2—O6 ⁱⁱ	94.00 (7)	O8—S4—N2	108.63 (11)
O7 ⁱⁱ —Li2—O6	94.00 (7)	O7—S4—N2	115.75 (11)
O7—Li2—O6	86.00 (7)	O8—S4—C4	102.51 (12)
O6 ⁱⁱ —Li2—O6	180.00 (8)	O7—S4—C4	105.05 (11)
O7 ⁱⁱ —Li2—O2	91.11 (7)	N2—S4—C4	105.86 (11)
O7—Li2—O2	88.89 (7)	S3—O5—Li1	157.68 (11)
O6 ⁱⁱ —Li2—O2	90.76 (7)	S3—O6—Li2	128.77 (11)
O6—Li2—O2	89.24 (7)	S4—O7—Li2	135.66 (11)
O7 ⁱⁱ —Li2—O2 ⁱⁱ	88.89 (7)	S4—O8—Li3	151.60 (18)
O7—Li2—O2 ⁱⁱ	91.11 (7)	S4—N2—S3	125.01 (13)
O6 ⁱⁱ —Li2—O2 ⁱⁱ	89.24 (7)	F8—C3—F9	109.2 (3)
O6—Li2—O2 ⁱⁱ	90.76 (7)	F8—C3—F7	108.1 (2)
O2—Li2—O2 ⁱⁱ	180.00 (6)	F9—C3—F7	108.5 (2)
O4—Li3—O8	101.3 (2)	F8—C3—S3	111.08 (18)
O4—Li3—N3	102.0 (2)	F9—C3—S3	110.49 (19)
O8—Li3—N3	117.6 (2)	F7—C3—S3	109.38 (19)
O4—Li3—N4	116.6 (2)	F11—C4—F10	109.1 (2)
O8—Li3—N4	100.6 (2)	F11—C4—F12	108.9 (2)
N3—Li3—N4	118.1 (2)	F10—C4—F12	108.8 (2)
O2—S1—O1	118.69 (11)	F11—C4—S4	110.56 (18)
O2—S1—N1	110.18 (11)	F10—C4—S4	109.24 (17)
O1—S1—N1	115.64 (11)	F12—C4—S4	110.19 (17)
O2—S1—C1	103.54 (12)	C5—N3—Li3	168.4 (3)
O1—S1—C1	104.28 (12)	N3—C5—C6	179.6 (3)
N1—S1—C1	102.06 (12)	C5—C6—H61	109.5
O4—S2—O3	117.61 (11)	C5—C6—H62	109.5
O4—S2—N1	108.98 (11)	H61—C6—H62	109.5
O3—S2—N1	115.77 (11)	C5—C6—H63	109.5
O4—S2—C2	102.09 (12)	H61—C6—H63	109.5
O3—S2—C2	105.03 (11)	H62—C6—H63	109.5
N1—S2—C2	105.62 (12)	C7—N4—Li3	167.9 (3)
S1—O1—Li1	128.84 (11)	N4—C7—C8	179.5 (3)
S1—O2—Li2	157.89 (12)	C7—C8—H81	109.5
S2—O3—Li1	135.48 (11)	C7—C8—H82	109.5
S2—O4—Li3	152.09 (18)	H81—C8—H82	109.5
S1—N1—S2	125.29 (13)	C7—C8—H83	109.5
F1—C1—F2	109.5 (2)	H81—C8—H83	109.5
F1—C1—F3	108.2 (2)	H82—C8—H83	109.5
O2—S1—O1—Li1	93.14 (15)	O3 ⁱ —Li1—O5—S3	139.2 (3)
N1—S1—O1—Li1	-41.19 (18)	O3—Li1—O5—S3	-40.8 (3)
C1—S1—O1—Li1	-152.37 (14)	O1—Li1—O5—S3	44.7 (3)
O3 ⁱ —Li1—O1—S1	-141.25 (14)	O1 ⁱ —Li1—O5—S3	-135.3 (3)
O3—Li1—O1—S1	38.75 (14)	O5—S3—O6—Li2	94.77 (15)
O5 ⁱ —Li1—O1—S1	128.77 (14)	N2—S3—O6—Li2	-39.14 (18)
O5—Li1—O1—S1	-51.23 (14)	C3—S3—O6—Li2	-150.52 (14)

O1—S1—O2—Li2	-86.1 (3)	O7 ⁱⁱ —Li2—O6—S3	-142.32 (14)
N1—S1—O2—Li2	50.5 (4)	O7—Li2—O6—S3	37.68 (14)
C1—S1—O2—Li2	159.0 (3)	O2—Li2—O6—S3	-51.26 (14)
O7 ⁱⁱ —Li2—O2—S1	137.1 (3)	O2 ⁱⁱ —Li2—O6—S3	128.74 (14)
O7—Li2—O2—S1	-42.9 (3)	O8—S4—O7—Li2	-144.13 (14)
O6 ⁱⁱ —Li2—O2—S1	-136.9 (3)	N2—S4—O7—Li2	-13.6 (2)
O6—Li2—O2—S1	43.1 (3)	C4—S4—O7—Li2	102.77 (16)
O4—S2—O3—Li1	-143.85 (14)	O6 ⁱⁱ —Li2—O7—S4	170.77 (16)
N1—S2—O3—Li1	-12.6 (2)	O6—Li2—O7—S4	-9.23 (16)
C2—S2—O3—Li1	103.50 (17)	O2—Li2—O7—S4	80.09 (16)
O1—Li1—O3—S2	-9.75 (15)	O2 ⁱⁱ —Li2—O7—S4	-99.91 (16)
O1 ⁱ —Li1—O3—S2	170.25 (15)	O7—S4—O8—Li3	115.4 (4)
O5 ⁱ —Li1—O3—S2	-99.65 (16)	N2—S4—O8—Li3	-18.4 (4)
O5—Li1—O3—S2	80.35 (16)	C4—S4—O8—Li3	-130.1 (4)
O3—S2—O4—Li3	107.9 (4)	O4—Li3—O8—S4	-28.7 (5)
N1—S2—O4—Li3	-26.5 (4)	N3—Li3—O8—S4	81.5 (5)
C2—S2—O4—Li3	-137.8 (4)	N4—Li3—O8—S4	-148.9 (3)
O8—Li3—O4—S2	-19.3 (5)	O8—S4—N2—S3	155.10 (15)
N3—Li3—O4—S2	-141.1 (3)	O7—S4—N2—S3	20.5 (2)
N4—Li3—O4—S2	88.7 (4)	C4—S4—N2—S3	-95.43 (17)
O2—S1—N1—S2	-131.85 (16)	O5—S3—N2—S4	-133.72 (15)
O1—S1—N1—S2	6.2 (2)	O6—S3—N2—S4	4.1 (2)
C1—S1—N1—S2	118.67 (17)	C3—S3—N2—S4	116.90 (17)
O4—S2—N1—S1	154.01 (15)	O5—S3—C3—F8	-170.8 (2)
O3—S2—N1—S1	18.8 (2)	O6—S3—C3—F8	64.2 (2)
C2—S2—N1—S1	-96.96 (17)	N2—S3—C3—F8	-56.7 (2)
O2—S1—C1—F1	70.7 (2)	O5—S3—C3—F9	-49.4 (2)
O1—S1—C1—F1	-54.1 (2)	O6—S3—C3—F9	-174.4 (2)
N1—S1—C1—F1	-174.84 (18)	N2—S3—C3—F9	64.7 (2)
O2—S1—C1—F2	-49.6 (2)	O5—S3—C3—F7	70.1 (2)
O1—S1—C1—F2	-174.4 (2)	O6—S3—C3—F7	-54.9 (2)
N1—S1—C1—F2	64.9 (2)	N2—S3—C3—F7	-175.92 (17)
O2—S1—C1—F3	-170.5 (2)	O8—S4—C4—F11	-177.28 (17)
O1—S1—C1—F3	64.7 (2)	O7—S4—C4—F11	-54.0 (2)
N1—S1—C1—F3	-56.1 (2)	N2—S4—C4—F11	68.9 (2)
O4—S2—C2—F6	-58.6 (2)	O8—S4—C4—F10	-57.2 (2)
O3—S2—C2—F6	64.6 (2)	O7—S4—C4—F10	66.1 (2)
N1—S2—C2—F6	-172.51 (19)	N2—S4—C4—F10	-170.98 (17)
O4—S2—C2—F5	61.7 (2)	O8—S4—C4—F12	62.3 (2)
O3—S2—C2—F5	-175.04 (18)	O7—S4—C4—F12	-174.42 (17)
N1—S2—C2—F5	-52.2 (2)	N2—S4—C4—F12	-51.5 (2)
O4—S2—C2—F4	-178.96 (17)	O4—Li3—N3—C5	-56.2 (14)
O3—S2—C2—F4	-55.7 (2)	O8—Li3—N3—C5	-166.0 (12)
N1—S2—C2—F4	67.1 (2)	N4—Li3—N3—C5	73.1 (14)
O6—S3—O5—Li1	-88.8 (3)	O4—Li3—N4—C7	-157.1 (12)

N2—S3—O5—Li1	47.7 (4)	O8—Li3—N4—C7	-48.6 (14)
C3—S3—O5—Li1	156.1 (3)	N3—Li3—N4—C7	80.8 (13)

Symmetry codes: (i) $-x+2, -y-1, -z+1$; (ii) $-x+2, -y, -z+1$.