

Acta Crystallographica Section E

Structure Reports

Online

ISSN 1600-5368

Poly[μ -aqua-aqua(μ -benzene-1,2,4,5-tetracarboxylato)gadolinium(III)-potassium(I)]

Xue Yun Gong* and Lei Zhang

Department of Physics and Chemistry, Henan Polytechnic University, Jiaozuo, Henan 454000, People's Republic of China

Correspondence e-mail: gxy@hpu.edu.cn

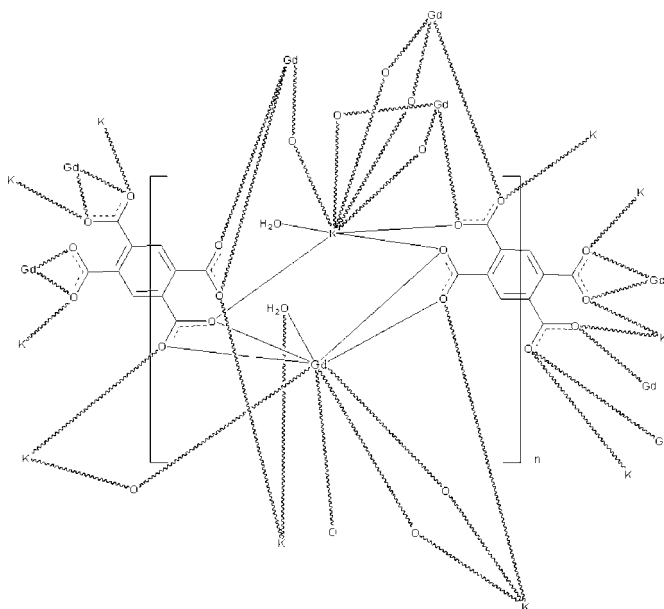
Received 11 April 2011; accepted 29 April 2011

Key indicators: single-crystal X-ray study; $T = 296$ K; mean $\sigma(\text{C}-\text{C}) = 0.005$ Å; R factor = 0.024; wR factor = 0.051; data-to-parameter ratio = 15.1.

In the title compound, $[\text{KGd}(\text{C}_{10}\text{H}_2\text{O}_8)(\text{H}_2\text{O})_2]_n$, the Gd^{3+} ion is nine-coordinated by eight O atoms from five individual benzene-1,2,4,5-tetracarboxylate (btec) ligands and one water molecule, and the K^+ ion is eight-coordinated by six O atoms from five individual btec ligands and two water molecules. In the crystal, the btec half-molecules are completed by crystallographic inversion symmetry. GdO_9 and KO_8 polyhedra are connected, forming layers in the ab plane, which are further interconnected by μ_8 - or μ_{12} -bridging btec ligands, forming a three-dimensional structure.

Related literature

For structures based on H_4btec ligand, see: Huang *et al.* (2009); Lu *et al.* (2005); Wu *et al.* (2001); Zhang *et al.* (2005). For the isotopic neodymium(III) compound, see: Dai *et al.* (2008).



Experimental

Crystal data

 $[\text{KGd}(\text{C}_{10}\text{H}_2\text{O}_8)(\text{H}_2\text{O})_2]$
 $M_r = 482.50$
Monoclinic, $P2_1/c$ $a = 8.9003$ (1) Å $b = 7.7816$ (1) Å $c = 17.5150$ (3) Å $\beta = 91.857$ (1)° $V = 1212.43$ (3) Å³ $Z = 4$ Mo $K\alpha$ radiation $\mu = 5.87$ mm⁻¹ $T = 296$ K $0.20 \times 0.10 \times 0.10$ mm

Data collection

Bruker SMART APEXII CCD
area-detector diffractometerAbsorption correction: multi-scan
(*SADABS*; Sheldrick, 1996) $T_{\min} = 0.386$, $T_{\max} = 0.591$

14043 measured reflections

3002 independent reflections

2588 reflections with $I > 2\sigma(I)$ $R_{\text{int}} = 0.037$

Refinement

 $R[F^2 > 2\sigma(F^2)] = 0.024$ $wR(F^2) = 0.051$ $S = 1.04$

3002 reflections

199 parameters

H-atom parameters constrained

 $\Delta\rho_{\text{max}} = 0.91$ e Å⁻³ $\Delta\rho_{\text{min}} = -1.29$ e Å⁻³
Table 1

Selected bond lengths (Å).

Gd1—O6 ⁱ	2.337 (3)	K1—O2	2.714 (3)
Gd1—O7 ⁱⁱ	2.376 (2)	K1—O6	2.783 (3)
Gd1—O8	2.433 (2)	K1—O8	2.795 (3)
Gd1—O3	2.441 (2)	K1—O10	2.842 (3)
Gd1—O1	2.447 (3)	K1—O1 ^{iv}	2.860 (3)
Gd1—O5 ⁱⁱⁱ	2.451 (2)	K1—O4 ^{iv}	2.875 (3)
Gd1—O4 ⁱⁱⁱ	2.503 (2)	K1—O7 ⁱ	2.891 (3)
Gd1—O9	2.520 (3)	K1—O9 ^v	2.893 (3)
Gd1—O2	2.604 (2)		

Symmetry codes: (i) $-x, y - \frac{1}{2}, -z + \frac{3}{2}$; (ii) $x, y - 1, z$; (iii) $-x + 1, y - \frac{1}{2}, -z + \frac{3}{2}$; (iv) $-x + 1, y + \frac{1}{2}, -z + \frac{3}{2}$; (v) $-x, y + \frac{1}{2}, -z + \frac{3}{2}$.

Data collection: *APEX2* (Bruker, 2008); cell refinement: *S SAINT* (Bruker, 2008); data reduction: *S SAINT*; program(s) used to solve structure: *SHELXS97* (Sheldrick, 2008); program(s) used to refine structure: *SHELXL97* (Sheldrick, 2008); molecular graphics: *SHELXTL* (Sheldrick, 2008); software used to prepare material for publication: *SHELXL97*.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: SI2351).

References

- Bruker (2008). *APEX2* and *S SAINT*. Bruker AXS Inc., Madison, Wisconsin, USA.
- Dai, Y. M., Tang, E., Wang, X. Q., Huang, J. F., Wang, L. H. & Huang, X. D. (2008). *Chin. J. Struct. Chem.* **27**, 1031–1034.
- Huang, R. Y., Xu, H. M., Zhu, K., Liu, G. X. & Ren, X. M. (2009). *Chin. J. Struct. Chem.* **28**, 1661–1665.
- Lu, K. L., Chen, Y. F., Liu, Y. H., Cheng, Y. W., Liao, R. T. & Wen, Y. S. (2005). *Cryst. Growth Des.* **5**, 403–407.
- Sheldrick, G. M. (1996). *SADABS*. University of Göttingen, Germany.
- Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.
- Wu, C. D., Lu, C. Z., Wu, D. M., Zhuang, H. H. & Huang, J. S. (2001). *Inorg. Chem. Commun.* **4**, 561–564.
- Zhang, L. J., Yu, J. H., Xu, J. Q., Lu, J., Bie, H. Y. & Zhang, X. (2005). *Inorg. Chem. Commun.* **8**, 638–642.

supporting information

Acta Cryst. (2011). E67, m736 [doi:10.1107/S1600536811016254]

Poly[μ -aqua-aqua(μ -benzene-1,2,4,5-tetracarboxylato)gadolate(III)potassium(I)]

Xue Yun Gong and Lei Zhang

S1. Comment

The btec ligand is a remarkably versatile building block for the construction of supramolecular architectures due to its four rigid carboxyl groups and various coordination modes in the self-assembly reaction (Huang *et al.*, 2009; Lu *et al.*, 2005; Wu *et al.*, 2001; Zhang *et al.*, 2005). Furthermore, they can provide directional conformation of network structures *via* noncovalent contacts like hydrogen bonding and aromatic stacking. In this paper, we report the preparation and crystal structure of a new potassium(I)-gadolinium(III) complex, $[\text{KGd}(\text{btec})(\text{H}_2\text{O})_2]_n$, where btec = benzene-1,2,4,5-tetracarboxylate. The crystal structures of a Nd^{III} analogue has been reported recently (Dai *et al.*, 2008).

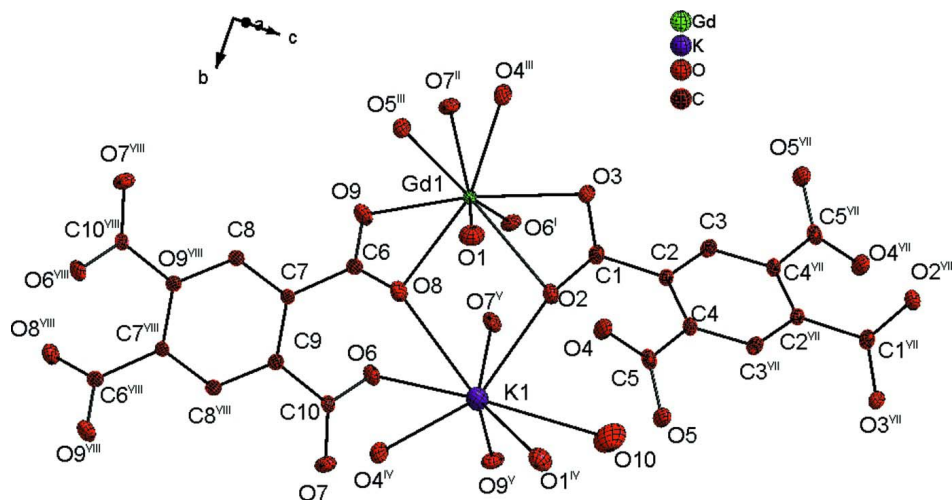
As shown in Fig. 1, the asymmetric building unit of title compound comprises one Gd^{III} atom, one K^{I} atom, two coordinated water molecules and two btec ligands. The two crystallographic distinct btec ligands occupy inversion symmetry in the structure. One of them acts as a μ_{12} -bridge linking six Gd^{III} and six K^{I} atoms, while the other one acts as a μ_8 -bridge linking four Gd^{III} and four K^{I} atoms. Considering the linking environment of the gadolinium(III) and potassium(I) atoms, Gd^{III} is nine-coordinated by eight O atoms from five individual btec ligands and one water molecule, while the K^{I} atom is eight-coordinated by six O atoms from five individual btec ligands and two water molecules, as listed in Tab. 1. As shown in Fig. 2, when C and H atoms are omitted, a two-dimensional Gd—K—O framework is emerged in the *ab* plane. Furthermore, these two-dimensional layers are integrated by C atoms of btec ligands into a three-dimensional framework.

S2. Experimental

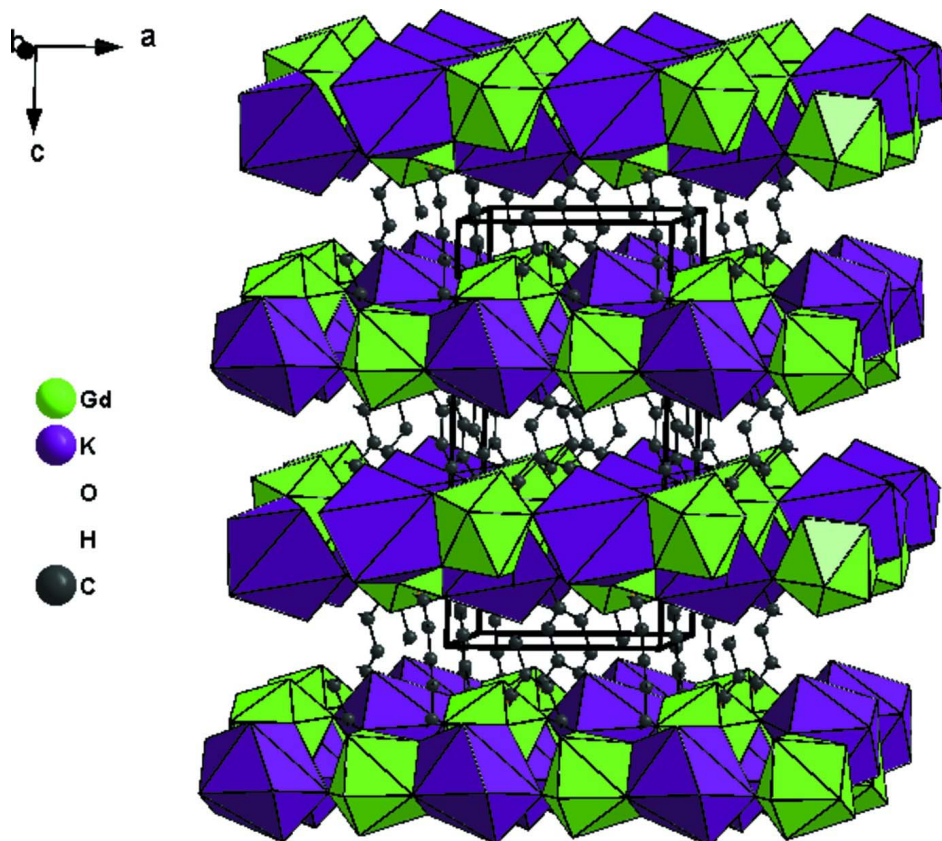
A mixture of 1,2,4,5-benzenetetracarboxylic (0.05 g), Gd_2O_3 (0.05 g), KOH (0.05 g) and H_2O (15 ml) was heated at 448 K for 7 d in a sealed 25 ml Teflon-lined stainless steel vessel under autogenous pressure. After cooling to room temperature at a rate of 5 C h^{-1} , colorless prismatic crystals were obtained in low yield.

S3. Refinement

The H atoms of C atoms were positioned geometrically and refined with a riding model, with $\text{C—H} = 0.93 \text{ \AA}$ and $U_{\text{iso}}(\text{H}) = 1.2U_{\text{eq}}(\text{C})$. The water H atoms were located in difference fourier maps, and then refined with a riding model, with $\text{O—H} = 0.85$ and 0.87 \AA , and $U_{\text{iso}}(\text{H}) = 1.2U_{\text{eq}}(\text{O})$.


Figure 1

The Gd^{III} and K^I coordination environment of the title compound indicating the inversion symmetry of the btc ligands by symmetry codes vii and viii. Displacement ellipsoids are drawn at the 50% probability level for non-H atoms. [Symmetry codes: (i) $-x, y - 1/2, -z + 3/2$; (ii) $x, y - 1, z$; (iii) $-x + 1, y - 1/2, -z + 3/2$; (iv) $-x + 1, y + 1/2, -z + 3/2$; (v) $-x, y + 1/2, -z + 3/2$; (vi) $-x + 1, -y + 1, -z + 2$; (vii) $-x + 1, -y + 1, -z + 2$; (viii) $-x, -y + 2, -z + 1$].


Figure 2

View of the three-dimensional network for the title compound.

Poly[μ -aqua-aqua(μ -benzene-1,2,4,5-tetracarboxylato)gadolinate(III)potassium(I)]

Crystal data

[KGd(C₁₀H₂O₈)(H₂O)₂] $M_r = 482.50$ Monoclinic, $P2_1/c$

Hall symbol: -P 2ybc

 $a = 8.9003$ (1) Å $b = 7.7816$ (1) Å $c = 17.5150$ (3) Å $\beta = 91.857$ (1)° $V = 1212.43$ (3) Å³ $Z = 4$ $F(000) = 916$ $D_x = 2.643$ Mg m⁻³Mo $K\alpha$ radiation, $\lambda = 0.71073$ Å

Cell parameters from 2537 reflections

 $\theta = 2.3$ – 25.1 ° $\mu = 5.87$ mm⁻¹ $T = 296$ K

Prism, colourless

 $0.20 \times 0.10 \times 0.10$ mm

Data collection

Bruker SMART APEXII CCD area-detector
diffractometer

Radiation source: fine-focus sealed tube

Graphite monochromator

Detector resolution: 83.33 pixels mm⁻¹ ω scans

Absorption correction: multi-scan

(SADABS; Sheldrick, 1996)

 $T_{\min} = 0.386$, $T_{\max} = 0.591$

14043 measured reflections

3002 independent reflections

2588 reflections with $I > 2\sigma(I)$ $R_{\text{int}} = 0.037$ $\theta_{\max} = 28.3$ °, $\theta_{\min} = 2.3$ ° $h = -11 \rightarrow 11$ $k = -10 \rightarrow 9$ $l = -23 \rightarrow 23$

Refinement

Refinement on F^2

Least-squares matrix: full

 $R[F^2 > 2\sigma(F^2)] = 0.024$ $wR(F^2) = 0.051$ $S = 1.04$

3002 reflections

199 parameters

0 restraints

Primary atom site location: structure-invariant
direct methodsSecondary atom site location: difference Fourier
mapHydrogen site location: inferred from
neighbouring sites

H-atom parameters constrained

 $w = 1/[\sigma^2(F_o^2) + (0.0208P)^2 + 1.8584P]$ where $P = (F_o^2 + 2F_c^2)/3$ $(\Delta/\sigma)_{\max} = 0.002$ $\Delta\rho_{\max} = 0.91$ e Å⁻³ $\Delta\rho_{\min} = -1.29$ e Å⁻³

Special details

Geometry. All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

Refinement. Refinement of F^2 against ALL reflections. The weighted R -factor wR and goodness of fit S are based on F^2 , conventional R -factors R are based on F , with F set to zero for negative F^2 . The threshold expression of $F^2 > \sigma(F^2)$ is used only for calculating R -factors(gt) etc. and is not relevant to the choice of reflections for refinement. R -factors based on F^2 are statistically about twice as large as those based on F , and R -factors based on ALL data will be even larger.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (Å²)

	x	y	z	$U_{\text{iso}}^*/U_{\text{eq}}$
Gd1	0.21753 (2)	0.47536 (2)	0.699264 (9)	0.00997 (6)
K1	0.22962 (11)	0.97212 (11)	0.78942 (5)	0.02529 (19)
O1	0.4699 (3)	0.5723 (3)	0.66830 (15)	0.0226 (6)
H1A	0.5081	0.6065	0.7107	0.027*

H1B	0.4533	0.6604	0.6406	0.027*
C1	0.3791 (4)	0.5106 (4)	0.8437 (2)	0.0147 (7)
O2	0.3319 (3)	0.6478 (3)	0.81457 (14)	0.0183 (6)
C2	0.4485 (4)	0.5076 (4)	0.92329 (19)	0.0128 (7)
O3	0.3601 (3)	0.3676 (3)	0.81063 (14)	0.0210 (6)
C3	0.3828 (4)	0.3974 (4)	0.97488 (18)	0.0142 (7)
H3	0.3041	0.3270	0.9581	0.017*
O4	0.6594 (3)	0.6935 (3)	0.82750 (13)	0.0180 (6)
C4	0.5683 (4)	0.6106 (4)	0.94877 (18)	0.0128 (7)
O5	0.7106 (3)	0.8636 (3)	0.92519 (13)	0.0173 (6)
C5	0.6512 (4)	0.7290 (4)	0.89702 (19)	0.0139 (7)
O6	-0.0404 (3)	1.0020 (3)	0.70586 (14)	0.0163 (5)
C6	0.0794 (4)	0.7479 (4)	0.61673 (19)	0.0129 (7)
O7	0.0284 (3)	1.2656 (3)	0.67405 (14)	0.0168 (5)
C7	0.0324 (4)	0.8804 (4)	0.55820 (18)	0.0105 (7)
O8	0.1973 (3)	0.7726 (3)	0.65718 (14)	0.0189 (6)
C8	0.0245 (4)	0.8287 (4)	0.48207 (18)	0.0118 (7)
H8	0.0403	0.7138	0.4700	0.014*
O9	0.0079 (3)	0.6102 (3)	0.61982 (15)	0.0236 (6)
C9	0.0067 (4)	1.0533 (4)	0.57629 (19)	0.0121 (7)
C10	-0.0015 (4)	1.1124 (4)	0.65777 (18)	0.0107 (7)
H10A	0.3331	1.0155	0.9851	0.013*
H10B	0.4337	0.9339	0.9384	0.013*
O10	0.3392 (4)	0.9561 (4)	0.94345 (18)	0.0398 (8)

Atomic displacement parameters (Å²)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Gd1	0.01314 (10)	0.00955 (8)	0.00718 (8)	0.00160 (7)	-0.00007 (6)	-0.00017 (6)
K1	0.0245 (5)	0.0240 (4)	0.0270 (5)	-0.0026 (4)	-0.0061 (4)	0.0027 (3)
O1	0.0190 (15)	0.0213 (13)	0.0278 (15)	-0.0025 (11)	0.0022 (12)	-0.0034 (11)
C1	0.0161 (19)	0.0175 (17)	0.0104 (16)	0.0008 (14)	0.0006 (14)	0.0011 (13)
O2	0.0226 (15)	0.0168 (13)	0.0153 (13)	-0.0012 (11)	-0.0046 (11)	0.0045 (10)
C2	0.0161 (19)	0.0125 (16)	0.0096 (16)	0.0008 (13)	-0.0010 (13)	0.0008 (12)
O3	0.0335 (17)	0.0156 (12)	0.0133 (13)	0.0060 (11)	-0.0071 (12)	-0.0033 (10)
C3	0.0158 (19)	0.0157 (17)	0.0111 (16)	-0.0033 (14)	-0.0003 (14)	0.0000 (13)
O4	0.0225 (15)	0.0206 (13)	0.0109 (12)	-0.0066 (11)	0.0026 (11)	0.0019 (10)
C4	0.0151 (19)	0.0140 (17)	0.0092 (16)	0.0013 (14)	0.0001 (14)	0.0018 (13)
O5	0.0225 (15)	0.0175 (12)	0.0121 (12)	-0.0048 (11)	0.0011 (11)	0.0015 (10)
C5	0.0122 (18)	0.0161 (17)	0.0134 (17)	0.0005 (14)	0.0003 (14)	0.0050 (13)
O6	0.0220 (14)	0.0159 (13)	0.0111 (12)	0.0023 (10)	0.0044 (10)	0.0046 (9)
C6	0.020 (2)	0.0116 (16)	0.0075 (15)	0.0030 (14)	0.0051 (14)	-0.0011 (12)
O7	0.0199 (15)	0.0144 (12)	0.0161 (13)	-0.0036 (10)	0.0023 (11)	-0.0040 (10)
C7	0.0137 (18)	0.0095 (15)	0.0083 (15)	-0.0020 (13)	0.0009 (13)	0.0015 (12)
O8	0.0193 (15)	0.0172 (13)	0.0199 (14)	0.0003 (11)	-0.0055 (11)	0.0045 (10)
C8	0.0151 (19)	0.0109 (16)	0.0096 (16)	0.0013 (13)	0.0026 (13)	-0.0005 (12)
O9	0.0280 (17)	0.0165 (13)	0.0255 (15)	-0.0050 (11)	-0.0090 (12)	0.0082 (11)
C9	0.0133 (18)	0.0117 (16)	0.0112 (16)	-0.0010 (13)	-0.0001 (13)	0.0004 (12)

C10	0.0106 (18)	0.0124 (16)	0.0090 (15)	0.0034 (13)	0.0008 (13)	0.0010 (12)
O10	0.045 (2)	0.046 (2)	0.0290 (17)	-0.0029 (16)	0.0128 (15)	-0.0107 (14)

Geometric parameters (Å, °)

Gd1—O6 ⁱ	2.337 (3)	C2—C4	1.396 (5)
Gd1—O7 ⁱⁱ	2.376 (2)	O3—K1 ⁱⁱ	3.306 (3)
Gd1—O8	2.433 (2)	C3—C4 ^{vii}	1.394 (4)
Gd1—O3	2.441 (2)	C3—H3	0.9300
Gd1—O1	2.447 (3)	O4—C5	1.253 (4)
Gd1—O5 ⁱⁱⁱ	2.451 (2)	O4—Gd1 ^{iv}	2.503 (2)
Gd1—O4 ⁱⁱⁱ	2.503 (2)	O4—K1 ⁱⁱⁱ	2.875 (3)
Gd1—O9	2.520 (3)	C4—C3 ^{vii}	1.394 (4)
Gd1—O2	2.604 (2)	C4—C5	1.502 (5)
Gd1—C6	2.825 (3)	O5—C5	1.266 (4)
Gd1—C5 ⁱⁱⁱ	2.831 (3)	O5—Gd1 ^{iv}	2.451 (2)
Gd1—C1	2.882 (3)	C5—Gd1 ^{iv}	2.831 (3)
K1—O2	2.714 (3)	O6—C10	1.259 (4)
K1—O6	2.783 (3)	O6—Gd1 ^v	2.337 (3)
K1—O8	2.795 (3)	C6—O9	1.249 (4)
K1—O10	2.842 (3)	C6—O8	1.261 (4)
K1—O1 ^{iv}	2.860 (3)	C6—C7	1.504 (4)
K1—O4 ^{iv}	2.875 (3)	O7—C10	1.253 (4)
K1—O7 ⁱ	2.891 (3)	O7—Gd1 ^{vi}	2.376 (2)
K1—O9 ^v	2.893 (3)	O7—K1 ^v	2.891 (3)
K1—C10	3.230 (3)	C7—C8	1.392 (4)
K1—O3 ^{vi}	3.306 (3)	C7—C9	1.402 (5)
K1—Gd1 ^v	3.9912 (10)	C8—C9 ^{viii}	1.396 (4)
O1—K1 ⁱⁱⁱ	2.860 (3)	C8—H8	0.9300
O1—H1A	0.8501	O9—K1 ⁱ	2.893 (3)
O1—H1B	0.8500	C9—C8 ^{viii}	1.396 (4)
C1—O2	1.250 (4)	C9—C10	1.503 (4)
C1—O3	1.263 (4)	O10—H10A	0.8671
C1—C2	1.506 (4)	O10—H10B	0.8656
C2—C3	1.388 (5)		
O6 ⁱ —Gd1—O7 ⁱⁱ	72.72 (8)	O6—K1—O3 ^{vi}	105.99 (7)
O6 ⁱ —Gd1—O8	94.93 (9)	O8—K1—O3 ^{vi}	129.52 (7)
O7 ⁱⁱ —Gd1—O8	123.50 (8)	O10—K1—O3 ^{vi}	79.96 (8)
O6 ⁱ —Gd1—O3	78.90 (9)	O1 ^{iv} —K1—O3 ^{vi}	52.77 (7)
O7 ⁱⁱ —Gd1—O3	105.04 (9)	O4 ^{iv} —K1—O3 ^{vi}	52.76 (7)
O8—Gd1—O3	126.89 (8)	O7 ⁱ —K1—O3 ^{vi}	140.46 (8)
O6 ⁱ —Gd1—O1	140.86 (9)	O9 ^v —K1—O3 ^{vi}	81.54 (7)
O7 ⁱⁱ —Gd1—O1	145.14 (9)	C10—K1—O3 ^{vi}	88.80 (7)
O8—Gd1—O1	72.49 (9)	O2—K1—Gd1 ^v	109.12 (6)
O3—Gd1—O1	79.97 (9)	O6—K1—Gd1 ^v	34.92 (5)
O6 ⁱ —Gd1—O5 ⁱⁱⁱ	149.95 (9)	O8—K1—Gd1 ^v	88.21 (6)
O7 ⁱⁱ —Gd1—O5 ⁱⁱⁱ	78.16 (8)	O10—K1—Gd1 ^v	105.38 (8)

O8—Gd1—O5 ⁱⁱⁱ	94.98 (8)	O1 ^{iv} —K1—Gd1 ^v	155.64 (6)
O3—Gd1—O5 ⁱⁱⁱ	116.41 (8)	O4 ^{iv} —K1—Gd1 ^v	113.43 (6)
O1—Gd1—O5 ⁱⁱⁱ	69.16 (9)	O7 ⁱ —K1—Gd1 ^v	36.12 (5)
O6 ⁱ —Gd1—O4 ⁱⁱⁱ	121.37 (8)	O9 ^v —K1—Gd1 ^v	38.99 (5)
O7 ⁱⁱ —Gd1—O4 ⁱⁱⁱ	71.02 (8)	C10—K1—Gd1 ^v	54.57 (6)
O8—Gd1—O4 ⁱⁱⁱ	143.63 (9)	O3 ^{vi} —K1—Gd1 ^v	109.62 (5)
O3—Gd1—O4 ⁱⁱⁱ	68.24 (8)	O2—K1—Gd1	37.34 (5)
O1—Gd1—O4 ⁱⁱⁱ	79.53 (9)	O6—K1—Gd1	82.38 (5)
O5 ⁱⁱⁱ —Gd1—O4 ⁱⁱⁱ	52.70 (8)	O8—K1—Gd1	34.09 (5)
O6 ⁱ —Gd1—O9	81.44 (9)	O10—K1—Gd1	108.80 (7)
O7 ⁱⁱ —Gd1—O9	71.09 (8)	O1 ^{iv} —K1—Gd1	111.26 (6)
O8—Gd1—O9	52.45 (8)	O4 ^{iv} —K1—Gd1	106.89 (5)
O3—Gd1—O9	160.19 (9)	O7 ⁱ —K1—Gd1	63.78 (5)
O1—Gd1—O9	114.70 (9)	O9 ^v —K1—Gd1	122.78 (6)
O5 ⁱⁱⁱ —Gd1—O9	82.34 (9)	C10—K1—Gd1	92.00 (6)
O4 ⁱⁱⁱ —Gd1—O9	125.60 (8)	O3 ^{vi} —K1—Gd1	155.35 (6)
O6 ⁱ —Gd1—O2	70.03 (8)	Gd1 ^v —K1—Gd1	90.638 (18)
O7 ⁱⁱ —Gd1—O2	139.01 (8)	Gd1—O1—K1 ⁱⁱⁱ	135.72 (11)
O8—Gd1—O2	76.60 (8)	Gd1—O1—H1A	104.3
O3—Gd1—O2	51.49 (8)	K1 ⁱⁱⁱ —O1—H1A	61.0
O1—Gd1—O2	71.01 (9)	Gd1—O1—H1B	103.4
O5 ⁱⁱⁱ —Gd1—O2	139.97 (9)	K1 ⁱⁱⁱ —O1—H1B	120.7
O4 ⁱⁱⁱ —Gd1—O2	115.76 (8)	H1A—O1—H1B	107.7
O9—Gd1—O2	118.52 (8)	O2—C1—O3	121.8 (3)
O6 ⁱ —Gd1—C6	90.28 (9)	O2—C1—C2	120.9 (3)
O7 ⁱⁱ —Gd1—C6	97.28 (10)	O3—C1—C2	117.1 (3)
O8—Gd1—C6	26.43 (9)	O2—C1—Gd1	64.62 (18)
O3—Gd1—C6	150.81 (9)	O3—C1—Gd1	57.19 (17)
O1—Gd1—C6	92.43 (10)	C2—C1—Gd1	171.3 (2)
O5 ⁱⁱⁱ —Gd1—C6	86.17 (9)	C1—O2—Gd1	89.7 (2)
O4 ⁱⁱⁱ —Gd1—C6	138.40 (8)	C1—O2—K1	165.2 (2)
O9—Gd1—C6	26.23 (9)	Gd1—O2—K1	103.46 (8)
O2—Gd1—C6	99.35 (8)	C3—C2—C4	118.7 (3)
O6 ⁱ —Gd1—C5 ⁱⁱⁱ	141.71 (9)	C3—C2—C1	116.3 (3)
O7 ⁱⁱ —Gd1—C5 ⁱⁱⁱ	74.19 (9)	C4—C2—C1	125.0 (3)
O8—Gd1—C5 ⁱⁱⁱ	119.44 (10)	C1—O3—Gd1	97.0 (2)
O3—Gd1—C5 ⁱⁱⁱ	91.69 (9)	C1—O3—K1 ⁱⁱ	155.9 (2)
O1—Gd1—C5 ⁱⁱⁱ	71.17 (9)	Gd1—O3—K1 ⁱⁱ	93.34 (8)
O5 ⁱⁱⁱ —Gd1—C5 ⁱⁱⁱ	26.51 (9)	C2—C3—C4 ^{vii}	121.8 (3)
O4 ⁱⁱⁱ —Gd1—C5 ⁱⁱⁱ	26.26 (9)	C2—C3—H3	119.1
O9—Gd1—C5 ⁱⁱⁱ	105.40 (9)	C4 ^{vii} —C3—H3	119.1
O2—Gd1—C5 ⁱⁱⁱ	130.73 (9)	C5—O4—Gd1 ^{iv}	91.6 (2)
C6—Gd1—C5 ⁱⁱⁱ	112.63 (10)	C5—O4—K1 ⁱⁱⁱ	148.9 (2)
O6 ⁱ —Gd1—C1	72.32 (10)	Gd1 ^{iv} —O4—K1 ⁱⁱⁱ	103.25 (9)
O7 ⁱⁱ —Gd1—C1	123.98 (9)	C3 ^{vii} —C4—C2	119.5 (3)
O8—Gd1—C1	101.85 (9)	C3 ^{vii} —C4—C5	117.5 (3)
O3—Gd1—C1	25.79 (9)	C2—C4—C5	123.0 (3)
O1—Gd1—C1	74.32 (10)	C5—O5—Gd1 ^{iv}	93.7 (2)

O5 ⁱⁱⁱ —Gd1—C1	132.62 (10)	O4—C5—O5	121.6 (3)
O4 ⁱⁱⁱ —Gd1—C1	92.23 (9)	O4—C5—C4	119.8 (3)
O9—Gd1—C1	141.67 (9)	O5—C5—C4	118.6 (3)
O2—Gd1—C1	25.71 (8)	O4—C5—Gd1 ^{iv}	62.10 (18)
C6—Gd1—C1	125.03 (10)	O5—C5—Gd1 ^{iv}	59.77 (18)
C5 ⁱⁱⁱ —Gd1—C1	112.55 (10)	C4—C5—Gd1 ^{iv}	174.2 (2)
O2—K1—O6	116.27 (8)	C10—O6—Gd1 ^v	138.0 (2)
O2—K1—O8	69.09 (7)	C10—O6—K1	99.1 (2)
O6—K1—O8	63.05 (8)	Gd1 ^v —O6—K1	102.10 (9)
O2—K1—O10	72.67 (9)	O9—C6—O8	121.5 (3)
O6—K1—O10	140.08 (10)	O9—C6—C7	119.1 (3)
O8—K1—O10	141.74 (9)	O8—C6—C7	119.1 (3)
O2—K1—O1 ^{iv}	84.58 (8)	O9—C6—Gd1	63.11 (18)
O6—K1—O1 ^{iv}	153.86 (8)	O8—C6—Gd1	59.14 (17)
O8—K1—O1 ^{iv}	115.86 (9)	C7—C6—Gd1	166.0 (2)
O10—K1—O1 ^{iv}	58.46 (9)	C10—O7—Gd1 ^{vi}	147.2 (2)
O2—K1—O4 ^{iv}	123.48 (8)	C10—O7—K1 ^v	114.5 (2)
O6—K1—O4 ^{iv}	83.45 (7)	Gd1 ^{vi} —O7—K1 ^v	98.05 (8)
O8—K1—O4 ^{iv}	76.77 (7)	C8—C7—C9	119.4 (3)
O10—K1—O4 ^{iv}	125.96 (9)	C8—C7—C6	117.3 (3)
O1 ^{iv} —K1—O4 ^{iv}	71.42 (8)	C9—C7—C6	123.2 (3)
O2—K1—O7 ⁱ	73.25 (8)	C6—O8—Gd1	94.4 (2)
O6—K1—O7 ⁱ	58.96 (7)	C6—O8—K1	127.7 (2)
O8—K1—O7 ⁱ	79.25 (8)	Gd1—O8—K1	105.81 (9)
O10—K1—O7 ⁱ	90.92 (9)	C7—C8—C9 ^{viii}	120.9 (3)
O1 ^{iv} —K1—O7 ⁱ	146.80 (8)	C7—C8—H8	119.5
O4 ^{iv} —K1—O7 ⁱ	141.64 (7)	C9 ^{viii} —C8—H8	119.5
O2—K1—O9 ^v	120.23 (8)	C6—O9—Gd1	90.7 (2)
O6—K1—O9 ^v	67.91 (7)	C6—O9—K1 ⁱ	136.5 (2)
O8—K1—O9 ^v	127.17 (8)	Gd1—O9—K1 ⁱ	94.77 (8)
O10—K1—O9 ^v	74.28 (9)	C8 ^{viii} —C9—C7	119.7 (3)
O1 ^{iv} —K1—O9 ^v	116.76 (8)	C8 ^{viii} —C9—C10	118.6 (3)
O4 ^{iv} —K1—O9 ^v	116.29 (8)	C7—C9—C10	121.4 (3)
O7 ⁱ —K1—O9 ^v	59.01 (7)	O7—C10—O6	123.9 (3)
O2—K1—C10	129.24 (8)	O7—C10—C9	119.4 (3)
O6—K1—C10	22.64 (8)	O6—C10—C9	116.7 (3)
O8—K1—C10	63.26 (8)	O7—C10—K1	91.9 (2)
O10—K1—C10	152.09 (10)	O6—C10—K1	58.30 (18)
O1 ^{iv} —K1—C10	131.40 (9)	C9—C10—K1	121.7 (2)
O4 ^{iv} —K1—C10	60.96 (8)	K1—O10—H10A	138.3
O7 ⁱ —K1—C10	81.59 (8)	K1—O10—H10B	102.5
O9 ^v —K1—C10	78.87 (8)	H10A—O10—H10B	106.3
O2—K1—O3 ^{vi}	137.10 (8)		

Symmetry codes: (i) $-x, y-1/2, -z+3/2$; (ii) $x, y-1, z$; (iii) $-x+1, y-1/2, -z+3/2$; (iv) $-x+1, y+1/2, -z+3/2$; (v) $-x, y+1/2, -z+3/2$; (vi) $x, y+1, z$; (vii) $-x+1, -y+1, -z+2$; (viii) $-x, -y+2, -z+1$.