

Acta Crystallographica Section E

Structure Reports

Online

ISSN 1600-5368

Tetramethylammonium borohydride from powder data

 Tomasz Jaroń^{a,*} and Wojciech Grochala^{a,b}
^aFaculty of Chemistry, University of Warsaw, Pasteura 1, 02093 Warsaw, Poland, and ^bICM, University of Warsaw, Pawińskiego 5a, 02106 Warsaw, Poland
Correspondence e-mail: tjaron@chem.uw.edu.pl


Received 15 June 2011; accepted 20 July 2011

 Key indicators: powder X-ray study; $T = 298$ K; mean $\sigma(N-C) = 0.003$ Å; R factor = 0.014; wR factor = 0.020; data-to-parameter ratio = 164.6.

In the crystal structure of the title compound, $C_4H_{12}N^+ \cdot BH_4^-$, the tetramethylammonium cations are situated on special positions with site symmetry $\bar{4}m2$. The borohydride anions are situated on special positions with $4mm$ site symmetry and show rotational disorder around the fourfold axis.

Related literature

For details of the synthesis, see: Banus *et al.* (1952); King *et al.* (1956). For previous studies of the title compound, see: Harmon *et al.* (1974); Eckert *et al.* (2004). The isostructural compounds $(CH_3)_4NClO_4$ and $(CH_3)_4NBF_4$ were reported by McCullough (1964) and Giuseppetti *et al.* (1992), respectively. For applications of the title compound, see: Evans *et al.* (1988).

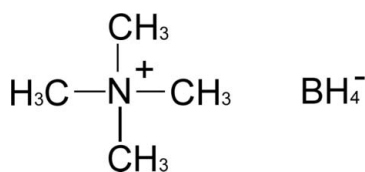

Experimental

Crystal data

 $C_4H_{12}N^+ \cdot BH_4^-$
 $M_r = 88.99$
 Tetragonal, $P4/nmm$
 $a = 7.9133$ (2) Å
 $c = 5.65696$ (17) Å
 $V = 354.24$ (2) Å³
 $Z = 2$
 Cu $K\alpha$ radiation, $\lambda = 1.54051$,
 1.54433 Å
 $\mu = 0.33$ mm⁻¹
 $T = 298$ K
 cylinder, 18×1 mm

Data collection

 Bruker D8 Discover diffractometer
 Specimen mounting: quartz capillary
 Data collection mode: transmission

 Scan method: continuous
 $2\theta_{\min} = 8^\circ$, $2\theta_{\max} = 121^\circ$,
 $2\theta_{\text{step}} = 0.012^\circ$

Refinement

 $R_p = 0.014$
 $R_{wp} = 0.020$
 $R_{\text{exp}} = 0.007$
 $R_{\text{Bragg}} = 0.053$
 $\chi^2 = 7.673$
 9220 data points

 56 parameters
 14 restraints
 H atoms treated by a mixture of independent and constrained refinement

Data collection: *DIFFRACplus* (Bruker, 2006); cell refinement: *X-CELL* (Neumann, 2003) and *JANA2006* (Petricek *et al.*, 2006); data reduction: *DIFFRACplus*; program(s) used to solve structure: *JANA2006*; program(s) used to refine structure: *JANA2006*; molecular graphics: *CrystalMaker* (Palmer, 2005); software used to prepare material for publication: *publCIF* (Westrip, 2010).

Przemysław Malinowski MSc and Dominik Kurzydłowski MSc are acknowledged for discussions about *JANA2006*, and Armand Budzianowski PhD for help with CIF preparation and discussions.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: CV5120).

References

- Banus, M. D., Bragdon, R. W. & Gibb, T. R. P. Jr (1952). *J. Am. Chem. Soc.* **74**, 2346–2348.
- Bruker (2006). *DIFFRACplus*. Bruker AXS Inc., Madison, Wisconsin, USA.
- Eckert, J., Sewell, T. D., Kress, J. D., Kober, E. M., Wang, L. L. & Olah, G. (2004). *J. Phys. Chem. A*, **108**, 11369–11374.
- Evans, D. A., Chapman, K. T. & Carreira, M. (1988). *J. Am. Chem. Soc.* **110**, 3560–3578.
- Giuseppetti, G., Mazzi, F., Tadani, C., Ferloni, P. & Torre, S. (1992). *Z. Kristallogr.* **202**, 81–88.
- Harmon, K. M., Gennick, I. & Madeira, S. L. (1974). *J. Phys. Chem.* **78**, 2585–2591.
- King, A. J., Kanda, F. A., Russel, V. A. & Katz, W. (1956). *J. Am. Chem. Soc.* **78**, 4176.
- McCullough, J. D. (1964). *Acta Cryst.* **17**, 1067–1070.
- Neumann, M. A. (2003). *J. Appl. Cryst.* **36**, 356–365.
- Palmer, D. (2005). *CrystalMaker*. CrystalMaker Software Ltd, Oxfordshire, England.
- Petricek, V., Dusek, M. & Palatinus, L. (2006). *JANA2006*. Institute of Physics, Praha, Czech Republic.
- Westrip, S. P. (2010). *J. Appl. Cryst.* **43**, 920–925.

supporting information

Acta Cryst. (2011). E67, o2171 [doi:10.1107/S1600536811029291]

Tetramethylammonium borohydride from powder data

Tomasz Jaroń and Wojciech Grochala

S1. Comment

Tetramethylammonium borohydride (I) and its derivatives have been used as selective reductors in organic chemistry (Evans *et al.*, 1988) or as a source of hydrogen-rich BH_4^- anions for inorganic synthesis.

The structure of compound (I) has not been reported before; only the unit-cell parameters ($a = 7.29 \text{ \AA}$, $c = 5.696 \text{ \AA}$), the tentative space group (P4/n) (King *et al.*, 1956) and several interatomic distances (Eckert *et al.*, 2004) have been given. The structure presented here is isomorphous to the ambient temperature structures of $(\text{CH}_3)_4\text{NBF}_4$ (Giuseppetti *et al.*, 1992) and $(\text{CH}_3)_4\text{NClO}_4$ (McCullough, 1964) and is composed of distinct $(\text{CH}_3)_4\text{N}^+$ cations and BH_4^- anions.

The central atoms of the ions are separated by $d(\text{N1}, \text{B1}) = 4.537 (4) \text{ \AA}$, which compares well with the shortest N—B distances seen for fluoroborate (4.79 \AA , s.u. not given in the paper) and N—Cl distances in perchlorate (4.86 \AA , s.u. not given in the paper). Methyl groups in (I) are ordered (in contrast to $(\text{CH}_3)_4\text{NClO}_4$, where the hydrogen positions are disordered) and arranged in a staggered conformation like in $(\text{CH}_3)_4\text{NBF}_4$. This is explained by an increasing separation of cations as measured by $d(\text{N}—\text{N}')$ distance of $5.5955 (2)$, 5.82 (s.u. not given in the paper), and 5.90 (s.u. not given in the paper) for (I), $(\text{CH}_3)_4\text{NBF}_4$, and $(\text{CH}_3)_4\text{NClO}_4$, respectively. The borohydride anions are centred at $2c$ (4 mm) site with B1 and H3 atoms at the fourfold symmetry axis, while H4 and H5 are used for the representation of disorder (four BH_4^- tetrahedra sharing vertex of H3 can be constructed). The B—H infrared absorption bands ($\delta_{\text{H}—\text{B}—\text{H}} = 1072 \text{ cm}^{-1}$, $\nu_{\text{B}—\text{H}} = 2225 \text{ cm}^{-1}$ and 2288 cm^{-1}) are very broad, up to *ca* 800 cm^{-1} for stretching bands (!), which confirms H disorder of the BH_4^- anions in compound (I) (Harmon *et al.*, 1974). In such arrangement the closest distances between hydrogen atoms of $(\text{CH}_3)_4\text{N}^+$ and BH_4^- are: $d(\text{H1}—\text{H3}) = 2.39 (2) \text{ \AA}$, $d(\text{H2}—\text{H4}) = 2.47 (3) \text{ \AA}$ and $d(\text{H2}—\text{H5}) = 2.49 (3) \text{ \AA}$, thus above the maximum range of a typical dihydrogen bond length of 2.2 \AA .

S2. Experimental

Compound (I) commercially available from Sigma-Aldrich (> 95%) has been used for powder XRD measurements without additional purification. The FTIR spectrum of compound (I) in KBr pellet has been recorded using Bruker Vertex 80v vacuum spectrometer.

S3. Refinement

The powder diffraction pattern of (I) was indexed with X-Cell (Neumann, 2003) in a tetragonal system of extinction class P4/nmm. The initial model of the structure of compound (I) was constructed according to the symmetry considerations, with all heavy atoms at special positions: N1 at $2b$ ($\bar{4}m2$), C1 at $8i$ (m), and B1 at $2c$ (4 mm). H1 and H2 (hydrogen atoms of the methyl groups) were placed at sites $8i$ (m), and $16k$ (1), respectively. An alternative structure with disordered methyl groups led to a worse Rietveld fit. Location of the hydrogen atoms of BH_4^- group was more problematic, as the tetragonal axis is incompatible with the symmetry elements of tetrahedron. The model containing four overlapping BH_4^- tetrahedra has been used for the Rietveld refinement performed using Jana2006 (Petricek *et al.* 2006). The following

restraints have been applied for the refinement: $d(\text{C1—H1}), d(\text{C1—H2}) = 1.00 \text{ s.u.} = 0.005 \text{ [\AA]}$, $d(\text{B1—H3}) = 1.12, \text{ s.u.} = 0.005 \text{ [\AA]}$, $d(\text{B1—H4}), d(\text{B1—H5}) = 1.12, \text{ s.u.} = 0.01 \text{ [\AA]}$; $a(\text{Hi—C1—Hj}), a(\text{Hi—C1—N1}) = 109.47, \text{ s.u.} = 0.01 \text{ [^\circ]}$, and $a(\text{H3—B1—H4}), a(\text{H3—B1—H5}), a(\text{H4—B1—H5}) = 109.47, \text{ s.u.} = 0.01 \text{ [^\circ]}$. The atomic displacement parameters (ADP) of hydrogen atoms were restricted according to the riding model to $U_{\text{isoH1}} = U_{\text{isoH2}} = 1.2U_{\text{isoC1}}$ and $U_{\text{isoH3}} = U_{\text{isoH4}} = U_{\text{isoH5}} = 1.5U_{\text{isoB1}}$.

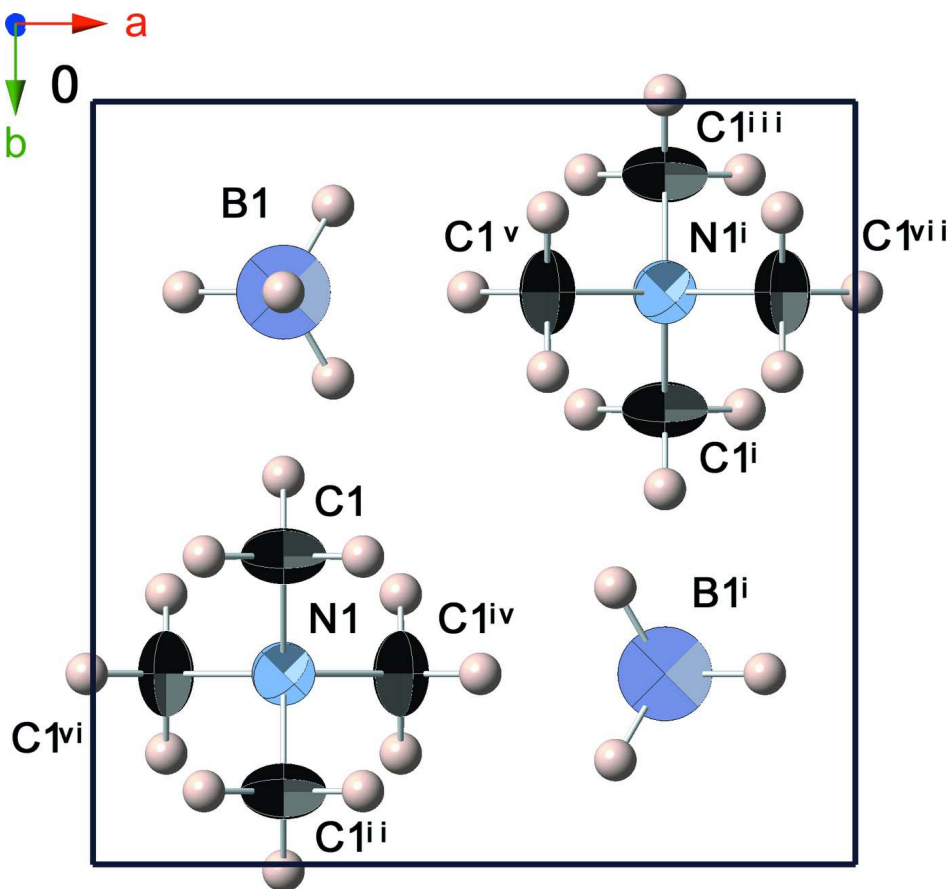


Figure 1

A content of the unit cell of (I) viewed along axis c and showing the atomic labelling and 50% probability displacement ellipsoids [symmetry codes: (i) $-x + 1, -y + 1, -z + 1$; (ii) $-x + 1/2, -y + 3/2, z$; (iii) $x + 1/2, y - 1/2, -z + 1$; (iv) $-y + 1, x + 1/2, -z + 1$; (v) $y, -x + 1/2, z$; (vi) $y - 1/2, -x + 1, -z + 1$; (vii) $-y + 3/2, x, z$]. The H atoms are shown as spheres of arbitrary radius. Only one orientation of disordered BH_4 anions is shown for clarity.


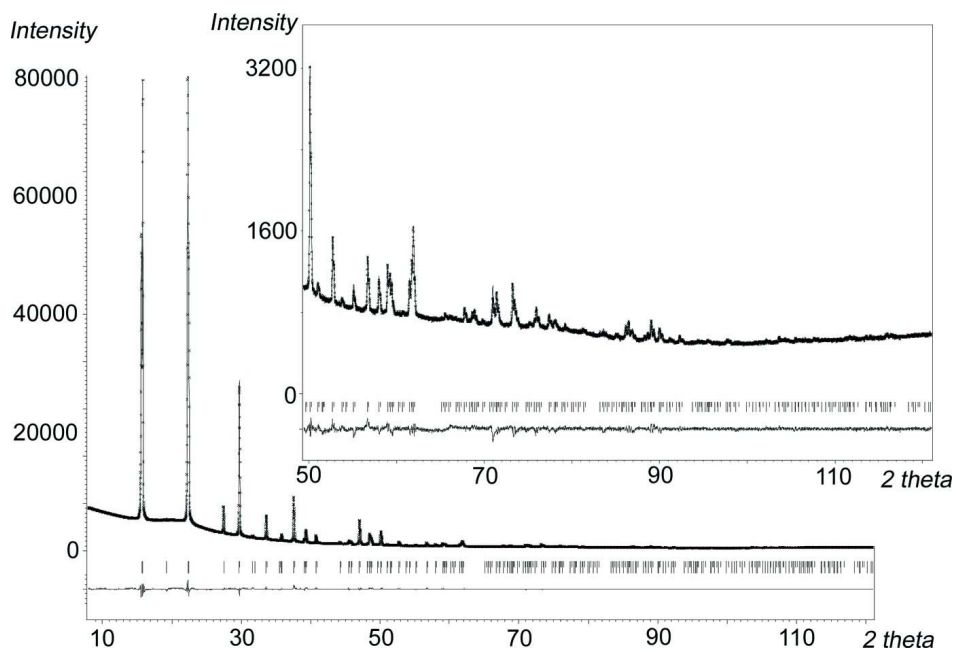


Figure 2

The results of Rietveld refinement. Measured data are given as asterisks, the calculated profile as a solid line, and the difference profile as a solid line below. Vertical markers above the difference profile indicate the calculated Bragg reflection positions. The insert shows high-angle part magnified *ca* 18 times.

tetramethylammonium borohydride

Crystal data



$M_r = 88.99$

Tetragonal, $P4/nmm$

Hall symbol: $-P\ 4a\ 2a$

$a = 7.9133\ (2)\ \text{\AA}$

$c = 5.65696\ (17)\ \text{\AA}$

$V = 354.24\ (2)\ \text{\AA}^3$

$Z = 2$

$F(000) = 104$

$D_x = 0.834\ \text{Mg m}^{-3}$

$D_m = 0.813\ \text{Mg m}^{-3}$

D_m measured by helium pycnometry (Banus et al., 1952)

Cu $K\alpha$ radiation, $\lambda = 1.54051, 1.54433\ \text{\AA}$

$\mu = 0.33\ \text{mm}^{-1}$

$T = 298\ \text{K}$

white

cylinder, $18 \times 1\ \text{mm}$

Specimen preparation: Prepared at 298 K

Data collection

Bruker D8 Discover
diffractometer

None monochromator

Specimen mounting: quartz capillary

Data collection mode: transmission

Scan method: continuous

$2\theta_{\min} = 8^\circ$, $2\theta_{\max} = 120.999^\circ$, $2\theta_{\text{step}} = 0.012^\circ$

Refinement

$R_p = 0.014$

$R_{\text{wp}} = 0.020$

$R_{\text{exp}} = 0.007$

$R_{\text{Bragg}} = 0.053$

$\chi^2 = 7.673$

9220 data points

Profile function: Pseudo-Voigt

56 parameters

14 restraints

2 constraints

All H-atom parameters refined

Weighting scheme based on measured s.u.'s $w = 1/[\sigma^2(I) + 0.0016I^2]$
 $(\Delta/\sigma)_{\max} = 0.009$

Background function: 25 Legendre polynoms
 Preferred orientation correction: none

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	<i>x</i>	<i>y</i>	<i>z</i>	$U_{\text{iso}}^*/U_{\text{eq}}$	Occ. (<1)
H4	0.315 (2)	0.363 (4)	0.957 (3)	0.14971 (4)*	0.25
H2	0.1457 (17)	0.5963 (4)	0.2429 (17)	0.10060 (2)*	
B1	0.25	0.25	0.8925 (14)	0.084 (5)	
H3	0.25	0.25	0.702 (4)	0.14971 (4)*	
C1	0.25	0.5959 (3)	0.3460 (5)	0.065 (2)	
H1	0.25	0.492 (2)	0.4477 (19)	0.10060 (2)*	
H5	0.25	0.119 (5)	0.957 (3)	0.14971 (4)*	0.25
N1	0.25	0.75	0.5	0.045 (3)	

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
B1	0.100 (7)	0.100 (7)	0.053 (9)	0	0	0
C1	0.084 (4)	0.036 (3)	0.075 (4)	0	0	-0.013 (3)
N1	0.045 (4)	0.045 (4)	0.045 (7)	0	0	0

Geometric parameters (\AA , $^\circ$)

B1—H3	1.08 (2)	C1—H1	1.004 (15)
B1—H4	1.10 (3)	C1—H2	1.010 (12)
B1—H5	1.10 (4)	C1—N1	1.498 (3)
H1—C1—H2	109.5 (5)	H4—B1—H4 ⁱⁱ	109.5 (16)
H2—C1—N1	109.5 (4)	H4—B1—H5 ⁱⁱⁱ	109.5 (12)
H2—C1—H2 ⁱ	109.5 (9)	C1—N1—C1 ^{iv}	108.91 (14)
H3—B1—H5	109.5 (12)	C1—N1—C1 ^v	109.75 (7)
H4—B1—H3	109.5 (10)		

Symmetry codes: (i) $-x+1/2, y, z$; (ii) $x, -y+1/2, z$; (iii) $y, -x+1/2, z$; (iv) $-x+1/2, -y+3/2, z$; (v) $y-1/2, x+1/2, -z+1$.