

catena-Poly[[3-methylpyridine)-copper(I)]- μ -cyanido-copper(I)- μ -cyanido]

Jin-Biao Cai, Ting-Ting Chen, Ze-Ying Xie and Hong Deng*

School of Chemistry and Environment, South China Normal University, Guangzhou 510006, People's Republic of China

Correspondence e-mail: dh@sncnu.edu.cn


Received 16 April 2011; accepted 15 July 2011

Key indicators: single-crystal X-ray study; $T = 296$ K; mean $\sigma(\text{C}-\text{C}) = 0.005$ Å; disorder in main residue; R factor = 0.042; wR factor = 0.118; data-to-parameter ratio = 16.1.

In the title complex, $[\text{Cu}_2(\text{CN})_2(\text{C}_6\text{H}_7\text{N})]_n$, there are two copper atoms with different coordination environments. One Cu atom (Cu1) is linked to the two cyanide ligands, one N atom from a pyridine ring while the other (Cu2) is coordinated by the two cyanide ligands in a slightly distorted tetrahedral geometry and linked to Cu1, forming a triangular coordination environment. The Cu atoms are bridged by bidentate cyanide ligands, forming an infinite Cu–CN chain. One cyanide ligand is equally disordered over two sets of sites, exchanging C and N atoms coordinated to both metal atoms. However, one cyanide group is not disordered and it coordinates to Cu1 via the N atom whereas its C-atom counterpart coordinates Cu2. The 3-methylpyridine (3MP) ligand coordinates through the N atom to Cu1 as a terminal ligand, which originates from decyanation of 3-pyridylacetonitrile under hydrothermal conditions. Adjacent Cu–CN chains are interconnected through $\text{Cu}\cdots\text{Cu}$ interactions [$2.8364(10)$ Å], forming a three-dimensional framework.

Related literature

For applications of coordination polymers, see: Gu & Xue (2007); Cheng *et al.* (2007); Ley *et al.* (2010); Etaiw *et al.* (2009); Li *et al.* (2009).

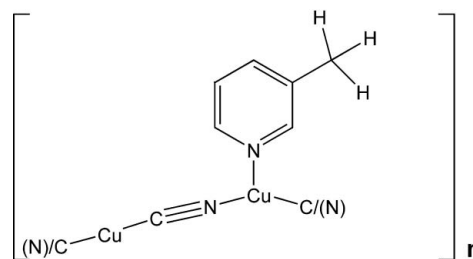

Experimental

Crystal data

$[\text{Cu}_2(\text{CN})_2(\text{C}_6\text{H}_7\text{N})]$

$M_r = 272.27$

Monoclinic, $P2_1/c$

$a = 9.3027(18)$ Å

$b = 12.090(2)$ Å

$c = 8.8738(17)$ Å

$\beta = 105.927(2)^\circ$

$V = 959.7(3)$ Å³

$Z = 4$

Mo $K\alpha$ radiation

$\mu = 4.38$ mm⁻¹

$T = 296$ K

$0.15 \times 0.12 \times 0.10$ mm

Data collection

Bruker SMART APEX CCD diffractometer

Absorption correction: multi-scan (SADABS; Bruker, 2004)

$T_{\min} = 0.559$, $T_{\max} = 0.668$

4802 measured reflections

1725 independent reflections

1396 reflections with $I > 2\sigma(I)$

$R_{\text{int}} = 0.035$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.042$

$wR(F^2) = 0.118$

$S = 1.03$

1725 reflections

107 parameters

2 restraints

H-atom parameters constrained

$\Delta\rho_{\text{max}} = 0.76$ e Å⁻³

$\Delta\rho_{\text{min}} = -0.77$ e Å⁻³

Table 1

Selected bond lengths (Å).

N1–Cu1	2.057 (2)	C9–Cu2	1.838 (5)
C7–Cu2	1.839 (4)	Cu1–N2	1.891 (4)
C8–Cu1	1.886 (4)		

Data collection: APEX2 (Bruker, 2004); cell refinement: SAINT (Bruker, 2004); data reduction: SAINT; program(s) used to solve structure: SHELXS97 (Sheldrick, 2008); program(s) used to refine structure: SHELXL97 (Sheldrick, 2008); molecular graphics: SHELXTL (Sheldrick, 2008); software used to prepare material for publication: SHELXTL.

The authors acknowledge South China Normal University and the National Natural Science Foundation of China (grant No. 20871048) for supporting this work.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: KP2324).

References

- Bruker (2004). *APEX2, SAINT and SADABS*. Bruker AXS Inc., Madison, Wisconsin, USA.
- Cheng, J. W., Zheng, S. T., Ma, E. & Yang, G. Y. (2007). *Inorg. Chem.* **46**, 10534–10538.
- Etaiw, S., El-din, H., Amer, S. A. & El-bendary, M. M. (2009). *Polyhedron*, **28**, 2385–2390.
- Gu, X. & Xue, D. F. (2007). *CrystEngComm*, **9**, 471–477.
- Ley, A. N., Dunaway, L. E., Brewster, T. P., Dembo, M. D., Harris, T. D., Brill-Robert, F., Li, X. B., Patterson, H. H. & Pike, R. B. (2010). *Chem. Commun.* **46**, 4565–4567.
- Li, Z. Y., Wang, N., Dai, J. W., Yue, S. T. & Li, Y. L. (2009). *CrystEngComm*, **11**, 2003–2008.
- Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.

supporting information

Acta Cryst. (2011). E67, m1136–m1137 [doi:10.1107/S1600536811028509]

catena-Poly[[3-methylpyridine)copper(I)]- μ -cyanido-copper(I)- μ -cyanido]**Jin-Biao Cai, Ting-Ting Chen, Ze-Ying Xie and Hong Deng****S1. Comment**


Much attention has been focused on the rational design and synthesis of coordination polymers due to their intriguing structural features as well as potential applications in catalysis, fluorescence, and as chemical sensors (Gu *et al.*, 2007; Cheng *et al.*, 2007; Ley *et al.*, 2010; Etaiw *et al.*, 2009). Some polymers with rigid ligands such as isonicotinic acid has been reported (Li *et al.*, 2009). A cyano group is a well bridging ligand, which plays an important role in assembling of polymers acting as a monodentate, bidentate or tridentate ligand (Ley *et al.*, 2010). A careful review of the literature suggests that 3-methylpyridine(3MP) use as a ligand to construct metal coordination framework has not been reported yet. Herein, we report the title complex synthesised by the reaction of cuprous cyanide and 3PAT ligands under hydrothermal conditions. Cu1 is coordinated by two cyano ligands, one nitrogen atom from pyridine ring and Cu2 centre with the Cu \cdots Cu distance of 2.836 (4) Å, forming a slightly distorted tetrahedral coordination. Cu2 is coordinated by a carbon atom from one cyano ligand, whereas the second coordination sites is occupied either by N or C atoms (due to the disorder of ligand), and Cu1 centre forming a triangular coordination environment (Fig. 1, Table 1). The adjacent copper-cyano chains are joined through the Cu \cdots Cu interaction forming a three dimensional framework. The site occupancy of cyano ligands C9 \equiv N4 and C8 \equiv N3 is 0.5, each.

S2. Experimental

A mixture of 3-pyridylacetonitrile (2 mL), cuprous cyanide (0.092 g; 0.1 mmol), strong ammonia water (2 mL) and 8 mL water were sealed in a 23 mL teflon reactor, and the mixture was heated at 443 K for 3 d then cooled to room temperature at a rate of 5 K / h. Yellow crystals were obtained in a yield of 37% based on Cu.

S3. Refinement

All H atoms were placed in calculated positions and refined using a Riding model, with (C—H= 0.93–0.96 Å), and with $U_{\text{iso}}(\text{H}) = 1.2 U_{\text{eq}}(\text{C})$ for methyl H atoms. Two of the cyano ligands are disordered over two sites with occupancies 0.5:0.5.

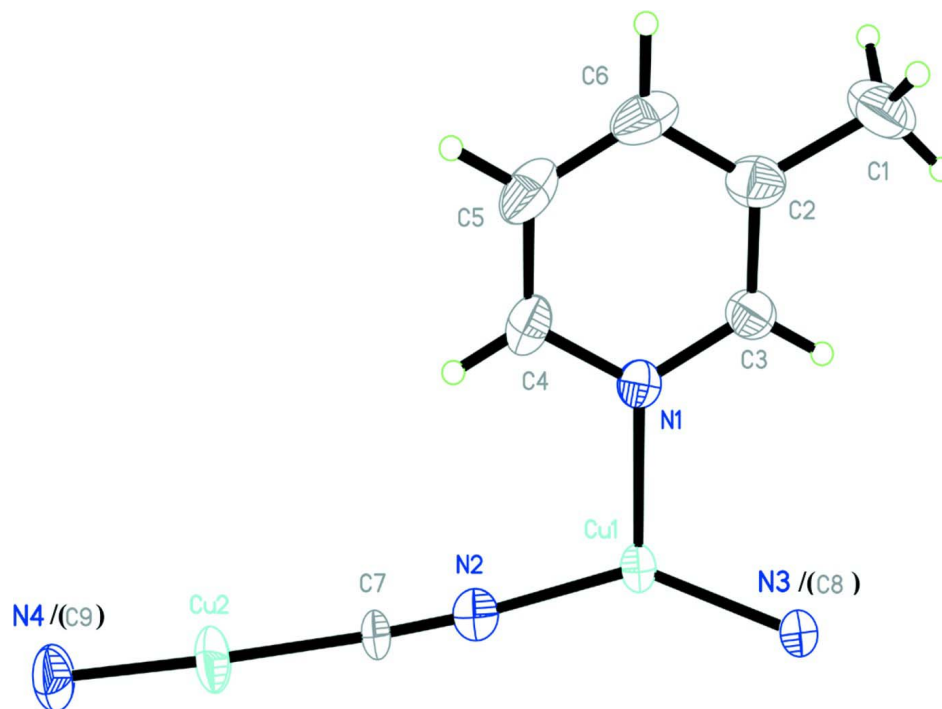**Figure 1**

The asymmetric unit of the title complex. Non-H atoms are shown as 50% probability displacement ellipsoids. Two of the cyano ligands N3/(C8) and N4/(C9) are disordered over two sites with occupancy 0.5, each.

catena-Poly[[3-methylpyridine)copper(I)]- μ -cyanido-copper(I)- μ -cyanido]

Crystal data

[Cu₂(CN)₂(C₆H₇N)]

$M_r = 272.27$

Monoclinic, $P2_1/c$

Hall symbol: -P 2ybc

$a = 9.3027 (18) \text{ \AA}$

$b = 12.090 (2) \text{ \AA}$

$c = 8.8738 (17) \text{ \AA}$

$\beta = 105.927 (2)^\circ$

$V = 959.7 (3) \text{ \AA}^3$

$Z = 4$

$F(000) = 536$

$D_x = 1.884 \text{ Mg m}^{-3}$

Mo $K\alpha$ radiation, $\lambda = 0.71073 \text{ \AA}$

Cell parameters from 1725 reflections

$\theta = 2.3\text{--}25.2^\circ$

$\mu = 4.38 \text{ mm}^{-1}$

$T = 296 \text{ K}$

Block, yellow

$0.15 \times 0.12 \times 0.10 \text{ mm}$

Data collection

Bruker SMART APEX CCD
diffractometer

Radiation source: fine-focus sealed tube

Graphite monochromator

ω scans

Absorption correction: multi-scan

(*SADABS*; Bruker, 2004)

$T_{\min} = 0.559$, $T_{\max} = 0.668$

4802 measured reflections

1725 independent reflections

1396 reflections with $I > 2\sigma(I)$

$R_{\text{int}} = 0.035$

$\theta_{\max} = 25.2^\circ$, $\theta_{\min} = 2.3^\circ$

$h = -10 \rightarrow 11$

$k = -13 \rightarrow 14$

$l = -10 \rightarrow 10$

Refinement

Refinement on F^2

Least-squares matrix: full

$R[F^2 > 2\sigma(F^2)] = 0.042$

$wR(F^2) = 0.118$

$S = 1.03$

1725 reflections

107 parameters

2 restraints

Primary atom site location: structure-invariant
direct methods

Secondary atom site location: difference Fourier
map

Hydrogen site location: inferred from
neighbouring sites

H-atom parameters constrained

$w = 1/[\sigma^2(F_o^2) + (0.0603P)^2 + 1.271P]$

where $P = (F_o^2 + 2F_c^2)/3$

$(\Delta/\sigma)_{\max} = 0.001$

$\Delta\rho_{\max} = 0.76 \text{ e } \text{\AA}^{-3}$

$\Delta\rho_{\min} = -0.77 \text{ e } \text{\AA}^{-3}$

Special details

Geometry. All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

Refinement. Refinement of F^2 against ALL reflections. The weighted R -factor wR and goodness of fit S are based on F^2 , conventional R -factors R are based on F , with F set to zero for negative F^2 . The threshold expression of $F^2 > \sigma(F^2)$ is used only for calculating R -factors(gt) etc. and is not relevant to the choice of reflections for refinement. R -factors based on F^2 are statistically about twice as large as those based on F , and R -factors based on ALL data will be even larger.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	x	y	z	$U_{\text{iso}}^*/U_{\text{eq}}$	Occ. (<1)
C1	0.3796 (8)	0.8237 (6)	-0.1465 (8)	0.085 (2)	
H1A	0.4815	0.8216	-0.0832	0.127*	
H1B	0.3695	0.8783	-0.2273	0.127*	
H1C	0.3520	0.7525	-0.1933	0.127*	
C2	0.2797 (3)	0.8529 (3)	-0.0463 (4)	0.0574 (13)	
C3	0.1740 (4)	0.7751 (2)	-0.0325 (3)	0.0514 (12)	
H3	0.1677	0.7076	-0.0843	0.062*	
N1	0.0778 (3)	0.7981 (2)	0.0587 (3)	0.0464 (9)	
C4	0.0872 (3)	0.8990 (2)	0.1361 (4)	0.0539 (12)	
H4	0.0228	0.9144	0.1971	0.065*	
C5	0.1929 (4)	0.9768 (2)	0.1222 (4)	0.0705 (16)	
H5	0.1992	1.0442	0.1740	0.085*	
C6	0.2891 (4)	0.9537 (3)	0.0310 (5)	0.0703 (16)	
H6	0.3599	1.0057	0.0218	0.084*	
C7	-0.2726 (5)	0.7996 (4)	0.2481 (5)	0.0447 (11)	
C8	-0.0191 (5)	0.5420 (3)	0.0191 (5)	0.0479 (10)	0.50
C9	-0.4653 (6)	0.9731 (5)	0.4697 (6)	0.0674 (14)	0.50
Cu1	-0.07682 (7)	0.68136 (4)	0.07839 (7)	0.0473 (2)	
Cu2	-0.35513 (8)	0.88478 (6)	0.37450 (8)	0.0680 (3)	
N2	-0.2093 (5)	0.7508 (4)	0.1768 (5)	0.0576 (11)	
N3	-0.0191 (5)	0.5420 (3)	0.0191 (5)	0.0479 (10)	0.50
N4	-0.4653 (6)	0.9731 (5)	0.4697 (6)	0.0674 (14)	0.50

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
C1	0.069 (4)	0.102 (5)	0.097 (5)	-0.027 (4)	0.045 (4)	-0.012 (4)
C2	0.052 (3)	0.061 (3)	0.058 (3)	-0.013 (3)	0.012 (3)	-0.001 (3)
C3	0.057 (3)	0.051 (3)	0.050 (3)	-0.010 (2)	0.020 (2)	-0.008 (2)
N1	0.056 (2)	0.040 (2)	0.047 (2)	-0.0042 (18)	0.0218 (18)	-0.0066 (17)
C4	0.066 (3)	0.040 (3)	0.052 (3)	0.010 (2)	0.012 (2)	-0.004 (2)
C5	0.071 (4)	0.043 (3)	0.089 (4)	-0.005 (3)	0.008 (3)	-0.015 (3)
C6	0.066 (4)	0.046 (3)	0.093 (4)	-0.017 (3)	0.011 (3)	0.000 (3)
C7	0.052 (3)	0.038 (3)	0.050 (2)	0.0047 (19)	0.025 (2)	-0.0047 (19)
C8	0.059 (3)	0.038 (2)	0.057 (2)	0.0056 (19)	0.034 (2)	-0.0012 (19)
C9	0.073 (3)	0.069 (3)	0.066 (3)	0.026 (3)	0.029 (3)	-0.009 (3)
Cu1	0.0561 (4)	0.0377 (4)	0.0583 (4)	0.0040 (2)	0.0328 (3)	-0.0070 (2)
Cu2	0.0727 (5)	0.0675 (5)	0.0772 (5)	0.0212 (4)	0.0429 (4)	-0.0155 (4)
N2	0.067 (3)	0.050 (3)	0.068 (3)	0.007 (2)	0.038 (2)	-0.008 (2)
N3	0.059 (3)	0.038 (2)	0.057 (2)	0.0056 (19)	0.034 (2)	-0.0012 (19)
N4	0.073 (3)	0.069 (3)	0.066 (3)	0.026 (3)	0.029 (3)	-0.009 (3)

Geometric parameters (\AA , $^\circ$)

C1—C2	1.493 (6)	C5—H5	0.9300
C1—H1A	0.9600	C6—H6	0.9300
C1—H1B	0.9600	C7—N2	1.140 (5)
C1—H1C	0.9600	C7—Cu2	1.839 (4)
C2—C3	1.3900	C8—N3 ⁱ	1.158 (8)
C2—C6	1.3900	C8—C8 ⁱ	1.158 (8)
C3—N1	1.3900	C8—Cu1	1.886 (4)
C3—H3	0.9300	C9—N4 ⁱⁱ	1.150 (9)
N1—C4	1.3900	C9—C9 ⁱⁱ	1.150 (9)
N1—Cu1	2.057 (2)	C9—Cu2	1.838 (5)
C4—C5	1.3900	Cu1—N2	1.891 (4)
C4—H4	0.9300	Cu1—Cu2 ⁱⁱⁱ	2.8364 (10)
C5—C6	1.3900	Cu2—Cu1 ^{iv}	2.8364 (10)
C2—C1—H1A	109.5	C5—C6—C2	120.0
C2—C1—H1B	109.5	C5—C6—H6	120.0
H1A—C1—H1B	109.5	C2—C6—H6	120.0
C2—C1—H1C	109.5	N2—C7—Cu2	173.8 (5)
H1A—C1—H1C	109.5	N3 ⁱ —C8—C8 ⁱ	0.0 (5)
H1B—C1—H1C	109.5	N3 ⁱ —C8—Cu1	178.1 (5)
C3—C2—C6	120.0	C8 ⁱ —C8—Cu1	178.1 (5)
C3—C2—C1	117.6 (3)	N4 ⁱⁱ —C9—C9 ⁱⁱ	0.0 (5)
C6—C2—C1	122.4 (3)	N4 ⁱⁱ —C9—Cu2	178.9 (8)
C2—C3—N1	120.0	C9 ⁱⁱ —C9—Cu2	178.9 (8)
C2—C3—H3	120.0	C8—Cu1—N2	142.80 (19)
N1—C3—H3	120.0	C8—Cu1—N1	109.28 (15)
C4—N1—C3	120.0	N2—Cu1—N1	107.10 (16)

C4—N1—Cu1	120.73 (15)	C8—Cu1—Cu2 ⁱⁱⁱ	81.38 (15)
C3—N1—Cu1	119.27 (15)	N2—Cu1—Cu2 ⁱⁱⁱ	79.83 (14)
N1—C4—C5	120.0	N1—Cu1—Cu2 ⁱⁱⁱ	132.57 (9)
N1—C4—H4	120.0	C9—Cu2—C7	169.9 (2)
C5—C4—H4	120.0	C9—Cu2—Cu1 ^{iv}	113.40 (17)
C6—C5—C4	120.0	C7—Cu2—Cu1 ^{iv}	76.72 (15)
C6—C5—H5	120.0	C7—N2—Cu1	170.8 (5)
C4—C5—H5	120.0		

Symmetry codes: (i) $-x, -y+1, -z$; (ii) $-x-1, -y+2, -z+1$; (iii) $x, -y+3/2, z-1/2$; (iv) $x, -y+3/2, z+1/2$.