



Acta Crystallographica Section E

## Structure Reports

Online

ISSN 1600-5368

NaFe(TeO<sub>3</sub>)<sub>2</sub>

Matthias Weil\* and Berthold Stöger

Institute for Chemical Technologies and Analytics, Division of Structural Chemistry, Vienna University of Technology, Getreidemarkt 9/164-SC, A-1060 Vienna, Austria  
Correspondence e-mail: mweil@mail.zserv.tuwien.ac.at

Received 29 November 2007; accepted 4 December 2007

Key indicators: single-crystal X-ray study;  $T = 293$  K; mean  $\sigma(\text{Te}-\text{O}) = 0.004$  Å;  
R factor = 0.027;  $wR$  factor = 0.061; data-to-parameter ratio = 17.6.

The hydrothermally prepared title compound, sodium iron(III) bis[trioxotellurate(IV)], is isotypic with its Ga<sup>III</sup> analogue and consists of corrugated layers with an overall composition of [FeTe<sub>2</sub>O<sub>6</sub>]<sup>−</sup> together with Na<sup>+</sup> cations. The layers extend parallel to (001) and are made up of [Fe<sub>2</sub>O<sub>10</sub>] edge-shared octahedral dimers and TeO<sub>3</sub> trigonal pyramids sharing vertices. The Na<sup>+</sup> cations are located in the cavities of this arrangement and link adjacent [FeTe<sub>2</sub>O<sub>6</sub>]<sup>−</sup> layers *via* distorted [NaO<sub>8</sub>] polyhedra.

## Related literature

For the isotypic structure NaGa(TeO<sub>3</sub>)<sub>2</sub>, see: Miletich & Pertlik (1998). For related structures, see: Weil (2005, 2007); Weil & Stöger (2007). For a review on the crystal chemistry of tellurate(IV) oxocompounds, see: Dolgikh (1991).

## Experimental

## Crystal data

NaFe(TeO <sub>3</sub> ) <sub>2</sub>	$V = 1102.5$ (4) Å <sup>3</sup>
$M_r = 430.04$	$Z = 8$
Orthorhombic, $Pcab$	Mo $K\alpha$ radiation
$a = 7.8530$ (15) Å	$\mu = 13.15$ mm <sup>−1</sup>
$b = 10.448$ (2) Å	$T = 293$ (2) K
$c = 13.438$ (3) Å	$0.08 \times 0.02 \times 0.01$ mm

## Data collection

Bruker SMART APEX CCD diffractometer	Absorption correction: multi-scan (SADABS; Bruker, 2002)
	$T_{\min} = 0.405$ , $T_{\max} = 0.858$

11127 measured reflections  
1598 independent reflections

1329 reflections with  $I > 2\sigma(I)$   
 $R_{\text{int}} = 0.053$

## Refinement

$R[F^2 > 2\sigma(F^2)] = 0.027$   
 $wR(F^2) = 0.061$   
 $S = 1.03$   
1598 reflections

91 parameters  
 $\Delta\rho_{\text{max}} = 1.77$  e Å<sup>−3</sup>  
 $\Delta\rho_{\text{min}} = -0.96$  e Å<sup>−3</sup>

Table 1

Selected bond lengths (Å).

Na—O5 <sup>i</sup>	2.434 (4)	Fe—O5 <sup>vi</sup>	2.036 (3)
Na—O6 <sup>ii</sup>	2.436 (4)	Fe—O6	2.037 (4)
Na—O3 <sup>iii</sup>	2.491 (4)	Fe—O4 <sup>vii</sup>	2.055 (4)
Na—O2 <sup>iiii</sup>	2.581 (5)	Fe—O4 <sup>vi</sup>	2.078 (4)
Na—O2 <sup>ii</sup>	2.755 (5)	Te1—O1	1.893 (4)
Na—O1 <sup>i</sup>	2.758 (4)	Te1—O3 <sup>ii</sup>	1.901 (4)
Na—O4 <sup>i</sup>	2.788 (4)	Te1—O4	1.901 (4)
Na—O3 <sup>iii</sup>	2.958 (4)	Te2—O2 <sup>viii</sup>	1.849 (4)
Fe—O3 <sup>iv</sup>	1.942 (4)	Te2—O6 <sup>ix</sup>	1.892 (4)
Fe—O1 <sup>v</sup>	1.955 (4)	Te2—O5 <sup>x</sup>	1.899 (4)

Symmetry codes: (i)  $x + \frac{1}{2}, -y + \frac{1}{2}, z$ ; (ii)  $-x + 1, -y + \frac{1}{2}, z + \frac{1}{2}$ ; (iii)  $-x + \frac{3}{2}, y, z + \frac{1}{2}$ ; (iv)  $-x + \frac{1}{2}, y + \frac{1}{2}, -z$ ; (v)  $-x + \frac{1}{2}, y, z - \frac{1}{2}$ ; (vi)  $x, y + \frac{1}{2}, -z + \frac{1}{2}$ ; (vii)  $-x + 1, -y + \frac{1}{2}, z - \frac{1}{2}$ ; (viii)  $-x + \frac{1}{2}, y, z + \frac{1}{2}$ ; (ix)  $-x + \frac{1}{2}, y - \frac{1}{2}, -z + 1$ ; (x)  $x - \frac{1}{2}, -y, -z + \frac{3}{2}$ .

Data collection: SMART (Bruker, 2002); cell refinement: SAINT (Bruker, 2002); data reduction: SAINT; method used to solve structure: coordinates taken from an isotypic structure; program(s) used to refine structure: SHELXL97 (Sheldrick, 1997); molecular graphics: ATOMS (Dowty, 2006); software used to prepare material for publication: SHELXL97.

Financial support by the FWF (Fonds zur Förderung der wissenschaftlichen Forschung), project P19099-N17, is gratefully acknowledged.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: HB2673).

## References

- Bruker (2002). SMART, SAINT and SADABS. Bruker AXS Inc., Madison, Wisconsin, USA.  
Dolgikh, V. A. (1991). *Russ. J. Inorg. Chem. (Eng. Transl.)*, **36**, 1117–1129.  
Dowty, E. (2006). ATOMS for Windows. Version 6.3. Shape Software, Kingsport, Tennessee, USA.  
Miletich, R. & Pertlik, F. (1998). *J. Alloys Compds*, **268**, 107–111.  
Sheldrick, G. M. (1997). SHELXL97. University of Göttingen, Germany.  
Weil, M. (2005). *Acta Cryst.* **C61**, i103–i105.  
Weil, M. (2007). *Z. Anorg. Allg. Chem.* **633**, 1217–1222.  
Weil, M. & Stöger, B. (2007). *Acta Cryst.* **E63**, i202.

**supplementary materials**

*Acta Cryst.* (2008). E64, i3 [ doi:10.1107/S1600536807065403 ]

## NaFe(TeO<sub>3</sub>)<sub>2</sub>

M. Weil and B. Stöger

### Comment

The present communication is part of our ongoing studies of the phase formation and structures of Te(IV)-containing oxo-compounds formed under hydrothermal conditions (*e.g.* Weil, 2005, 2007; Weil & Stöger, 2007).

The crystal structure of the title compound, (I), is built up of layers with an overall composition [FeTe<sub>2</sub>O<sub>6</sub>]<sup>−</sup> extending parallel to (001). Adjacent layers are linked by Na<sup>+</sup> cations that are located in the voids of this arrangement (Fig. 1).

The anionic layers consists of octahedral [FeO<sub>6</sub>] and trigonal-pyramidal TeO<sub>3</sub> units as simple building blocks (Table 1). Two edge-sharing [FeO<sub>6</sub>] octahedra [mean Fe—O = 2.017 Å] form a centrosymmetric [Fe<sub>2</sub>O<sub>10</sub>] dimer which is connected to eight TeO<sub>3</sub> units *via* oxygen-atom corners. The equatorial oxygen atoms of the dimer are linked to six TeO<sub>3</sub> groups whereas the axial oxygen atoms of the dimer are part of two Te<sub>2</sub>O<sub>3</sub> groups capping both Fe atoms at the top and at the bottom (Fig. 2). Each of the free corners of the TeO<sub>3</sub> groups are further linked to adjacent [Fe<sub>2</sub>O<sub>10</sub>] dimers thus establishing the layered arrangement. The lone-pair electrons of the tellurium(IV) atoms point towards the free space and are aligned approximately parallel to [001]. The Na<sup>+</sup> cations are surrounded by eight oxygen atoms, leading to distorted polyhedra with a mean Na—O of 2.650 Å. The Te—O bond lengths and mean O—Te—O angle of 96.3° are typical values for trigonal-pyramidal TeO<sub>3</sub> units (Dolgikh, 1991). The next nearest O sites relative to the Te centres are outside of the first coordination spheres with distances of Te1—O2 = 2.549 (4) Å, Te1—O1[x + 1/2, −y + 1/2, z] = 2.570 (4) Å and Te2—O5 = 2.703 (4) Å.

The crystal structure of NaFe(TeO<sub>3</sub>)<sub>2</sub> is isotypic with the Ga<sup>III</sup> analogue, NaGa(TeO<sub>3</sub>)<sub>2</sub> (Miletich & Pertlik, 1998), and exhibits similar interatomic distances and angles.

### Experimental

All chemicals used were of analytical grade (Merck, p.A.) and employed without further purification: 20 mg (0.5 mmol) NaOH, 53 mg (0.33 mmol) Fe<sub>2</sub>O<sub>3</sub> and 160 mg (1 mmol) TeO<sub>2</sub> were placed in a 5-ml Teflon-lined steel autoclave that was filled with 2 ml demineralized water. The autoclave was heated at 493 K for 6 d and then cooled to room temperature within 3 h. The reaction product consisted mainly of a mixture of unreacted Fe<sub>2</sub>O<sub>3</sub> and TeO<sub>2</sub>. Only few colourless crystals of (I) with unspecific habit were obtained.

### Refinement

For better comparison with the isotypic NaGa(TeO<sub>3</sub>)<sub>2</sub> structure, the refinement was carried out in the non-standard setting *Pcab* of space group No. 61 (standard setting *Pbca*). The atomic coordinates of the Ga analogue were taken as starting parameters. The highest remaining peak in the final difference Fourier map is 0.71 Å from Te2 and the deepest hole is 0.79 Å from O4.

## Figures

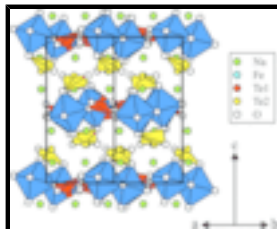


Fig. 1. The crystal structure of  $\text{NaGa}(\text{TeO}_3)_2$  in projection along  $[110]$ .

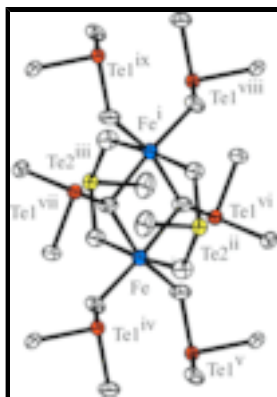


Fig. 2. The  $[\text{Fe}_2\text{O}_{10}]$  dimer with the corner-sharing  $\text{TeO}_3$  trigonal-pyramids attached. Atoms are drawn as displacement ellipsoids at the 90% probability level. [Symmetry operators: (i)  $-x + 1, -y + 1, z$ ; (ii)  $-x + 1/2, y + 1/2, -z + 1$ ; (iii)  $x + 1/2, -y + 1/2, z - 1$ ; (iv)  $x - 1/2, -y + 1, -z + 1/2$ ; (v)  $-x + 1/2, -y + 1/2, z - 1$ ; (vi)  $-x + 1, -y + 1/2, z - 1/2$ ; (vii)  $x, y + 1/2, -z + 1/2$ ; (viii)  $-x + 1.5, y, z - 1/2$ ; (ix)  $x + 1/2, -y + 1, -z + 1/2$ .]

## sodium iron(III) bis[trioxotellurate(IV)]

### Crystal data

$\text{NaFe}(\text{TeO}_3)_2$

$M_r = 430.04$

Orthorhombic,  $Pcab$

Hall symbol:  $-P\ 2bc\ 2ac$

$a = 7.8530$  (15) Å

$b = 10.448$  (2) Å

$c = 13.438$  (3) Å

$V = 1102.5$  (4) Å<sup>3</sup>

$Z = 8$

$F_{000} = 1512$

$D_x = 5.182$  Mg m<sup>-3</sup>

Mo  $K\alpha$  radiation

$\lambda = 0.71073$  Å

Cell parameters from 2569 reflections

$\theta = 3.0$ – $30.0^\circ$

$\mu = 13.15$  mm<sup>-1</sup>

$T = 293$  (2) K

Prism, colourless

$0.08 \times 0.02 \times 0.01$  mm

### Data collection

Bruker SMART APEX CCD  
diffractometer

Radiation source: fine-focus sealed tube

Monochromator: graphite

$T = 293$  (2) K

$\omega$  scans

Absorption correction: multi-scan  
(SADABS; Bruker, 2002)

$T_{\min} = 0.405$ ,  $T_{\max} = 0.858$

1598 independent reflections

1329 reflections with  $I > 2\sigma(I)$

$R_{\text{int}} = 0.053$

$\theta_{\text{max}} = 30.0^\circ$

$\theta_{\text{min}} = 3.0^\circ$

$h = -11 \rightarrow 9$

$k = -14 \rightarrow 14$

11127 measured reflections

$l = -18 \rightarrow 18$

*Refinement*

Refinement on  $F^2$

Primary atom site location: isomorphous structure methods

Least-squares matrix: full

$$w = 1/[\sigma^2(F_o^2) + (0.0323P)^2]$$

$$\text{where } P = (F_o^2 + 2F_c^2)/3$$

$$R[F^2 > 2\sigma(F^2)] = 0.027$$

$$(\Delta/\sigma)_{\max} < 0.001$$

$$wR(F^2) = 0.061$$

$$\Delta\rho_{\max} = 1.77 \text{ e } \text{\AA}^{-3}$$

$$S = 1.03$$

$$\Delta\rho_{\min} = -0.96 \text{ e } \text{\AA}^{-3}$$

1598 reflections

Extinction correction: none

91 parameters

*Special details*

**Geometry.** All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

**Refinement.** Refinement of  $F^2$  against ALL reflections. The weighted  $R$ -factor  $wR$  and goodness of fit  $S$  are based on  $F^2$ , conventional  $R$ -factors  $R$  are based on  $F$ , with  $F$  set to zero for negative  $F^2$ . The threshold expression of  $F^2 > 2\sigma(F^2)$  is used only for calculating  $R$ -factors(gt) *etc.* and is not relevant to the choice of reflections for refinement.  $R$ -factors based on  $F^2$  are statistically about twice as large as those based on  $F$ , and  $R$ -factors based on ALL data will be even larger.

*Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters ( $\text{\AA}^2$ )*

	$x$	$y$	$z$	$U_{\text{iso}}^*/U_{\text{eq}}$
Te1	0.54652 (4)	0.28714 (3)	0.42454 (2)	0.00780 (9)
Te2	0.08184 (4)	0.00810 (3)	0.76667 (2)	0.00932 (9)
Fe	0.30472 (10)	0.49980 (6)	-0.02064 (5)	0.00866 (15)
Na	0.8320 (3)	0.2417 (2)	0.64216 (19)	0.0254 (6)
O1	0.3210 (4)	0.3435 (3)	0.4480 (3)	0.0122 (7)
O2	0.4293 (5)	0.1849 (4)	0.2665 (3)	0.0169 (8)
O3	0.3696 (4)	0.1292 (3)	0.0402 (3)	0.0106 (7)
O4	0.4983 (4)	0.1292 (3)	0.4888 (3)	0.0104 (7)
O5	0.3769 (5)	0.0296 (3)	0.6643 (3)	0.0107 (7)
O6	0.2625 (5)	0.4796 (3)	0.1281 (3)	0.0119 (7)

*Atomic displacement parameters ( $\text{\AA}^2$ )*

	$U^{11}$	$U^{22}$	$U^{33}$	$U^{12}$	$U^{13}$	$U^{23}$
Te1	0.00751 (16)	0.00640 (14)	0.00950 (15)	-0.00033 (11)	0.00003 (11)	0.00063 (11)
Te2	0.00962 (16)	0.00905 (15)	0.00928 (16)	0.00021 (11)	0.00013 (11)	-0.00144 (11)
Fe	0.0085 (3)	0.0069 (3)	0.0106 (4)	0.0000 (3)	-0.0002 (3)	-0.0005 (2)
Na	0.0326 (15)	0.0142 (11)	0.0294 (13)	-0.0056 (10)	-0.0082 (11)	0.0034 (10)
O1	0.0065 (17)	0.0113 (16)	0.0188 (19)	0.0005 (14)	0.0010 (14)	-0.0019 (14)

## supplementary materials

---

O2	0.022 (2)	0.0110 (17)	0.0175 (19)	-0.0020 (15)	-0.0020 (16)	0.0000 (14)
O3	0.0087 (17)	0.0094 (16)	0.0138 (17)	-0.0030 (14)	-0.0017 (14)	0.0023 (13)
O4	0.0074 (17)	0.0085 (16)	0.0152 (17)	0.0012 (13)	-0.0020 (13)	0.0028 (13)
O5	0.0096 (17)	0.0156 (17)	0.0071 (17)	0.0007 (14)	-0.0014 (13)	-0.0017 (14)
O6	0.0119 (18)	0.0154 (17)	0.0084 (17)	-0.0003 (14)	0.0003 (14)	-0.0006 (13)

### Geometric parameters ( $\text{\AA}$ , $^\circ$ )

Na—O5 <sup>i</sup>	2.434 (4)	Fe—O5 <sup>vi</sup>	2.036 (3)
Na—O6 <sup>ii</sup>	2.436 (4)	Fe—O6	2.037 (4)
Na—O3 <sup>iii</sup>	2.491 (4)	Fe—O4 <sup>vii</sup>	2.055 (4)
Na—O2 <sup>iii</sup>	2.581 (5)	Fe—O4 <sup>vi</sup>	2.078 (4)
Na—O2 <sup>ii</sup>	2.755 (5)	Te1—O1	1.893 (4)
Na—O1 <sup>i</sup>	2.758 (4)	Te1—O3 <sup>ii</sup>	1.901 (4)
Na—O4 <sup>i</sup>	2.788 (4)	Te1—O4	1.901 (4)
Na—O3 <sup>iii</sup>	2.958 (4)	Te2—O2 <sup>viii</sup>	1.849 (4)
Fe—O3 <sup>iv</sup>	1.942 (4)	Te2—O6 <sup>ix</sup>	1.892 (4)
Fe—O1 <sup>v</sup>	1.955 (4)	Te2—O5 <sup>x</sup>	1.899 (4)
O1—Te1—O3 <sup>ii</sup>	92.59 (15)	O6 <sup>ii</sup> —Na—O4 <sup>i</sup>	123.02 (15)
O1—Te1—O4	90.44 (15)	O3 <sup>ii</sup> —Na—O4 <sup>i</sup>	68.23 (12)
O3 <sup>ii</sup> —Te1—O4	95.54 (16)	O2 <sup>iii</sup> —Na—O4 <sup>i</sup>	104.45 (14)
O2 <sup>viii</sup> —Te2—O6 <sup>ix</sup>	100.85 (16)	O2 <sup>ii</sup> —Na—O4 <sup>i</sup>	131.48 (14)
O2 <sup>viii</sup> —Te2—O5 <sup>x</sup>	99.64 (16)	O1 <sup>i</sup> —Na—O4 <sup>i</sup>	58.10 (12)
O6 <sup>ix</sup> —Te2—O5 <sup>x</sup>	98.64 (16)	O5 <sup>i</sup> —Na—O3 <sup>iii</sup>	109.39 (14)
O3 <sup>iv</sup> —Fe—O1 <sup>v</sup>	101.34 (15)	O6 <sup>ii</sup> —Na—O3 <sup>iii</sup>	80.11 (13)
O3 <sup>iv</sup> —Fe—O5 <sup>vi</sup>	87.79 (15)	O3 <sup>ii</sup> —Na—O3 <sup>iii</sup>	117.64 (17)
O1 <sup>v</sup> —Fe—O5 <sup>vi</sup>	93.64 (15)	O2 <sup>iii</sup> —Na—O3 <sup>iii</sup>	68.48 (13)
O3 <sup>iv</sup> —Fe—O6	95.17 (15)	O2 <sup>ii</sup> —Na—O3 <sup>iii</sup>	168.98 (14)
O1 <sup>v</sup> —Fe—O6	92.48 (15)	O1 <sup>i</sup> —Na—O3 <sup>iii</sup>	57.21 (11)
O5 <sup>vi</sup> —Fe—O6	172.55 (15)	O4 <sup>i</sup> —Na—O3 <sup>iii</sup>	58.59 (11)
O3 <sup>iv</sup> —Fe—O4 <sup>vii</sup>	174.47 (15)	Te1—O1—Fe <sup>viii</sup>	140.2 (2)
O1 <sup>v</sup> —Fe—O4 <sup>vii</sup>	81.12 (15)	Te1—O1—Na <sup>xi</sup>	91.60 (15)
O5 <sup>vi</sup> —Fe—O4 <sup>vii</sup>	87.11 (14)	Fe <sup>viii</sup> —O1—Na <sup>xi</sup>	94.66 (14)
O6—Fe—O4 <sup>vii</sup>	89.65 (14)	Te2 <sup>v</sup> —O2—Na <sup>xii</sup>	105.36 (18)
O3 <sup>iv</sup> —Fe—O4 <sup>vi</sup>	95.20 (15)	Te2 <sup>v</sup> —O2—Na <sup>vii</sup>	104.09 (17)
O1 <sup>v</sup> —Fe—O4 <sup>vi</sup>	163.16 (15)	Na <sup>xii</sup> —O2—Na <sup>vii</sup>	94.82 (15)
O5 <sup>vi</sup> —Fe—O4 <sup>vi</sup>	83.80 (14)	Te1 <sup>vii</sup> —O3—Fe <sup>xiii</sup>	116.98 (18)
O6—Fe—O4 <sup>vi</sup>	89.11 (14)	Te1 <sup>vii</sup> —O3—Na <sup>vii</sup>	114.90 (17)
O4 <sup>vii</sup> —Fe—O4 <sup>vi</sup>	82.13 (15)	Fe <sup>xiii</sup> —O3—Na <sup>vii</sup>	90.19 (14)
O5 <sup>i</sup> —Na—O6 <sup>ii</sup>	170.30 (17)	Te1 <sup>vii</sup> —O3—Na <sup>xii</sup>	85.51 (13)
O5 <sup>i</sup> —Na—O3 <sup>ii</sup>	68.14 (13)	Fe <sup>xiii</sup> —O3—Na <sup>xii</sup>	153.87 (17)
O6 <sup>ii</sup> —Na—O3 <sup>ii</sup>	106.13 (15)	Na <sup>vii</sup> —O3—Na <sup>xii</sup>	91.93 (13)

O5 <sup>i</sup> —Na—O2 <sup>iii</sup>	92.37 (15)	Te1—O4—Fe <sup>ii</sup>	113.01 (17)
O6 <sup>ii</sup> —Na—O2 <sup>iii</sup>	93.05 (14)	Te1—O4—Fe <sup>xiv</sup>	143.49 (19)
O3 <sup>ii</sup> —Na—O2 <sup>iii</sup>	160.49 (15)	Fe <sup>ii</sup> —O4—Fe <sup>xiv</sup>	97.87 (15)
O5 <sup>i</sup> —Na—O2 <sup>ii</sup>	76.12 (14)	Te1—O4—Na <sup>xi</sup>	90.52 (14)
O6 <sup>ii</sup> —Na—O2 <sup>ii</sup>	94.86 (14)	Fe <sup>ii</sup> —O4—Na <sup>xi</sup>	135.71 (17)
O3 <sup>ii</sup> —Na—O2 <sup>ii</sup>	73.11 (14)	Fe <sup>xiv</sup> —O4—Na <sup>xi</sup>	79.65 (12)
O2 <sup>iii</sup> —Na—O2 <sup>ii</sup>	102.25 (16)	Te2 <sup>xv</sup> —O5—Fe <sup>xiv</sup>	131.84 (19)
O5 <sup>i</sup> —Na—O1 <sup>i</sup>	115.91 (14)	Te2 <sup>xv</sup> —O5—Na <sup>xi</sup>	112.72 (17)
O6 <sup>ii</sup> —Na—O1 <sup>i</sup>	67.10 (12)	Fe <sup>xiv</sup> —O5—Na <sup>xi</sup>	89.63 (14)
O3 <sup>ii</sup> —Na—O1 <sup>i</sup>	68.55 (13)	Te2 <sup>xvi</sup> —O6—Fe	127.7 (2)
O2 <sup>iii</sup> —Na—O1 <sup>i</sup>	124.14 (15)	Te2 <sup>xvi</sup> —O6—Na <sup>vii</sup>	106.73 (16)
O2 <sup>ii</sup> —Na—O1 <sup>i</sup>	129.82 (15)	Fe—O6—Na <sup>vii</sup>	102.93 (15)
O5 <sup>i</sup> —Na—O4 <sup>i</sup>	63.09 (12)		

Symmetry codes: (i)  $x+1/2, -y+1/2, z$ ; (ii)  $-x+1, -y+1/2, z+1/2$ ; (iii)  $-x+3/2, y, z+1/2$ ; (iv)  $-x+1/2, y+1/2, -z$ ; (v)  $-x+1/2, y, z-1/2$ ; (vi)  $x, y+1/2, -z+1/2$ ; (vii)  $-x+1, -y+1/2, z-1/2$ ; (viii)  $-x+1/2, y, z+1/2$ ; (ix)  $-x+1/2, y-1/2, -z+1$ ; (x)  $x-1/2, -y, -z+3/2$ ; (xi)  $x-1/2, -y+1/2, z$ ; (xii)  $-x+3/2, y, z-1/2$ ; (xiii)  $-x+1/2, y-1/2, -z$ ; (xiv)  $x, y-1/2, -z+1/2$ ; (xv)  $x+1/2, -y, -z+3/2$ ; (xvi)  $-x+1/2, y+1/2, -z+1$ .

Fig. 1

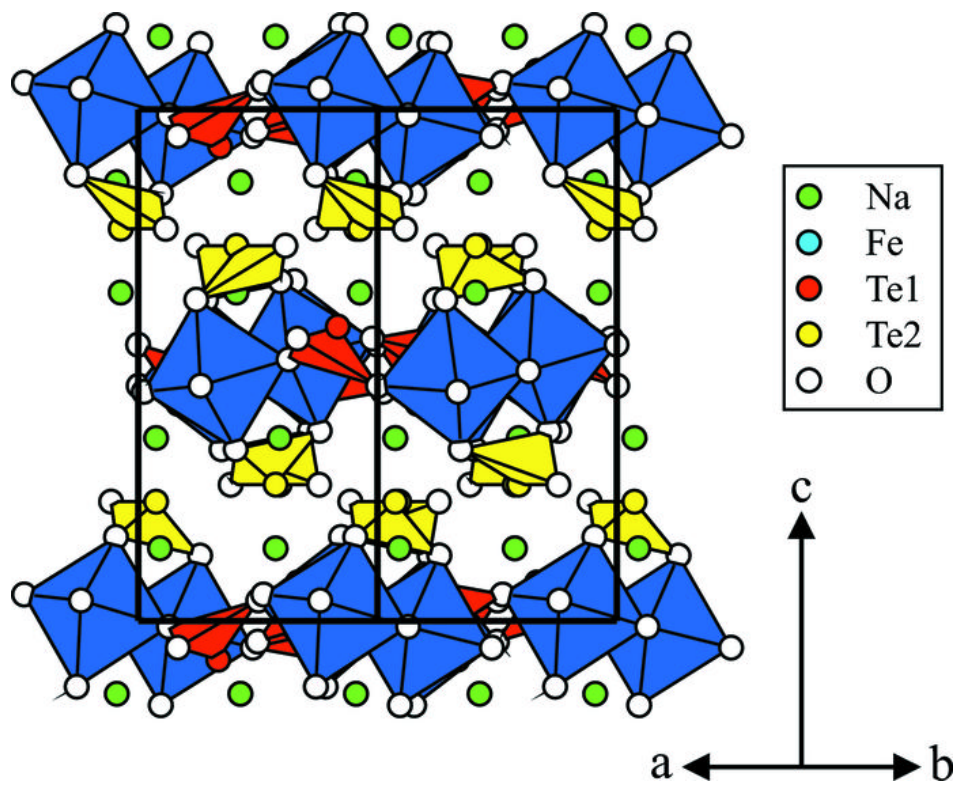


Fig. 2

