

## A new sodium dimagnesium trivanadate, NaMg<sub>2</sub>V<sub>3</sub>O<sub>10</sub>

 Brahim Ayed<sup>a\*</sup> and Amor Haddad<sup>b</sup>
<sup>a</sup>Institut Préparatoire aux Études d'Ingénieur de Monastir, Avenue Ibn-El-Jazzar, 5019 Monastir, Tunisia, and <sup>b</sup>Département de Chimie, Faculté des Sciences de Monastir, 5000 Monastir, Tunisia

Correspondence e-mail: brahimayed@yahoo.fr

Received 13 December 2007; accepted 29 January 2008

 Key indicators: single-crystal X-ray study;  $T = 293$  K; mean  $\sigma(\text{Mg}-\text{O}) = 0.003$  Å;  $R$  factor = 0.033;  $wR$  factor = 0.096; data-to-parameter ratio = 11.7.

A single crystal of NaMg<sub>2</sub>V<sub>3</sub>O<sub>10</sub> has been prepared by solid-state reaction at 1173 K. The [Mg<sub>2</sub>(V<sub>3</sub>O<sub>10</sub>)]<sup>-</sup> anions are built up from edge-sharing MgO<sub>6</sub> octahedra to form [Mg<sub>4</sub>O<sub>18</sub>] units, which are linked to each other by trivanadate groups (V<sub>3</sub>O<sub>10</sub>). The Na<sup>+</sup> ions are located in the tunnel space.

### Related literature

For related literature, see: Barbier (1988); Brown & Altermatt (1985); Gopal & Calvo (1974); Krishnamachari & Calvo (1971); Mitiaev *et al.* (2004); Murashova *et al.* (1988a, 1988b); Ng & Calvo (1972); Saux & Galy (1973).

### Experimental

#### Crystal data

NaMg <sub>2</sub> V <sub>3</sub> O <sub>10</sub>	$\gamma = 101.696$ (1)°
$M_r = 384.42$	$V = 402.63$ (1) Å <sup>3</sup>
Triclinic, $P\bar{1}$	$Z = 2$
$a = 6.7369$ (1) Å	Mo $K\alpha$ radiation
$b = 6.7553$ (1) Å	$\mu = 3.66$ mm <sup>-1</sup>
$c = 9.6222$ (1) Å	$T = 293$ (2) K
$\alpha = 104.325$ (1)°	$0.4 \times 0.07 \times 0.03$ mm
$\beta = 100.604$ (1)°	

#### Data collection

Enraf–Nonius CAD-4 diffractometer	1712 independent reflections
Absorption correction: $\psi$ scan (North <i>et al.</i> , 1968)	1415 reflections with $I > 2\sigma(I)$
$T_{\min} = 0.871$ , $T_{\max} = 0.965$ (expected range = 0.809–0.896)	$R_{\text{int}} = 0.049$
3118 measured reflections	2 standard reflections
	frequency: 120 min
	intensity decay: 0.4%

#### Refinement

$R[F^2 > 2\sigma(F^2)] = 0.033$	146 parameters
$wR(F^2) = 0.095$	$\Delta\rho_{\text{max}} = 0.73$ e Å <sup>-3</sup>
$S = 1.06$	$\Delta\rho_{\text{min}} = -1.18$ e Å <sup>-3</sup>
1712 reflections	

Table 1

Selected bond lengths (Å).

V1–O4	1.672 (3)	V2–O7	1.717 (3)
V1–O6	1.688 (3)	V2–O5	1.848 (3)
V1–O2	1.704 (3)	V3–O8	1.642 (3)
V1–O1	1.806 (3)	V3–O3	1.655 (3)
V2–O9	1.643 (3)	V3–O1 <sup>i</sup>	1.757 (3)
V2–O10	1.694 (3)	V3–O5 <sup>ii</sup>	1.827 (3)

 Symmetry codes: (i)  $-x, -y, -z + 1$ ; (ii)  $-x, -y - 1, -z$ .

Data collection: *CAD-4 EXPRESS* (Duisenberg, 1992; Macíček & Yordanov, 1992); cell refinement: *CAD-4 EXPRESS*; data reduction: *MolEN* (Fair, 1990); program(s) used to solve structure: *SHELXS97* (Sheldrick, 2008); program(s) used to refine structure: *SHELXL97* (Sheldrick, 2008); molecular graphics: *DIAMOND* (Brandenburg, 1998); software used to prepare material for publication: *SHELXL97*.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: BR2067).

### References

- Barbier, J. (1988). *Eur. J. Solid State Inorg. Chem.* **25**, 609–619.
- Brandenburg, K. (1998). *DIAMOND*. University of Bonn, Germany.
- Brown, I. D. & Altermatt, D. (1985). *Acta Cryst.* **B41**, 244–247.
- Duisenberg, A. J. M. (1992). *J. Appl. Cryst.* **25**, 92–96.
- Fair, C. K. (1990). *MolEN*. Enraf–Nonius, Delft, The Netherlands.
- Gopal, R. & Calvo, C. (1974). *Acta Cryst.* **B30**, 2491–2493.
- Krishnamachari, N. & Calvo, C. (1971). *Can. J. Chem.* **49**, 1629–1637.
- Macíček, J. & Yordanov, A. (1992). *J. Appl. Cryst.* **25**, 73–80.
- Mitiaev, A., Mironov, A., Shpanchenko, R. & Antipov, E. (2004). *Acta Cryst.* **C60**, i56–i58.
- Murashova, E. V., Velikodnyi, Yu. A. & Trunov, V. K. (1988a). *Zh. Strukt. Khim.* **29**, 182–184.
- Murashova, E. V., Velikodnyi, Yu. A. & Trunov, V. K. (1988b). *Russ. J. Inorg. Chem. (Zh. Neorg. Khim.)*, **33**, 904–905.
- Ng, H. N. & Calvo, C. (1972). *Can. J. Chem.* **50**, 3619–3624.
- North, A. C. T., Phillips, D. C. & Mathews, F. S. (1968). *Acta Cryst.* **A24**, 351–359.
- Saux, M. & Galy, J. (1973). *C. R. Acad. Sci. Ser. C*, **276**, 81–84.
- Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.

**supplementary materials**

*Acta Cryst.* (2008). E64, i21 [ doi:10.1107/S160053680800322X ]

## A new sodium dimagnesium trivanadate, NaMg<sub>2</sub>V<sub>3</sub>O<sub>10</sub>

B. Ayed and A. Haddad

### Comment

The synthesis and structural characterization of new materials characterized by mixed open frameworks of MO<sub>6</sub> octahedra and XO<sub>4</sub> tetrahedra sharing edges and/or corners delimiting tunnels where cations are located and study of their properties are an active area of research in solid state chemistry, due to their interest in the fields of catalysis, ion exchange and ion conduction. In the system MgO–V<sub>2</sub>O<sub>5</sub>, a small number of compounds have been structurally characterized now, namely, Mg<sub>2</sub>V<sub>2</sub>O<sub>7</sub> (Gopal & Calvo, 1974), MgV<sub>2</sub>O<sub>6</sub> (Ng & Calvo, 1972), Mg<sub>3</sub>(VO<sub>4</sub>)<sub>2</sub> (Krishnamachari & Calvo, 1971) and MgV<sub>3</sub>O<sub>8</sub> (Saux & Galy, 1973). The same is true for the inclusion of alkali elements into this system, to our knowledge, only the structure of NaMg<sub>4</sub>(VO<sub>4</sub>)<sub>3</sub> (Murashova *et al.*, 1988*a*), LiMg(VO<sub>4</sub>) (Barbier, 1988), K<sub>2</sub>MgV<sub>2</sub>O<sub>7</sub> (Murashova *et al.*, 1988*b*) and Na<sub>6</sub>Mg<sub>2</sub>(V<sub>4</sub>O<sub>15</sub>) (Mitiaev *et al.*, 2004) have been determined. Extending our investigation a new magnesium trivanadate, NaMg<sub>2</sub>V<sub>3</sub>O<sub>10</sub> has been prepared by a conventional solid-state reaction and characterized by single-crystal X-ray diffraction. The structure of NaMg<sub>2</sub>V<sub>3</sub>O<sub>10</sub> consists of MgO<sub>6</sub> octahedra and VO<sub>4</sub> tetrahedral sharing corners and edges to form a three-dimensional framework. The Na<sup>+</sup> are located in the tunnels space. A projection of the structure, showing the displacement ellipsoids, is presented in Fig 1. The Mg<sub>2</sub>(V<sub>3</sub>O<sub>10</sub>)<sup>−</sup> anions are built up from edge sharing MgO<sub>6</sub> octahedra to form [Mg<sub>4</sub>O<sub>18</sub>] units, which are linked to each other by trivanadate groups (V<sub>3</sub>O<sub>10</sub>). The Mg<sub>4</sub>O<sub>18</sub> basal unit is built up by the edge linkages of four MgO<sub>6</sub> octahedra, Such a unit is formed by two kind of divalent-metal cations, one labeled as Mg1 share edge with another labelled Mg2 forming Mg<sub>2</sub>O<sub>10</sub> dimers, repetition of the dimers ensured by centres of symmetry on the shared edge between two Mg1O<sub>6</sub> leads to the formation of Mg<sub>4</sub>O<sub>10</sub> unit. Each trivanadate is formed by three tetrahedra, V1O<sub>4</sub>, V2O<sub>4</sub> and V3O<sub>4</sub>, interconnected through the corners O1 and O5. The V1, V2 and V3 tetrahedron shares the eight remaining O-atom corners with five Mg<sub>4</sub>O<sub>18</sub> units forming ribbons running along the [011] direction (Fig. 2). The projection of the structure along the [001] show that the trivanadate groups and the MgO<sub>6</sub> polyhedra form six side tunnels running along [001] in which Na<sup>+</sup> cations are located (Fig3). The geometry of the VO<sub>4</sub> tetrahedra is close to that generally observed. Two groups of distances can be distinguished. The V—O bonds corresponding to the two V—O—V bridges of the V<sub>3</sub>O<sub>10</sub> groups are the largest one. Consequently, the two external tetrahedra V1 and V2 present one long V—O distance and three smaller ones. Whereas the central V3 tetrahedron has two long and two shorter. The Mg atoms are surrounded by six O atoms and the sodium cations exhibit a sixfold coordination. The bond valence sums determined using the Brown & Altermatt (1985) formulation are in the agreement with the formal charges deduced from the chemical formula: 5.088, 5.020, 5.100 from V1 to V3 respectively; 0.858 for Na; 2.188, 1.960 for Mg1 and Mg2 respectively, and ranging from 1.928 to 2.197 for the oxygen atoms.

### Experimental

The starting materials for synthesizing NaMg<sub>2</sub>V<sub>3</sub>O<sub>10</sub> were NaVO<sub>3</sub>, V<sub>2</sub>O<sub>5</sub> and Mg(NO<sub>3</sub>)<sub>2</sub>·7H<sub>2</sub>O. The stoichiometric mixture was heated in air, in a platinum crucible, after a progressive heating to 873 K, the mixture was heated at 1173 K, cooled

## supplementary materials

---

to 773 K at rate of 5 K.hr<sup>-1</sup> and then to room temperature. The parallelepiped crystals obtained after washing with hot water were brown. Quantitative analysis of these crystals, by electron microscope probe, revealed that they contain sodium, magnesium and vanadium.

### Figures

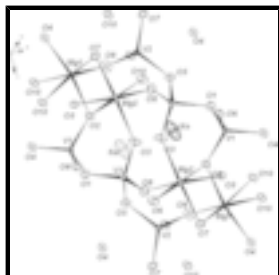


Fig. 1. A projection of NaMg<sub>2</sub>V<sub>3</sub>O<sub>10</sub>, showing the displacement ellipsoids.

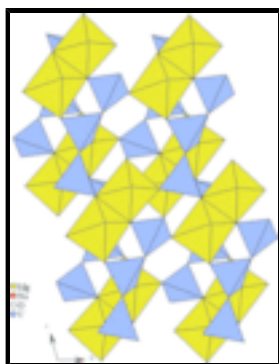


Fig. 2. View showing the ribbons running along the [011] direction.

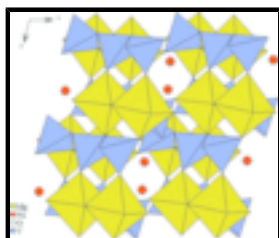


Fig. 3. Projection of the structure of NaMg<sub>2</sub>V<sub>3</sub>O<sub>10</sub> along [001] direction.

### Sodium dimagnesium trivanadate

#### Crystal data

NaMg<sub>2</sub>V<sub>3</sub>O<sub>10</sub>

$M_r = 384.42$

Triclinic, *PT*

Hall symbol: -P 1

$a = 6.7369$  (1) Å

$b = 6.7553$  (1) Å

$c = 9.6222$  (1) Å

$\alpha = 104.325$  (1)°

$\beta = 100.604$  (1)°

$\gamma = 101.696$  (1)°

$Z = 2$

$F_{000} = 368$

$D_x = 3.171$  Mg m<sup>-3</sup>

Mo  $K\alpha$  radiation

$\lambda = 0.71073$  Å

Cell parameters from 25 reflections

$\theta = 1.5$ – $27.0$ °

$\mu = 3.66$  mm<sup>-1</sup>

$T = 293$  (2) K

Parallelepiped, brown

$0.4 \times 0.07 \times 0.03$  mm

$$V = 402.625 (9) \text{ \AA}^3$$

### Data collection

Enraf–Nonius CAD-4 diffractometer	$R_{\text{int}} = 0.049$
Radiation source: fine-focus sealed tube	$\theta_{\text{max}} = 27.0^\circ$
Monochromator: graphite	$\theta_{\text{min}} = 2.3^\circ$
$T = 293(2)$ K	$h = -8 \rightarrow 8$
$\omega/2\theta$ scans	$k = -8 \rightarrow 8$
Absorption correction: $\psi$ scan (North <i>et al.</i> , 1968)	$l = -12 \rightarrow 12$
$T_{\text{min}} = 0.871$ , $T_{\text{max}} = 0.965$	2 standard reflections
3118 measured reflections	every 120 min
1712 independent reflections	intensity decay: 0.4%
1415 reflections with $I > 2\sigma(I)$	

### Refinement

Refinement on $F^2$	Secondary atom site location: difference Fourier map
Least-squares matrix: full	$w = 1/[\sigma^2(F_o^2) + (0.0426P)^2 + 0.4338P]$
$R[F^2 > 2\sigma(F^2)] = 0.033$	where $P = (F_o^2 + 2F_c^2)/3$
$wR(F^2) = 0.095$	$(\Delta/\sigma)_{\text{max}} < 0.001$
$S = 1.06$	$\Delta\rho_{\text{max}} = 0.73 \text{ e \AA}^{-3}$
1712 reflections	$\Delta\rho_{\text{min}} = -1.18 \text{ e \AA}^{-3}$
146 parameters	Extinction correction: SHELXL97 (Sheldrick, 2008),
Primary atom site location: structure-invariant direct methods	$F_c^* = kFc[1 + 0.001xFc^2\lambda^3/\sin(2\theta)]^{-1/4}$
	Extinction coefficient: 0.003 (2)

### Special details

**Geometry.** All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

**Refinement.** Refinement of  $F^2$  against ALL reflections. The weighted  $R$ -factor  $wR$  and goodness of fit  $S$  are based on  $F^2$ , conventional  $R$ -factors  $R$  are based on  $F$ , with  $F$  set to zero for negative  $F^2$ . The threshold expression of  $F^2 > 2\sigma(F^2)$  is used only for calculating  $R$ -factors(gt) *etc.* and is not relevant to the choice of reflections for refinement.  $R$ -factors based on  $F^2$  are statistically about twice as large as those based on  $F$ , and  $R$ -factors based on ALL data will be even larger.

### Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters ( $\text{\AA}^2$ )

	$x$	$y$	$z$	$U_{\text{iso}}^*/U_{\text{eq}}$
V1	0.11192 (10)	0.04819 (10)	0.30906 (7)	0.00700 (18)
V2	0.23427 (10)	-0.33675 (10)	-0.04757 (7)	0.00795 (18)

## supplementary materials

---

V3	-0.22756 (10)	-0.42610 (10)	0.38667 (7)	0.00858 (19)
Mg1	-0.20718 (18)	-0.18407 (18)	-0.01815 (13)	0.0043 (3)
Mg2	-0.76019 (19)	-0.4331 (2)	0.29306 (14)	0.0098 (3)
Na	0.6408 (4)	0.0239 (3)	0.3640 (3)	0.0416 (6)
O1	0.0677 (4)	0.1930 (5)	0.4803 (3)	0.0156 (6)
O2	0.2277 (4)	0.2383 (4)	0.2402 (3)	0.0118 (6)
O3	-0.2797 (5)	-0.6006 (5)	0.4778 (3)	0.0172 (6)
O4	-0.1271 (4)	-0.0914 (5)	0.2063 (3)	0.0143 (6)
O5	0.0972 (4)	-0.4778 (4)	-0.2430 (3)	0.0118 (6)
O6	0.2690 (5)	-0.1090 (5)	0.3424 (3)	0.0163 (6)
O7	0.2151 (4)	-0.5009 (4)	0.0627 (3)	0.0130 (6)
O8	-0.4437 (4)	-0.3693 (5)	0.3187 (3)	0.0159 (6)
O9	0.4808 (5)	-0.2374 (5)	-0.0409 (3)	0.0188 (7)
O10	0.1292 (4)	-0.1322 (4)	0.0086 (3)	0.0116 (5)

### Atomic displacement parameters ( $\text{\AA}^2$ )

	$U^{11}$	$U^{22}$	$U^{33}$	$U^{12}$	$U^{13}$	$U^{23}$
V1	0.0082 (3)	0.0063 (3)	0.0071 (3)	0.0016 (2)	0.0016 (2)	0.0034 (2)
V2	0.0112 (3)	0.0072 (3)	0.0066 (3)	0.0036 (2)	0.0021 (2)	0.0032 (2)
V3	0.0110 (3)	0.0083 (3)	0.0078 (3)	0.0031 (2)	0.0034 (2)	0.0033 (2)
Mg1	0.0063 (6)	0.0029 (5)	0.0037 (6)	0.0009 (4)	0.0012 (4)	0.0014 (4)
Mg2	0.0104 (7)	0.0096 (6)	0.0093 (6)	0.0022 (5)	0.0016 (5)	0.0033 (5)
Na	0.0371 (13)	0.0245 (11)	0.0622 (16)	0.0043 (9)	0.0221 (11)	0.0066 (11)
O1	0.0171 (15)	0.0156 (14)	0.0122 (14)	0.0003 (11)	0.0059 (11)	0.0020 (11)
O2	0.0143 (14)	0.0099 (13)	0.0114 (13)	0.0023 (10)	0.0029 (11)	0.0045 (11)
O3	0.0259 (16)	0.0128 (14)	0.0188 (15)	0.0092 (12)	0.0101 (13)	0.0087 (12)
O4	0.0123 (14)	0.0150 (14)	0.0136 (14)	-0.0011 (11)	0.0024 (11)	0.0053 (11)
O5	0.0140 (14)	0.0133 (14)	0.0101 (13)	0.0054 (11)	0.0050 (11)	0.0043 (11)
O6	0.0184 (15)	0.0149 (14)	0.0198 (15)	0.0075 (11)	0.0059 (12)	0.0092 (12)
O7	0.0150 (14)	0.0129 (14)	0.0124 (13)	0.0059 (11)	0.0014 (11)	0.0057 (11)
O8	0.0124 (14)	0.0175 (14)	0.0190 (15)	0.0051 (11)	0.0034 (11)	0.0069 (12)
O9	0.0173 (16)	0.0167 (15)	0.0241 (17)	0.0046 (12)	0.0073 (13)	0.0074 (13)
O10	0.0127 (13)	0.0097 (13)	0.0142 (13)	0.0038 (10)	0.0041 (11)	0.0054 (11)

### Geometric parameters ( $\text{\AA}$ , $^\circ$ )

V1—O4	1.672 (3)	Mg2—Mg1 <sup>i</sup>	3.1470 (17)
V1—O6	1.688 (3)	Mg2—V2 <sup>i</sup>	3.4044 (14)
V1—O2	1.704 (3)	Mg2—Na <sup>iv</sup>	3.492 (3)
V1—O1	1.806 (3)	Mg2—Na <sup>ii</sup>	3.575 (3)
V2—O9	1.643 (3)	Na—O3 <sup>viii</sup>	2.404 (4)
V2—O10	1.694 (3)	Na—O6	2.435 (4)
V2—O7	1.717 (3)	Na—O4 <sup>ix</sup>	2.477 (4)
V2—O5	1.848 (3)	Na—O8 <sup>ix</sup>	2.509 (4)
V2—Mg1	3.3760 (14)	Na—O6 <sup>x</sup>	2.665 (4)
V2—Mg2 <sup>i</sup>	3.4044 (14)	Na—O1 <sup>ix</sup>	2.771 (4)

V3—O8	1.642 (3)	Na—V1 <sup>ix</sup>	3.291 (2)
V3—O3	1.655 (3)	Na—V3 <sup>ix</sup>	3.380 (2)
V3—O1 <sup>ii</sup>	1.757 (3)	Na—V1 <sup>x</sup>	3.474 (3)
V3—O5 <sup>iii</sup>	1.827 (3)	Na—Mg2 <sup>ix</sup>	3.492 (3)
V3—Na <sup>iv</sup>	3.380 (2)	Na—Na <sup>x</sup>	3.543 (5)
V3—Na <sup>v</sup>	3.582 (2)	O1—V3 <sup>ii</sup>	1.757 (3)
Mg1—O9 <sup>iv</sup>	2.020 (3)	O1—Na <sup>iv</sup>	2.771 (4)
Mg1—O4	2.028 (3)	O2—Mg1 <sup>vi</sup>	2.049 (3)
Mg1—O2 <sup>vi</sup>	2.049 (3)	O2—Mg2 <sup>viii</sup>	2.132 (3)
Mg1—O7 <sup>iii</sup>	2.051 (3)	O3—Mg2 <sup>vii</sup>	2.120 (3)
Mg1—O10 <sup>vi</sup>	2.069 (3)	O3—Na <sup>v</sup>	2.404 (4)
Mg1—O10	2.178 (3)	O4—Na <sup>iv</sup>	2.477 (4)
Mg1—Mg2 <sup>i</sup>	3.1470 (17)	O5—V3 <sup>iii</sup>	1.827 (3)
Mg1—Mg1 <sup>vi</sup>	3.240 (2)	O5—Mg2 <sup>i</sup>	2.156 (3)
Mg1—V1 <sup>vi</sup>	3.2839 (13)	O6—Mg2 <sup>ix</sup>	2.082 (3)
Mg2—O8	2.043 (3)	O6—Na <sup>x</sup>	2.665 (4)
Mg2—O6 <sup>iv</sup>	2.082 (3)	O7—Mg1 <sup>iii</sup>	2.051 (3)
Mg2—O7 <sup>iv</sup>	2.117 (3)	O7—Mg2 <sup>ix</sup>	2.117 (3)
Mg2—O3 <sup>vii</sup>	2.120 (3)	O8—Na <sup>iv</sup>	2.509 (4)
Mg2—O2 <sup>v</sup>	2.132 (3)	O9—Mg1 <sup>ix</sup>	2.020 (3)
Mg2—O5 <sup>i</sup>	2.156 (3)	O10—Mg1 <sup>vi</sup>	2.069 (3)
O4—V1—O6	112.10 (15)	O10 <sup>vi</sup> —Mg1—O10	80.59 (12)
O4—V1—O2	113.54 (14)	O8—Mg2—O6 <sup>iv</sup>	88.16 (13)
O6—V1—O2	111.46 (14)	O8—Mg2—O7 <sup>iv</sup>	86.61 (12)
O4—V1—O1	104.42 (14)	O6 <sup>iv</sup> —Mg2—O7 <sup>iv</sup>	98.45 (12)
O6—V1—O1	110.07 (14)	O8—Mg2—O3 <sup>vii</sup>	90.45 (13)
O2—V1—O1	104.72 (14)	O6 <sup>iv</sup> —Mg2—O3 <sup>vii</sup>	88.10 (13)
O9—V2—O10	107.80 (14)	O7 <sup>iv</sup> —Mg2—O3 <sup>vii</sup>	172.73 (13)
O9—V2—O7	110.35 (15)	O8—Mg2—O2 <sup>v</sup>	88.64 (13)
O10—V2—O7	111.25 (14)	O6 <sup>iv</sup> —Mg2—O2 <sup>v</sup>	176.66 (13)
O9—V2—O5	107.91 (14)	O7 <sup>iv</sup> —Mg2—O2 <sup>v</sup>	80.40 (12)
O10—V2—O5	107.49 (13)	O3 <sup>vii</sup> —Mg2—O2 <sup>v</sup>	92.89 (12)
O7—V2—O5	111.87 (13)	O8—Mg2—O5 <sup>i</sup>	173.94 (13)
O8—V3—O3	109.72 (15)	O6 <sup>iv</sup> —Mg2—O5 <sup>i</sup>	95.28 (12)
O8—V3—O1 <sup>ii</sup>	106.39 (15)	O7 <sup>iv</sup> —Mg2—O5 <sup>i</sup>	87.95 (11)
O3—V3—O1 <sup>ii</sup>	106.04 (14)	O3 <sup>vii</sup> —Mg2—O5 <sup>i</sup>	94.64 (12)
O8—V3—O5 <sup>iii</sup>	111.97 (14)	O2 <sup>v</sup> —Mg2—O5 <sup>i</sup>	87.83 (11)
O3—V3—O5 <sup>iii</sup>	111.02 (14)	O3 <sup>viii</sup> —Na—O6	105.48 (13)
O1 <sup>ii</sup> —V3—O5 <sup>iii</sup>	111.43 (13)	O3 <sup>viii</sup> —Na—O4 <sup>ix</sup>	115.05 (13)
O9 <sup>iv</sup> —Mg1—O4	96.22 (13)	O6—Na—O4 <sup>ix</sup>	131.92 (14)

## supplementary materials

---

O9 <sup>iv</sup> —Mg1—O2 <sup>vi</sup>	94.40 (13)	O3 <sup>viii</sup> —Na—O8 <sup>ix</sup>	163.72 (16)
O4—Mg1—O2 <sup>vi</sup>	168.05 (13)	O6—Na—O8 <sup>ix</sup>	70.96 (12)
O9 <sup>iv</sup> —Mg1—O7 <sup>iii</sup>	93.58 (13)	O4 <sup>ix</sup> —Na—O8 <sup>ix</sup>	76.24 (12)
O4—Mg1—O7 <sup>iii</sup>	100.80 (12)	O3 <sup>viii</sup> —Na—O6 <sup>x</sup>	70.20 (12)
O2 <sup>vi</sup> —Mg1—O7 <sup>iii</sup>	83.95 (12)	O6—Na—O6 <sup>x</sup>	92.11 (12)
O9 <sup>iv</sup> —Mg1—O10 <sup>vi</sup>	100.55 (13)	O4 <sup>ix</sup> —Na—O6 <sup>x</sup>	124.66 (14)
O4—Mg1—O10 <sup>vi</sup>	88.02 (12)	O8 <sup>ix</sup> —Na—O6 <sup>x</sup>	93.84 (13)
O2 <sup>vi</sup> —Mg1—O10 <sup>vi</sup>	84.66 (12)	O3 <sup>viii</sup> —Na—O1 <sup>ix</sup>	69.27 (11)
O7 <sup>iii</sup> —Mg1—O10 <sup>vi</sup>	162.47 (13)	O6—Na—O1 <sup>ix</sup>	162.23 (15)
O9 <sup>iv</sup> —Mg1—O10	178.74 (12)	O4 <sup>ix</sup> —Na—O1 <sup>ix</sup>	62.91 (10)
O4—Mg1—O10	83.25 (12)	O8 <sup>ix</sup> —Na—O1 <sup>ix</sup>	109.07 (13)
O2 <sup>vi</sup> —Mg1—O10	86.24 (12)	O6 <sup>x</sup> —Na—O1 <sup>ix</sup>	70.12 (11)
O7 <sup>iii</sup> —Mg1—O10	85.40 (11)		

Symmetry codes: (i)  $-x-1, -y-1, -z$ ; (ii)  $-x, -y, -z+1$ ; (iii)  $-x, -y-1, -z$ ; (iv)  $x-1, y, z$ ; (v)  $x-1, y-1, z$ ; (vi)  $-x, -y, -z$ ; (vii)  $-x-1, -y-1, -z+1$ ; (viii)  $x+1, y+1, z$ ; (ix)  $x+1, y, z$ ; (x)  $-x+1, -y, -z+1$ .

Fig. 1

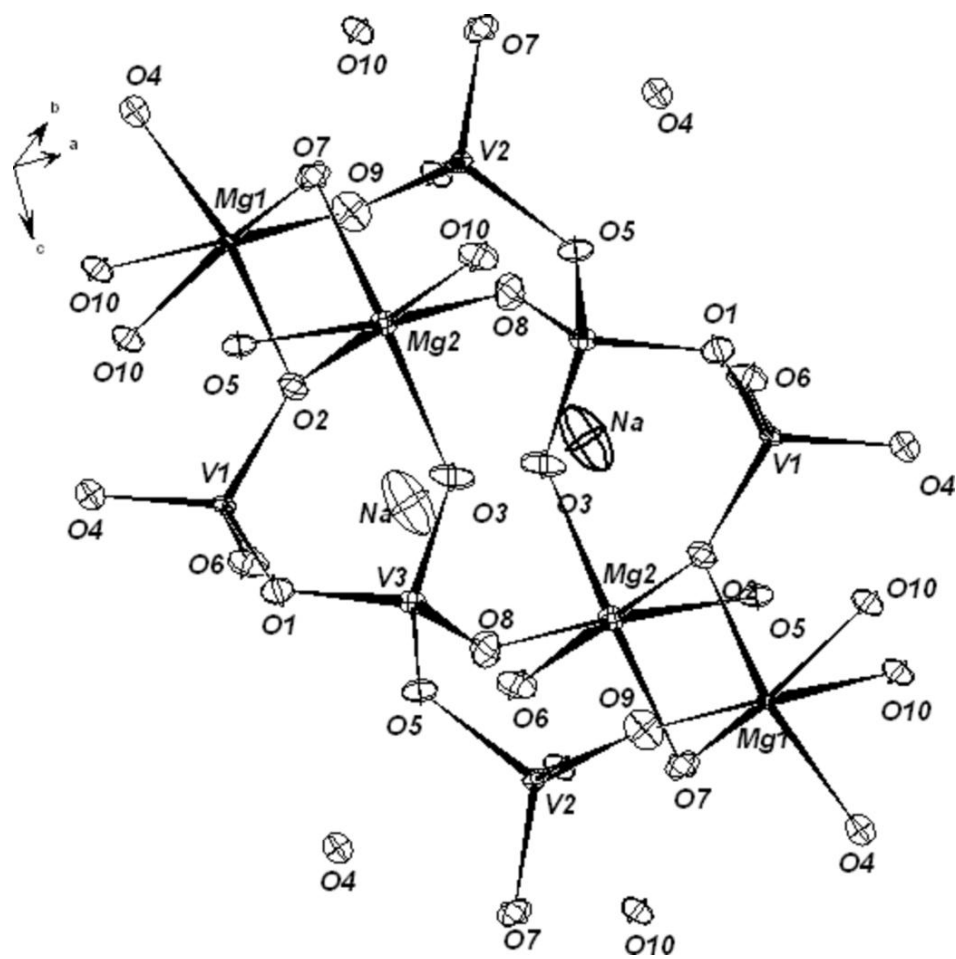


Fig. 2

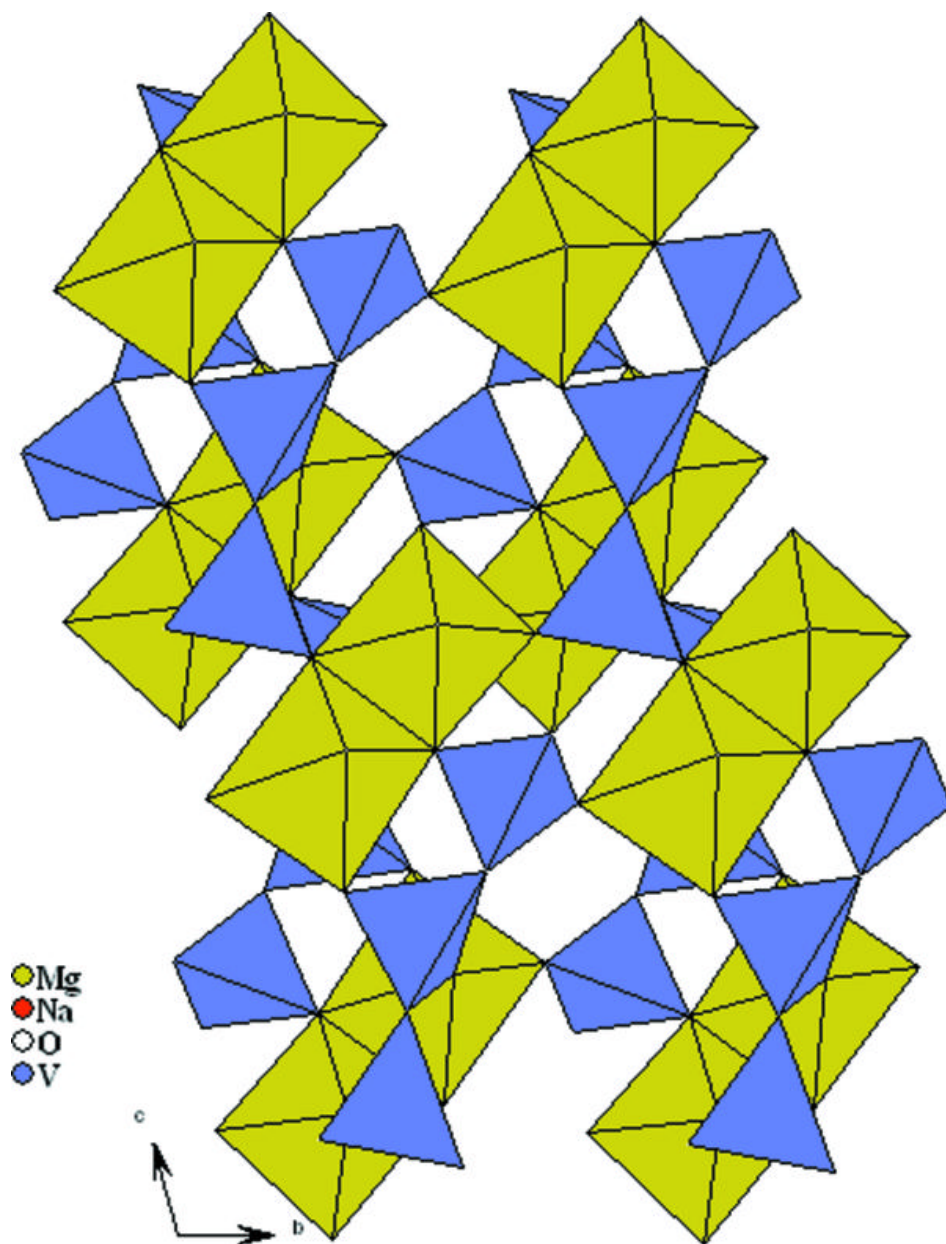


Fig. 3

