

catena-Poly[tetrasodium [[cis-dioxido-trans-bis(sulfato- κ O)molybdate(VI)]- μ -sulfato- κ^2 O:O']]

 Susan J. Cline Schäffer^{a*} and Rolf W. Berg^b

^aTårnby Gymnasium & HF, Tejn Allé 5, DK-2770 Kastrup, Denmark, and ^bThe Technical University of Denmark, The Department of Chemistry, Building 207, DK-2800 Lyngby, Denmark
Correspondence e-mail: su@tgy.dk


Received 15 July 2008; accepted 21 September 2008

Key indicators: single-crystal X-ray study; $T = 120$ K; mean $\sigma(\text{S}-\text{O}) = 0.002$ Å; R factor = 0.017; wR factor = 0.042; data-to-parameter ratio = 14.4.

Single crystals of the title compound, $[\text{Na}_4[\text{Mo}^{\text{VI}}\text{O}_2(\text{SO}_4)_3]]_n$, were grown from a melt of MoO_3 and Na_2SO_4 in $\text{Na}_2\text{S}_2\text{O}_7$. In contrast to the structure of the isoformular K compound, $\text{K}_4[\text{Mo}^{\text{VI}}\text{O}_2(\text{SO}_4)_3]$, with its monomeric anion, this sodium analogue contains a polymeric anion of the type $\{[\text{Mo}^{\text{VI}}\text{O}_2(\text{SO}_4)_2-\mu-(\text{SO}_4)]^{4-}\}_n$. The Mo^{VI} cations, surrounded by two tightly bonded O atoms and four O atoms of one bridging and two terminal sulfato ligands, form zigzag chains parallel to $[100]$. All four Na^+ cations are situated between the anionic chains and have distorted octahedral coordination spheres.

Related literature

The structure of the title isoformular potassium compound, $\text{K}_4[\text{Mo}^{\text{VI}}\text{O}_2(\text{SO}_4)_3]$, was determined by Schäffer & Berg (2008). For related Mo-containing compounds, see Salles *et al.* (1996) and Nørbygaard *et al.* (1998). Related compounds with Mo replaced by W were discussed by Schäffer & Berg (2005) and Berg *et al.* (2006). Other sulfato complexes coordinated to late transition metal centers were reported by Berg & Thorup (2005), Borup *et al.* (1990), Nielsen *et al.* (1993) and Rasmussen *et al.* (2003).

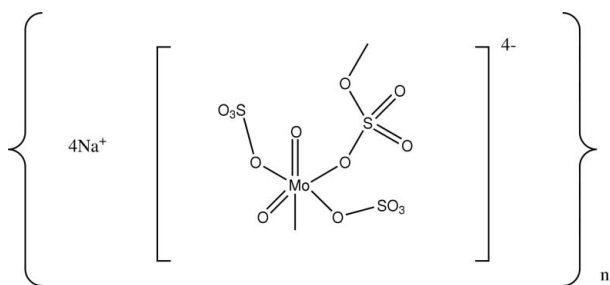

Experimental

Crystal data

$\text{Na}_4[\text{MoO}_2(\text{SO}_4)_3]$
 $M_r = 508.08$
 Orthorhombic, $P2_12_12_1$
 $a = 8.4739$ (6) Å
 $b = 9.2892$ (7) Å
 $c = 15.1046$ (11) Å
 $V = 1188.97$ (15) Å³
 $Z = 4$
 Mo $K\alpha$ radiation
 $\mu = 1.85$ mm⁻¹
 $T = 120$ (2) K
 $0.24 \times 0.18 \times 0.02$ mm

Data collection

Bruker SMART APEX CCD diffractometer
 Absorption correction: gaussian (*SHELXTL*; Sheldrick, 2008)
 $T_{\text{min}} = 0.665$, $T_{\text{max}} = 0.964$
 14125 measured reflections
 2861 independent reflections
 2817 reflections with $I > 2\sigma(I)$
 $R_{\text{int}} = 0.031$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.017$
 $wR(F^2) = 0.042$
 $S = 1.10$
 2861 reflections
 199 parameters
 $\Delta\rho_{\text{max}} = 0.51$ e Å⁻³
 $\Delta\rho_{\text{min}} = -0.26$ e Å⁻³
 Absolute structure: Flack (1983),
 1205 Friedel pairs
 Flack parameter: 0.01 (2)

Table 1

Selected bond lengths (Å).

Mo1—O2	1.6905 (16)	Mo1—O4	2.0102 (16)
Mo1—O1	1.7108 (16)	Mo1—O6 ⁱ	2.1661 (15)
Mo1—O5	1.9925 (16)	Mo1—O3	2.1907 (15)

 Symmetry code: (i) $x + \frac{1}{2}, -y + \frac{1}{2}, -z + 1$.

Data collection: *SMART* (Bruker, 2002); cell refinement: *SAINT* (Bruker, 2002); data reduction: *SAINT*; program(s) used to solve structure: *SHELXTL* (Sheldrick, 2008); program(s) used to refine structure: *SHELXTL*; molecular graphics: *SHELXTL*; software used to prepare material for publication: *SHELXTL*.

The authors thank Astrid Schøneberg and Bodil Holten for their help and advice.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: WM2186).

References

- Berg, R. W., Ferré, I. M. & Schäffer, S. J. C. (2006). *Vib. Spectrosc.* **42**, 346–352.
 Berg, R. W. & Thorup, N. (2005). *Inorg. Chem.* **44**, 3485–3493.
 Borup, F., Berg, R. W. & Nielsen, K. (1990). *Acta Chem. Scand.* **44**, 328–331.
 Bruker (2002). *SMART* and *SAINT*. Bruker AXS Inc., Madison, Wisconsin, USA.
 Flack, H. D. (1983). *Acta Cryst.* **A39**, 876–881.
 Nielsen, K., Fehrmann, R. & Eriksen, K. M. (1993). *Inorg. Chem.* **32**, 4825–4828.
 Nørbygaard, T., Berg, R. W. & Nielsen, K. (1998). *Molten Salts XI*, Proceedings of the Electrochemical Society 98–11, pp. 553–565. Pennington, NJ: Electrochemical Society.
 Rasmussen, S. B., Rasmussen, R. M., Fehrmann, R. & Nielsen, K. (2003). *Inorg. Chem.* **42**, 7123–7128.
 Salles, L., Robert, F., Semmer, V., Jeannin, Y. & Bregeault, J. (1996). *Bull. Soc. Chim. Fr.* **133**, 319–328.
 Schäffer, S. J. C. & Berg, R. W. (2005). *Acta Cryst.* **E61**, i49–i51.
 Schäffer, S. J. C. & Berg, R. W. (2008). *Acta Cryst.* **E64**, i20.
 Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.

supplementary materials

Acta Cryst. (2008). E64, i73 [doi:10.1107/S1600536808030328]

***catena*-Poly[tetrasodium [[*cis*-dioxido-*trans*-bis(sulfato- κ O)molybdate(VI)]- μ -sulfato- κ^2 O:O']]**

S. J. C. Schäffer and R. W. Berg

Comment

Considerable amounts of molybdenum(VI) oxide, a solid well known for its insolubility in many acids, can be dissolved in sulfate melts at high temperatures, as was previously found for the chemically related tungsten(VI) oxide (Schäffer & Berg, 2005, Berg *et al.*, 2006). When varying molar amounts of MoO₃, Na₂SO₄, and hygroscopic Na₂S₂O₇ are placed in ampoules in a dry box, sealed, and heated to equilibration in a rocking furnace at 773 K for *ca.* 1 h, the resulting clear melts contain [MoO₂]²⁺ moieties that are bonded to SO₄²⁻ units. The compositions of the reaction products have been determined to be in the stoichiometric ratio 1:1:1, or MoO₃ + M₂SO₄ + M₂S₂O₇ → M₄[Mo(SO₄)₃O₂]. In the case where M = K, a monomeric anion is formed (Schäffer & Berg, 2008), while for M = Na the anion is in a polymeric form.

The distorted octahedral coordination sphere of the Mo^{VI} cation contains two oxido ligands (*cis*), two terminally bound sulfato ligands (*trans*), and two O atoms of symmetry-related ($x + 1/2$, $-y + 1/2$, $-z + 1$) bridging sulfato ligands (*cis*), with O–Mo–O angles between any two *cis* oxygen atoms deviating as much as 15° from ideal values. The Mo–O bond distances to the tightly-bonded oxido ligands are similar (1.6905 (16) Å, 1.7108 (16) Å), which is expected as both bonds are *trans* to oxygen atoms in the bridging sulfato ligands. The Mo–O distances to the terminal sulfato ligands (Mo1–O4 and Mo1–O5) are slightly shorter than those to the bridging sulfato ligands, Mo1–O3 and Mo1–O6A. The Mo–O distances compare well with previously reported values for related structures (Salles *et al.*, 1996; Nørbygaard *et al.*, 1998; Schäffer & Berg, 2008).

The coordination geometry of the sulfato ligands can be described as slightly distorted from tetrahedral, with angles ranging from 103.55 (9) to 113.77 (10)°. From the shortest to the longest, the S–O bond distances vary by type: S to terminal O atoms, 1.4516 (17)–1.4681 (17) Å; S to bridging O atoms, 1.4941 (16) Å and 1.4953 (16) Å; S in the terminal sulfato ligands to the coordinating O atoms, 1.5589 (17) Å and 1.5346 (16) Å. This variation is typical for sulfato complexes of many different transition metal centers (Borup *et al.*, 1990; Nielsen *et al.*, 1993; Rasmussen *et al.*, 2003, and Berg & Thorup, 2005).

All four sodium cations are situated between the anionic chains and are six-coordinate with Na–O bond distances ranging from 2.2713 (18) to 2.7652 (18) Å.

Experimental

Crystals were grown from a melt of equimolar amounts of MoO₃, Na₂SO₄, and Na₂S₂O₇, using a method described previously (Nørbygaard *et al.*, 1998).

Refinement

On the basis of 1205 unmerged Friedel opposites, the fractional contribution of the racemic twin was negligible (Flack, 1983). The two highest peaks in the final difference Fourier map were, respectively, 0.78 Å and 0.79 Å from Mo1, and the deepest hole was 1.31 Å from S2.

Figures

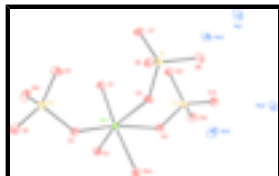


Fig. 1. Plot of the asymmetric unit of $\text{Na}_4[\text{Mo}^{\text{VI}}(\text{SO}_4)_3\text{O}_2]$, showing atoms as ellipsoids at the 50% probability level. [Symmetry code A) $x+0.5, -y+0.5, -z+1.$]

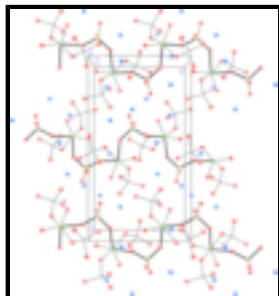


Fig. 2. The crystal packing of $\text{Na}_4[\text{Mo}^{\text{VI}}(\text{SO}_4)_3\text{O}_2]$, viewed along the b axis, showing the chains (thick black lines). Ellipsoids are displayed at the 50% probability level.

catena-Poly[tetrasodium [[cis-dioxido-trans- bis(sulfato- κ O)molybdate(VI)]- μ -sulfato- κ^2 O:O']]

Crystal data

$\text{Na}_4[\text{Mo}(\text{SO}_4)_3\text{O}_2]$

$M_r = 508.08$

Orthorhombic, $P2_12_12_1$

Hall symbol: P 2ac 2ab

$a = 8.4739$ (6) Å

$b = 9.2892$ (7) Å

$c = 15.1046$ (11) Å

$V = 1188.97$ (15) Å³

$Z = 4$

$F_{000} = 984$

$D_x = 2.838$ Mg m⁻³

Mo $K\alpha$ radiation

$\lambda = 0.71073$ Å

Cell parameters from 5457 reflections

$\theta = 2.6\text{--}27.9^\circ$

$\mu = 1.86$ mm⁻¹

$T = 120$ (2) K

Tabular, colorless

$0.24 \times 0.18 \times 0.02$ mm

Data collection

Bruker SMART APEX CCD diffractometer

Radiation source: normal-focus sealed tube

Monochromator: graphite

$T = 120$ (2) K

ω scans

Absorption correction: Gaussian
(SHELXTL; Sheldrick, 2008)

$T_{\min} = 0.665, T_{\max} = 0.964$

14125 measured reflections

2861 independent reflections

2817 reflections with $I > 2\sigma(I)$

$R_{\text{int}} = 0.031$

$\theta_{\max} = 28.0^\circ$

$\theta_{\min} = 2.6^\circ$

$h = -11 \rightarrow 11$

$k = -12 \rightarrow 12$

$l = -19 \rightarrow 19$

Refinement

Refinement on F^2

Secondary atom site location: difference Fourier map

Least-squares matrix: full	$w = 1/[\sigma^2(F_o^2) + (0.0214P)^2 + 0.3747P]$
	where $P = (F_o^2 + 2F_c^2)/3$
$R[F^2 > 2\sigma(F^2)] = 0.017$	$(\Delta/\sigma)_{\max} = 0.001$
$wR(F^2) = 0.042$	$\Delta\rho_{\max} = 0.51 \text{ e } \text{\AA}^{-3}$
$S = 1.10$	$\Delta\rho_{\min} = -0.26 \text{ e } \text{\AA}^{-3}$
2861 reflections	Extinction correction: none
199 parameters	Absolute structure: Flack (1983), 1205 Friedel pairs
Primary atom site location: structure-invariant direct methods	Flack parameter: 0.01 (2)

Special details

Geometry. All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

Refinement. Five frame series were filtered for statistical outliers then corrected for absorption by integration using *SHELXTL/XPREF* (Bruker, 2001) before using *SAINTEADABS* (Bruker, 2002) to sort, merge, and scale the combined data. A series of identical frames was collected twice during the experiment to monitor decay. No decay correction was applied. The systematic conditions suggested the unambiguous space group. The structure was solved by direct methods (Sheldrick, 2001). The final space group choice was confirmed by successful convergence of the full-matrix least-squares refinement on F^2 . An extinction correction was not applied. The two highest peaks in the final difference Fourier map were, respectively, 0.78 Å and 0.79 Å from Mo1; the deepest hole was 1.31 Å from S2. The final map had no other significant features. A final analysis of variance between observed and calculated structure factors showed no dependence on amplitude or resolution.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	x	y	z	$U_{\text{iso}}^*/U_{\text{eq}}$
Mo1	0.77389 (2)	0.108886 (19)	0.426923 (11)	0.00683 (5)
S1	0.42167 (6)	0.29669 (6)	0.38157 (3)	0.00770 (11)
S2	0.52730 (7)	-0.14389 (6)	0.48393 (3)	0.00870 (11)
S3	0.87553 (6)	0.37753 (6)	0.29746 (3)	0.00819 (10)
Na1	0.20072 (11)	0.58268 (10)	0.34042 (6)	0.01293 (19)
Na2	0.80653 (11)	0.75841 (10)	0.31656 (6)	0.01239 (19)
Na3	0.67303 (11)	0.51270 (10)	0.46834 (6)	0.0144 (2)
Na4	0.57005 (11)	0.46216 (10)	0.21305 (6)	0.01274 (19)
O1	0.70335 (19)	0.03236 (17)	0.33180 (10)	0.0107 (3)
O2	0.94651 (19)	0.02131 (17)	0.44263 (11)	0.0119 (3)
O3	0.57359 (18)	0.25797 (17)	0.42577 (11)	0.0107 (3)
O4	0.6456 (2)	-0.02040 (17)	0.50576 (10)	0.0116 (3)
O5	0.88450 (19)	0.28237 (18)	0.38036 (10)	0.0120 (3)
O6	0.29354 (19)	0.27689 (17)	0.44854 (9)	0.0096 (3)
O7	0.3902 (2)	0.20606 (18)	0.30489 (10)	0.0123 (3)
O8	0.4313 (2)	0.44896 (18)	0.35609 (11)	0.0124 (3)
O9	0.49519 (19)	-0.20813 (17)	0.56967 (11)	0.0130 (3)
O10	0.60611 (19)	-0.24259 (18)	0.42327 (12)	0.0147 (3)
O11	0.38958 (19)	-0.07781 (18)	0.44282 (11)	0.0139 (3)

supplementary materials

O12	0.7888 (2)	0.29908 (17)	0.22934 (10)	0.0124 (3)
O13	0.7899 (2)	0.50790 (17)	0.32281 (10)	0.0126 (3)
O14	1.03833 (19)	0.40786 (18)	0.27218 (10)	0.0133 (3)

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Mo1	0.00576 (8)	0.00737 (9)	0.00738 (8)	0.00034 (7)	-0.00028 (6)	-0.00021 (7)
S1	0.0056 (2)	0.0096 (3)	0.0078 (2)	0.0014 (2)	-0.00017 (19)	-0.0001 (2)
S2	0.0073 (2)	0.0093 (2)	0.0095 (2)	-0.0009 (2)	0.0006 (2)	-0.00087 (19)
S3	0.0073 (2)	0.0087 (2)	0.0086 (2)	-0.0001 (2)	0.00067 (18)	0.0004 (2)
Na1	0.0125 (5)	0.0130 (5)	0.0133 (4)	0.0022 (4)	0.0012 (3)	0.0019 (3)
Na2	0.0111 (5)	0.0126 (4)	0.0135 (4)	0.0012 (4)	0.0018 (4)	0.0017 (3)
Na3	0.0123 (4)	0.0166 (5)	0.0145 (5)	-0.0034 (4)	0.0023 (4)	-0.0024 (4)
Na4	0.0107 (4)	0.0156 (5)	0.0120 (4)	0.0010 (4)	-0.0008 (4)	0.0020 (4)
O1	0.0097 (8)	0.0119 (8)	0.0104 (7)	0.0002 (6)	-0.0002 (6)	-0.0008 (6)
O2	0.0113 (8)	0.0112 (8)	0.0130 (8)	0.0020 (6)	-0.0021 (6)	-0.0007 (6)
O3	0.0086 (7)	0.0128 (7)	0.0107 (7)	0.0044 (6)	-0.0029 (7)	-0.0008 (7)
O4	0.0138 (8)	0.0116 (8)	0.0095 (7)	-0.0053 (7)	-0.0018 (6)	0.0001 (6)
O5	0.0116 (8)	0.0121 (8)	0.0122 (8)	-0.0036 (6)	-0.0020 (6)	0.0042 (6)
O6	0.0080 (7)	0.0110 (7)	0.0098 (7)	-0.0010 (6)	0.0006 (6)	-0.0012 (6)
O7	0.0116 (8)	0.0162 (9)	0.0092 (7)	0.0016 (7)	-0.0016 (6)	-0.0028 (6)
O8	0.0121 (8)	0.0111 (8)	0.0140 (8)	0.0018 (7)	0.0023 (7)	0.0023 (6)
O9	0.0141 (8)	0.0131 (8)	0.0119 (7)	-0.0042 (6)	-0.0001 (7)	0.0028 (7)
O10	0.0151 (8)	0.0119 (8)	0.0171 (8)	-0.0010 (7)	0.0051 (7)	-0.0045 (7)
O11	0.0093 (8)	0.0190 (9)	0.0133 (8)	0.0021 (7)	-0.0016 (6)	0.0017 (6)
O12	0.0141 (8)	0.0120 (8)	0.0109 (7)	-0.0002 (7)	-0.0015 (6)	-0.0011 (6)
O13	0.0106 (8)	0.0108 (8)	0.0163 (8)	0.0025 (7)	-0.0008 (7)	-0.0015 (6)
O14	0.0095 (8)	0.0167 (9)	0.0136 (7)	-0.0012 (7)	0.0042 (6)	0.0008 (7)

Geometric parameters (\AA , $^\circ$)

Mo1—O2	1.6905 (16)	Na1—O9 ^{iv}	2.4972 (19)
Mo1—O1	1.7108 (16)	Na1—O1 ⁱⁱ	2.7652 (18)
Mo1—O5	1.9925 (16)	Na2—O13	2.3333 (18)
Mo1—O4	2.0102 (16)	Na2—O14 ^v	2.3350 (19)
Mo1—O6 ⁱ	2.1661 (15)	Na2—O10 ^{vi}	2.3415 (19)
Mo1—O3	2.1907 (15)	Na2—O9 ⁱ	2.3932 (19)
S1—O7	1.4564 (16)	Na2—O7 ⁱⁱ	2.5262 (18)
S1—O8	1.4681 (17)	Na2—O1 ^{vi}	2.7006 (19)
S1—O3	1.4941 (16)	Na2—S3 ^v	3.3837 (11)
S1—O6	1.4953 (16)	Na3—O11 ⁱ	2.3524 (19)
S2—O9	1.4516 (17)	Na3—O2 ^{iv}	2.3649 (19)
S2—O11	1.4575 (17)	Na3—O13	2.4115 (18)
S2—O10	1.4581 (17)	Na3—O10 ^{vi}	2.4398 (19)
S2—O4	1.5589 (17)	Na3—O3	2.5928 (19)
S3—O14	1.4590 (17)	Na3—O8	2.724 (2)

S3—O12	1.4595 (16)	Na4—O7 ⁱⁱ	2.3065 (19)
S3—O13	1.4627 (16)	Na4—O12	2.407 (2)
S3—O5	1.5346 (16)	Na4—O11 ⁱⁱ	2.4078 (19)
Na1—O12 ⁱⁱ	2.2713 (18)	Na4—O8	2.4629 (19)
Na1—O8	2.3273 (19)	Na4—O1 ⁱⁱ	2.5003 (19)
Na1—O14 ⁱⁱⁱ	2.3649 (19)	Na4—O13	2.5297 (19)
Na1—O4 ^{iv}	2.4394 (18)		
O2—Mo1—O1	102.72 (8)	O11 ⁱ —Na3—O3	129.03 (7)
O2—Mo1—O5	91.81 (7)	O2 ^{iv} —Na3—O3	75.84 (6)
O1—Mo1—O5	101.77 (7)	O13—Na3—O3	83.71 (6)
O2—Mo1—O4	95.58 (7)	O10 ^{vi} —Na3—O3	134.87 (6)
O1—Mo1—O4	93.46 (7)	O11 ⁱ —Na3—O8	175.92 (7)
O5—Mo1—O4	161.18 (7)	O2 ^{iv} —Na3—O8	73.41 (6)
O2—Mo1—O6 ⁱ	92.71 (7)	O13—Na3—O8	74.78 (6)
O1—Mo1—O6 ⁱ	163.68 (7)	O10 ^{vi} —Na3—O8	81.61 (6)
O5—Mo1—O6 ⁱ	82.77 (6)	O3—Na3—O8	53.34 (5)
O4—Mo1—O6 ⁱ	79.62 (6)	O7 ⁱⁱ —Na4—O12	121.20 (7)
O2—Mo1—O3	167.36 (7)	O7 ⁱⁱ —Na4—O11 ⁱⁱ	90.91 (6)
O1—Mo1—O3	89.16 (7)	O12—Na4—O11 ⁱⁱ	83.88 (6)
O5—Mo1—O3	81.39 (6)	O7 ⁱⁱ —Na4—O8	102.80 (7)
O4—Mo1—O3	87.91 (6)	O12—Na4—O8	104.28 (6)
O6 ⁱ —Mo1—O3	75.92 (6)	O11 ⁱⁱ —Na4—O8	156.62 (7)
O7—S1—O8	111.01 (10)	O7 ⁱⁱ —Na4—O1 ⁱⁱ	81.21 (6)
O7—S1—O3	111.95 (9)	O12—Na4—O1 ⁱⁱ	154.90 (7)
O8—S1—O3	107.53 (10)	O11 ⁱⁱ —Na4—O1 ⁱⁱ	84.66 (6)
O7—S1—O6	109.52 (9)	O8—Na4—O1 ⁱⁱ	78.95 (6)
O8—S1—O6	109.65 (10)	O7 ⁱⁱ —Na4—O13	78.73 (6)
O3—S1—O6	107.08 (9)	O12—Na4—O13	58.10 (6)
O9—S2—O11	113.77 (10)	O11 ⁱⁱ —Na4—O13	124.20 (7)
O9—S2—O10	112.83 (10)	O8—Na4—O13	77.59 (6)
O11—S2—O10	111.33 (10)	O1 ⁱⁱ —Na4—O13	144.70 (7)
O9—S2—O4	103.55 (9)	Mo1—O1—Na4 ^{vii}	131.27 (9)
O11—S2—O4	107.18 (10)	Mo1—O1—Na2 ^{viii}	110.49 (7)
O10—S2—O4	107.52 (10)	Na4 ^{vii} —O1—Na2 ^{viii}	91.78 (6)
O14—S3—O12	112.83 (10)	Mo1—O1—Na1 ^{vii}	128.10 (8)
O14—S3—O13	112.19 (10)	Na4 ^{vii} —O1—Na1 ^{vii}	93.53 (5)
O12—S3—O13	110.37 (10)	Na2 ^{viii} —O1—Na1 ^{vii}	89.08 (5)
O14—S3—O5	106.14 (9)	Mo1—O2—Na3 ⁱ	147.82 (9)
O12—S3—O5	108.22 (9)	S1—O3—Mo1	145.42 (10)
O13—S3—O5	106.73 (10)	S1—O3—Na3	99.86 (8)
O12 ⁱⁱ —Na1—O8	119.12 (7)	Mo1—O3—Na3	108.85 (6)
O12 ⁱⁱ —Na1—O14 ⁱⁱⁱ	115.36 (7)	S2—O4—Mo1	131.46 (9)

supplementary materials

O8—Na1—O14 ⁱⁱⁱ	99.58 (7)	S2—O4—Na1 ⁱ	98.63 (8)
O12 ⁱⁱ —Na1—O4 ^{iv}	131.24 (7)	Mo1—O4—Na1 ⁱ	127.05 (8)
O8—Na1—O4 ^{iv}	86.40 (6)	S3—O5—Mo1	136.93 (10)
O14 ⁱⁱⁱ —Na1—O4 ^{iv}	98.10 (6)	S1—O6—Mo1 ^{iv}	125.67 (9)
O12 ⁱⁱ —Na1—O9 ^{iv}	82.33 (6)	S1—O7—Na4 ^{vii}	129.39 (10)
O8—Na1—O9 ^{iv}	141.19 (7)	S1—O7—Na2 ^{vii}	125.94 (10)
O14 ⁱⁱⁱ —Na1—O9 ^{iv}	98.72 (7)	Na4 ^{vii} —O7—Na2 ^{vii}	101.54 (7)
O4 ^{iv} —Na1—O9 ^{iv}	57.26 (6)	S1—O8—Na1	119.62 (10)
O12 ⁱⁱ —Na1—O1 ⁱⁱ	72.64 (6)	S1—O8—Na4	107.73 (9)
O8—Na1—O1 ⁱⁱ	76.04 (6)	Na1—O8—Na4	106.56 (7)
O14 ⁱⁱⁱ —Na1—O1 ⁱⁱ	69.21 (5)	S1—O8—Na3	95.05 (8)
O4 ^{iv} —Na1—O1 ⁱⁱ	155.81 (6)	Na1—O8—Na3	125.35 (7)
O9 ^{iv} —Na1—O1 ⁱⁱ	142.71 (6)	Na4—O8—Na3	100.15 (7)
O13—Na2—O14 ^v	130.56 (7)	S2—O9—Na2 ^{iv}	147.79 (11)
O13—Na2—O10 ^{vi}	85.66 (6)	S2—O9—Na1 ⁱ	99.36 (8)
O14 ^v —Na2—O10 ^{vi}	143.70 (7)	Na2 ^{iv} —O9—Na1 ⁱ	99.58 (7)
O13—Na2—O9 ⁱ	79.43 (6)	S2—O10—Na2 ^{viii}	139.66 (10)
O14 ^v —Na2—O9 ⁱ	98.75 (7)	S2—O10—Na3 ^{viii}	121.13 (10)
O10 ^{vi} —Na2—O9 ⁱ	89.40 (7)	Na2 ^{viii} —O10—Na3 ^{viii}	91.56 (6)
O13—Na2—O7 ⁱⁱ	78.32 (6)	S2—O11—Na3 ^{iv}	119.33 (9)
O14 ^v —Na2—O7 ⁱⁱ	93.97 (6)	S2—O11—Na4 ^{vii}	111.58 (9)
O10 ^{vi} —Na2—O7 ⁱⁱ	91.17 (7)	Na3 ^{iv} —O11—Na4 ^{vii}	128.97 (8)
O9 ⁱ —Na2—O7 ⁱⁱ	157.64 (7)	S3—O12—Na1 ^{vii}	138.53 (11)
O13—Na2—O1 ^{vi}	156.46 (7)	S3—O12—Na4	98.37 (8)
O14 ^v —Na2—O1 ^{vi}	70.79 (6)	Na1 ^{vii} —O12—Na4	122.67 (8)
O10 ^{vi} —Na2—O1 ^{vi}	73.15 (6)	S3—O13—Na2	141.74 (10)
O9 ⁱ —Na2—O1 ^{vi}	109.81 (6)	S3—O13—Na3	117.23 (9)
O7 ⁱⁱ —Na2—O1 ^{vi}	91.70 (6)	Na2—O13—Na3	92.48 (6)
O11 ⁱ —Na3—O2 ^{iv}	110.07 (7)	S3—O13—Na4	93.14 (8)
O11 ⁱ —Na3—O13	101.80 (6)	Na2—O13—Na4	100.69 (7)
O2 ^{iv} —Na3—O13	148.13 (7)	Na3—O13—Na4	107.34 (7)
O11 ⁱ —Na3—O10 ^{vi}	95.79 (7)	S3—O14—Na2 ^{ix}	124.60 (10)
O2 ^{iv} —Na3—O10 ^{vi}	95.42 (7)	S3—O14—Na1 ^x	124.66 (10)
O13—Na3—O10 ^{vi}	81.85 (6)	Na2 ^{ix} —O14—Na1 ^x	109.32 (7)

Symmetry codes: (i) $x+1/2, -y+1/2, -z+1$; (ii) $-x+1, y+1/2, -z+1/2$; (iii) $x-1, y, z$; (iv) $x-1/2, -y+1/2, -z+1$; (v) $-x+2, y+1/2, -z+1/2$; (vi) $x, y+1, z$; (vii) $-x+1, y-1/2, -z+1/2$; (viii) $x, y-1, z$; (ix) $-x+2, y-1/2, -z+1/2$; (x) $x+1, y, z$.

Fig. 1

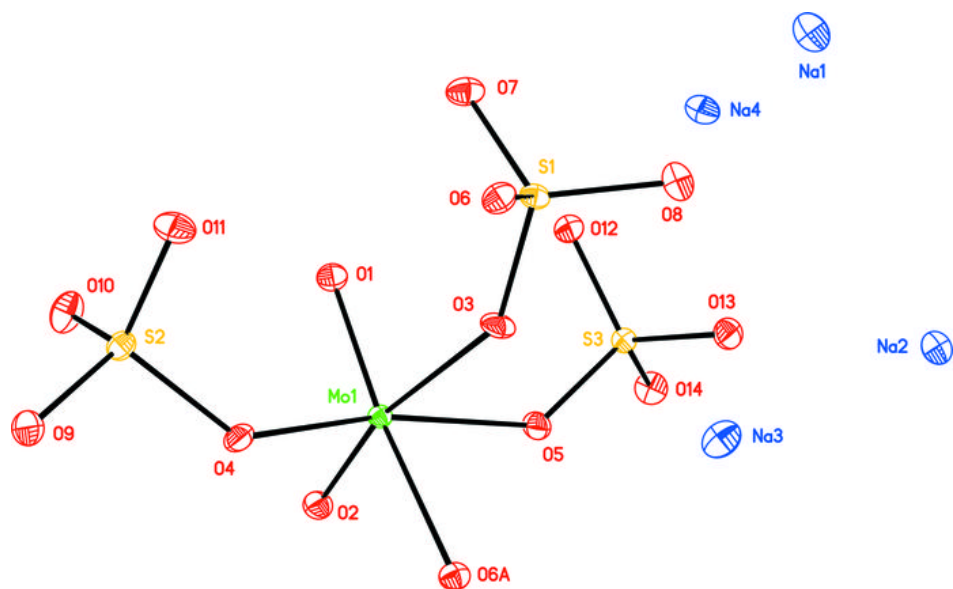


Fig. 2

