

## Disodium tricopper(II) tetrakis-[selenate(IV)] tetrahydrate

Wei Liu,<sup>a\*</sup> Lan Zhang,<sup>a</sup> Kai Hu,<sup>b</sup> Lixin Cao,<sup>a</sup> Ge Su<sup>a</sup> and Jingtao Zhao<sup>c</sup>

<sup>a</sup>Institute of Materials Science and Engineering, The Ocean University of China, Qingdao 266100, People's Republic of China, <sup>b</sup>Department of Computer Science, Dezhou University, Shandong 253023, People's Republic of China, and <sup>c</sup>State Key Laboratory of High Performance Ceramics and Superfine Microstructure, Shanghai Institute of Ceramics, Chinese Academy of Science, Shanghai 200050, People's Republic of China  
Correspondence e-mail: weiliu@ouc.edu.cn

Received 9 September 2008; accepted 21 October 2008

Key indicators: single-crystal X-ray study;  $T = 296\text{ K}$ ; mean  $\sigma(\text{Cu}=\text{O}) = 0.003\text{ \AA}$ ;  $R$  factor = 0.033;  $wR$  factor = 0.068; data-to-parameter ratio = 18.6.

The title compound,  $\text{Na}_2\text{Cu}_3(\text{SeO}_3)_4(\text{H}_2\text{O})_4$ , has been prepared under hydrothermal conditions. The crystal structure contains a three-dimensional anionic framework made up from distorted  $[\text{CuO}_4(\text{H}_2\text{O})_2]$  octahedra ( $\bar{1}$  symmetry),  $[\text{CuO}_4(\text{H}_2\text{O})]$  square pyramids and trigonal-pyramidal  $\text{SeO}_3$  units sharing common corners. The connectivity among these units leads to four- and eight-membered polyhedral rings, which by edge-sharing interconnect into walls. A rhombus-like 16-membered polyhedral ring channel system with a longest length of approximately  $14.0\text{ \AA}$  and a shortest length of  $5.3\text{ \AA}$  is enclosed by such walls along the  $a$  axis. The water molecules attached to the Cu atoms, as well as the electron lone pairs of the  $\text{Se}^{IV}$  atoms, protrude into these channels. The seven-coordinated  $\text{Na}^+$  counter-cations occupy the remaining free space of the 16-membered polyhedral ring channels. An intricate network of  $\text{O}-\text{H}\cdots\text{O}$  hydrogen bonds further consolidates the three-dimensional structure.

### Related literature

For the structures of other hydrous copper(II) selenates(IV) or selenates(VI), see: Asai & Kiriya (1973), Giester (1991); Iskhakova & Kozlova (1995).

### Experimental

#### Crystal data

$\text{Na}_2\text{Cu}_3(\text{SeO}_3)_4(\text{H}_2\text{O})_4$	$V = 740.74(10)\text{ \AA}^3$
$M_r = 816.50$	$Z = 2$
Monoclinic, $P2_1/c$	$\text{Mo K}\alpha$ radiation
$a = 5.2218(5)\text{ \AA}$	$\mu = 14.24\text{ mm}^{-1}$
$b = 8.9863(6)\text{ \AA}$	$T = 296(2)\text{ K}$
$c = 15.7960(11)\text{ \AA}$	$0.15 \times 0.10 \times 0.10\text{ mm}$
$\beta = 92.071(4)^\circ$	

#### Data collection

Bruker SMART CCD diffractometer	6010 measured reflections
Absorption correction: multi-scan ( <i>SADABS</i> ; Sheldrick, 2004)	2142 independent reflections
$R_{\text{int}} = 0.027$	2065 reflections with $I > 2\sigma(I)$
$T_{\min} = 0.204$ , $T_{\max} = 0.250$	

#### Refinement

$R[F^2 > 2\sigma(F^2)] = 0.033$	H atoms treated by a mixture of independent and constrained refinement
$wR(F^2) = 0.068$	$\Delta\rho_{\max} = 0.77\text{ e \AA}^{-3}$
$S = 1.12$	$\Delta\rho_{\min} = -1.02\text{ e \AA}^{-3}$
2142 reflections	
115 parameters	

**Table 1**  
Selected bond lengths ( $\text{\AA}$ ).

Se1—O7	1.698 (3)	Cu1—O6	1.990 (3)
Se1—O2	1.705 (3)	Cu1—O8 <sup>i</sup>	2.475 (3)
Se1—O4	1.709 (3)	Cu2—O1 <sup>ii</sup>	1.947 (3)
Se2—O8	1.673 (3)	Cu2—O3	1.962 (3)
Se2—O1	1.708 (3)	Cu2—O2	1.968 (3)
Se2—O3	1.717 (3)	Cu2—O7 <sup>iii</sup>	1.980 (3)
Cu1—O4	1.968 (3)	Cu2—O5	2.268 (3)

Symmetry codes: (i)  $-x - 1, y - \frac{1}{2}, -z + \frac{1}{2}$ ; (ii)  $x + 1, y, z$ ; (iii)  $x - 1, y, z$ .

**Table 2**  
Hydrogen-bond geometry ( $\text{\AA}$ ,  $^\circ$ ).

D—H···A	D—H	H···A	D···A	D—H···A
O5—H1···O4 <sup>iv</sup>	0.80 (8)	2.00 (8)	2.786 (4)	168 (7)
O5—H2···O3 <sup>v</sup>	0.87 (8)	1.88 (8)	2.746 (4)	174 (7)
O6—H3···O8 <sup>vi</sup>	0.87 (8)	1.91 (8)	2.758 (5)	163 (7)
O6—H4···O1 <sup>i</sup>	0.89 (8)	1.76 (8)	2.641 (4)	169 (8)

Symmetry codes: (i)  $-x - 1, y - \frac{1}{2}, -z + \frac{1}{2}$ ; (ii)  $-x, -y + 1, -z$ ; (v)  $-x - 1, y + \frac{1}{2}, -z + \frac{1}{2}$ ; (vi)  $-x, y - \frac{1}{2}, -z + \frac{1}{2}$ .

Data collection: *SMART* (Bruker, 2001); cell refinement: *SAINT* (Bruker, 2001); data reduction: *SAINT*; program(s) used to solve structure: *SHELXS97* (Sheldrick, 2008); program(s) used to refine structure: *SHELXL97* (Sheldrick, 2008); molecular graphics: *ORTEP-3* (Farrugia, 1997) and *DIAMOND* (Crystal Impact, 2004); software used to prepare material for publication: *WinGX* (Farrugia, 1999).

This work was supported by the opening project of the State Key Laboratory of High Performance Ceramics and Superfine Microstructure (grant No. SKL200706SIC).

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: WM2197).

### References

- Asai, T. & Kiriya, R. (1973). *Bull. Chem. Soc. Jpn.*, **46**, 2395–2401.
- Bruker (2001). *SMART* and *SAINT*. Bruker AXS Inc., Madison, Wisconsin, USA.
- Crystal Impact (2004). *DIAMOND*. Crystal Impact GbR, Bonn, Germany.
- Farrugia, L. J. (1997). *J. Appl. Cryst.*, **30**, 565.
- Farrugia, L. J. (1999). *J. Appl. Cryst.*, **32**, 837–838.
- Giester, G. (1991). *Monatsh. Chem.*, **122**, 229–234.
- Iskhakova, L. D. & Kozlova, N. P. (1995). *Kristallografiya*, **40**, 635–638.
- Sheldrick, G. M. (2008). *Acta Cryst. A*, **64**, 112–122.
- Sheldrick, G. M. (2004). *SADABS*. University of Göttingen, Germany.

# supporting information

*Acta Cryst.* (2008). E64, i78 [doi:10.1107/S160053680803434X]

## Disodium tricopper(II) tetrakis[selenate(IV)] tetrahydrate

Wei Liu, Lan Zhang, Kai Hu, Lixin Cao, Ge Su and Jingtai Zhao

### S1. Comment

Studies of hydrous copper selenites and selenates with three-dimensional frameworks have been reported previously, e.g. by Asai & Kiriyma (1973), Giester (1991) and Iskhakova & Kozlova (1995). Among the corresponding structures various polyhedral ring channel systems are established. The current article presents the result of the single-crystal X-ray analysis of a new sodium copper selenite,  $\text{Na}_2\text{Cu}_3(\text{SeO}_3)_4(\text{H}_2\text{O})_4$ , (I), with a 16-membered polyhedral ring channel system.

In the asymmetric unit of (I) there are two crystallographically distinct copper atoms. The six-coordinated Cu1 site is a typical Jahn-Teller ion with a distorted, tetragonally elongated octahedral  $[\text{Cu}1\text{O}_4(\text{H}_2\text{O})_2]$  coordination, whereas Cu2 is surrounded by five O-atoms, leading to a distorted square-pyramidal  $[\text{Cu}2\text{O}_4(\text{H}_2\text{O})]$  environment. The two independent selenium atoms are coordinated by three oxygen atoms, forming the characteristic trigonal-pyramidal  $\text{SeO}_3^{2-}$  anion (Fig. 1).

The square-pyramidal  $[\text{Cu}2\text{O}_4(\text{H}_2\text{O})]$  units share its basal O atoms with four neighboring  $\text{SeO}_3$  units leading to chains of corner-shared four-membered polyhedral rings running along [100]. The  $[\text{Cu}1\text{O}_4(\text{H}_2\text{O})_2]$  units are located between such parallel chains and bridge them via Cu—O—Se bonds into an open framework. The water molecules attached to Cu1 and Cu2 as well as the electron lone-pairs of the selenium(IV) atoms protrude into the free space of this network (Fig. 2).

The basic features of the structure could also be described as the assemblage of linear chains of Cu and Se centres leading to 4-membered and 8-membered rings that interconnect by edge-sharing into two similar wavy layer packings extending along [011] and [011̄], respectively. Such layers intersect at the Cu(1) sites, eventually forming a rhombus-like 16-membered ring channel system extending along the  $a$  axis with the biggest length of approximately 14.0 Å and the smallest length of 5.3 Å (Fig.3).

The  $\text{Na}^+$  counter cations are coordinated by seven oxygen atoms and occupy the central space of the 16-membered ring polyhedral channels to keep the structural stability and satisfy the charge balance. An intricate network of O—H···O hydrogen bonds further consolidates the three-dimensional structure (Table 2).


### S2. Experimental

The title compound was synthesized under hydrothermal conditions. A mixture of  $\text{Na}_2\text{SeO}_3$  and  $\text{CuSO}_4 \cdot 5\text{H}_2\text{O}$  in a molar ratio of 1:1 was placed in a Teflon-lined stainless steel autoclave and heated to 443 K for 5 d, cooled at 2 K/h to 373 K, and finally cooled to room temperature. Light blue crystals with a rod-like habit were obtained. Cu, Se and Na contents were analyzed using ICP-AES (Varian Vista, radial observation): Obs./calc. mass%: Cu, 23.33/23.91; Se, 38.70/39.23; Na, 5.63/5.42.

### S3. Refinement


Charge balance considerations and bond valence sum (BVS) calculations indicate that atoms O5 and O6 belong to water molecules. For the metal atoms, the oxidation states of +2 for Cu ions (BVS Cu1: +2.05 and Cu2: +2.01), +4 for the Se

ions (BVS Se1: +4.01 and Se2: +4.06) and +1 for the Na ions (BVS Na1: +1.02) were confirmed. The hydrogen atoms of the water molecules were located from difference Fourier maps and were refined with distance restraints of  $d(\text{O—H}) = 0.80(8)\text{—}0.89(8)\text{ \AA}$  and a common  $U_{\text{iso}}$  parameter of  $0.05\text{ \AA}^2$ .

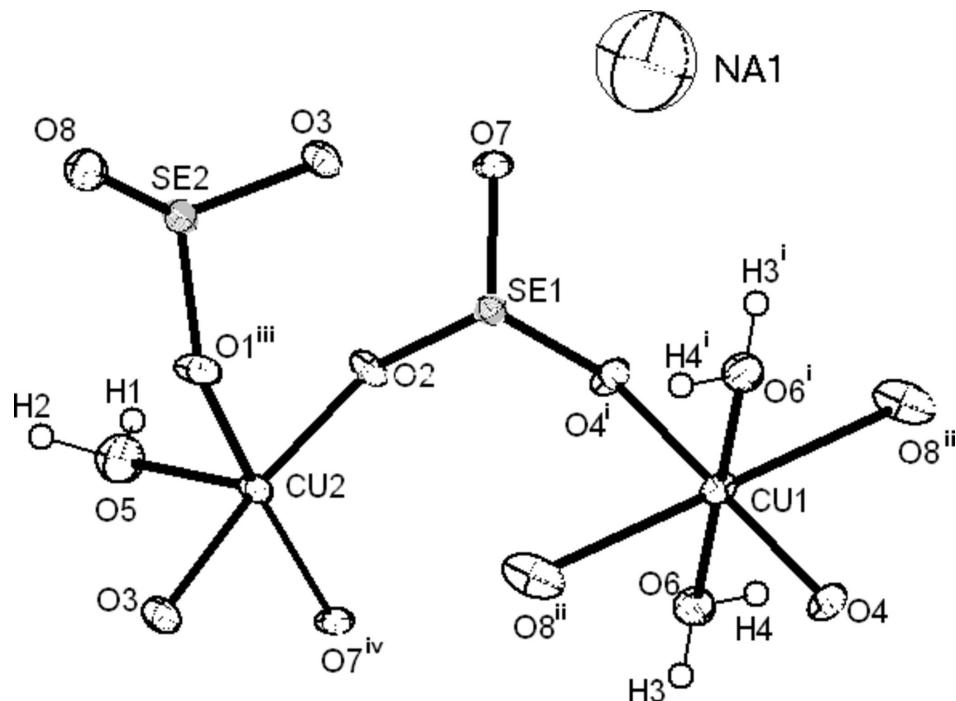


**Figure 1**

The coordination environment of copper and selenium atoms with anisotropic thermal ellipsoids drawn at the 60% probability level. H atoms are drawn as small spheres of arbitrary radius. [Symmetry codes: (i)  $-x, -y, -z$ ; (ii)  $-x - 1, y - 1/2, -z + 1/2$ ; (iii)  $x + 1, y, z$ ; (iv)  $x - 1, y, z$ .]

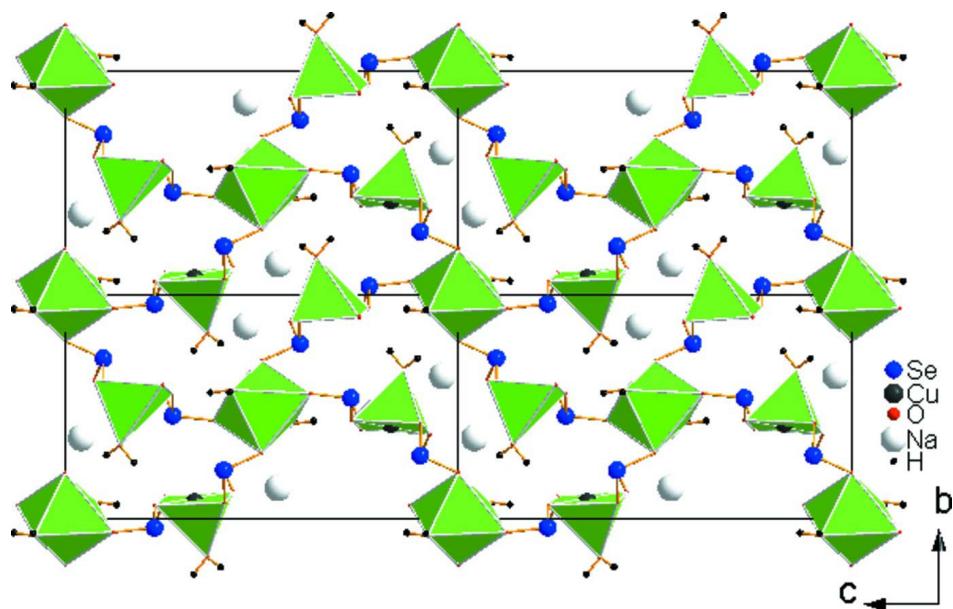

**Figure 2**

The 16-membered polyhedral ring channels of (I), filled with  $\text{Na}^+$  counter cations.

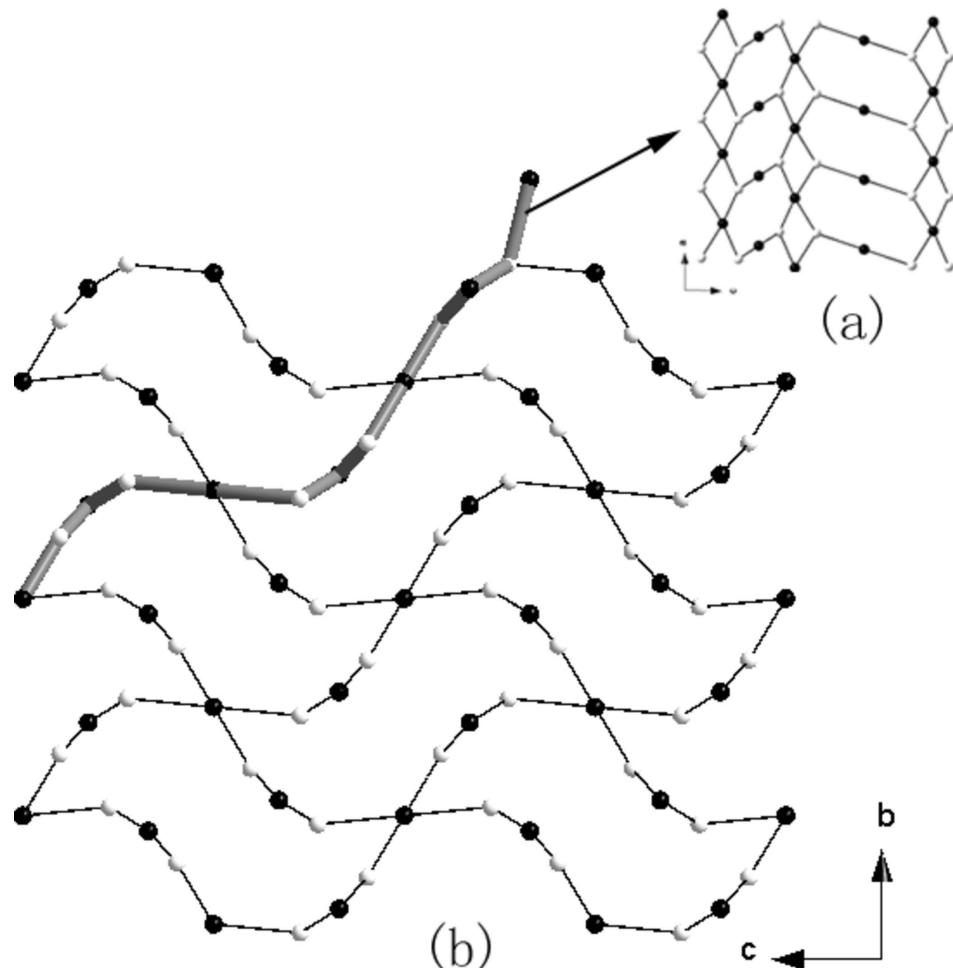**Figure 3**

Schematic representation of the formation of the anionic framework structure of (I). (a): The wavy layer built from an edge-sharing linear chain by corner-sharing 4-membered rings and ladders by edge-sharing 8-membered rings; (b): The wavy layers intersecting each other with an approximate angle of  $110^\circ$  to the entire three-dimensional open-framework. (Black spheres: Cu atoms; white spheres: Se atoms).

### disodium tricopper(II) tetrakis[selenate(IV)] tetrahydrate

#### Crystal data



$M_r = 816.50$

Monoclinic,  $P2_1/c$

Hall symbol: -P 2ybc

$a = 5.2218 (5)$  Å

$b = 8.9863 (6)$  Å

$c = 15.7960 (11)$  Å

$\beta = 92.071 (4)^\circ$

$V = 740.74 (10)$  Å<sup>3</sup>

$Z = 2$

$F(000) = 762$

$D_x = 3.661 \text{ Mg m}^{-3}$

Mo  $K\alpha$  radiation,  $\lambda = 0.71073$  Å

Cell parameters from 986 reflections

$\theta = 2.6\text{--}22.8^\circ$

$\mu = 14.24 \text{ mm}^{-1}$

$T = 296$  K

Rod, light blue

$0.15 \times 0.10 \times 0.10$  mm

*Data collection*

Bruker SMART CCD  
diffractometer  
Radiation source: fine-focus sealed tube  
Graphite monochromator  
 $\omega$  scans  
Absorption correction: multi-scan  
(SADABS; Sheldrick, 2004)  
 $T_{\min} = 0.204$ ,  $T_{\max} = 0.250$

6010 measured reflections  
2142 independent reflections  
2065 reflections with  $I > 2\sigma(I)$   
 $R_{\text{int}} = 0.027$   
 $\theta_{\max} = 30.0^\circ$ ,  $\theta_{\min} = 2.6^\circ$   
 $h = -7 \rightarrow 7$   
 $k = -12 \rightarrow 12$   
 $l = -21 \rightarrow 22$

*Refinement*

Refinement on  $F^2$   
Least-squares matrix: full  
 $R[F^2 > 2\sigma(F^2)] = 0.033$   
 $wR(F^2) = 0.068$   
 $S = 1.12$   
2142 reflections  
115 parameters  
0 restraints  
Primary atom site location: structure-invariant  
direct methods

Secondary atom site location: difference Fourier  
map  
Hydrogen site location: inferred from  
neighbouring sites  
H atoms treated by a mixture of independent  
and constrained refinement  
 $w = 1/[\sigma^2(F_o^2) + (0.0202P)^2 + 3.7977P]$   
where  $P = (F_o^2 + 2F_c^2)/3$   
 $(\Delta/\sigma)_{\max} = 0.001$   
 $\Delta\rho_{\max} = 0.77 \text{ e } \text{\AA}^{-3}$   
 $\Delta\rho_{\min} = -1.02 \text{ e } \text{\AA}^{-3}$

*Special details*

**Geometry.** All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

**Refinement.** Refinement of  $F^2$  against ALL reflections. The weighted  $R$ -factor  $wR$  and goodness of fit  $S$  are based on  $F^2$ , conventional  $R$ -factors  $R$  are based on  $F$ , with  $F$  set to zero for negative  $F^2$ . The threshold expression of  $F^2 > \sigma(F^2)$  is used only for calculating  $R$ -factors(gt) etc. and is not relevant to the choice of reflections for refinement.  $R$ -factors based on  $F^2$  are statistically about twice as large as those based on  $F$ , and  $R$ -factors based on ALL data will be even larger.

*Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters ( $\text{\AA}^2$ )*

	<i>x</i>	<i>y</i>	<i>z</i>	$U_{\text{iso}}^*/U_{\text{eq}}$
Se1	0.20254 (7)	0.28287 (4)	0.09687 (2)	0.01090 (10)
Se2	-0.79415 (7)	0.53958 (5)	0.27304 (2)	0.01476 (11)
Cu1	0.0000	0.0000	0.0000	0.01381 (14)
Cu2	-0.29891 (8)	0.42910 (6)	0.17116 (3)	0.01266 (11)
O1	-1.0733 (5)	0.4403 (4)	0.27181 (18)	0.0207 (6)
O2	-0.0088 (5)	0.4276 (3)	0.09497 (18)	0.0153 (5)
O3	-0.5831 (5)	0.4016 (3)	0.24757 (18)	0.0165 (5)
O4	0.1289 (6)	0.2058 (3)	0.00011 (18)	0.0166 (5)
O5	-0.3653 (7)	0.6725 (4)	0.1392 (2)	0.0209 (6)
O6	0.2781 (6)	-0.0756 (4)	0.07804 (19)	0.0199 (6)
O7	0.4702 (5)	0.3793 (3)	0.07309 (17)	0.0149 (5)
O8	-0.7371 (6)	0.5600 (4)	0.3773 (2)	0.0272 (7)
Na1	0.7415 (3)	0.3619 (2)	-0.04070 (11)	0.0226 (4)
H1	-0.277 (15)	0.707 (9)	0.104 (5)	0.050*
H2	-0.372 (14)	0.748 (9)	0.174 (5)	0.050*

H4	0.226 (15)	-0.063 (9)	0.131 (5)	0.050*
H3	0.437 (15)	-0.049 (9)	0.088 (5)	0.050*

*Atomic displacement parameters ( $\text{\AA}^2$ )*

	$U^{11}$	$U^{22}$	$U^{33}$	$U^{12}$	$U^{13}$	$U^{23}$
Se1	0.01040 (17)	0.01286 (18)	0.00949 (17)	-0.00189 (12)	0.00133 (12)	-0.00064 (12)
Se2	0.01172 (18)	0.0176 (2)	0.01500 (18)	0.00083 (13)	0.00180 (13)	-0.00071 (14)
Cu1	0.0139 (3)	0.0124 (3)	0.0149 (3)	-0.0023 (2)	-0.0030 (2)	-0.0004 (2)
Cu2	0.0085 (2)	0.0195 (2)	0.0101 (2)	0.00022 (17)	0.00143 (15)	-0.00087 (17)
O1	0.0097 (12)	0.0415 (19)	0.0110 (12)	-0.0042 (12)	0.0007 (10)	-0.0034 (12)
O2	0.0107 (12)	0.0208 (14)	0.0146 (12)	0.0036 (10)	0.0042 (10)	0.0019 (11)
O3	0.0137 (12)	0.0207 (14)	0.0152 (12)	0.0002 (11)	0.0044 (10)	0.0009 (11)
O4	0.0211 (14)	0.0166 (13)	0.0121 (12)	-0.0080 (11)	0.0015 (10)	-0.0022 (10)
O5	0.0298 (16)	0.0117 (14)	0.0215 (15)	-0.0011 (12)	0.0048 (13)	-0.0013 (11)
O6	0.0177 (14)	0.0280 (17)	0.0138 (13)	0.0011 (12)	-0.0030 (11)	-0.0043 (12)
O7	0.0099 (11)	0.0215 (14)	0.0135 (12)	-0.0054 (10)	0.0010 (9)	-0.0021 (11)
O8	0.0190 (14)	0.045 (2)	0.0176 (14)	-0.0028 (14)	0.0012 (12)	-0.0149 (14)
Na1	0.0193 (8)	0.0307 (10)	0.0177 (8)	0.0015 (7)	0.0015 (6)	0.0005 (7)

*Geometric parameters ( $\text{\AA}$ ,  $^\circ$ )*

Se1—O7	1.698 (3)	Cu2—O1 <sup>iii</sup>	1.947 (3)
Se1—O2	1.705 (3)	Cu2—O3	1.962 (3)
Se1—O4	1.709 (3)	Cu2—O2	1.968 (3)
Se2—O8	1.673 (3)	Cu2—O7 <sup>iv</sup>	1.980 (3)
Se2—O1	1.708 (3)	Cu2—O5	2.268 (3)
Se2—O3	1.717 (3)	Na1—O7	2.333 (4)
Cu1—O4	1.968 (3)	Na1—O5 <sup>v</sup>	2.482 (4)
Cu1—O4 <sup>i</sup>	1.968 (3)	Na1—O2 <sup>vi</sup>	2.519 (4)
Cu1—O6	1.990 (3)	Na1—O4 <sup>iii</sup>	2.526 (4)
Cu1—O6 <sup>i</sup>	1.990 (3)	Na1—O2 <sup>iii</sup>	2.537 (3)
Cu1—O8 <sup>ii</sup>	2.475 (3)	Na1—O7 <sup>vii</sup>	2.618 (4)
Cu1—O8 <sup>ii</sup>	2.475 (3)	Na1—O6 <sup>vii</sup>	2.641 (4)
O7—Se1—O2	98.30 (14)	Cu2—O5—H2	129 (5)
O7—Se1—O4	99.75 (13)	Na1 <sup>v</sup> —O5—H2	116 (5)
O2—Se1—O4	99.71 (14)	H1—O5—H2	100 (7)
O8—Se2—O1	100.95 (16)	Cu1—O6—Na1 <sup>vii</sup>	99.94 (13)
O8—Se2—O3	102.54 (16)	Cu1—O6—H4	107 (5)
O1—Se2—O3	100.08 (15)	Na1 <sup>vii</sup> —O6—H4	109 (5)
O4—Cu1—O4 <sup>i</sup>	180.00 (6)	Cu1—O6—H3	133 (5)
O4—Cu1—O6	94.50 (13)	Na1 <sup>vii</sup> —O6—H3	110 (5)
O4 <sup>i</sup> —Cu1—O6	85.50 (13)	H4—O6—H3	97 (7)
O4—Cu1—O6 <sup>i</sup>	85.50 (13)	Se1—O7—Cu2 <sup>iii</sup>	115.16 (15)
O4 <sup>i</sup> —Cu1—O6 <sup>i</sup>	94.50 (13)	Se1—O7—Na1	131.60 (16)
O6—Cu1—O6 <sup>i</sup>	180.00 (14)	Cu2 <sup>iii</sup> —O7—Na1	104.37 (12)
O1 <sup>iii</sup> —Cu2—O3	87.30 (12)	Se1—O7—Na1 <sup>vi</sup>	98.71 (13)

O1 <sup>iii</sup> —Cu2—O2	92.48 (12)	Cu2 <sup>iii</sup> —O7—Na1 <sup>vi</sup>	101.13 (12)
O3—Cu2—O2	172.34 (13)	Na1—O7—Na1 <sup>vi</sup>	99.95 (12)
O1 <sup>iii</sup> —Cu2—O7 <sup>iv</sup>	169.80 (14)	O7—Na1—O5 <sup>v</sup>	90.14 (12)
O3—Cu2—O7 <sup>iv</sup>	90.00 (12)	O7—Na1—O2 <sup>vi</sup>	124.83 (13)
O2—Cu2—O7 <sup>iv</sup>	88.88 (11)	O5 <sup>v</sup> —Na1—O2 <sup>vi</sup>	108.41 (12)
O1 <sup>iii</sup> —Cu2—O5	102.39 (14)	O7—Na1—O4 <sup>iii</sup>	110.09 (12)
O3—Cu2—O5	98.36 (13)	O5 <sup>v</sup> —Na1—O4 <sup>iii</sup>	134.38 (13)
O2—Cu2—O5	89.17 (12)	O2 <sup>vi</sup> —Na1—O4 <sup>iii</sup>	93.18 (11)
O7 <sup>iv</sup> —Cu2—O5	87.73 (12)	O7—Na1—O2 <sup>iii</sup>	69.01 (10)
Se2—O1—Cu2 <sup>iv</sup>	121.82 (17)	O5 <sup>v</sup> —Na1—O2 <sup>iii</sup>	158.39 (13)
Se1—O2—Cu2	120.42 (16)	O2 <sup>vi</sup> —Na1—O2 <sup>iii</sup>	80.72 (11)
Se1—O2—Na1 <sup>vi</sup>	102.26 (13)	O4 <sup>iii</sup> —Na1—O2 <sup>iii</sup>	62.06 (10)
Cu2—O2—Na1 <sup>vi</sup>	130.61 (15)	O7—Na1—O7 <sup>vi</sup>	80.06 (12)
Se1—O2—Na1 <sup>iv</sup>	98.62 (14)	O5 <sup>v</sup> —Na1—O7 <sup>vi</sup>	70.66 (11)
Cu2—O2—Na1 <sup>iv</sup>	97.75 (12)	O2 <sup>vi</sup> —Na1—O7 <sup>vi</sup>	60.11 (10)
Na1 <sup>vi</sup> —O2—Na1 <sup>iv</sup>	99.28 (11)	O4 <sup>iii</sup> —Na1—O7 <sup>vi</sup>	150.69 (12)
Se2—O3—Cu2	124.02 (17)	O2 <sup>iii</sup> —Na1—O7 <sup>vi</sup>	99.14 (11)
Se1—O4—Cu1	116.58 (15)	O7—Na1—O6 <sup>vii</sup>	102.55 (12)
Se1—O4—Na1 <sup>iv</sup>	98.94 (14)	O5 <sup>v</sup> —Na1—O6 <sup>vii</sup>	73.44 (11)
Cu1—O4—Na1 <sup>iv</sup>	104.54 (13)	O2 <sup>vi</sup> —Na1—O6 <sup>vii</sup>	132.30 (12)
Cu2—O5—Na1 <sup>v</sup>	97.49 (13)	O4 <sup>iii</sup> —Na1—O6 <sup>vii</sup>	62.63 (11)
Cu2—O5—H1	116 (6)	O2 <sup>iii</sup> —Na1—O6 <sup>vii</sup>	115.47 (12)
Na1 <sup>v</sup> —O5—H1	94 (5)	O7 <sup>vi</sup> —Na1—O6 <sup>vii</sup>	144.02 (11)

Symmetry codes: (i)  $-x, -y, -z$ ; (ii)  $-x-1, y-1/2, -z+1/2$ ; (iii)  $x+1, y, z$ ; (iv)  $x-1, y, z$ ; (v)  $-x, -y+1, -z$ ; (vi)  $-x+1, -y+1, -z$ ; (vii)  $-x+1, -y, -z$ .

#### Hydrogen-bond geometry ( $\text{\AA}$ , $^\circ$ )

$D\text{—H}\cdots A$	$D\text{—H}$	$H\cdots A$	$D\cdots A$	$D\text{—H}\cdots A$
O5—H1 $\cdots$ O4 <sup>v</sup>	0.80 (8)	2.00 (8)	2.786 (4)	168 (7)
O5—H2 $\cdots$ O3 <sup>viii</sup>	0.87 (8)	1.88 (8)	2.746 (4)	174 (7)
O6—H3 $\cdots$ O8 <sup>ix</sup>	0.87 (8)	1.91 (8)	2.758 (5)	163 (7)
O6—H4 $\cdots$ O1 <sup>ii</sup>	0.89 (8)	1.76 (8)	2.641 (4)	169 (8)

Symmetry codes: (ii)  $-x-1, y-1/2, -z+1/2$ ; (v)  $-x, -y+1, -z$ ; (viii)  $-x-1, y+1/2, -z+1/2$ ; (ix)  $-x, y-1/2, -z+1/2$ .