

catena-Poly[{di- μ -isonicotinato-bis-[diaquaisonicotinatioeuropium(III)]- μ -isonicotinato-[diisonicotinatocopper(II)]- μ -isonicotinato}]

Miao-Ling Huang

Department of Chemistry and Life Sciences, Quanzhou Normal University, Fujian 362000, People's Republic of China

Correspondence e-mail: hml301@163.com


Received 27 October 2008; accepted 18 November 2008

 Key indicators: single-crystal X-ray study; $T = 295$ K; mean $\sigma(\text{C}-\text{C}) = 0.004$ Å; R factor = 0.021; wR factor = 0.049; data-to-parameter ratio = 13.5.

The title compound, $[\text{CuEu}_2(\text{C}_6\text{H}_4\text{NO}_2)_8(\text{H}_2\text{O})_4]_n$, displays a one-dimensional chain structure. The four-coordinate Cu^{II} ion (site symmetry $\bar{1}$) adopts a *trans*- CuN_2O_2 geometry and is bridged by two carboxylate groups from two isonicotinate ligands. The Eu^{III} ion adopts a distorted square-antiprismatic geometry, being coordinated by four O atoms from bridging carboxylate groups of four isonicotinate ligands, two O atoms from chelating carboxylate groups of one isonicotinate ligand and two O atoms from coordinated water molecules; adjacent Eu^{III} ions in the chain are related by inversion. The water molecules interact with the ligands *via* $\text{O}-\text{H}\cdots\text{N}$ hydrogen bonds [$\text{O}\cdots\text{O} = 2.782$ (3)– 2.881 (3) Å], which link the chains into a three-dimensional structure.

Related literature

For background literature, see: Zhao *et al.* (2006); Ma *et al.* (2001). For related structures, see: Liang *et al.* (2007); Zhang *et al.* (2005); Deng *et al.* (2008).

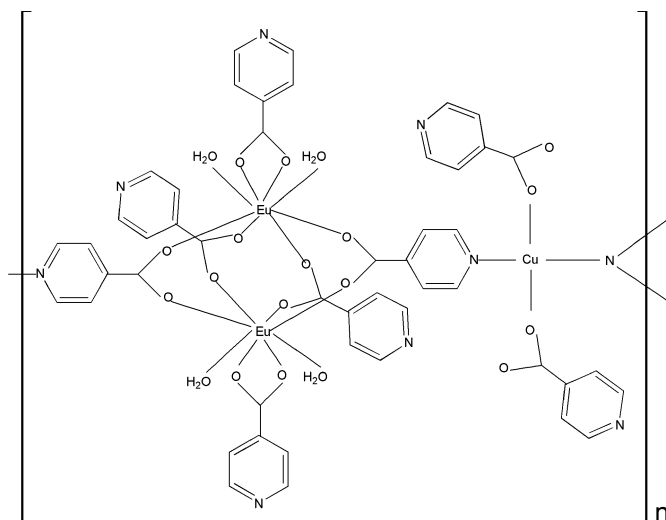

Experimental

Crystal data

$[\text{CuEu}_2(\text{C}_6\text{H}_4\text{NO}_2)_8(\text{H}_2\text{O})_4]$
 $M_r = 1416.34$
 Monoclinic, $P2_1/n$
 $a = 9.5218$ (9) Å
 $b = 15.0371$ (13) Å
 $c = 18.2850$ (16) Å
 $\beta = 93.822$ (1)°

$V = 2612.2$ (4) Å³
 $Z = 2$
 Mo $K\alpha$ radiation
 $\mu = 2.86$ mm⁻¹
 $T = 295$ (2) K
 $0.40 \times 0.30 \times 0.27$ mm

Data collection

Bruker SMART CCD area-detector diffractometer
 Absorption correction: multi-scan (SADABS; Sheldrick, 2003)
 $T_{\text{min}} = 0.397$, $T_{\text{max}} = 0.517$
 (expected range = 0.355–0.462)

18387 measured reflections
 4853 independent reflections
 4222 reflections with $I > 2\sigma(I)$
 $R_{\text{int}} = 0.036$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.021$
 $wR(F^2) = 0.049$
 $S = 1.04$
 4853 reflections
 359 parameters

6 restraints
 H-atom parameters constrained
 $\Delta\rho_{\text{max}} = 0.36$ e Å⁻³
 $\Delta\rho_{\text{min}} = -0.37$ e Å⁻³

Table 1

Hydrogen-bond geometry (Å, °).

$D-\text{H}\cdots A$	$D-\text{H}$	$\text{H}\cdots A$	$D\cdots A$	$D-\text{H}\cdots A$
$\text{O}10-\text{H}4\text{W}\cdots\text{O}8^{\text{i}}$	0.83	1.97	2.782 (3)	165
$\text{O}9-\text{H}2\text{W}\cdots\text{O}1^{\text{i}}$	0.83	1.98	2.790 (3)	164
$\text{O}10-\text{H}3\text{W}\cdots\text{N}1^{\text{ii}}$	0.83	2.06	2.881 (3)	169
$\text{O}9-\text{H}1\text{W}\cdots\text{N}4^{\text{iii}}$	0.83	2.00	2.807 (3)	161

Symmetry codes: (i) $-x, -y + 2, -z$; (ii) $x + \frac{1}{2}, -y + \frac{5}{2}, z - \frac{1}{2}$; (iii) $-x - \frac{1}{2}, y + \frac{1}{2}, -z - \frac{1}{2}$.

Data collection: SMART (Bruker, 2001); cell refinement: SAINT (Bruker, 2003); data reduction: SAINT; program(s) used to solve structure: SHELXS97 (Sheldrick, 2008); program(s) used to refine structure: SHELXL97 (Sheldrick, 2008); molecular graphics: ORTEP-3 for Windows (Farrugia, 1997); software used to prepare material for publication: SHELXTL (Sheldrick, 2008).

This work was supported by the Natural Science Foundation of Quanzhou Normal University of China (grant No. 2008 K J01).

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: PV2118).

References

Bruker (2001). *SMART*. Bruker AXS Inc., Madison, Wisconsin, USA.

- Bruker (2003). *S SAINT*. Bruker AXS Inc., Madison, Wisconsin, USA.
- Deng, H., Liu, Z.-H., Qiu, Y.-C., Li, Y.-H. & Zeller, M. (2008). *Inorg. Chem. Commun.* pp. 978–981.
- Farrugia, L. J. (1997). *J. Appl. Cryst.* **30**, 565.
- Liang, F.-P., Huang, M.-L., Jiang, C.-F., Li, Y. & Hu, R.-X. (2007). *J. Coord. Chem.* pp. 2343–2350.
- Ma, B.-Q., Gao, S., Su, G. & Xu, G.-X. (2001). *Angew. Chem. Int. Ed.* **40**, 434–437.
- Sheldrick, G. M. (2003). *SADABS*. University of Göttingen, Germany.
- Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.
- Zhang, M.-B., Zhang, J., Zheng, S.-T. & Yang, G.-Y. (2005). *Angew. Chem. Int. Ed.* **44**, 1385–1388.
- Zhao, B., Gao, H.-L., Chen, X.-Y., Cheng, P., Shi, W., Liao, D.-Z., Yan, S. P. & Jiang, Z.-H. (2006). *Chem. Eur. J.* **12**, 149–158.

supplementary materials

Acta Cryst. (2008). E64, m1595-m1596 [doi:10.1107/S1600536808038476]

***catena*-Poly[{di- μ -isonicotinato-bis[di μ quaisonicotinatoeuropium(III)] }- μ -isonicotinato-[diisonicotinatocopper(II)]- μ -isonicotinato]**

M.-L. Huang

Comment

In recent years, the study of heterometallic lanthanide-transition metal polymers has played an important role due to their potential applications in catalytic, magnetic and hightemperaturesupraleiter materials (Zhao *et al.*, 2006; Ma *et al.*, 2001). Isonicotinic acid is a good linear bridging ligand with oxygen and nitrogen donors on opposite sides. the crystal structures of heterometallic lanthanide-transition metal complexes with isonicotinate ligand have been reported (Liang *et al.*, 2007; Zhang *et al.*, 2005; Deng *et al.*, 2008;). In order to extend further the study of these compounds, the title complex, (I), has been synthesized and its structure is presented in this article.

The molecular structure and the crystal packing diagram of the title compound are shown in Figs. 1 and 2, respectively. The complex structure is a one-dimensional chain consisting of two metal centres - Cu(II) and Eu(III), which are linked to each other by tridentate bridging isonicotinate ligands. It is worthwhile to note that one-dimensional chain is an axial-symmetric structure. Each Eu(III) cation is of an eight coordination consisting of eight oxygen atoms from four bridging carboxylate O atoms of four isonicotinate ligands [Eu—O distances ranging from 2.341 (2) to 2.366 (2) Å], two from chelating carboxylate O atoms of one isonicotinate ligand [Eu—O distances 2.477 (2) and 2.5428 (19) Å] and two water molecules [Eu—O distances 2.4133 (19) and 2.4548 (19) Å]. The O—Eu—O bond angles are in the range from 51.88 (6) to 152.34 (8)°. Therefore, the coordination polyhedron can be described as a distorted square antiprism. Two Eu(III) ions are connected by four bridging carboxylate groups of four isonicotinate ligands with a Eu...Eu distance of 4.5265 (4) Å. The Cu(II) cation, lies on an inversion center and is of four-coordination with an quadrilateral planar geometry, in which two coordinated oxygen atoms belong to two monodentate coordinating carboxylate O atoms of two isonicotinate ligands [Cu—O distance 1.9867 (19) Å] and two nitrogen atoms from two tridentate bridging isonicotinate ligands [Cu—N distance 2.011 (2) Å]. The O—Cu—N bond angles lie in a very narrow range of 89.26 (9) to 90.74 (9)°. Two weak Cu—N bonds with a distance of 2.654 (3)Å on both sides of the quadrilateral planar copper center are observed, in which the coordination N atoms come from pyridyl groups of two isonicotinate ligands bridging two Eu(III) ions *via* carboxylates in two adjacent molecular chains. The water molecules are hydrogen bonded to the N atoms of the pyridyl groups of the ligands *via* O—H...N type hydrogen bonds which link the complex into a three-dimensional structure (details of hydrogen bonding geometry are given in Table 1).

Experimental

A mixture of Eu₂O₃ (0.1811 g, 0.5 mmol), CuO (0.0801 g, 1 mmol), isonicotinic acid (0.4923 g, 4.0 mmol), and H₂O (20.0 ml) was sealed in a 40 ml Teflon-lined stainless steel reactor, heated in an oven at 413 K for 72 h, and then slowly cooled to room temperature. The blue block single crystals suitable for X-ray analysis were collected.

Refinement

H atoms bonded to C atoms were placed geometrically and treated as riding, (C—H distances are 0.93 Å), with $U_{\text{iso}}(\text{H}) = 1.2U_{\text{eq}}(\text{C})$. The water H atoms found from Fourier difference maps were included in the refinements with restraints for O—H distances (0.829–0.833 Å) and $U_{\text{iso}}(\text{H}) = 1.5U_{\text{eq}}(\text{O})$.

Figures

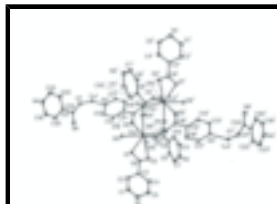


Fig. 1. The ORTEP-3 (Farrugia, 1997) drawing of the title compound. Displacement ellipsoids are drawn at 30% probability level. Symmetry codes: (i) $-x + 1, -y + 2, -z$.

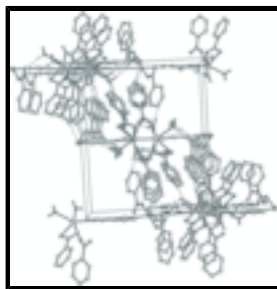


Fig. 2. Projection showing the three-dimensional structure formed by H-bonding interaction of the compound (I).

catena-poly[[di- μ -isonicotinato-bis[di- μ -isonicotinatoeuropium(III)]]- μ -isonicotinato-[diisonicotinatocopper(II)]- μ -isonicotinato]

Crystal data

$[\text{CuEu}_2(\text{C}_6\text{H}_4\text{NO}_2)_8(\text{H}_2\text{O})_4]$

$M_r = 1416.34$

Monoclinic, $P2_1/n$

Hall symbol: $-P\ 2_1/n$

$a = 9.5218\ (9)\ \text{\AA}$

$b = 15.0371\ (13)\ \text{\AA}$

$c = 18.2850\ (16)\ \text{\AA}$

$\beta = 93.8220\ (10)^\circ$

$V = 2612.2\ (4)\ \text{\AA}^3$

$Z = 2$

$F_{000} = 1398$

$D_x = 1.801\ \text{Mg m}^{-3}$

Mo $K\alpha$ radiation

$\lambda = 0.71073\ \text{\AA}$

Cell parameters from 6922 reflections

$\theta = 2.5\text{--}28.0^\circ$

$\mu = 2.86\ \text{mm}^{-1}$

$T = 295\ (2)\ \text{K}$

Block, green

$0.40 \times 0.30 \times 0.27\ \text{mm}$

Data collection

Bruker SMART CCD area-detector
diffractometer

Radiation source: fine-focus sealed tube

4853 independent reflections

4222 reflections with $I > 2\sigma(I)$

Monochromator: graphite $R_{\text{int}} = 0.036$
 $T = 295(2)$ K $\theta_{\text{max}} = 25.5^\circ$
 φ and ω scans $\theta_{\text{min}} = 2.5^\circ$
 Absorption correction: multi-scan (SADABS; Sheldrick, 2003) $h = -10 \rightarrow 11$
 $T_{\text{min}} = 0.397$, $T_{\text{max}} = 0.517$ $k = -17 \rightarrow 18$
 18387 measured reflections $l = -22 \rightarrow 22$

Refinement

Refinement on F^2 Secondary atom site location: difference Fourier map
 Least-squares matrix: full Hydrogen site location: inferred from neighbouring sites
 $R[F^2 > 2\sigma(F^2)] = 0.021$ H-atom parameters constrained
 $wR(F^2) = 0.049$ $w = 1/[\sigma^2(F_o^2) + (0.0175P)^2 + 1.449P]$
 where $P = (F_o^2 + 2F_c^2)/3$
 $S = 1.04$ $(\Delta/\sigma)_{\text{max}} = 0.006$
 4853 reflections $\Delta\rho_{\text{max}} = 0.36 \text{ e } \text{\AA}^{-3}$
 359 parameters $\Delta\rho_{\text{min}} = -0.36 \text{ e } \text{\AA}^{-3}$
 6 restraints Extinction correction: SHELXL97 (Sheldrick, 2008),
 $F_c^* = kFc[1 + 0.001x Fc^2 \lambda^3 / \sin(2\theta)]^{-1/4}$
 Primary atom site location: structure-invariant direct methods Extinction coefficient: 0.00683 (17)

Special details

Geometry. All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes)

are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

Refinement. Refinement of F^2 against ALL reflections. The weighted R -factor wR and

goodness of fit S are based on F^2 , conventional R -factors R are based on F , with F set to zero for negative F^2 . The threshold expression of $F^2 > \sigma(F^2)$ is used only for calculating R -factors(gt) *etc.* and is not relevant to the choice of reflections for refinement. R -factors based on F^2 are statistically about twice as large as those based on F , and R -factors based on ALL data will be even larger.

supplementary materials

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	<i>x</i>	<i>y</i>	<i>z</i>	$U_{\text{iso}}^*/U_{\text{eq}}$
Eu1	0.303549 (14)	1.084800 (9)	-0.000640 (7)	0.01521 (6)
Cu1	0.0000	0.5000	0.0000	0.02112 (12)
O1	0.1022 (2)	1.06985 (13)	0.08317 (11)	0.0256 (5)
O2	0.2241 (2)	1.19395 (13)	0.08933 (11)	0.0319 (5)
O3	0.4104 (2)	1.03423 (18)	0.11132 (12)	0.0440 (6)
O4	0.6048 (3)	0.95248 (17)	0.11231 (12)	0.0437 (6)
O5	0.2714 (2)	0.92881 (14)	-0.00398 (13)	0.0378 (6)
O6	0.4704 (2)	0.85317 (15)	-0.00984 (14)	0.0454 (6)
O7	-0.1420 (2)	0.55366 (14)	-0.07136 (11)	0.0276 (5)
O8	-0.3139 (2)	0.62128 (16)	-0.01438 (11)	0.0370 (6)
N1	-0.0769 (4)	1.2279 (2)	0.30315 (16)	0.0494 (8)
N2	0.5926 (3)	1.0505 (3)	0.37273 (15)	0.0521 (9)
N3	0.1135 (2)	0.61288 (15)	0.00239 (12)	0.0193 (5)
N4	-0.4825 (3)	0.6230 (2)	-0.28160 (15)	0.0448 (8)
C1	-0.1334 (4)	1.1683 (3)	0.2564 (2)	0.0579 (12)
H1	-0.2213	1.1456	0.2656	0.069*
C2	-0.0711 (4)	1.1377 (3)	0.1950 (2)	0.0463 (10)
H2	-0.1151	1.0949	0.1648	0.056*
C3	0.0576 (3)	1.1721 (2)	0.17983 (15)	0.0259 (7)
C4	0.1180 (4)	1.2343 (2)	0.22750 (18)	0.0420 (9)
H4	0.2050	1.2589	0.2189	0.050*
C5	0.0485 (4)	1.2599 (3)	0.2882 (2)	0.0507 (10)
H5	0.0914	1.3015	0.3201	0.061*
C6	0.1329 (3)	1.1432 (2)	0.11331 (15)	0.0226 (6)
C7	0.5089 (4)	1.1027 (3)	0.33001 (19)	0.0462 (10)
H7	0.4656	1.1504	0.3518	0.055*
C8	0.4824 (4)	1.0906 (2)	0.25533 (17)	0.0314 (7)
H8	0.4216	1.1283	0.2282	0.038*
C9	0.5483 (3)	1.0211 (2)	0.22209 (15)	0.0229 (6)
C10	0.6410 (4)	0.9697 (3)	0.26468 (17)	0.0406 (9)
H10	0.6913	0.9242	0.2439	0.049*
C11	0.6578 (4)	0.9867 (3)	0.33875 (19)	0.0573 (12)
H11	0.7197	0.9507	0.3669	0.069*
C12	0.5193 (3)	1.0016 (2)	0.14180 (15)	0.0252 (7)
C13	0.0470 (3)	0.69169 (19)	0.00148 (15)	0.0233 (6)
H13	-0.0508	0.6921	0.0004	0.028*
C14	0.1172 (3)	0.77197 (19)	0.00207 (15)	0.0231 (6)
H14	0.0676	0.8252	0.0027	0.028*
C15	0.2621 (3)	0.77222 (19)	0.00173 (14)	0.0207 (6)
C16	0.3327 (3)	0.69096 (19)	0.00510 (15)	0.0241 (7)
H16	0.4305	0.6889	0.0072	0.029*
C17	0.2545 (3)	0.6135 (2)	0.00524 (15)	0.0229 (6)
H17	0.3018	0.5594	0.0074	0.027*
C18	0.3420 (3)	0.8586 (2)	-0.00392 (16)	0.0254 (7)
C19	-0.5216 (3)	0.6665 (2)	-0.22291 (19)	0.0408 (9)

H19	-0.5995	0.7038	-0.2288	0.049*
C20	-0.4541 (3)	0.6600 (2)	-0.15378 (17)	0.0320 (7)
H20	-0.4856	0.6926	-0.1148	0.038*
C21	-0.3387 (3)	0.6041 (2)	-0.14357 (16)	0.0258 (7)
C22	-0.2961 (4)	0.5588 (2)	-0.20395 (18)	0.0420 (9)
H22	-0.2191	0.5207	-0.1994	0.050*
C23	-0.3693 (4)	0.5708 (3)	-0.2715 (2)	0.0532 (11)
H23	-0.3379	0.5410	-0.3118	0.064*
C24	-0.2594 (3)	0.59323 (18)	-0.06933 (16)	0.0239 (7)
O9	0.0897 (2)	1.07055 (13)	-0.07832 (11)	0.0284 (5)
H1W	0.0757	1.0919	-0.1202	0.043*
H2W	0.0301	1.0314	-0.0715	0.043*
O10	0.2777 (2)	1.22483 (13)	-0.06923 (11)	0.0299 (5)
H3W	0.3208	1.2307	-0.1068	0.045*
H4W	0.2738	1.2729	-0.0473	0.045*

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Eu1	0.01495 (9)	0.01529 (9)	0.01549 (8)	-0.00210 (6)	0.00169 (5)	-0.00087 (5)
Cu1	0.0205 (3)	0.0153 (3)	0.0264 (3)	-0.0064 (2)	-0.0071 (2)	0.0056 (2)
O1	0.0249 (12)	0.0272 (12)	0.0251 (11)	-0.0042 (9)	0.0061 (9)	-0.0054 (9)
O2	0.0394 (13)	0.0233 (12)	0.0351 (12)	-0.0072 (10)	0.0194 (10)	-0.0044 (9)
O3	0.0394 (15)	0.0656 (18)	0.0255 (12)	0.0092 (13)	-0.0078 (11)	0.0041 (12)
O4	0.0550 (16)	0.0506 (15)	0.0274 (12)	0.0129 (13)	0.0161 (11)	-0.0074 (11)
O5	0.0373 (14)	0.0178 (12)	0.0576 (16)	-0.0060 (10)	-0.0016 (12)	0.0012 (10)
O6	0.0214 (13)	0.0354 (14)	0.0796 (19)	-0.0127 (11)	0.0041 (12)	0.0022 (13)
O7	0.0268 (12)	0.0267 (12)	0.0281 (11)	-0.0024 (10)	-0.0083 (9)	0.0054 (9)
O8	0.0475 (15)	0.0358 (14)	0.0272 (12)	0.0008 (11)	-0.0022 (11)	-0.0020 (10)
N1	0.064 (2)	0.0436 (19)	0.0442 (18)	-0.0060 (17)	0.0313 (16)	-0.0110 (15)
N2	0.046 (2)	0.088 (3)	0.0216 (15)	-0.0102 (19)	-0.0030 (14)	-0.0089 (16)
N3	0.0209 (13)	0.0159 (12)	0.0208 (12)	-0.0044 (10)	-0.0011 (10)	0.0023 (9)
N4	0.049 (2)	0.0461 (19)	0.0368 (17)	0.0086 (16)	-0.0195 (14)	-0.0070 (14)
C1	0.049 (2)	0.062 (3)	0.067 (3)	-0.017 (2)	0.040 (2)	-0.023 (2)
C2	0.037 (2)	0.050 (2)	0.054 (2)	-0.0138 (18)	0.0207 (18)	-0.0225 (18)
C3	0.0276 (17)	0.0260 (17)	0.0250 (16)	0.0029 (14)	0.0077 (13)	-0.0016 (13)
C4	0.045 (2)	0.043 (2)	0.041 (2)	-0.0128 (18)	0.0190 (17)	-0.0108 (16)
C5	0.065 (3)	0.045 (2)	0.044 (2)	-0.013 (2)	0.0199 (19)	-0.0180 (18)
C6	0.0195 (16)	0.0263 (17)	0.0219 (15)	0.0037 (13)	0.0021 (12)	0.0027 (12)
C7	0.057 (3)	0.050 (2)	0.034 (2)	-0.007 (2)	0.0143 (18)	-0.0162 (17)
C8	0.0341 (19)	0.0342 (19)	0.0267 (16)	0.0047 (15)	0.0072 (14)	-0.0006 (14)
C9	0.0208 (16)	0.0294 (17)	0.0184 (14)	-0.0025 (13)	0.0018 (12)	0.0014 (12)
C10	0.040 (2)	0.054 (2)	0.0282 (18)	0.0150 (18)	0.0034 (15)	0.0054 (16)
C11	0.046 (2)	0.100 (4)	0.0249 (19)	0.018 (2)	-0.0035 (17)	0.011 (2)
C12	0.0283 (18)	0.0276 (17)	0.0198 (15)	-0.0068 (14)	0.0032 (13)	0.0029 (13)
C13	0.0177 (15)	0.0229 (16)	0.0289 (16)	-0.0017 (12)	-0.0013 (12)	0.0014 (12)
C14	0.0211 (16)	0.0169 (15)	0.0313 (16)	0.0008 (12)	0.0003 (12)	0.0002 (12)
C15	0.0217 (16)	0.0209 (16)	0.0190 (14)	-0.0076 (12)	-0.0011 (12)	-0.0006 (11)

supplementary materials

C16	0.0168 (16)	0.0236 (17)	0.0319 (16)	-0.0036 (12)	0.0015 (13)	0.0012 (13)
C17	0.0221 (16)	0.0184 (15)	0.0278 (16)	0.0002 (13)	-0.0006 (12)	0.0017 (12)
C18	0.0270 (18)	0.0219 (17)	0.0268 (16)	-0.0085 (13)	-0.0021 (13)	0.0001 (12)
C19	0.0283 (19)	0.045 (2)	0.047 (2)	0.0097 (17)	-0.0104 (16)	0.0023 (17)
C20	0.0272 (18)	0.037 (2)	0.0319 (17)	0.0040 (15)	-0.0007 (14)	-0.0001 (14)
C21	0.0246 (17)	0.0228 (17)	0.0291 (16)	-0.0030 (13)	-0.0060 (13)	0.0019 (12)
C22	0.046 (2)	0.042 (2)	0.0360 (19)	0.0178 (18)	-0.0124 (17)	-0.0118 (16)
C23	0.062 (3)	0.057 (3)	0.038 (2)	0.022 (2)	-0.0196 (19)	-0.0229 (18)
C24	0.0262 (17)	0.0156 (15)	0.0289 (16)	-0.0055 (13)	-0.0055 (13)	0.0038 (12)
O9	0.0247 (12)	0.0343 (13)	0.0250 (11)	-0.0101 (10)	-0.0081 (9)	0.0053 (9)
O10	0.0414 (13)	0.0221 (11)	0.0277 (11)	0.0021 (10)	0.0129 (10)	0.0045 (9)

Geometric parameters (Å, °)

Eu1—O4 ⁱ	2.341 (2)	C3—C6	1.516 (4)
Eu1—O6 ⁱ	2.342 (2)	C4—C5	1.385 (5)
Eu1—O3	2.351 (2)	C4—H4	0.9300
Eu1—O5	2.366 (2)	C5—H5	0.9300
Eu1—O9	2.4133 (19)	C7—C8	1.384 (5)
Eu1—O10	2.4548 (19)	C7—H7	0.9300
Eu1—O2	2.477 (2)	C8—C9	1.381 (4)
Eu1—O1	2.5428 (19)	C8—H8	0.9300
Eu1—C6	2.864 (3)	C9—C10	1.376 (4)
Cu1—O7 ⁱⁱ	1.9867 (19)	C9—C12	1.504 (4)
Cu1—O7	1.9867 (19)	C10—C11	1.377 (5)
Cu1—N3	2.011 (2)	C10—H10	0.9300
Cu1—N3 ⁱⁱ	2.011 (2)	C11—H11	0.9300
O1—C6	1.259 (3)	C13—C14	1.380 (4)
O2—C6	1.256 (3)	C13—H13	0.9300
O3—C12	1.245 (4)	C14—C15	1.380 (4)
O4—C12	1.248 (4)	C14—H14	0.9300
O4—Eu1 ⁱ	2.341 (2)	C15—C16	1.394 (4)
O5—C18	1.251 (4)	C15—C18	1.513 (4)
O6—C18	1.237 (4)	C16—C17	1.383 (4)
O6—Eu1 ⁱ	2.342 (2)	C16—H16	0.9300
O7—C24	1.269 (4)	C17—H17	0.9300
O8—C24	1.235 (4)	C19—C20	1.383 (4)
N1—C1	1.326 (5)	C19—H19	0.9300
N1—C5	1.333 (5)	C20—C21	1.386 (4)
N2—C11	1.320 (5)	C20—H20	0.9300
N2—C7	1.334 (5)	C21—C22	1.381 (4)
N3—C17	1.340 (4)	C21—C24	1.517 (4)
N3—C13	1.343 (4)	C22—C23	1.389 (5)
N4—C19	1.331 (4)	C22—H22	0.9300
N4—C23	1.336 (5)	C23—H23	0.9300
C1—C2	1.382 (5)	O9—H1W	0.8334
C1—H1	0.9300	O9—H2W	0.8326
C2—C3	1.376 (4)	O10—H3W	0.8291

C2—H2	0.9300	O10—H4W	0.8292
C3—C4	1.378 (4)		
O4 ⁱ —Eu1—O6 ⁱ	76.87 (9)	N1—C5—H5	118.5
O4 ⁱ —Eu1—O3	121.14 (8)	C4—C5—H5	118.5
O6 ⁱ —Eu1—O3	73.47 (9)	O2—C6—O1	121.7 (3)
O4 ⁱ —Eu1—O5	78.18 (9)	O2—C6—C3	118.8 (3)
O6 ⁱ —Eu1—O5	120.90 (8)	O1—C6—C3	119.6 (3)
O3—Eu1—O5	75.49 (9)	O2—C6—Eu1	59.57 (14)
O4 ⁱ —Eu1—O9	79.30 (8)	O1—C6—Eu1	62.56 (14)
O6 ⁱ —Eu1—O9	144.92 (8)	C3—C6—Eu1	173.2 (2)
O3—Eu1—O9	141.54 (8)	N2—C7—C8	124.3 (3)
O5—Eu1—O9	78.12 (7)	N2—C7—H7	117.9
O4 ⁱ —Eu1—O10	77.90 (8)	C8—C7—H7	117.9
O6 ⁱ —Eu1—O10	76.15 (8)	C7—C8—C9	118.4 (3)
O3—Eu1—O10	138.18 (8)	C7—C8—H8	120.8
O5—Eu1—O10	145.98 (7)	C9—C8—H8	120.8
O9—Eu1—O10	73.94 (7)	C10—C9—C8	118.0 (3)
O4 ⁱ —Eu1—O2	152.34 (8)	C10—C9—C12	120.8 (3)
O6 ⁱ —Eu1—O2	90.07 (8)	C8—C9—C12	121.2 (3)
O3—Eu1—O2	76.68 (8)	C9—C10—C11	118.7 (3)
O5—Eu1—O2	129.00 (7)	C9—C10—H10	120.6
O9—Eu1—O2	99.60 (7)	C11—C10—H10	120.6
O10—Eu1—O2	75.30 (7)	N2—C11—C10	124.8 (4)
O4 ⁱ —Eu1—O1	147.58 (8)	N2—C11—H11	117.6
O6 ⁱ —Eu1—O1	135.36 (8)	C10—C11—H11	117.6
O3—Eu1—O1	75.31 (7)	O3—C12—O4	126.0 (3)
O5—Eu1—O1	80.01 (7)	O3—C12—C9	117.0 (3)
O9—Eu1—O1	72.93 (7)	O4—C12—C9	117.0 (3)
O10—Eu1—O1	109.25 (7)	N3—C13—C14	122.9 (3)
O2—Eu1—O1	51.88 (6)	N3—C13—H13	118.5
O4 ⁱ —Eu1—C6	165.98 (8)	C14—C13—H13	118.5
O6 ⁱ —Eu1—C6	112.40 (9)	C15—C14—C13	119.1 (3)
O3—Eu1—C6	72.50 (8)	C15—C14—H14	120.4
O5—Eu1—C6	104.14 (8)	C13—C14—H14	120.4
O9—Eu1—C6	87.60 (8)	C14—C15—C16	118.5 (3)
O10—Eu1—C6	93.78 (7)	C14—C15—C18	120.7 (3)
O2—Eu1—C6	25.93 (7)	C16—C15—C18	120.8 (3)
O1—Eu1—C6	26.07 (7)	C17—C16—C15	118.7 (3)
O7 ⁱⁱ —Cu1—O7	180.0	C17—C16—H16	120.7
O7 ⁱⁱ —Cu1—N3	89.26 (9)	C15—C16—H16	120.7
O7—Cu1—N3	90.74 (9)	N3—C17—C16	123.0 (3)
O7 ⁱⁱ —Cu1—N3 ⁱⁱ	90.74 (9)	N3—C17—H17	118.5
O7—Cu1—N3 ⁱⁱ	89.26 (9)	C16—C17—H17	118.5
N3—Cu1—N3 ⁱⁱ	180.0	O6—C18—O5	126.2 (3)
C6—O1—Eu1	91.37 (16)	O6—C18—C15	116.9 (3)

supplementary materials

C6—O2—Eu1	94.50 (17)	O5—C18—C15	116.8 (3)
C12—O3—Eu1	144.7 (2)	N4—C19—C20	124.4 (3)
C12—O4—Eu1 ⁱ	144.1 (2)	N4—C19—H19	117.8
C18—O5—Eu1	140.1 (2)	C20—C19—H19	117.8
C18—O6—Eu1 ⁱ	151.0 (2)	C19—C20—C21	118.8 (3)
C24—O7—Cu1	137.19 (19)	C19—C20—H20	120.6
C1—N1—C5	116.3 (3)	C21—C20—H20	120.6
C11—N2—C7	115.7 (3)	C22—C21—C20	117.6 (3)
C17—N3—C13	117.7 (2)	C22—C21—C24	120.5 (3)
C17—N3—Cu1	122.85 (19)	C20—C21—C24	121.9 (3)
C13—N3—Cu1	119.46 (19)	C21—C22—C23	119.3 (3)
C19—N4—C23	116.3 (3)	C21—C22—H22	120.3
N1—C1—C2	124.8 (3)	C23—C22—H22	120.3
N1—C1—H1	117.6	N4—C23—C22	123.5 (3)
C2—C1—H1	117.6	N4—C23—H23	118.2
C3—C2—C1	118.3 (3)	C22—C23—H23	118.2
C3—C2—H2	120.8	O8—C24—O7	127.0 (3)
C1—C2—H2	120.8	O8—C24—C21	118.7 (3)
C2—C3—C4	117.9 (3)	O7—C24—C21	114.3 (3)
C2—C3—C6	122.0 (3)	Eu1—O9—H1W	125.7
C4—C3—C6	120.1 (3)	Eu1—O9—H2W	122.1
C3—C4—C5	119.6 (3)	H1W—O9—H2W	110.0
C3—C4—H4	120.2	Eu1—O10—H3W	118.5
C5—C4—H4	120.2	Eu1—O10—H4W	120.4
N1—C5—C4	123.1 (3)	H3W—O10—H4W	110.4
O4 ⁱ —Eu1—O1—C6	-154.11 (17)	O10—Eu1—C6—O2	-44.17 (18)
O6 ⁱ —Eu1—O1—C6	33.3 (2)	O1—Eu1—C6—O2	-172.2 (3)
O3—Eu1—O1—C6	80.12 (17)	O4 ⁱ —Eu1—C6—O1	75.1 (4)
O5—Eu1—O1—C6	157.60 (17)	O6 ⁱ —Eu1—C6—O1	-155.36 (16)
O9—Eu1—O1—C6	-121.87 (17)	O3—Eu1—C6—O1	-92.26 (17)
O10—Eu1—O1—C6	-56.31 (17)	O5—Eu1—C6—O1	-22.77 (18)
O2—Eu1—O1—C6	-4.30 (16)	O9—Eu1—C6—O1	54.35 (16)
O4 ⁱ —Eu1—O2—C6	148.82 (19)	O10—Eu1—C6—O1	128.07 (16)
O6 ⁱ —Eu1—O2—C6	-150.30 (18)	O2—Eu1—C6—O1	172.2 (3)
O3—Eu1—O2—C6	-77.32 (18)	C11—N2—C7—C8	3.6 (6)
O5—Eu1—O2—C6	-18.9 (2)	N2—C7—C8—C9	-1.3 (6)
O9—Eu1—O2—C6	63.58 (18)	C7—C8—C9—C10	-2.4 (5)
O10—Eu1—O2—C6	134.05 (18)	C7—C8—C9—C12	177.2 (3)
O1—Eu1—O2—C6	4.33 (16)	C8—C9—C10—C11	3.5 (5)
O4 ⁱ —Eu1—O3—C12	16.4 (4)	C12—C9—C10—C11	-176.2 (3)
O6 ⁱ —Eu1—O3—C12	-46.5 (4)	C7—N2—C11—C10	-2.4 (6)
O5—Eu1—O3—C12	82.6 (4)	C9—C10—C11—N2	-1.1 (7)
O9—Eu1—O3—C12	130.7 (4)	Eu1—O3—C12—O4	-29.2 (6)
O10—Eu1—O3—C12	-91.6 (4)	Eu1—O3—C12—C9	152.7 (3)
O2—Eu1—O3—C12	-140.6 (4)	Eu1 ⁱ —O4—C12—O3	26.5 (6)
O1—Eu1—O3—C12	165.8 (4)	Eu1 ⁱ —O4—C12—C9	-155.4 (3)

C6—Eu1—O3—C12	-167.2 (4)	C10—C9—C12—O3	161.7 (3)
O4 ⁱ —Eu1—O5—C18	64.0 (3)	C8—C9—C12—O3	-17.9 (4)
O6 ⁱ —Eu1—O5—C18	-2.7 (4)	C10—C9—C12—O4	-16.6 (4)
O3—Eu1—O5—C18	-62.9 (3)	C8—C9—C12—O4	163.8 (3)
O9—Eu1—O5—C18	145.3 (3)	C17—N3—C13—C14	1.1 (4)
O10—Eu1—O5—C18	110.1 (3)	Cu1—N3—C13—C14	-179.2 (2)
O2—Eu1—O5—C18	-121.8 (3)	N3—C13—C14—C15	1.7 (4)
O1—Eu1—O5—C18	-140.2 (3)	C13—C14—C15—C16	-3.7 (4)
C6—Eu1—O5—C18	-130.2 (3)	C13—C14—C15—C18	175.0 (3)
N3—Cu1—O7—C24	-95.7 (3)	C14—C15—C16—C17	2.9 (4)
N3 ⁱⁱ —Cu1—O7—C24	84.3 (3)	C18—C15—C16—C17	-175.7 (3)
O7 ⁱⁱ —Cu1—N3—C17	39.1 (2)	C13—N3—C17—C16	-1.9 (4)
O7—Cu1—N3—C17	-140.9 (2)	Cu1—N3—C17—C16	178.4 (2)
O7 ⁱⁱ —Cu1—N3—C13	-140.6 (2)	C15—C16—C17—N3	-0.1 (4)
O7—Cu1—N3—C13	39.4 (2)	Eu1 ⁱ —O6—C18—O5	22.8 (7)
C5—N1—C1—C2	0.6 (7)	Eu1 ⁱ —O6—C18—C15	-159.1 (3)
N1—C1—C2—C3	-1.4 (7)	Eu1—O5—C18—O6	-8.6 (5)
C1—C2—C3—C4	1.0 (6)	Eu1—O5—C18—C15	173.3 (2)
C1—C2—C3—C6	-179.3 (3)	C14—C15—C18—O6	-174.3 (3)
C2—C3—C4—C5	-0.1 (5)	C16—C15—C18—O6	4.3 (4)
C6—C3—C4—C5	-179.8 (3)	C14—C15—C18—O5	3.9 (4)
C1—N1—C5—C4	0.4 (6)	C16—C15—C18—O5	-177.5 (3)
C3—C4—C5—N1	-0.7 (6)	C23—N4—C19—C20	-0.7 (6)
Eu1—O2—C6—O1	-8.1 (3)	N4—C19—C20—C21	-0.7 (5)
Eu1—O2—C6—C3	172.4 (2)	C19—C20—C21—C22	1.1 (5)
Eu1—O1—C6—O2	7.9 (3)	C19—C20—C21—C24	-179.8 (3)
Eu1—O1—C6—C3	-172.7 (2)	C20—C21—C22—C23	0.0 (5)
C2—C3—C6—O2	158.1 (3)	C24—C21—C22—C23	-179.1 (3)
C4—C3—C6—O2	-22.2 (4)	C19—N4—C23—C22	1.9 (6)
C2—C3—C6—O1	-21.4 (5)	C21—C22—C23—N4	-1.5 (7)
C4—C3—C6—O1	158.3 (3)	Cu1—O7—C24—O8	10.8 (5)
O4 ⁱ —Eu1—C6—O2	-97.1 (4)	Cu1—O7—C24—C21	-168.0 (2)
O6 ⁱ —Eu1—C6—O2	32.40 (19)	C22—C21—C24—O8	-167.1 (3)
O3—Eu1—C6—O2	95.50 (18)	C20—C21—C24—O8	13.9 (4)
O5—Eu1—C6—O2	164.99 (17)	C22—C21—C24—O7	11.8 (4)
O9—Eu1—C6—O2	-117.89 (18)	C20—C21—C24—O7	-167.3 (3)

Symmetry codes: (i) $-x+1, -y+2, -z$; (ii) $-x, -y+1, -z$.

Hydrogen-bond geometry ($\text{\AA}, ^\circ$)

<i>D</i> —H \cdots <i>A</i>	<i>D</i> —H	H \cdots <i>A</i>	<i>D</i> \cdots <i>A</i>	<i>D</i> —H \cdots <i>A</i>
O10—H4W \cdots O8 ⁱⁱⁱ	0.83	1.97	2.782 (3)	165
O9—H2W \cdots O1 ⁱⁱⁱ	0.83	1.98	2.790 (3)	164
O10—H3W \cdots N1 ^{iv}	0.83	2.06	2.881 (3)	169
O9—H1W \cdots N4 ^v	0.83	2.00	2.807 (3)	161

Symmetry codes: (iii) $-x, -y+2, -z$; (iv) $x+1/2, -y+5/2, z-1/2$; (v) $-x-1/2, y+1/2, -z-1/2$.

Fig. 1

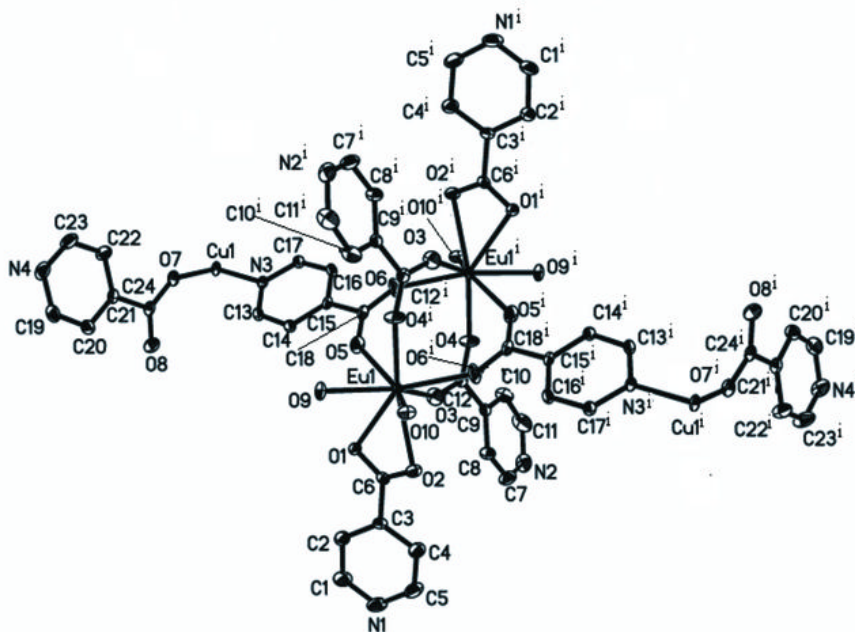


Fig. 2

