

catena-Poly[[[triqua(nitrato- κ^2O,O')-neodymium(III)]-bis(μ_2 -pyridinium-4-carboxylato- $\kappa^2O:O'$)] bis(perchlorate) monohydrate]

Jia-Zhi Pu

Department of Pharmacy, Zunyi Medical College, Zunyi, Guizhou 563003, People's Republic of China

Correspondence e-mail: pujz70@yahoo.com.cn


Received 14 December 2008; accepted 26 December 2008

Key indicators: single-crystal X-ray study; $T = 273$ K; mean $\sigma(C-C) = 0.006$ Å; R factor = 0.029; wR factor = 0.077; data-to-parameter ratio = 12.2.

In the title compound, $\{[Nd(NO_3)(C_6H_5NO_2)_2(H_2O)_3](ClO_4)_2 \cdot H_2O\}_n$, the Nd^{III} atom is nine-coordinated by four O atoms from four pyridinium-4-carboxylate ligands, two O atoms from a chelating nitrate anion and three water molecules in a distorted tricapped trigonal-prismatic coordination geometry. Adjacent Nd atoms are linked by the bidentate pyridinium-4-carboxylate ligands into a chain running along the b axis. The chains are further connected by $O-H \cdots O$ and $N-H \cdots O$ hydrogen bonds into a three-dimensional network.

Related literature

For related structures, see: Liao *et al.* (2004); Wang *et al.* (2004).

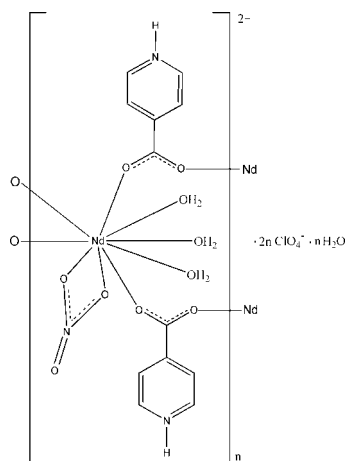

Experimental

Crystal data

$[Nd(NO_3)(C_6H_5NO_2)_2(H_2O)_3](ClO_4)_2 \cdot H_2O$	$\beta = 79.601 (1)^\circ$
$M_r = 723.43$	$\gamma = 71.334 (1)^\circ$
Triclinic, $P\bar{1}$	$V = 1159.68 (16) \text{ \AA}^3$
$a = 8.3962 (7) \text{ \AA}$	$Z = 2$
$b = 10.1119 (8) \text{ \AA}$	Mo $K\alpha$ radiation
$c = 14.7229 (12) \text{ \AA}$	$\mu = 2.57 \text{ mm}^{-1}$
$\alpha = 81.663 (1)^\circ$	$T = 273 (2) \text{ K}$
	$0.32 \times 0.26 \times 0.20 \text{ mm}$

Data collection

Bruker APEXII CCD diffractometer	5967 measured reflections
Absorption correction: multi-scan (SADABS; Sheldrick, 1996)	4073 independent reflections
$T_{\min} = 0.459, T_{\max} = 0.605$	3923 reflections with $I > 2\sigma(I)$
	$R_{\text{int}} = 0.017$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.029$	12 restraints
$wR(F^2) = 0.077$	H-atom parameters constrained
$S = 0.99$	$\Delta\rho_{\text{max}} = 1.00 \text{ e \AA}^{-3}$
4073 reflections	$\Delta\rho_{\text{min}} = -1.11 \text{ e \AA}^{-3}$
334 parameters	

Table 1

Selected bond lengths (Å).

Nd1—O1	2.428 (3)	Nd1—O7 ⁱⁱ	2.390 (3)
Nd1—O2 ⁱ	2.392 (3)	Nd1—O1W	2.542 (3)
Nd1—O3	2.446 (3)	Nd1—O2W	2.567 (3)
Nd1—O4	2.571 (3)	Nd1—O3W	2.505 (3)
Nd1—O5	2.651 (3)		

Symmetry codes: (i) $-x + 1, -y + 1, -z + 1$; (ii) $-x + 1, -y, -z + 1$.

Table 2

Hydrogen-bond geometry (Å, °).

$D-H \cdots A$	$D-H$	$H \cdots A$	$D \cdots A$	$D-H \cdots A$
O4W—H7W \cdots O12	0.84	2.59	3.256 (11)	136
O4W—H8W \cdots O5 ⁱ	0.84	2.52	3.023 (8)	119
O4W—H8W \cdots O8 ⁱ	0.84	2.04	2.801 (9)	150
O3W—H5W \cdots O12 ⁱⁱ	0.84	2.11	2.945 (7)	170
O3W—H6W \cdots O8	0.84	2.04	2.846 (8)	162
O2W—H3W \cdots O1W ⁱⁱⁱ	0.84	2.12	2.900 (5)	154
O2W—H4W \cdots O4 ⁱⁱⁱ	0.84	2.04	2.861 (4)	167
O1W—H2W \cdots O4W	0.84	1.83	2.593 (7)	150
O1W—H1W \cdots O6 ^{iv}	0.84	2.04	2.880 (5)	178
N2—H2A \cdots O9 ^{vii}	0.86	2.51	3.045 (5)	121
N2—H2A \cdots O13 ^v	0.86	2.48	3.033 (5)	123
N2—H2A \cdots O10 ^{vi}	0.86	2.15	2.868 (5)	141
N1—H1 \cdots O13 ^{vii}	0.86	2.46	2.994 (6)	121
N1—H1 \cdots O9 ^{viii}	0.86	2.46	2.988 (6)	120
N1—H1 \cdots O14 ^{ix}	0.86	2.24	2.953 (6)	140

Symmetry codes: (i) $-x + 1, -y + 1, -z + 1$; (ii) $-x + 1, -y, -z + 1$; (iii) $-x + 2, -y, -z + 1$; (iv) $x - 1, y, z$; (v) $-x + 1, -y, -z + 2$; (vi) $x, y - 1, z + 1$; (vii) $-x, -y + 1, -z + 1$; (viii) $-x + 1, -y + 1, -z$; (ix) $x, y + 1, z - 1$.

Data collection: APEX2 (Bruker, 2007); cell refinement: SAINT (Bruker, 2007); data reduction: SAINT; program(s) used to solve structure: SHELXS97 (Sheldrick, 2008); program(s) used to refine structure: SHELXL97 (Sheldrick, 2008); molecular graphics: SHELXTL (Sheldrick, 2008); software used to prepare material for publication: SHELXTL.

The author acknowledges Zunyi Medical College for supporting this work.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: HY2175).

References

Bruker (2007). *APEX2* and *SAINT*. Bruker AXS Inc., Madison, Wisconsin, USA.

Liao, J.-H., Lai, C.-Y., Ho, C.-D. & Su, C.-T. (2004). *Inorg. Chem. Commun.* **7**, 402–404.

Sheldrick, G. M. (1996). *SADABS*. University of Göttingen, Germany.

Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.

Wang, C.-M., Chuang, Y.-L., Chuang, S.-T. & Lii, K.-H. (2004). *J. Solid State Chem.* **177**, 2305–2310.

supplementary materials

Acta Cryst. (2009). E65, m146-m147 [doi:10.1107/S1600536808043997]

***catena*-Poly[[[triqua(nitrato- κ^2O,O')neodymium(III)]-bis(μ_2 -pyridinium-4-carboxylato- $\kappa^2O:O'$)] bis(perchlorate) monohydrate]**

J.-Z. Pu

Comment

In the structural investigation of isonicotinate complexes, it has been found that the isonicotinate functions as a multidentate ligand with versatile binding and coordination modes (Liao *et al.*, 2004; Wang *et al.*, 2004). In this paper, we report the crystal structure of the title compound, a new Nd^{III} complex resulted from the hydrothermal treatment of isonicotinic acid, Nd₂O₃ and a little nitric acid.

As depicted in Fig. 1, the asymmetric unit consists of one Nd^{III} atom, two pyridinium-4-carboxylate (Hint) ligands, one coordinated nitrate anion, three coordinated water molecules, two perchlorate anions and one uncoordinated water molecule. The Nd^{III} atom is nine-coordinated in a distorted tricapped trigonal prismatic coordination geometry, defined by four O atoms from four different Hint ligands, two O atoms from a nitrate anion and three water molecules (Table 1). The Hint ligands link the metal centres to form a polymeric chain (Fig. 2), in which the Nd^{III} atoms are separated by 5.586 (2) and 5.281 (3) Å. The chains are further self-assembled into a three-dimensional supramolecular network through O—H...O and N—H...O hydrogen bonds (Table 2 and Fig. 3).

Experimental

A mixture of Nd₂O₃ (0.168 g, 0.5 mmol), isonicotinic acid (0.123 g, 1 mmol), HNO₃ (0.12 ml) and H₂O (10 ml) was placed in a 23 ml Teflon-lined reactor, which was heated to 433 K for 3 d and then cooled to room temperature at a rate of 10 K h⁻¹. The crystals obtained were washed with water and dried in air.

Refinement

H atoms on C and N atoms were positioned geometrically and treated as riding atoms, with C—H = 0.93 Å and N—H = 0.86 Å and with $U_{\text{iso}}(\text{H}) = 1.2U_{\text{eq}}(\text{C},\text{N})$. H atoms of water molecules were located in difference Fourier maps and fixed in refinements, with O—H = 0.84 Å and $U_{\text{iso}}(\text{H}) = 1.5U_{\text{eq}}(\text{O})$.

Figures

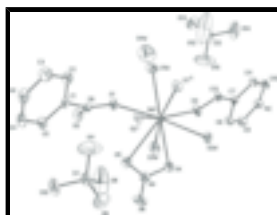


Fig. 1. The asymmetric unit of the title compound, extended to show the Nd coordination. Displacement ellipsoids are drawn at the 30% probability level. H atoms have been omitted for clarity. [Symmetry codes: (i) 1 - x, 1 - y, 1 - z; (ii) 1 - x, -y, 1 - z.]

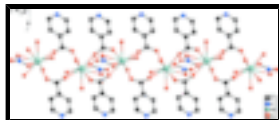


Fig. 2. View of the polymeric chain. H atoms, perchlorate anions and uncoordinated water molecules are not shown for clarity.

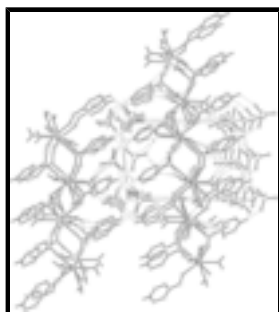


Fig. 3. A packing view of the title compound, showing hydrogen bonds (dashed lines).

catena-Poly[[[triqua(nitrato- κ^2O,O')neodymium(III)]- bis(μ_2 -pyridinium-4-carboxylato- $\kappa^2O:O'$)] bis(perchlorate) monohydrate]

Crystal data

[Nd(NO₃)(C₆H₅NO₂)₂(H₂O)₃](ClO₄)₂·H₂O

$M_r = 723.43$

Triclinic, $P\bar{1}$

Hall symbol: -P 1

$a = 8.3962$ (7) Å

$b = 10.1119$ (8) Å

$c = 14.7229$ (12) Å

$\alpha = 81.663$ (1)°

$\beta = 79.601$ (1)°

$\gamma = 71.334$ (1)°

$V = 1159.68$ (16) Å³

$Z = 2$

$F_{000} = 714$

$D_x = 2.072$ Mg m⁻³

Mo $K\alpha$ radiation

$\lambda = 0.71073$ Å

Cell parameters from 8000 reflections

$\theta = 1.7$ – 26.0°

$\mu = 2.57$ mm⁻¹

$T = 273$ (2) K

Block, colourless

$0.32 \times 0.26 \times 0.20$ mm

Data collection

Bruker APEXII CCD
diffractometer

Radiation source: fine-focus sealed tube

Monochromator: graphite

$T = 273$ (2) K

φ and ω scans

Absorption correction: multi-scan
(SADABS; Sheldrick, 1996)

$T_{\min} = 0.459$, $T_{\max} = 0.605$

5967 measured reflections

4073 independent reflections

3923 reflections with $I > 2\sigma(I)$

$R_{\text{int}} = 0.017$

$\theta_{\text{max}} = 25.2^\circ$

$\theta_{\text{min}} = 2.1^\circ$

$h = -7 \rightarrow 10$

$k = -11 \rightarrow 12$

$l = -16 \rightarrow 17$

Refinement

Refinement on F^2

Secondary atom site location: difference Fourier map

Least-squares matrix: full

$$R[F^2 > 2\sigma(F^2)] = 0.029$$

$$wR(F^2) = 0.077$$

$$S = 0.99$$

4073 reflections

334 parameters

12 restraints

Primary atom site location: structure-invariant direct methods

Hydrogen site location: inferred from neighbouring sites

H-atom parameters constrained

$$w = 1/[\sigma^2(F_o^2) + (0.0448P)^2 + 3.0364P]$$

$$\text{where } P = (F_o^2 + 2F_c^2)/3$$

$$(\Delta/\sigma)_{\max} = 0.001$$

$$\Delta\rho_{\max} = 1.00 \text{ e } \text{\AA}^{-3}$$

$$\Delta\rho_{\min} = -1.11 \text{ e } \text{\AA}^{-3}$$

Extinction correction: none

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	x	y	z	$U_{\text{iso}}^*/U_{\text{eq}}$
C1	0.3296 (5)	0.6208 (4)	0.2806 (3)	0.0285 (8)
C11	0.75800 (16)	0.47280 (12)	0.09482 (8)	0.0430 (3)
N1	0.2205 (6)	0.7323 (4)	0.1159 (3)	0.0493 (11)
H1	0.1879	0.7654	0.0628	0.059*
Nd1	0.61497 (2)	0.219206 (19)	0.462773 (12)	0.02175 (9)
O1	0.4362 (4)	0.4217 (3)	0.3801 (2)	0.0329 (6)
C2	0.2041 (6)	0.5822 (5)	0.2522 (3)	0.0432 (11)
H2	0.1574	0.5168	0.2886	0.052*
C12	0.24041 (16)	0.02494 (12)	0.89509 (8)	0.0416 (3)
N2	0.7879 (5)	-0.2315 (4)	0.8926 (2)	0.0364 (8)
H2A	0.8157	-0.2643	0.9467	0.044*
O2	0.4255 (4)	0.6291 (3)	0.4190 (2)	0.0406 (7)
C3	0.1495 (7)	0.6428 (6)	0.1687 (4)	0.0557 (14)
H3	0.0624	0.6207	0.1494	0.067*
O3	0.6604 (4)	0.0616 (3)	0.6047 (2)	0.0374 (7)
C4	0.3394 (7)	0.7728 (5)	0.1414 (3)	0.0440 (11)
H4	0.3859	0.8362	0.1025	0.053*
N4	0.9277 (5)	0.3174 (4)	0.4383 (3)	0.0388 (9)
O4	0.9213 (4)	0.1992 (3)	0.4802 (3)	0.0451 (8)
C5	0.3937 (6)	0.7207 (5)	0.2256 (3)	0.0380 (10)
H5	0.4729	0.7523	0.2456	0.046*
O5	0.7969 (4)	0.3949 (3)	0.4069 (2)	0.0455 (8)
C6	0.4021 (5)	0.5516 (4)	0.3681 (3)	0.0247 (8)
O6	1.0567 (5)	0.3518 (5)	0.4292 (3)	0.0688 (12)
C7	0.6913 (5)	-0.1202 (4)	0.7252 (3)	0.0246 (8)
O7	0.5371 (4)	-0.1017 (3)	0.6025 (2)	0.0350 (7)
C8	0.8138 (6)	-0.0818 (5)	0.7579 (3)	0.0336 (9)
H8	0.8628	-0.0169	0.7227	0.040*
O8	0.8174 (13)	0.4411 (6)	0.1813 (4)	0.152 (4)
C9	0.8617 (6)	-0.1400 (5)	0.8421 (3)	0.0380 (10)
H9	0.9450	-0.1164	0.8643	0.046*
O9	0.8797 (5)	0.3853 (5)	0.0322 (3)	0.0626 (11)
C10	0.6734 (6)	-0.2736 (5)	0.8629 (3)	0.0376 (10)

supplementary materials

H10	0.6267	-0.3387	0.8995	0.045*
O10	0.7386 (6)	0.6160 (4)	0.0700 (3)	0.0720 (13)
C11	0.6248 (6)	-0.2203 (4)	0.7777 (3)	0.0329 (9)
H11	0.5475	-0.2513	0.7553	0.039*
O11	0.6059 (8)	0.4456 (7)	0.1061 (8)	0.177 (5)
C12	0.6247 (5)	-0.0482 (4)	0.6362 (3)	0.0256 (8)
O12	0.1848 (15)	0.0322 (7)	0.8114 (4)	0.197 (5)
O13	0.1153 (5)	0.1236 (5)	0.9500 (3)	0.0634 (11)
O14	0.2627 (8)	-0.1133 (5)	0.9314 (4)	0.108 (2)
O15	0.3841 (9)	0.0555 (9)	0.8782 (10)	0.256 (8)
O1W	0.3147 (4)	0.2628 (4)	0.5492 (2)	0.0426 (7)
H1W	0.2375	0.2900	0.5154	0.064*
H2W	0.2927	0.3121	0.5938	0.064*
O2W	0.8124 (4)	-0.0227 (3)	0.4206 (2)	0.0397 (7)
H4W	0.8961	-0.0633	0.4488	0.060*
H3W	0.7594	-0.0782	0.4151	0.060*
O3W	0.7472 (4)	0.2088 (3)	0.2962 (2)	0.0430 (8)
H6W	0.7505	0.2762	0.2560	0.065*
H5W	0.7699	0.1337	0.2717	0.065*
O4W	0.2124 (9)	0.3371 (7)	0.7164 (4)	0.123 (2)
H8W	0.2054	0.4183	0.7270	0.184*
H7W	0.2016	0.2855	0.7659	0.184*

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
C1	0.033 (2)	0.0229 (19)	0.029 (2)	-0.0026 (16)	-0.0122 (17)	-0.0030 (15)
Cl1	0.0593 (7)	0.0339 (6)	0.0312 (5)	-0.0140 (5)	0.0023 (5)	0.0009 (4)
N1	0.065 (3)	0.048 (2)	0.035 (2)	-0.011 (2)	-0.029 (2)	0.0090 (18)
Nd1	0.02726 (13)	0.01985 (12)	0.02122 (12)	-0.00926 (8)	-0.01255 (8)	0.00457 (8)
O1	0.0427 (17)	0.0241 (14)	0.0348 (15)	-0.0086 (12)	-0.0216 (13)	0.0045 (12)
C2	0.050 (3)	0.042 (3)	0.044 (3)	-0.018 (2)	-0.024 (2)	0.008 (2)
Cl2	0.0524 (7)	0.0347 (6)	0.0369 (6)	-0.0145 (5)	-0.0004 (5)	-0.0050 (4)
N2	0.041 (2)	0.045 (2)	0.0238 (17)	-0.0116 (17)	-0.0175 (15)	0.0086 (15)
O2	0.065 (2)	0.0323 (16)	0.0311 (16)	-0.0156 (15)	-0.0235 (15)	-0.0024 (13)
C3	0.062 (3)	0.066 (4)	0.052 (3)	-0.028 (3)	-0.038 (3)	0.011 (3)
O3	0.058 (2)	0.0298 (15)	0.0322 (15)	-0.0202 (14)	-0.0244 (14)	0.0116 (12)
C4	0.062 (3)	0.036 (2)	0.030 (2)	-0.011 (2)	-0.012 (2)	0.0079 (19)
N4	0.034 (2)	0.047 (2)	0.040 (2)	-0.0181 (17)	-0.0146 (16)	0.0039 (17)
O4	0.0366 (17)	0.0373 (17)	0.064 (2)	-0.0136 (14)	-0.0242 (16)	0.0137 (16)
C5	0.049 (3)	0.034 (2)	0.032 (2)	-0.012 (2)	-0.0127 (19)	0.0032 (18)
O5	0.0405 (18)	0.0414 (18)	0.059 (2)	-0.0164 (15)	-0.0250 (16)	0.0149 (15)
C6	0.0240 (19)	0.027 (2)	0.0237 (19)	-0.0069 (15)	-0.0082 (15)	0.0011 (15)
O6	0.047 (2)	0.089 (3)	0.086 (3)	-0.046 (2)	-0.029 (2)	0.029 (2)
C7	0.0282 (19)	0.0228 (18)	0.0221 (18)	-0.0047 (15)	-0.0090 (15)	0.0001 (14)
O7	0.0481 (18)	0.0371 (16)	0.0299 (15)	-0.0207 (14)	-0.0227 (13)	0.0041 (12)
C8	0.038 (2)	0.037 (2)	0.032 (2)	-0.0184 (19)	-0.0124 (18)	0.0051 (17)
O8	0.310 (11)	0.075 (4)	0.046 (3)	-0.008 (5)	-0.060 (4)	-0.001 (3)

C9	0.041 (2)	0.046 (3)	0.034 (2)	-0.018 (2)	-0.0219 (19)	0.0064 (19)
O9	0.056 (2)	0.070 (3)	0.056 (2)	-0.003 (2)	-0.0086 (19)	-0.027 (2)
C10	0.046 (3)	0.037 (2)	0.031 (2)	-0.018 (2)	-0.0105 (19)	0.0115 (18)
O10	0.101 (3)	0.041 (2)	0.057 (2)	-0.016 (2)	0.005 (2)	0.0161 (18)
C11	0.038 (2)	0.034 (2)	0.031 (2)	-0.0159 (18)	-0.0149 (18)	0.0057 (17)
O11	0.071 (4)	0.115 (5)	0.352 (13)	-0.052 (4)	0.074 (6)	-0.117 (7)
C12	0.030 (2)	0.0241 (19)	0.0229 (18)	-0.0074 (16)	-0.0102 (15)	0.0022 (15)
O12	0.367 (14)	0.100 (5)	0.062 (3)	0.058 (6)	-0.084 (6)	-0.037 (3)
O13	0.056 (2)	0.072 (3)	0.058 (2)	0.002 (2)	-0.0162 (19)	-0.030 (2)
O14	0.131 (5)	0.053 (3)	0.093 (4)	0.002 (3)	0.023 (3)	0.027 (3)
O15	0.085 (5)	0.160 (7)	0.55 (2)	-0.082 (5)	0.127 (8)	-0.224 (11)
O1W	0.0390 (17)	0.058 (2)	0.0377 (17)	-0.0217 (15)	-0.0107 (14)	-0.0038 (15)
O2W	0.0407 (17)	0.0286 (15)	0.0522 (19)	-0.0082 (13)	-0.0218 (15)	0.0024 (13)
O3W	0.056 (2)	0.0402 (18)	0.0296 (16)	-0.0151 (15)	-0.0006 (14)	0.0030 (13)
O4W	0.143 (6)	0.133 (6)	0.088 (4)	-0.048 (5)	0.007 (4)	-0.009 (4)

Geometric parameters (Å, °)

C1—C2	1.382 (6)	O2—C6	1.240 (5)
C1—C5	1.385 (6)	O2—Nd1 ⁱ	2.392 (3)
C1—C6	1.506 (5)	C3—H3	0.9300
C11—O11	1.367 (6)	O3—C12	1.245 (5)
C11—O10	1.405 (4)	C4—C5	1.372 (6)
C11—O8	1.408 (6)	C4—H4	0.9300
C11—O9	1.413 (4)	N4—O6	1.220 (5)
N1—C4	1.321 (7)	N4—O5	1.250 (5)
N1—C3	1.324 (7)	N4—O4	1.275 (5)
N1—H1	0.8600	C5—H5	0.9300
Nd1—O1	2.428 (3)	C7—C11	1.383 (6)
Nd1—O2 ⁱ	2.392 (3)	C7—C8	1.389 (6)
Nd1—O3	2.446 (3)	C7—C12	1.512 (5)
Nd1—O4	2.571 (3)	C8—C9	1.365 (6)
Nd1—O5	2.651 (3)	C8—H8	0.9300
Nd1—O7 ⁱⁱ	2.390 (3)	C9—H9	0.9300
Nd1—O1W	2.542 (3)	C10—C11	1.371 (6)
Nd1—O2W	2.567 (3)	C10—H10	0.9300
Nd1—O3W	2.505 (3)	C11—H11	0.9300
O1—C6	1.245 (5)	C12—O7	1.242 (5)
C2—C3	1.379 (7)	O1W—H1W	0.8400
C2—H2	0.9300	O1W—H2W	0.8400
C12—O15	1.311 (6)	O2W—H4W	0.8400
C12—O12	1.379 (6)	O2W—H3W	0.8400
C12—O14	1.388 (5)	O3W—H6W	0.8400
C12—O13	1.417 (4)	O3W—H5W	0.8400
N2—C10	1.329 (6)	O4W—H8W	0.8400
N2—C9	1.339 (6)	O4W—H7W	0.8400
N2—H2A	0.8600		
C2—C1—C5	119.2 (4)	O12—C12—O14	104.1 (5)

supplementary materials

C2—C1—C6	120.9 (4)	O15—C12—O13	110.6 (4)
C5—C1—C6	119.9 (4)	O12—C12—O13	108.2 (4)
O11—C11—O10	111.3 (4)	O14—C12—O13	113.7 (3)
O11—C11—O8	107.8 (6)	C10—N2—C9	122.9 (4)
O10—C11—O8	106.1 (3)	C10—N2—H2A	118.6
O11—C11—O9	110.7 (4)	C9—N2—H2A	118.6
O10—C11—O9	113.1 (3)	C6—O2—Nd1 ⁱ	162.7 (3)
O8—C11—O9	107.4 (4)	N1—C3—C2	120.4 (5)
C4—N1—C3	122.6 (4)	N1—C3—H3	119.8
C4—N1—H1	118.7	C2—C3—H3	119.8
C3—N1—H1	118.7	C12—O3—Nd1	134.0 (3)
O7 ⁱⁱ —Nd1—O2 ⁱ	140.53 (12)	N1—C4—C5	119.6 (5)
O7 ⁱⁱ —Nd1—O1	81.57 (10)	N1—C4—H4	120.2
O2 ⁱ —Nd1—O1	85.82 (10)	C5—C4—H4	120.2
O7 ⁱⁱ —Nd1—O3	97.66 (10)	O6—N4—O5	122.0 (4)
O2 ⁱ —Nd1—O3	75.38 (10)	O6—N4—O4	121.0 (4)
O1—Nd1—O3	149.37 (11)	O5—N4—O4	117.0 (4)
O7 ⁱⁱ —Nd1—O3W	75.54 (11)	N4—O4—Nd1	98.8 (2)
O2 ⁱ —Nd1—O3W	136.17 (11)	C4—C5—C1	119.5 (4)
O1—Nd1—O3W	74.83 (10)	C4—C5—H5	120.2
O3—Nd1—O3W	134.93 (11)	C1—C5—H5	120.2
O7 ⁱⁱ —Nd1—O1W	69.63 (11)	N4—O5—Nd1	95.6 (2)
O2 ⁱ —Nd1—O1W	70.93 (11)	O2—C6—O1	127.0 (4)
O1—Nd1—O1W	73.20 (11)	O2—C6—C1	116.9 (3)
O3—Nd1—O1W	77.83 (11)	O1—C6—C1	116.1 (3)
O3W—Nd1—O1W	135.33 (11)	C11—C7—C8	119.0 (4)
O7 ⁱⁱ —Nd1—O2W	70.39 (10)	C11—C7—C12	120.4 (4)
O2 ⁱ —Nd1—O2W	137.28 (10)	C8—C7—C12	120.5 (3)
O1—Nd1—O2W	135.29 (10)	C9—C8—C7	119.4 (4)
O3—Nd1—O2W	70.71 (10)	C9—C8—H8	120.3
O3W—Nd1—O2W	65.02 (10)	C7—C8—H8	120.3
O1W—Nd1—O2W	124.20 (11)	N2—C9—C8	119.5 (4)
O7 ⁱⁱ —Nd1—O4	139.99 (11)	N2—C9—H9	120.2
O2 ⁱ —Nd1—O4	77.38 (12)	C8—C9—H9	120.2
O1—Nd1—O4	122.18 (10)	N2—C10—C11	119.5 (4)
O3—Nd1—O4	77.44 (10)	N2—C10—H10	120.3
O3W—Nd1—O4	80.43 (12)	C11—C10—H10	120.3
O1W—Nd1—O4	143.71 (11)	C10—C11—C7	119.6 (4)
O2W—Nd1—O4	70.58 (10)	C10—C11—H11	120.2
O7 ⁱⁱ —Nd1—O5	138.71 (10)	C7—C11—H11	120.2
O2 ⁱ —Nd1—O5	70.41 (12)	O7—C12—O3	126.1 (3)
O1—Nd1—O5	73.54 (10)	O7—C12—C7	117.5 (3)
O3—Nd1—O5	120.41 (10)	O3—C12—C7	116.4 (3)
O3W—Nd1—O5	66.52 (11)	Nd1—O1W—H1W	115.1
O1W—Nd1—O5	130.00 (11)	Nd1—O1W—H2W	114.5
O2W—Nd1—O5	105.70 (11)	H1W—O1W—H2W	111.6

O4—Nd1—O5	48.66 (10)	Nd1—O2W—H4W	120.0
C6—O1—Nd1	140.8 (3)	Nd1—O2W—H3W	112.9
C3—C2—C1	118.4 (5)	H4W—O2W—H3W	111.4
C3—C2—H2	120.8	Nd1—O3W—H6W	127.8
C1—C2—H2	120.8	Nd1—O3W—H5W	119.0
O15—C12—O12	107.9 (8)	H6W—O3W—H5W	111.3
O15—C12—O14	111.9 (6)	H8W—O4W—H7W	111.5

Symmetry codes: (i) $-x+1, -y+1, -z+1$; (ii) $-x+1, -y, -z+1$.

Hydrogen-bond geometry ($\text{\AA}, ^\circ$)

<i>D</i> —H \cdots <i>A</i>	<i>D</i> —H	H \cdots <i>A</i>	<i>D</i> \cdots <i>A</i>	<i>D</i> —H \cdots <i>A</i>
O4W—H7W \cdots O12	0.84	2.59	3.256 (11)	136
O4W—H8W \cdots O5 ⁱ	0.84	2.52	3.023 (8)	119
O4W—H8W \cdots O8 ⁱ	0.84	2.04	2.801 (9)	150
O3W—H5W \cdots O12 ⁱⁱ	0.84	2.11	2.945 (7)	170
O3W—H6W \cdots O8	0.84	2.04	2.846 (8)	162
O2W—H3W \cdots O1W ⁱⁱ	0.84	2.12	2.900 (5)	154
O2W—H4W \cdots O4 ⁱⁱⁱ	0.84	2.04	2.861 (4)	167
O1W—H2W \cdots O4W	0.84	1.83	2.593 (7)	150
O1W—H1W \cdots O6 ^{iv}	0.84	2.04	2.880 (5)	178
N2—H2A \cdots O9 ⁱⁱⁱ	0.86	2.51	3.045 (5)	121
N2—H2A \cdots O13 ^v	0.86	2.48	3.033 (5)	123
N2—H2A \cdots O10 ^{vi}	0.86	2.15	2.868 (5)	141
N1—H1 \cdots O13 ^{vii}	0.86	2.46	2.994 (6)	121
N1—H1 \cdots O9 ^{viii}	0.86	2.46	2.988 (6)	120
N1—H1 \cdots O14 ^{ix}	0.86	2.24	2.953 (6)	140

Symmetry codes: (i) $-x+1, -y+1, -z+1$; (ii) $-x+1, -y, -z+1$; (iii) $-x+2, -y, -z+1$; (iv) $x-1, y, z$; (v) $-x+1, -y, -z+2$; (vi) $x, y-1, z+1$; (vii) $-x, -y+1, -z+1$; (viii) $-x+1, -y+1, -z$; (ix) $x, y+1, z-1$.

Fig. 2

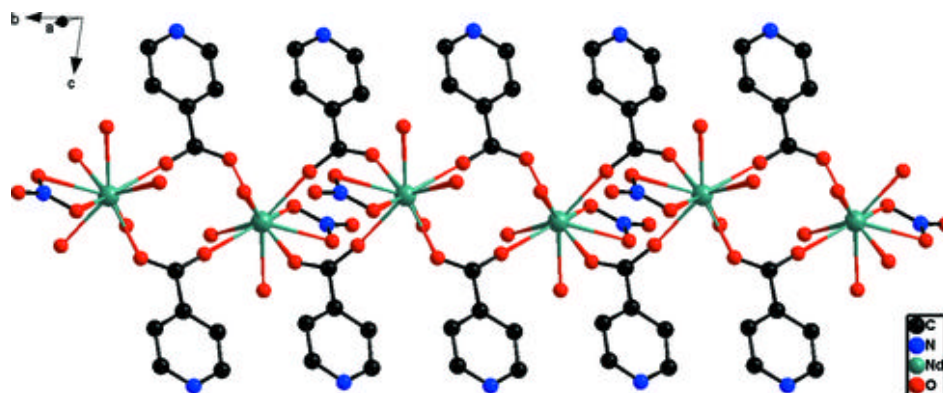


Fig. 3

