

Acta Crystallographica Section E

Structure Reports

Online

ISSN 1600-5368

2-(2-Ammonioethyl)pyridinium hexachloridorhenate(IV)

Andrzej Kochel

Faculty of Chemistry, University of Wrocław, 14 Joliot-Curie Street, 50-383 Wrocław, Poland

Correspondence e-mail: andrzej@wcheto.chem.uni.wroc.pl


Received 9 October 2008; accepted 28 December 2008

 Key indicators: single-crystal X-ray study; $T = 100$ K; mean $\sigma(\text{C}-\text{C}) = 0.005$ Å; R factor = 0.024; wR factor = 0.053; data-to-parameter ratio = 32.4.

In the title antiferromagnetic material, $(\text{C}_7\text{H}_{12}\text{N}_2)[\text{ReCl}_6]$, the Néel temperature is observed at 5 K. The salt is stabilized by an extensive network of $\text{N}-\text{H}\cdots\text{Cl}$ and $\text{C}-\text{H}\cdots\text{Cl}$ hydrogen bonds, where hydrogen-bonded anion chains and characteristic cation-anion motifs are present. Similar systems play an important role in crystal engineering as hydrogen bonds that can transmit magnetic interactions.

Related literature

For related literature, see: Kepert *et al.* (1997); Mrozinski *et al.* (2002); Sawusch & Schilde (1999); Kochel (2004); Koenig (1966).

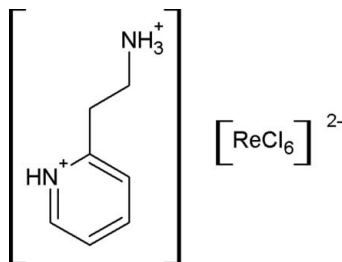

Experimental

Crystal data

$(\text{C}_7\text{H}_{12}\text{N}_2)[\text{ReCl}_6]$
 $M_r = 523.10$
 Triclinic, $P\bar{1}$
 $a = 7.371$ (2) Å
 $b = 14.204$ (3) Å
 $c = 15.159$ (3) Å
 $\alpha = 66.87$ (2)°
 $\beta = 84.74$ (2)°

$\gamma = 75.61$ (2)°
 $V = 1413.7$ (6) Å³
 $Z = 4$
 Mo $K\alpha$ radiation
 $\mu = 9.70$ mm⁻¹
 $T = 100$ (2) K
 $0.14 \times 0.10 \times 0.06$ mm

Data collection

Oxford Diffraction KM-4-CCD diffractometer
 Absorption correction: analytical (*CrysAlis RED*; Oxford Diffraction, 2006)
 $T_{\min} = 0.367$, $T_{\max} = 0.559$

21570 measured reflections
 10147 independent reflections
 8098 reflections with $I > 2\sigma(I)$
 $R_{\text{int}} = 0.023$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.024$
 $wR(F^2) = 0.053$
 $S = 0.98$
 10147 reflections
 313 parameters

H atoms treated by a mixture of independent and constrained refinement
 $\Delta\rho_{\text{max}} = 2.07$ e Å⁻³
 $\Delta\rho_{\text{min}} = -1.31$ e Å⁻³

Table 1

Hydrogen-bond geometry (Å, °).

$D-H\cdots A$	$D-H$	$H\cdots A$	$D\cdots A$	$D-H\cdots A$
$\text{N1}-\text{H1}\cdots\text{Cl3}^{\text{j}}$	0.86	2.76	3.280 (3)	120
$\text{N1}-\text{H1}\cdots\text{Cl12}^{\text{ii}}$	0.86	2.56	3.208 (3)	133
$\text{N2}-\text{H2N}\cdots\text{Cl1}^{\text{iii}}$	0.93 (4)	2.47 (4)	3.313 (3)	152 (3)
$\text{N3}-\text{H3A}\cdots\text{Cl7}^{\text{iv}}$	0.86	2.71	3.431 (3)	142
$\text{N3}-\text{H3A}\cdots\text{Cl12}^{\text{iv}}$	0.86	2.65	3.326 (3)	136
$\text{N2}-\text{H3N}\cdots\text{Cl1}^{\text{i}}$	0.83 (5)	2.50 (5)	3.328 (3)	174 (4)
$\text{N4}-\text{H6N}\cdots\text{Cl2}$	0.93 (6)	2.43 (5)	3.291 (4)	155 (4)
$\text{N4}-\text{H9N}\cdots\text{Cl7}$	1.04 (6)	2.70 (5)	3.199 (3)	110 (3)
$\text{N4}-\text{H9N}\cdots\text{Cl8}$	1.04 (6)	2.52 (6)	3.541 (3)	166 (4)
$\text{N4}-\text{H10N}\cdots\text{Cl11}^{\text{iii}}$	0.87 (5)	2.45 (4)	3.240 (4)	152 (4)
$\text{C4}-\text{H4}\cdots\text{Cl11}$	0.93	2.83	3.621 (3)	144
$\text{C7}-\text{H7B}\cdots\text{Cl1}^{\text{v}}$	0.97	2.80	3.711 (3)	156
$\text{C22}-\text{H22}\cdots\text{Cl2}^{\text{vi}}$	0.93	2.69	3.602 (4)	166
$\text{C26}-\text{H26B}\cdots\text{Cl8}$	0.97	2.82	3.589 (3)	137
$\text{C27}-\text{H27B}\cdots\text{Cl5}$	0.97	2.81	3.610 (3)	140

Symmetry codes: (i) $x-1, y+1, z-1$; (ii) $-x+1, -y+1, -z$; (iii) $-x+1, -y+1, -z+1$; (iv) $x-1, y, z$; (v) $x, y+1, z-1$; (vi) $-x+1, -y, -z+1$.

Data collection: *CrysAlis CCD* (Oxford Diffraction, 2006); cell refinement: *CrysAlis RED* (Oxford Diffraction, 2006); data reduction: *CrysAlis RED*; program(s) used to solve structure: *SHELXS97* (Sheldrick, 2008); program(s) used to refine structure: *SHELXL97* (Sheldrick, 2008); molecular graphics: *ORTEP-3* (Farrugia, 1997); software used to prepare material for publication: *SHELXL97*.

Financial support by the Polish Ministry of Science and Higher Education (grant No. N N204 016735, in years 2008–2010) is gratefully acknowledged. The author thanks Dr A. Pochaba (Faculty of Chemistry, University of Wrocław) for the magnetic measurements.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: BV2112).

References

- Farrugia, L. J. (1997). *J. Appl. Cryst.* **30**, 565.
 Kepert, C. J., Kurmoo, M. & Day, P. (1997). *J. Mater. Chem.* **7**, 221–228.
 Kochel, A. (2004). *Acta Cryst.* **E60**, m859–m860.
 Koenig, E. (1966). In *Magnetic Properties of Coordination and Organometallic Transition Metal Compounds*. Berlin: Springer Verlag.
 Mrozinski, J., Kochel, A. & Lis, T. (2002). *J. Mol. Struct.* **641**, 109–117.
 Oxford Diffraction (2006). *CrysAlis RED* and *CrysAlis CCD*. Oxford Diffraction Poland, Wrocław, Poland.
 Sawusch, S. & Schilde, U. (1999). *Z. Kristallogr. New Cryst. Struct.* **214**, 79–81.
 Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.

supplementary materials

Acta Cryst. (2009). E65, m245 [doi:10.1107/S1600536808044097]

2-(2-Ammonioethyl)pyridinium hexachloridorhenate(IV)

A. Kochel

Comment

Rhenium(IV) salts with ammonium cations are known and have been described previously (Sawusch *et al.*, 1999, Mrozinski *et al.*, 2002, Kochel 2004). Some of the hexachlororhenates(IV) have interesting properties, *e.g.* as semiconductors (Kepert *et al.*, 1997). The title salt comprises of 2-(2-aminoethyl)pyridinium cations and ReCl_6^{2-} anions. Figure 1 illustrates the two independent formula units of compound (1). The anion bond lengths are comparable to those for other anions of this type (see table in supplementary material). The crystal structure is stabilized by an extensive network of $\text{N—H}\cdots\text{Cl}$ and $\text{C—H}\cdots\text{Cl}$ hydrogen bonds (Fig. 2). Almost all amino H atoms bonded to the organic cation participate in hydrogen bonds as donors. Some of the hydrogen bonds *e.g.* $\text{N3—H3}\cdots\text{Cl12}$, $\text{N3—H3}\cdots\text{Cl1}$ are bifurcated. The hydrogen bonding parameters are included in Table 1. The use of small low-symmetry ammonium cations enable these ions to occupy general positions, so that the $\text{Re}\cdots\text{Re}$ distances are much smaller. In the crystal packing, two types of arrangement of molecules may be distinguished: in the [100] direction a layered arrangement [alternating anions and cations] is observed, while in the [010] direction, and the whole is stabilized by a network of hydrogen bonds. The shortest $\text{Re1}\cdots\text{Re1}_i$ distance is 7.371 (2) Å [symmetry code: (i) $x - 1, y, z$]. The magnetic susceptibility of (1) is measured in the temperature range from 2 to 300 K under the applied magnetic field of 0.5 T (Figure 3). The $\chi_{\text{m}}T$ values decrease slowly upon cooling. The effective magnetic moment of 3.55 B. *M.* at 300 K is reduced in comparison to the spin-only value (3.87 uB), and in 2 K is 0.84 B. *M.* Generally, the complex shows linear χ_{m} versus T behaviour in the 300–50 K range with $C = 1.70 \text{ cm}^3 \text{ mol}^{-1} \text{ K}$, $Q = -14.5 \text{ K}$. The susceptibility curves exhibit the maximum at 5 K, indicating directly the presence of antiferromagnetic interactions.

The $\chi_{\text{m}}T$ at 300 K is $1.58 \text{ cm}^3 \text{ K mol}^{-1}$ and this value is expected for an isolated Re(IV) ion. As the temperature is lowered, $\chi_{\text{m}}T$ decreases, and the value is $0.896 \text{ cm}^3 \text{ K mol}^{-1}$ at 2 K. This behaviour indicates antiferromagnetic interactions between the Re(IV) ions. The occurrence of antiferromagnetic interactions could be related to aspects of the structure. The smallest Re—Re distance is 7.371 (2) Å, and a substantial value, however, there are numerous hydrogen bonds in the crystal structure, forming a three-dimensional framework. The hydrogen bonds stabilize the crystal structure layered arrangement. Probably the hydrogen bonding system enhances the magnetic exchange interactions. Future perspectives concerning this work will involve further studies on hexachlororhenates(IV) as potential materials used as semiconductors.

Experimental

$(\text{NH}_4)_2\text{ReCl}_6$ (0.15 g) was dissolved in water (50 ml) with concentrated HCl (2 ml) and the mixture was heated under reflux at 340 K. After 30 min, 2-(2-aminoethyl)pyridine (0.25 g) was added. The mixture was heated for further 5 h. After cooling, the yellow precipitate was filtered off and washed with ethanol. Crystals for X-ray study were obtained by slow evaporation of an aqueous solution of the yellow precipitate with addition of 1 ml HCl solution. The crystals are in the form of plates. For data collection a small plate was used, cut from a larger one.

supplementary materials

Elemental analysis of C, H, Cl, and N for C₇H₁₂Cl₆N₂Re1: calcd. for C, 16.07; H, 2.31; Cl, 40.66; found: C, 15.03; H, 2.01; Cl, 39.12;

IR spectra were collected for samples prepared as KBr pellets on a BRUKER spectrometer.

(1) 3456 (*s*), 3010 (*s*), 2574 (*m*), 2015 (*m*), 1610 (*m*), 1545 (*s*), 1431 (*s*), 1403 (*m*), 1321 (*s*), 1120 (*s*), 935 (*s*), 715 (*versus*), 645 (*versus*), 554 (*versus*), 435 (*versus*), 303 (*m*), 295 (*versus*), 211 (*versus*), 174 (*versus*), 160 (*versus*).

The magnetic measurements of polycrystalline samples were carried out over the temperature range of 2–300 K using a Quantum design SQUID-Based Magnetometer MPMSXL5. The SQUID magnetometer was calibrated with a palladium rod sample, for which the gram susceptibility was assumed as $5.30 \times 10^{-6} \text{ cm}^3 \text{ g}^{-1}$ at 293 K (National Bureau of Standards, USA). The susceptibility measurements were made in the field of 0.5 T. Corrections were done for the diamagnetic response of the sample rod and of the sample using Pascal's constants (Koenig, 1966).

Refinement

The structure (1) was solved by direct methods using *SHELXS97* software (Sheldrick, 2008) and refined using *SHELXL97* (Sheldrick, 2008). In case of (1) *DFIX* restraints were used for all C—H bond lengths (0.93–0.97 Å with the allowed deviation of 0.002 Å). All H atoms were refined with U_{eq} set at 1.2 U_{eq} (parent atom). H atoms associated with N atoms were located on difference maps and then freely refined. In the final difference maps the following highest peaks were found: for (1) the maximum of -1.30 and 2.07 e/Å³ at 0.68 and 0.78 Å from the Re(2) atom

Figures

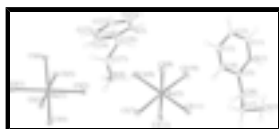


Fig. 1. Molecular structure of (1). Thermal ellipsoids are drawn at 50% probability level.

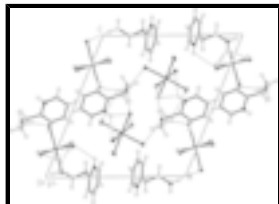


Fig. 2. The crystal structure packing scheme viewed along [100] showing the hydrogen bonds system.

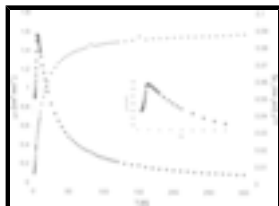


Fig. 3. The χ_m and $\chi_m T$ temperature dependence (χ_m - the molar magnetic susceptibility) for compound (1).

2-(2-Ammonioethyl)pyridinium hexachloridorhenate(IV)

Crystal data

(C₇H₁₂N₂)[ReCl₆]

Z = 4

$M_r = 523.10$	$F_{000} = 980$
Triclinic, $P\bar{1}$	$D_x = 2.458 \text{ Mg m}^{-3}$
Hall symbol: -P 1	Mo $K\alpha$ radiation
$a = 7.371 (2) \text{ \AA}$	$\lambda = 0.71073 \text{ \AA}$
$b = 14.204 (3) \text{ \AA}$	Cell parameters from 7350 reflections
$c = 15.159 (3) \text{ \AA}$	$\theta = 2.7\text{--}36.9^\circ$
$\alpha = 66.87 (2)^\circ$	$\mu = 9.70 \text{ mm}^{-1}$
$\beta = 84.74 (2)^\circ$	$T = 100 \text{ K}$
$\gamma = 75.61 (2)^\circ$	Needle, yellow
$V = 1413.7 (6) \text{ \AA}^3$	$0.14 \times 0.10 \times 0.06 \text{ mm}$

Data collection

Oxford Diffraction KM-4-CCD diffractometer	10147 independent reflections
Radiation source: fine-focus sealed tube	8098 reflections with $I > 2\sigma(I)$
Monochromator: graphite	$R_{\text{int}} = 0.023$
$T = 100 \text{ K}$	$\theta_{\text{max}} = 36.9^\circ$
/w scans	$\theta_{\text{min}} = 2.7^\circ$
Absorption correction: analytical (CrysAlis RED; Oxford Diffraction, 2006)	$h = -12 \rightarrow 10$
$T_{\text{min}} = 0.367$, $T_{\text{max}} = 0.559$	$k = -23 \rightarrow 18$
21570 measured reflections	$l = -25 \rightarrow 25$

Refinement

Refinement on F^2	Secondary atom site location: difference Fourier map
Least-squares matrix: full	Hydrogen site location: inferred from neighbouring sites
$R[F^2 > 2\sigma(F^2)] = 0.024$	H atoms treated by a mixture of independent and constrained refinement
$wR(F^2) = 0.053$	$w = 1/[\sigma^2(F_o^2) + (0.0289P)^2]$
$S = 0.98$	where $P = (F_o^2 + 2F_c^2)/3$
10147 reflections	$(\Delta/\sigma)_{\text{max}} = 0.001$
313 parameters	$\Delta\rho_{\text{max}} = 2.07 \text{ e \AA}^{-3}$
Primary atom site location: structure-invariant direct methods	$\Delta\rho_{\text{min}} = -1.31 \text{ e \AA}^{-3}$
	Extinction correction: none

Special details

Geometry. All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

supplementary materials

Refinement. Refinement of F^2 against ALL reflections. The weighted R -factor wR and goodness of fit S are based on F^2 , conventional R -factors R are based on F , with F set to zero for negative F^2 . The threshold expression of $F^2 > \sigma(F^2)$ is used only for calculating R -factors(gt) *etc.* and is not relevant to the choice of reflections for refinement. R -factors based on F^2 are statistically about twice as large as those based on F , and R -factors based on ALL data will be even larger.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	x	y	z	$U_{\text{iso}}^*/U_{\text{eq}}$
N1	0.0792 (4)	0.6798 (2)	-0.06898 (17)	0.0146 (5)
H1	0.1179	0.7004	-0.1273	0.018*
N2	0.2688 (4)	0.9123 (2)	-0.05025 (19)	0.0160 (5)
C1	-0.0762 (4)	0.6422 (3)	-0.0503 (2)	0.0182 (6)
H1A	-0.1404	0.6400	-0.0992	0.022*
C2	-0.1379 (4)	0.6072 (3)	0.0424 (2)	0.0189 (7)
H2	-0.2442	0.5798	0.0575	0.023*
C3	-0.0401 (4)	0.6128 (3)	0.1141 (2)	0.0177 (6)
H3	-0.0806	0.5888	0.1773	0.021*
C4	0.1171 (4)	0.6543 (3)	0.0911 (2)	0.0160 (6)
H4	0.1809	0.6597	0.1384	0.019*
C5	0.1791 (4)	0.6877 (2)	-0.0029 (2)	0.0126 (5)
C6	0.3564 (4)	0.7241 (3)	-0.0333 (2)	0.0161 (6)
H6A	0.3593	0.7542	-0.1028	0.019*
H6B	0.4610	0.6633	-0.0116	0.019*
C7	0.3845 (4)	0.8048 (3)	0.0037 (2)	0.0160 (6)
H7A	0.3516	0.7832	0.0711	0.019*
H7B	0.5157	0.8070	-0.0017	0.019*
N3	0.0641 (4)	0.2257 (2)	0.46864 (18)	0.0164 (5)
H3A	-0.0082	0.2847	0.4348	0.020*
N4	0.3743 (4)	0.3282 (3)	0.6043 (2)	0.0194 (6)
C21	0.1078 (5)	0.1501 (3)	0.4337 (2)	0.0213 (7)
H21	0.0610	0.1621	0.3744	0.026*
C22	0.2226 (5)	0.0542 (3)	0.4860 (2)	0.0188 (6)
H22	0.2526	0.0003	0.4631	0.023*
C23	0.2926 (4)	0.0396 (3)	0.5741 (2)	0.0164 (6)
H23	0.3720	-0.0240	0.6101	0.020*
C24	0.2437 (4)	0.1201 (3)	0.6074 (2)	0.0145 (6)
H24	0.2901	0.1102	0.6662	0.017*
C25	0.1265 (4)	0.2152 (2)	0.55434 (19)	0.0136 (6)
C26	0.0569 (4)	0.3072 (3)	0.5838 (2)	0.0144 (6)
H26A	-0.0620	0.3012	0.6162	0.017*
H26B	0.0338	0.3712	0.5264	0.017*
C27	0.1872 (4)	0.3179 (3)	0.6489 (2)	0.0155 (6)
H27A	0.1309	0.3793	0.6637	0.019*
H27B	0.2037	0.2566	0.7086	0.019*
Re1	0.774116 (15)	0.011796 (9)	0.795978 (7)	0.00979 (3)
Cl1	0.82082 (10)	-0.09836 (6)	0.96174 (4)	0.01273 (13)
Cl2	0.72966 (10)	0.12498 (6)	0.63386 (5)	0.01403 (13)
Cl3	1.05734 (10)	-0.08752 (6)	0.75988 (5)	0.01415 (13)

Cl4	0.93941 (10)	0.12262 (6)	0.82086 (5)	0.01445 (14)
Cl5	0.48903 (10)	0.10735 (6)	0.83435 (5)	0.01483 (14)
Cl6	0.61222 (10)	-0.10277 (6)	0.77706 (5)	0.01580 (14)
Re2	0.540061 (16)	0.419170 (10)	0.306599 (7)	0.01145 (3)
Cl7	0.66713 (10)	0.42137 (6)	0.44425 (5)	0.01578 (14)
Cl8	0.23337 (11)	0.46658 (7)	0.36098 (5)	0.02068 (16)
Cl9	0.54298 (12)	0.24161 (7)	0.38861 (6)	0.02359 (17)
Cl10	0.43132 (12)	0.42195 (7)	0.16505 (6)	0.02313 (17)
Cl11	0.53303 (10)	0.60222 (6)	0.22842 (5)	0.01651 (14)
Cl12	0.85405 (10)	0.37428 (7)	0.25762 (5)	0.01766 (15)
H2N	0.290 (5)	0.961 (3)	-0.028 (3)	0.019 (9)*
H3N	0.155 (6)	0.915 (3)	-0.050 (3)	0.029 (11)*
H4N	0.298 (5)	0.933 (3)	-0.107 (3)	0.024 (10)*
H6N	0.444 (6)	0.262 (4)	0.610 (3)	0.035 (12)*
H9N	0.346 (6)	0.378 (4)	0.533 (4)	0.047 (14)*
H10N	0.440 (6)	0.341 (3)	0.641 (3)	0.024 (10)*

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
N1	0.0165 (12)	0.0168 (13)	0.0139 (11)	-0.0070 (11)	0.0019 (9)	-0.0079 (10)
N2	0.0175 (14)	0.0154 (14)	0.0168 (12)	-0.0064 (12)	0.0007 (10)	-0.0066 (11)
C1	0.0161 (15)	0.0213 (17)	0.0184 (13)	-0.0066 (14)	-0.0016 (11)	-0.0071 (13)
C2	0.0172 (15)	0.0171 (16)	0.0214 (14)	-0.0071 (14)	0.0024 (11)	-0.0048 (13)
C3	0.0172 (15)	0.0170 (16)	0.0178 (13)	-0.0030 (13)	0.0001 (11)	-0.0059 (12)
C4	0.0167 (14)	0.0161 (15)	0.0146 (12)	-0.0040 (13)	-0.0007 (10)	-0.0048 (12)
C5	0.0132 (13)	0.0104 (14)	0.0135 (12)	-0.0015 (12)	0.0006 (10)	-0.0046 (11)
C6	0.0129 (14)	0.0154 (15)	0.0217 (14)	-0.0023 (13)	0.0009 (11)	-0.0096 (13)
C7	0.0143 (14)	0.0149 (15)	0.0194 (13)	-0.0019 (13)	-0.0042 (10)	-0.0071 (12)
N3	0.0154 (12)	0.0187 (14)	0.0151 (11)	-0.0031 (11)	-0.0031 (9)	-0.0063 (11)
N4	0.0157 (13)	0.0189 (15)	0.0286 (14)	-0.0056 (12)	0.0005 (11)	-0.0135 (13)
C21	0.0271 (17)	0.0229 (18)	0.0180 (14)	-0.0059 (15)	-0.0026 (12)	-0.0115 (14)
C22	0.0197 (15)	0.0181 (16)	0.0218 (14)	-0.0040 (14)	0.0000 (12)	-0.0112 (13)
C23	0.0166 (14)	0.0141 (15)	0.0181 (13)	-0.0042 (13)	-0.0003 (11)	-0.0053 (12)
C24	0.0141 (14)	0.0172 (16)	0.0115 (11)	-0.0075 (13)	0.0016 (10)	-0.0027 (11)
C25	0.0126 (14)	0.0158 (15)	0.0136 (12)	-0.0047 (13)	0.0008 (10)	-0.0062 (12)
C26	0.0126 (13)	0.0145 (15)	0.0171 (12)	-0.0038 (12)	-0.0008 (10)	-0.0064 (12)
C27	0.0157 (14)	0.0167 (16)	0.0156 (12)	-0.0028 (13)	0.0005 (10)	-0.0083 (12)
Re1	0.01005 (5)	0.01098 (6)	0.00933 (4)	-0.00349 (5)	0.00008 (3)	-0.00430 (4)
Cl1	0.0146 (3)	0.0142 (3)	0.0096 (3)	-0.0050 (3)	0.0005 (2)	-0.0040 (2)
Cl2	0.0158 (3)	0.0139 (3)	0.0114 (3)	-0.0034 (3)	-0.0010 (2)	-0.0037 (3)
Cl3	0.0135 (3)	0.0146 (3)	0.0139 (3)	-0.0017 (3)	0.0017 (2)	-0.0063 (3)
Cl4	0.0148 (3)	0.0152 (3)	0.0159 (3)	-0.0069 (3)	-0.0001 (2)	-0.0065 (3)
Cl5	0.0118 (3)	0.0171 (4)	0.0168 (3)	-0.0028 (3)	0.0013 (2)	-0.0084 (3)
Cl6	0.0183 (3)	0.0174 (4)	0.0159 (3)	-0.0087 (3)	-0.0002 (2)	-0.0079 (3)
Re2	0.01206 (6)	0.01075 (6)	0.01218 (5)	-0.00259 (5)	-0.00074 (4)	-0.00493 (4)
Cl7	0.0174 (3)	0.0174 (4)	0.0127 (3)	-0.0018 (3)	-0.0019 (2)	-0.0069 (3)
Cl8	0.0133 (3)	0.0242 (4)	0.0225 (3)	-0.0029 (3)	0.0022 (3)	-0.0081 (3)

supplementary materials

Cl9	0.0262 (4)	0.0128 (4)	0.0297 (4)	-0.0066 (3)	-0.0014 (3)	-0.0044 (3)
Cl10	0.0263 (4)	0.0244 (4)	0.0228 (4)	0.0010 (4)	-0.0093 (3)	-0.0155 (3)
Cl11	0.0193 (3)	0.0126 (3)	0.0170 (3)	-0.0048 (3)	-0.0037 (2)	-0.0034 (3)
Cl12	0.0151 (3)	0.0214 (4)	0.0140 (3)	-0.0007 (3)	0.0017 (2)	-0.0066 (3)

Geometric parameters (Å, °)

N1—C1	1.342 (4)	N4—H10N	0.87 (4)
N1—C5	1.349 (4)	C21—C22	1.379 (5)
N1—H1	0.8600	C21—H21	0.9300
N2—C7	1.492 (4)	C22—C23	1.396 (4)
N2—H2N	0.94 (4)	C22—H22	0.9300
N2—H3N	0.83 (4)	C23—C24	1.381 (5)
N2—H4N	0.82 (4)	C23—H23	0.9300
C1—C2	1.370 (4)	C24—C25	1.383 (4)
C1—H1A	0.9300	C24—H24	0.9300
C2—C3	1.396 (4)	C25—C26	1.501 (4)
C2—H2	0.9300	C26—C27	1.511 (4)
C3—C4	1.383 (4)	C26—H26A	0.9700
C3—H3	0.9300	C26—H26B	0.9700
C4—C5	1.386 (4)	C27—H27A	0.9700
C4—H4	0.9300	C27—H27B	0.9700
C5—C6	1.492 (4)	Re1—Cl2	2.3480 (9)
C6—C7	1.522 (4)	Re1—Cl6	2.3556 (8)
C6—H6A	0.9700	Re1—Cl5	2.3611 (10)
C6—H6B	0.9700	Re1—Cl3	2.3624 (10)
C7—H7A	0.9700	Re1—Cl4	2.3682 (8)
C7—H7B	0.9700	Re1—Cl1	2.3839 (9)
N3—C21	1.333 (4)	Re2—Cl9	2.3284 (10)
N3—C25	1.359 (4)	Re2—Cl10	2.3412 (9)
N3—H3A	0.8600	Re2—Cl8	2.3624 (10)
N4—C27	1.495 (4)	Re2—Cl12	2.3744 (10)
N4—H6N	0.92 (5)	Re2—Cl7	2.3783 (8)
N4—H9N	1.04 (5)	Re2—Cl11	2.3856 (10)
C1—N1—C5	124.7 (2)	C24—C23—C22	119.7 (3)
C1—N1—H1	117.6	C24—C23—H23	120.1
C5—N1—H1	117.6	C22—C23—H23	120.1
C7—N2—H2N	111 (2)	C23—C24—C25	120.7 (3)
C7—N2—H3N	114 (3)	C23—C24—H24	119.6
H2N—N2—H3N	110 (4)	C25—C24—H24	119.6
C7—N2—H4N	111 (3)	N3—C25—C24	117.1 (3)
H2N—N2—H4N	106 (4)	N3—C25—C26	116.7 (3)
H3N—N2—H4N	105 (4)	C24—C25—C26	126.1 (3)
N1—C1—C2	118.5 (3)	C25—C26—C27	115.2 (3)
N1—C1—H1A	120.8	C25—C26—H26A	108.5
C2—C1—H1A	120.8	C27—C26—H26A	108.5
C1—C2—C3	119.5 (3)	C25—C26—H26B	108.5
C1—C2—H2	120.3	C27—C26—H26B	108.5
C3—C2—H2	120.3	H26A—C26—H26B	107.5

C4—C3—C2	120.0 (3)	N4—C27—C26	112.1 (2)
C4—C3—H3	120.0	N4—C27—H27A	109.2
C2—C3—H3	120.0	C26—C27—H27A	109.2
C3—C4—C5	119.7 (3)	N4—C27—H27B	109.2
C3—C4—H4	120.2	C26—C27—H27B	109.2
C5—C4—H4	120.2	H27A—C27—H27B	107.9
N1—C5—C4	117.7 (3)	Cl2—Re1—Cl6	92.04 (3)
N1—C5—C6	118.6 (2)	Cl2—Re1—Cl5	89.96 (4)
C4—C5—C6	123.6 (3)	Cl6—Re1—Cl5	89.52 (3)
C5—C6—C7	115.3 (3)	Cl2—Re1—Cl3	90.99 (4)
C5—C6—H6A	108.4	Cl6—Re1—Cl3	89.50 (3)
C7—C6—H6A	108.4	Cl5—Re1—Cl3	178.66 (2)
C5—C6—H6B	108.4	Cl2—Re1—Cl4	90.04 (3)
C7—C6—H6B	108.4	Cl6—Re1—Cl4	177.91 (2)
H6A—C6—H6B	107.5	Cl5—Re1—Cl4	90.64 (3)
N2—C7—C6	112.2 (2)	Cl3—Re1—Cl4	90.31 (3)
N2—C7—H7A	109.2	Cl2—Re1—Cl1	178.08 (3)
C6—C7—H7A	109.2	Cl6—Re1—Cl1	89.74 (3)
N2—C7—H7B	109.2	Cl5—Re1—Cl1	89.34 (4)
C6—C7—H7B	109.2	Cl3—Re1—Cl1	89.74 (4)
H7A—C7—H7B	107.9	Cl4—Re1—Cl1	88.17 (3)
C21—N3—C25	124.1 (3)	Cl9—Re2—Cl10	92.44 (4)
C21—N3—H3A	118.0	Cl9—Re2—Cl8	90.47 (4)
C25—N3—H3A	118.0	Cl10—Re2—Cl8	92.67 (4)
C27—N4—H6N	109 (3)	Cl9—Re2—Cl12	90.34 (4)
C27—N4—H9N	105 (2)	Cl10—Re2—Cl12	90.12 (3)
H6N—N4—H9N	111 (4)	Cl8—Re2—Cl12	177.06 (3)
C27—N4—H10N	109 (3)	Cl9—Re2—Cl7	89.92 (4)
H6N—N4—H10N	100 (4)	Cl10—Re2—Cl7	176.13 (3)
H9N—N4—H10N	122 (4)	Cl8—Re2—Cl7	90.37 (3)
N3—C21—C22	119.7 (3)	Cl12—Re2—Cl7	86.80 (3)
N3—C21—H21	120.1	Cl9—Re2—Cl11	177.67 (3)
C22—C21—H21	120.1	Cl10—Re2—Cl11	89.43 (4)
C21—C22—C23	118.6 (3)	Cl8—Re2—Cl11	88.05 (4)
C21—C22—H22	120.7	Cl12—Re2—Cl11	91.05 (4)
C23—C22—H22	120.7	Cl7—Re2—Cl11	88.28 (3)

Hydrogen-bond geometry (\AA , $^\circ$)

$D-H\cdots A$	$D-H$	$H\cdots A$	$D\cdots A$	$D-H\cdots A$
N1—H1 \cdots Cl3 ⁱ	0.86	2.76	3.280 (3)	120
N1—H1 \cdots Cl12 ⁱⁱ	0.86	2.56	3.208 (3)	133
N2—H2N \cdots Cl1 ⁱⁱⁱ	0.93 (4)	2.47 (4)	3.313 (3)	152 (3)
N3—H3A \cdots Cl7 ^{iv}	0.86	2.71	3.431 (3)	142
N3—H3A \cdots Cl12 ^{iv}	0.86	2.65	3.326 (3)	136
N2—H3N \cdots Cl1 ⁱ	0.83 (5)	2.50 (5)	3.328 (3)	174 (4)
N4—H6N \cdots Cl2	0.93 (6)	2.43 (5)	3.291 (4)	155 (4)
N4—H9N \cdots Cl7	1.04 (6)	2.70 (5)	3.199 (3)	110 (3)

supplementary materials

N4—H9N···C18	1.04 (6)	2.52 (6)	3.541 (3)	166 (4)
N4—H10N···C111 ⁱⁱⁱ	0.87 (5)	2.45 (4)	3.240 (4)	152 (4)
C4—H4···C111	0.93	2.83	3.621 (3)	144
C7—H7B···C11 ^v	0.97	2.80	3.711 (3)	156
C22—H22···C12 ^{vi}	0.93	2.69	3.602 (4)	166
C26—H26B···C18	0.97	2.82	3.589 (3)	137
C27—H27B···C15	0.97	2.81	3.610 (3)	140

Symmetry codes: (i) $x-1, y+1, z-1$; (ii) $-x+1, -y+1, -z$; (iii) $-x+1, -y+1, -z+1$; (iv) $x-1, y, z$; (v) $x, y+1, z-1$; (vi) $-x+1, -y, -z+1$.

Fig. 1

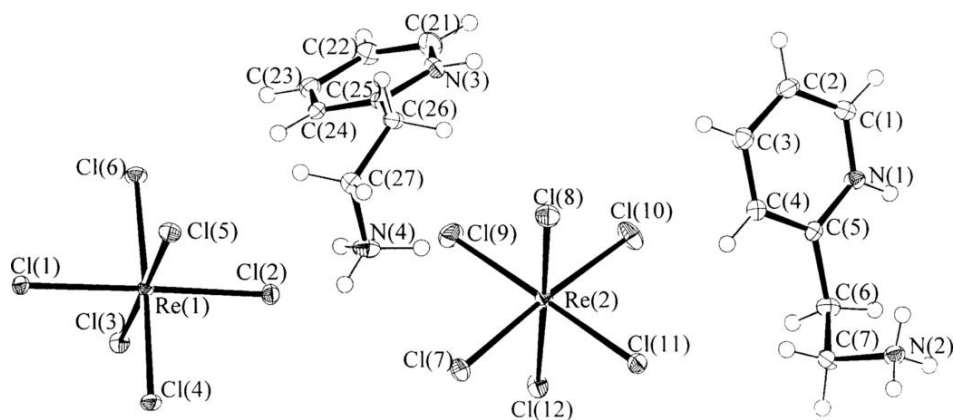


Fig. 2

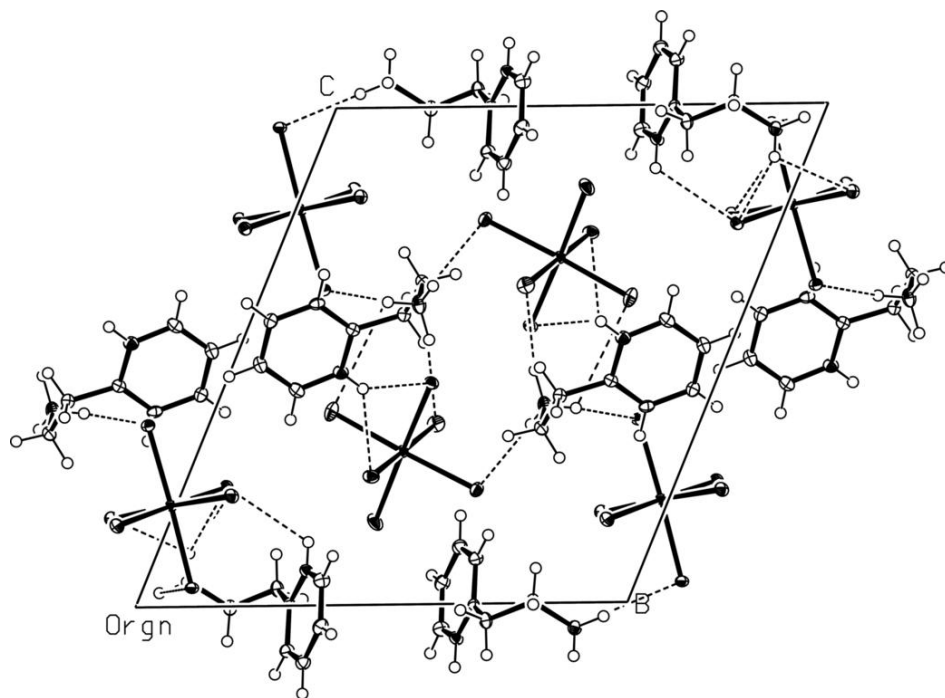


Fig. 3

