

catena-Poly[[aqua(3-methylbenzoato- κ^2O,O')lead(II)]- μ -3-methylbenzoato- $\kappa^4O:O,O':O'$]

 Jun Dai,^a Juan Yang^{b*} and Xiaobing An^b

^aInstitute of Safety Science and Engineering, Henan Polytechnic University, Jiaozuo 454003, People's Republic of China, and ^bDepartment of Physical Chemistry, Henan Polytechnic University, Jiaozuo 454003, People's Republic of China
Correspondence e-mail: yangjuan0302@yahoo.cn


Received 10 May 2009; accepted 25 May 2009

Key indicators: single-crystal X-ray study; $T = 296$ K; mean $\sigma(C-C) = 0.009$ Å; R factor = 0.035; wR factor = 0.061; data-to-parameter ratio = 20.4.

The reaction of lead(II) acetate and 3-methylbenzoic acid (MBA) in aqueous solution yielded the title polymer, $[Pb(C_8H_7O_2)_2(H_2O)]_n$. The asymmetric unit contains two Pb^{II} atoms, four MBA ligands and two water molecules. Each Pb^{II} cation is heptacoordinated and chelated by four carboxylate O atoms from two MBA ligands. The Pb atoms are bridged through the carboxylate O atoms from another two MBA ligands, leading to a central Pb_2O_2 core. The Pb—O bond lengths are in the range 2.325 (3)–2.757 (4) Å. The intra- and interdimer $Pb \cdots Pb$ distances are 4.2942 (3) and 4.2283 (3) Å, respectively, indicating little direct metal–metal interaction. The coordinating water molecules and carboxylate O atoms are involved in extensive O—H \cdots O hydrogen-bonding interactions. The complex has an extended ladder-like chain structure and the chains are assembled by hydrogen bonds and π – π interactions [centroid–centroid distance = 3.6246 (3) Å] into a three-dimensional supramolecular structure.

Related literature

For general background to metal-organic frameworks and their applications, see: Hamilton *et al.* (2004); Meng *et al.* (2003); Fan & Zhu (2006); Wang *et al.* (2006); Masaoka *et al.* (2001). For related structures, see: Shi *et al.* (2007).

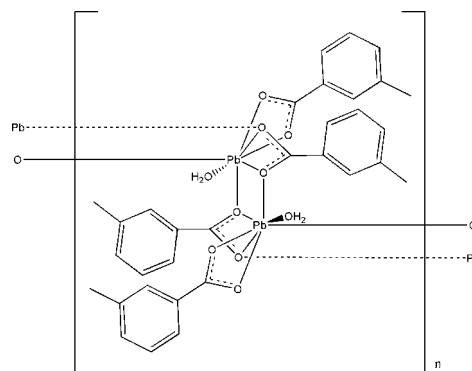

Experimental

Crystal data

$[Pb(C_8H_7O_2)_2(H_2O)]$
 $M_r = 495.48$
Monoclinic, $P2_1/n$
 $a = 7.1745$ (3) Å
 $b = 42.745$ (2) Å
 $c = 10.7126$ (5) Å
 $\beta = 90.765$ (1)°

$V = 3285.0$ (3) Å³
 $Z = 8$
Mo $K\alpha$ radiation
 $\mu = 10.29$ mm⁻¹
 $T = 296$ K
 $0.36 \times 0.17 \times 0.12$ mm

Data collection

Bruker APEXII CCD area-detector diffractometer
Absorption correction: multi-scan (SADABS; Bruker, 2007)
 $T_{min} = 0.144$, $T_{max} = 0.300$

40611 measured reflections
8096 independent reflections
6265 reflections with $I > 2\sigma(I)$
 $R_{int} = 0.056$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.035$
 $wR(F^2) = 0.061$
 $S = 1.03$
8096 reflections

397 parameters
H-atom parameters constrained
 $\Delta\rho_{max} = 0.87$ e Å⁻³
 $\Delta\rho_{min} = -1.00$ e Å⁻³

Table 1

Selected bond lengths (Å).

Pb1—O4	2.386 (3)	Pb2—O6	2.325 (3)
Pb1—O1	2.424 (3)	Pb2—O8	2.494 (4)
Pb1—O3	2.594 (3)	Pb2—O3 ⁱⁱ	2.538 (3)
Pb1—O5	2.603 (3)	Pb2—O7	2.565 (4)
Pb1—O2	2.622 (4)	Pb2—O10	2.665 (3)
Pb1—O9	2.724 (4)	Pb2—O4	2.712 (3)
Pb1—O6 ⁱ	2.751 (3)	Pb2—O5	2.757 (4)

 Symmetry codes: (i) $x - 1, y, z$; (ii) $x + 1, y, z$.

Table 2

Hydrogen-bond geometry (Å, °).

$D-H \cdots A$	$D-H$	$H \cdots A$	$D \cdots A$	$D-H \cdots A$
O9—H9A \cdots O8	0.82	2.03	2.805 (5)	158
O9—H9B \cdots O7 ⁱ	0.82	2.25	3.017 (5)	156
O10—H10B \cdots O2	0.82	2.12	2.881 (5)	153
O10—H10A \cdots O1 ⁱⁱ	0.82	1.97	2.774 (5)	166

 Symmetry codes: (i) $x - 1, y, z$; (ii) $x + 1, y, z$.

Data collection: *APEX2* (Bruker, 2007); cell refinement: *SAINTE* (Bruker, 2007); data reduction: *SAINTE*; program(s) used to solve structure: *SHELXS97* (Sheldrick, 2008); program(s) used to refine structure: *SHELXL97* (Sheldrick, 2008); molecular graphics: *SHELXTL* (Sheldrick, 2008); software used to prepare material for publication: *SHELXTL*.

The authors acknowledge the Doctoral Foundation of Henan Polytechnic University (B2008–58 648265).

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: FJ2218).

References

- Bruker (2007). *APEX2*, *SAINTE* and *SADABS*. Bruker AXS Inc., Madison, Wisconsin, USA.
- Fan, S. R. & Zhu, L. G. (2006). *Inorg. Chem.* **45**, 7935–7942.
- Hamilton, B. H., Kelly, K. A., Wagler, T. A., Espe, M. P. & Ziegler, C. J. (2004). *Inorg. Chem.* **43**, 50–56.
- Masaoka, S., Furukawa, S., Chang, H. C., Mizutani, T. & Kitagawa, S. (2001). *Angew. Chem. Int. Ed.* **40**, 3817–3819.
- Meng, X. R., Song, Y. L., Hou, H. W., Fan, Y. T., Li, G. & Zhu, Y. (2003). *Inorg. Chem.* **42**, 1306–1315.
- Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.
- Shi, J., Xu, J.-N., Zhang, P., Fan, Y., Wang, L., Bi, M.-H., Ma, K.-R. & Song, T.-Y. (2007). *Chem. J. Chin. Univ.* **28**, 1617–1621.
- Wang, X. L., Qin, C. & Wang, E. B. (2006). *Cryst. Growth. Des.* **6**, 439–443.

supplementary materials

Acta Cryst. (2009). E65, m709-m710 [doi:10.1107/S1600536809019771]

catena-Poly[[aqua(3-methylbenzoato- κ^2 O,O')lead(II)]- μ -3-methylbenzoato- κ^4 O:O,O':O']

J. Dai, J. Yang and X. An

Comment

Interest in porous metal-organic frameworks (MOFs) has been driven by the prospect of generating a wide range of materials with useful properties for applications such as ion-exchange, nonlinear optics and catalysis (Hamilton *et al.*, 2004; Meng *et al.*, 2003; Fan *et al.* 2006). On the other hand, lead(II) compounds have been increasingly studied (Shi *et al.* 2007) owing to their possible applications in different fields, especially in environmental protection due to the toxicity of lead and in biological systems for its diverse interactions with biological molecules. As an important family of multidentate O-donor ligands, aromatic carboxylate ligands have been extensively employed in the preparation of metal-organic complexes because of their potential properties and intriguing structural topologies (Wang *et al.*, 2006; Masaoka *et al.* 2001). Herein, we report the structure of the title complex.

The asymmetric unit of the title complex, $[\text{Pb}_2(\text{C}_8\text{H}_7\text{O}_2)_4(\text{H}_2\text{O})_2]_n$, contains two Pb^{II} cation, four MBA ligands and two coordinating water molecule, as illustrated in Fig. 1. The two Pb atoms are connected *via* two bridging O atoms belonging to two MBA ligands, resulting the central Pb_2O_2 core tetraatomic ring. The Pb—O bond lengths are in the range of 2.325 (3) to 2.757 (4) Å (Table 1). The average distance of two Pb atoms is 4.2942 Å, which leads to the weak metal-metal interactions. This coordination polymer structure presents extended ladder-like chain along the *a* axis direction. The coordinating water molecules and carboxylate O atoms are involved in extensive O—H \cdots O hydrogen-bonding interactions (Table 2). These chains are assembled by H-bonds and π - π interactions to three-dimensional supramolecular structure.

Experimental

A mixture of $\text{Pb}(\text{CH}_3\text{COO})_2 \cdot 3\text{H}_2\text{O}$ (0.1992 g, 0.52 mmol), MBA (0.1139 g, 0.84 mmol), melamine (0.0255 g, 0.20 mmol) and distilled water (10 ml) was sealed in a 25 ml Teflon-lined stainless autoclave (Shi *et al.* 2007). The mixture was heated at 373 K for 5 days to give colorless crystals suitable for X-ray diffraction analysis.

Refinement

All H atoms bounded to C atoms were positioned geometrically and allowed to ride on their parent atoms, with C—H distances in the range of 0.93–0.96 Å. The positions of the water H atoms were found from a difference Fourier map and refined with distance restraints O—H = 0.82 Å, $U_{\text{iso}}(\text{H}) = 1.2U_{\text{eq}}(\text{O})$.

Figures

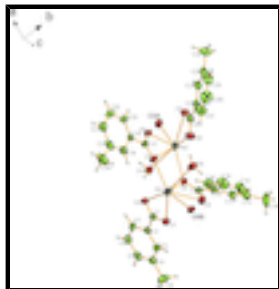


Fig. 1. The coordination environment around Pb(II) in the title complex with the atom-labeling scheme. Displacement ellipsoids for non-hydrogen atoms are drawn at the 30% probability level.



Fig. 2. The extended ladder-like chain structure of the title compound.

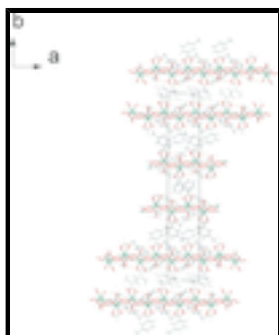


Fig. 3. The two-dimensional layer structure of the title compound.

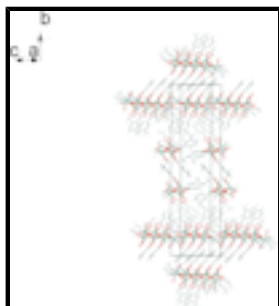


Fig. 4. The three-dimensional structure of the title compound.

catena-Poly[[aqua(3-methylbenzoato- κ^2 O,O')lead(II)]- μ -3-methylbenzoato- κ^4 O:O,O':O']

Crystal data

[Pb(C₈H₇O₂)₂(H₂O)]

$M_r = 495.48$

Monoclinic, $P2_1/n$

Hall symbol: -P 2yn

$a = 7.1745$ (3) Å

$b = 42.745$ (2) Å

$c = 10.7126$ (5) Å

$\beta = 90.7650$ (10)°

$F_{000} = 1872$

$D_x = 2.004$ Mg m⁻³

Mo $K\alpha$ radiation

$\lambda = 0.71073$ Å

Cell parameters from 7418 reflections

$\theta = 2.4$ – 25.2 °

$\mu = 10.29$ mm⁻¹

$T = 296$ K

Block, colourless

$V = 3285.0(3) \text{ \AA}^3$
 $Z = 8$ $0.36 \times 0.17 \times 0.12 \text{ mm}$

Data collection

Bruker APEXII CCD area-detector diffractometer	8096 independent reflections
Radiation source: fine-focus sealed tube	6265 reflections with $I > 2\sigma(I)$
Monochromator: graphite	$R_{\text{int}} = 0.056$
$T = 296 \text{ K}$	$\theta_{\text{max}} = 28.2^\circ$
φ and ω scans	$\theta_{\text{min}} = 1.9^\circ$
Absorption correction: Multi-Scan (SADABS; Bruker, 2007)	$h = -9 \rightarrow 9$
$T_{\text{min}} = 0.144$, $T_{\text{max}} = 0.300$	$k = -56 \rightarrow 56$
40611 measured reflections	$l = -14 \rightarrow 14$

Refinement

Refinement on F^2	Hydrogen site location: inferred from neighbouring sites
Least-squares matrix: full	H-atom parameters constrained
$R[F^2 > 2\sigma(F^2)] = 0.035$	$w = 1/[\sigma^2(F_o^2) + (0.0182P)^2 + 3.7836P]$
$wR(F^2) = 0.061$	where $P = (F_o^2 + 2F_c^2)/3$
$S = 1.03$	$(\Delta/\sigma)_{\text{max}} = 0.001$
8096 reflections	$\Delta\rho_{\text{max}} = 0.87 \text{ e \AA}^{-3}$
397 parameters	$\Delta\rho_{\text{min}} = -1.00 \text{ e \AA}^{-3}$
Primary atom site location: structure-invariant direct methods	Extinction correction: SHELXL97 (Sheldrick, 2008), $F_c^* = kFc[1 + 0.001xFc^2\lambda^3/\sin(2\theta)]^{-1/4}$
Secondary atom site location: difference Fourier map	Extinction coefficient: 0.082

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	<i>x</i>	<i>y</i>	<i>z</i>	$U_{\text{iso}}^*/U_{\text{eq}}$
Pb1	0.12243 (2)	0.097018 (5)	0.352944 (18)	0.03251 (6)
Pb2	0.63079 (2)	0.136517 (5)	0.498730 (18)	0.03285 (6)
O1	0.0014 (5)	0.06035 (8)	0.5043 (3)	0.0425 (9)
O2	0.2904 (5)	0.04888 (8)	0.4562 (3)	0.0422 (9)
O3	-0.0208 (5)	0.12954 (8)	0.5322 (3)	0.0417 (9)
O4	0.2740 (4)	0.11793 (8)	0.5341 (3)	0.0382 (8)
O5	0.4697 (5)	0.10648 (9)	0.2967 (3)	0.0431 (9)
O6	0.7648 (4)	0.11863 (8)	0.3157 (3)	0.0361 (8)
O7	0.7820 (5)	0.18516 (8)	0.4032 (4)	0.0456 (9)
O8	0.4875 (5)	0.17631 (9)	0.3567 (4)	0.0532 (11)
O9	0.1259 (5)	0.15838 (9)	0.2844 (4)	0.0536 (11)
H9A	0.2336	0.1648	0.2856	0.064*
H9B	0.0480	0.1635	0.3359	0.064*

supplementary materials

O10	0.6329 (5)	0.07555 (8)	0.5507 (3)	0.0435 (9)
H10B	0.5587	0.0665	0.5043	0.052*
H10A	0.7351	0.0704	0.5243	0.052*
C1	0.1464 (7)	0.04397 (11)	0.5191 (5)	0.0350 (12)
C2	0.1449 (7)	0.01859 (11)	0.6140 (5)	0.0327 (11)
C3	-0.0085 (7)	0.01413 (12)	0.6892 (5)	0.0419 (13)
H3A	-0.1126	0.0268	0.6775	0.050*
C4	-0.0118 (8)	-0.00864 (13)	0.7814 (5)	0.0449 (14)
C5	0.1437 (9)	-0.02741 (13)	0.7950 (6)	0.0501 (15)
H5A	0.1450	-0.0428	0.8563	0.060*
C6	0.2948 (8)	-0.02395 (13)	0.7213 (6)	0.0483 (15)
H6A	0.3966	-0.0372	0.7319	0.058*
C7	0.2988 (8)	-0.00088 (12)	0.6303 (5)	0.0416 (13)
H7A	0.4032	0.0016	0.5807	0.050*
C8	-0.1813 (10)	-0.01275 (18)	0.8623 (7)	0.080 (2)
H8A	-0.1591	-0.0294	0.9210	0.121*
H8B	-0.2874	-0.0178	0.8107	0.121*
H8C	-0.2050	0.0063	0.9066	0.121*
C9	0.1354 (7)	0.13040 (11)	0.5855 (4)	0.0297 (11)
C10	0.1578 (7)	0.14561 (12)	0.7091 (5)	0.0367 (12)
C11	0.0214 (9)	0.16600 (13)	0.7525 (6)	0.0514 (15)
H11A	-0.0821	0.1705	0.7024	0.062*
C12	0.0388 (12)	0.17949 (16)	0.8690 (7)	0.072 (2)
C13	0.1933 (15)	0.1719 (2)	0.9412 (7)	0.093 (3)
H13A	0.2058	0.1805	1.0205	0.111*
C14	0.3266 (12)	0.1524 (2)	0.8998 (7)	0.081 (2)
H14A	0.4297	0.1481	0.9505	0.097*
C15	0.3122 (9)	0.13865 (15)	0.7832 (5)	0.0563 (17)
H15A	0.4040	0.1251	0.7551	0.068*
C16	-0.1079 (14)	0.2018 (2)	0.9145 (9)	0.131 (4)
H16A	-0.0742	0.2091	0.9965	0.197*
H16B	-0.2258	0.1912	0.9175	0.197*
H16C	-0.1171	0.2193	0.8586	0.197*
C17	0.6265 (6)	0.10896 (11)	0.2509 (5)	0.0296 (11)
C18	0.6596 (7)	0.10073 (11)	0.1176 (5)	0.0308 (11)
C19	0.5301 (8)	0.08355 (12)	0.0511 (5)	0.0425 (13)
H19A	0.4204	0.0776	0.0896	0.051*
C20	0.5586 (10)	0.07500 (14)	-0.0711 (6)	0.0558 (17)
C21	0.7238 (11)	0.08378 (15)	-0.1256 (6)	0.0634 (19)
H21A	0.7476	0.0777	-0.2072	0.076*
C22	0.8544 (10)	0.10140 (15)	-0.0611 (6)	0.0612 (18)
H22A	0.9636	0.1076	-0.0999	0.073*
C23	0.8229 (8)	0.10979 (13)	0.0606 (5)	0.0420 (13)
H23A	0.9110	0.1215	0.1045	0.050*
C24	0.4110 (11)	0.05680 (17)	-0.1440 (7)	0.090 (3)
H24A	0.4543	0.0528	-0.2269	0.135*
H24B	0.2980	0.0688	-0.1483	0.135*
H24C	0.3875	0.0373	-0.1027	0.135*
C25	0.6358 (8)	0.19171 (13)	0.3421 (5)	0.0413 (13)

C26	0.6358 (8)	0.21833 (13)	0.2526 (5)	0.0437 (14)
C27	0.7935 (9)	0.23678 (13)	0.2416 (5)	0.0500 (15)
H27A	0.8980	0.2324	0.2908	0.060*
C28	0.7986 (11)	0.26149 (15)	0.1590 (6)	0.0643 (19)
C29	0.6435 (15)	0.26682 (19)	0.0853 (7)	0.091 (3)
H29A	0.6446	0.2832	0.0283	0.109*
C30	0.4891 (14)	0.2487 (2)	0.0936 (8)	0.095 (3)
H30A	0.3868	0.2526	0.0417	0.114*
C31	0.4833 (10)	0.22464 (17)	0.1785 (7)	0.069 (2)
H31A	0.3758	0.2126	0.1857	0.083*
C32	0.9668 (12)	0.28192 (18)	0.1483 (8)	0.107 (3)
H32A	0.9438	0.2978	0.0865	0.161*
H32B	1.0717	0.2695	0.1242	0.161*
H32C	0.9928	0.2916	0.2274	0.161*

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Pb1	0.02451 (10)	0.04213 (12)	0.03088 (11)	-0.00082 (8)	0.00003 (7)	-0.00184 (9)
Pb2	0.02385 (9)	0.04156 (12)	0.03319 (11)	0.00000 (8)	0.00229 (8)	-0.00581 (9)
O1	0.034 (2)	0.042 (2)	0.052 (2)	0.0036 (17)	0.0058 (18)	0.0068 (18)
O2	0.0285 (19)	0.049 (2)	0.050 (2)	-0.0036 (16)	0.0087 (17)	0.0043 (18)
O3	0.034 (2)	0.053 (2)	0.038 (2)	0.0047 (17)	-0.0067 (17)	-0.0090 (18)
O4	0.0249 (18)	0.049 (2)	0.041 (2)	-0.0005 (16)	0.0056 (16)	-0.0044 (18)
O5	0.0280 (19)	0.059 (2)	0.042 (2)	-0.0028 (17)	0.0080 (17)	-0.0055 (19)
O6	0.0273 (18)	0.050 (2)	0.031 (2)	-0.0020 (16)	-0.0003 (15)	-0.0068 (17)
O7	0.037 (2)	0.042 (2)	0.058 (3)	-0.0016 (17)	-0.0059 (19)	0.0046 (19)
O8	0.039 (2)	0.052 (2)	0.068 (3)	-0.0060 (19)	-0.012 (2)	0.005 (2)
O9	0.035 (2)	0.069 (3)	0.057 (3)	-0.007 (2)	0.0047 (19)	0.001 (2)
O10	0.033 (2)	0.053 (2)	0.045 (2)	0.0014 (17)	0.0021 (17)	-0.0025 (18)
C1	0.032 (3)	0.034 (3)	0.039 (3)	-0.005 (2)	0.000 (2)	-0.004 (2)
C2	0.036 (3)	0.030 (3)	0.033 (3)	-0.005 (2)	-0.001 (2)	-0.004 (2)
C3	0.034 (3)	0.041 (3)	0.051 (4)	-0.003 (2)	0.002 (3)	-0.006 (3)
C4	0.047 (3)	0.044 (3)	0.044 (4)	-0.010 (3)	0.003 (3)	0.001 (3)
C5	0.069 (4)	0.034 (3)	0.047 (4)	-0.003 (3)	-0.007 (3)	0.005 (3)
C6	0.052 (4)	0.038 (3)	0.055 (4)	0.008 (3)	-0.002 (3)	0.005 (3)
C7	0.041 (3)	0.037 (3)	0.047 (4)	0.008 (2)	0.004 (3)	-0.005 (3)
C8	0.069 (5)	0.098 (6)	0.074 (5)	-0.007 (4)	0.018 (4)	0.030 (4)
C9	0.028 (3)	0.035 (3)	0.026 (3)	-0.002 (2)	-0.002 (2)	0.002 (2)
C10	0.041 (3)	0.039 (3)	0.031 (3)	-0.007 (2)	-0.004 (2)	0.004 (2)
C11	0.064 (4)	0.046 (3)	0.044 (4)	0.005 (3)	0.003 (3)	-0.008 (3)
C12	0.111 (6)	0.056 (4)	0.049 (4)	-0.004 (4)	0.008 (4)	-0.013 (4)
C13	0.151 (9)	0.081 (6)	0.045 (5)	-0.023 (6)	-0.015 (5)	-0.022 (4)
C14	0.105 (7)	0.093 (6)	0.044 (4)	-0.022 (5)	-0.029 (4)	0.003 (4)
C15	0.058 (4)	0.073 (4)	0.038 (4)	-0.003 (3)	-0.016 (3)	0.004 (3)
C16	0.178 (10)	0.098 (7)	0.119 (8)	0.041 (7)	0.035 (7)	-0.058 (6)
C17	0.025 (2)	0.034 (3)	0.030 (3)	0.002 (2)	0.002 (2)	0.001 (2)
C18	0.031 (3)	0.027 (3)	0.034 (3)	0.004 (2)	0.005 (2)	0.002 (2)

supplementary materials

C19	0.056 (4)	0.041 (3)	0.030 (3)	-0.006 (3)	-0.001 (3)	0.001 (2)
C20	0.086 (5)	0.044 (4)	0.037 (4)	-0.009 (3)	-0.008 (3)	-0.008 (3)
C21	0.106 (6)	0.052 (4)	0.033 (4)	-0.005 (4)	0.020 (4)	-0.005 (3)
C22	0.073 (5)	0.066 (4)	0.046 (4)	-0.005 (4)	0.026 (3)	0.005 (3)
C23	0.043 (3)	0.045 (3)	0.038 (3)	-0.002 (3)	0.003 (3)	0.004 (3)
C24	0.139 (8)	0.079 (5)	0.052 (5)	-0.039 (5)	-0.021 (5)	-0.021 (4)
C25	0.039 (3)	0.040 (3)	0.046 (4)	0.000 (3)	-0.002 (3)	-0.005 (3)
C26	0.053 (4)	0.038 (3)	0.040 (3)	0.007 (3)	-0.004 (3)	-0.007 (3)
C27	0.065 (4)	0.043 (3)	0.042 (4)	0.007 (3)	0.005 (3)	0.000 (3)
C28	0.101 (6)	0.045 (4)	0.047 (4)	0.013 (4)	0.018 (4)	0.002 (3)
C29	0.148 (9)	0.069 (5)	0.057 (5)	0.025 (6)	0.020 (6)	0.025 (4)
C30	0.107 (7)	0.104 (7)	0.074 (6)	0.021 (6)	-0.022 (5)	0.034 (5)
C31	0.064 (5)	0.077 (5)	0.065 (5)	0.000 (4)	-0.014 (4)	0.011 (4)
C32	0.132 (8)	0.070 (5)	0.120 (8)	-0.018 (5)	0.045 (6)	0.028 (5)

Geometric parameters (Å, °)

Pb1—O4	2.386 (3)	C10—C15	1.387 (7)
Pb1—O1	2.424 (3)	C10—C11	1.395 (7)
Pb1—O3	2.594 (3)	C11—C12	1.380 (8)
Pb1—O5	2.603 (3)	C11—H11A	0.9300
Pb1—O2	2.622 (4)	C12—C13	1.381 (11)
Pb1—O9	2.724 (4)	C12—C16	1.505 (10)
Pb1—O6 ⁱ	2.751 (3)	C13—C14	1.348 (11)
Pb2—O6	2.325 (3)	C13—H13A	0.9300
Pb2—O8	2.494 (4)	C14—C15	1.384 (9)
Pb2—O3 ⁱⁱ	2.538 (3)	C14—H14A	0.9300
Pb2—O7	2.565 (4)	C15—H15A	0.9300
Pb2—O10	2.665 (3)	C16—H16A	0.9600
Pb2—O4	2.712 (3)	C16—H16B	0.9600
Pb2—O5	2.757 (4)	C16—H16C	0.9600
O1—C1	1.263 (6)	C17—C18	1.493 (7)
O2—C1	1.258 (6)	C18—C19	1.376 (7)
O3—C9	1.251 (5)	C18—C23	1.384 (7)
O3—Pb2 ⁱ	2.538 (3)	C19—C20	1.377 (8)
O4—C9	1.261 (5)	C19—H19A	0.9300
O5—C17	1.238 (5)	C20—C21	1.380 (9)
O6—C17	1.273 (5)	C20—C24	1.521 (8)
O6—Pb1 ⁱⁱ	2.751 (3)	C21—C22	1.381 (9)
O7—C25	1.261 (6)	C21—H21A	0.9300
O8—C25	1.263 (6)	C22—C23	1.373 (8)
O9—H9A	0.8200	C22—H22A	0.9300
O9—H9B	0.8200	C23—H23A	0.9300
O10—H10B	0.8200	C24—H24A	0.9600
O10—H10A	0.8200	C24—H24B	0.9600
C1—C2	1.487 (7)	C24—H24C	0.9600
C2—C3	1.386 (7)	C25—C26	1.488 (8)
C2—C7	1.392 (7)	C26—C31	1.370 (8)

C3—C4	1.387 (7)	C26—C27	1.386 (8)
C3—H3A	0.9300	C27—C28	1.378 (8)
C4—C5	1.380 (8)	C27—H27A	0.9300
C4—C8	1.513 (8)	C28—C29	1.375 (11)
C5—C6	1.358 (8)	C28—C32	1.495 (10)
C5—H5A	0.9300	C29—C30	1.355 (11)
C6—C7	1.388 (7)	C29—H29A	0.9300
C6—H6A	0.9300	C30—C31	1.375 (10)
C7—H7A	0.9300	C30—H30A	0.9300
C8—H8A	0.9600	C31—H31A	0.9300
C8—H8B	0.9600	C32—H32A	0.9600
C8—H8C	0.9600	C32—H32B	0.9600
C9—C10	1.482 (7)	C32—H32C	0.9600
O4—Pb1—O1	82.05 (12)	C4—C8—H8B	109.5
O4—Pb1—O3	51.51 (11)	H8A—C8—H8B	109.5
O1—Pb1—O3	72.68 (12)	C4—C8—H8C	109.5
O4—Pb1—O5	72.72 (11)	H8A—C8—H8C	109.5
O1—Pb1—O5	127.44 (12)	H8B—C8—H8C	109.5
O3—Pb1—O5	118.56 (11)	O3—C9—O4	119.7 (5)
O4—Pb1—O2	75.46 (12)	O3—C9—C10	120.4 (4)
O1—Pb1—O2	51.48 (11)	O4—C9—C10	119.9 (4)
O3—Pb1—O2	107.02 (11)	C15—C10—C11	120.2 (5)
O5—Pb1—O2	77.50 (11)	C15—C10—C9	119.5 (5)
O4—Pb1—O9	81.54 (12)	C11—C10—C9	120.2 (5)
O1—Pb1—O9	143.85 (12)	C12—C11—C10	120.5 (6)
O3—Pb1—O9	71.86 (12)	C12—C11—H11A	119.8
O5—Pb1—O9	77.05 (11)	C10—C11—H11A	119.8
O2—Pb1—O9	149.74 (11)	C11—C12—C13	118.1 (7)
O4—Pb1—O6 ⁱ	113.97 (10)	C11—C12—C16	120.2 (8)
O1—Pb1—O6 ⁱ	88.41 (11)	C13—C12—C16	121.8 (7)
O3—Pb1—O6 ⁱ	63.23 (10)	C14—C13—C12	121.9 (7)
O5—Pb1—O6 ⁱ	143.91 (11)	C14—C13—H13A	119.0
O2—Pb1—O6 ⁱ	138.35 (10)	C12—C13—H13A	119.0
O9—Pb1—O6 ⁱ	69.48 (10)	C13—C14—C15	121.0 (7)
O6—Pb2—O8	83.21 (13)	C13—C14—H14A	119.5
O6—Pb2—O3 ⁱⁱ	70.29 (11)	C15—C14—H14A	119.5
O8—Pb2—O3 ⁱⁱ	124.28 (12)	C14—C15—C10	118.4 (7)
O6—Pb2—O7	75.42 (12)	C14—C15—H15A	120.8
O8—Pb2—O7	51.46 (12)	C10—C15—H15A	120.8
O3 ⁱⁱ —Pb2—O7	74.37 (12)	C12—C16—H16A	109.5
O6—Pb2—O10	81.57 (11)	C12—C16—H16B	109.5
O8—Pb2—O10	142.70 (12)	H16A—C16—H16B	109.5
O3 ⁱⁱ —Pb2—O10	81.54 (11)	C12—C16—H16C	109.5
O7—Pb2—O10	151.05 (11)	H16A—C16—H16C	109.5
O6—Pb2—O4	115.06 (11)	H16B—C16—H16C	109.5
O8—Pb2—O4	84.44 (12)	O5—C17—O6	121.2 (5)

supplementary materials

O3 ⁱⁱ —Pb2—O4	151.11 (11)	O5—C17—C18	121.1 (4)
O7—Pb2—O4	134.31 (11)	O6—C17—C18	117.7 (4)
O10—Pb2—O4	71.75 (10)	C19—C18—C23	119.4 (5)
O6—Pb2—O5	50.10 (10)	C19—C18—C17	120.4 (5)
O8—Pb2—O5	70.96 (12)	C23—C18—C17	120.2 (5)
O3 ⁱⁱ —Pb2—O5	117.25 (10)	C18—C19—C20	121.8 (6)
O7—Pb2—O5	103.86 (11)	C18—C19—H19A	119.1
O10—Pb2—O5	73.13 (11)	C20—C19—H19A	119.1
O4—Pb2—O5	65.60 (10)	C19—C20—C21	118.0 (6)
C1—O1—Pb1	98.1 (3)	C19—C20—C24	120.8 (6)
C1—O2—Pb1	88.9 (3)	C21—C20—C24	121.2 (6)
C9—O3—Pb2 ⁱ	159.3 (3)	C20—C21—C22	121.2 (6)
C9—O3—Pb1	89.5 (3)	C20—C21—H21A	119.4
Pb2 ⁱ —O3—Pb1	110.94 (12)	C22—C21—H21A	119.4
C9—O4—Pb1	99.2 (3)	C23—C22—C21	119.9 (6)
C9—O4—Pb2	133.5 (3)	C23—C22—H22A	120.1
Pb1—O4—Pb2	114.63 (13)	C21—C22—H22A	120.1
C17—O5—Pb1	169.4 (3)	C22—C23—C18	119.8 (6)
C17—O5—Pb2	84.1 (3)	C22—C23—H23A	120.1
Pb1—O5—Pb2	106.44 (12)	C18—C23—H23A	120.1
C17—O6—Pb2	103.8 (3)	C20—C24—H24A	109.5
C17—O6—Pb1 ⁱⁱ	133.6 (3)	C20—C24—H24B	109.5
Pb2—O6—Pb1 ⁱⁱ	112.57 (13)	H24A—C24—H24B	109.5
C25—O7—Pb2	91.9 (3)	C20—C24—H24C	109.5
C25—O8—Pb2	95.2 (3)	H24A—C24—H24C	109.5
Pb1—O9—H9A	109.2	H24B—C24—H24C	109.5
Pb1—O9—H9B	93.9	O7—C25—O8	121.1 (5)
H9A—O9—H9B	123.4	O7—C25—C26	119.8 (5)
Pb2—O10—H10B	109.3	O8—C25—C26	119.1 (5)
Pb2—O10—H10A	101.0	C31—C26—C27	119.0 (6)
H10B—O10—H10A	103.9	C31—C26—C25	121.1 (6)
O2—C1—O1	121.4 (5)	C27—C26—C25	119.8 (5)
O2—C1—C2	120.1 (5)	C28—C27—C26	121.3 (6)
O1—C1—C2	118.5 (5)	C28—C27—H27A	119.4
C3—C2—C7	118.7 (5)	C26—C27—H27A	119.4
C3—C2—C1	120.7 (5)	C29—C28—C27	117.9 (7)
C7—C2—C1	120.6 (5)	C29—C28—C32	120.4 (7)
C2—C3—C4	122.1 (5)	C27—C28—C32	121.7 (7)
C2—C3—H3A	118.9	C30—C29—C28	121.5 (7)
C4—C3—H3A	118.9	C30—C29—H29A	119.2
C5—C4—C3	117.5 (5)	C28—C29—H29A	119.2
C5—C4—C8	121.8 (6)	C29—C30—C31	120.2 (8)
C3—C4—C8	120.7 (5)	C29—C30—H30A	119.9
C6—C5—C4	121.7 (6)	C31—C30—H30A	119.9
C6—C5—H5A	119.1	C26—C31—C30	120.0 (7)
C4—C5—H5A	119.1	C26—C31—H31A	120.0
C5—C6—C7	120.7 (5)	C30—C31—H31A	120.0
C5—C6—H6A	119.6	C28—C32—H32A	109.5

C7—C6—H6A	119.6	C28—C32—H32B	109.5
C6—C7—C2	119.3 (5)	H32A—C32—H32B	109.5
C6—C7—H7A	120.4	C28—C32—H32C	109.5
C2—C7—H7A	120.4	H32A—C32—H32C	109.5
C4—C8—H8A	109.5	H32B—C32—H32C	109.5

Symmetry codes: (i) $x-1, y, z$; (ii) $x+1, y, z$.

Hydrogen-bond geometry (\AA , $^\circ$)

$D-H\cdots A$	$D-H$	$H\cdots A$	$D\cdots A$	$D-H\cdots A$
O9—H9A \cdots O8	0.82	2.03	2.805 (5)	158
O9—H9B \cdots O7 ⁱ	0.82	2.25	3.017 (5)	156
O10—H10B \cdots O2	0.82	2.12	2.881 (5)	153
O10—H10A \cdots O1 ⁱⁱ	0.82	1.97	2.774 (5)	166

Symmetry codes: (i) $x-1, y, z$; (ii) $x+1, y, z$.

Fig. 1

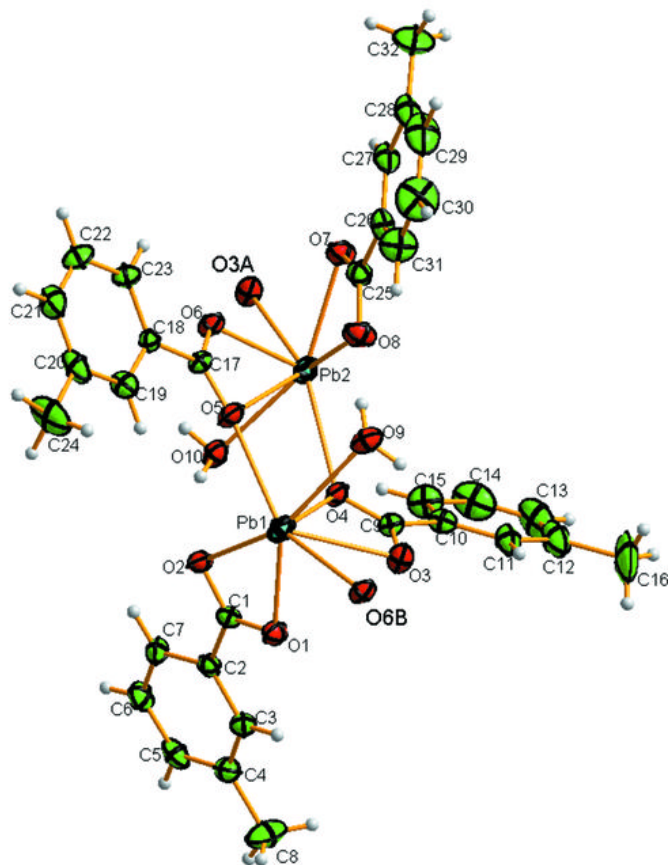



Fig. 2

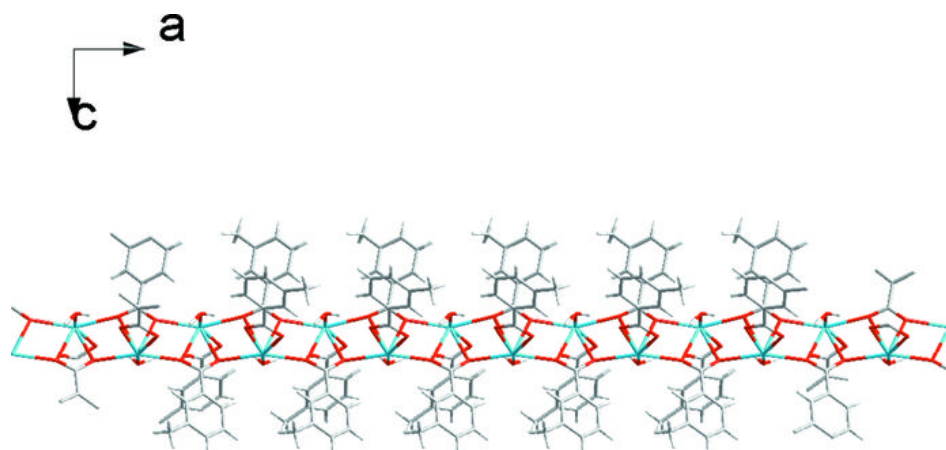


Fig. 3


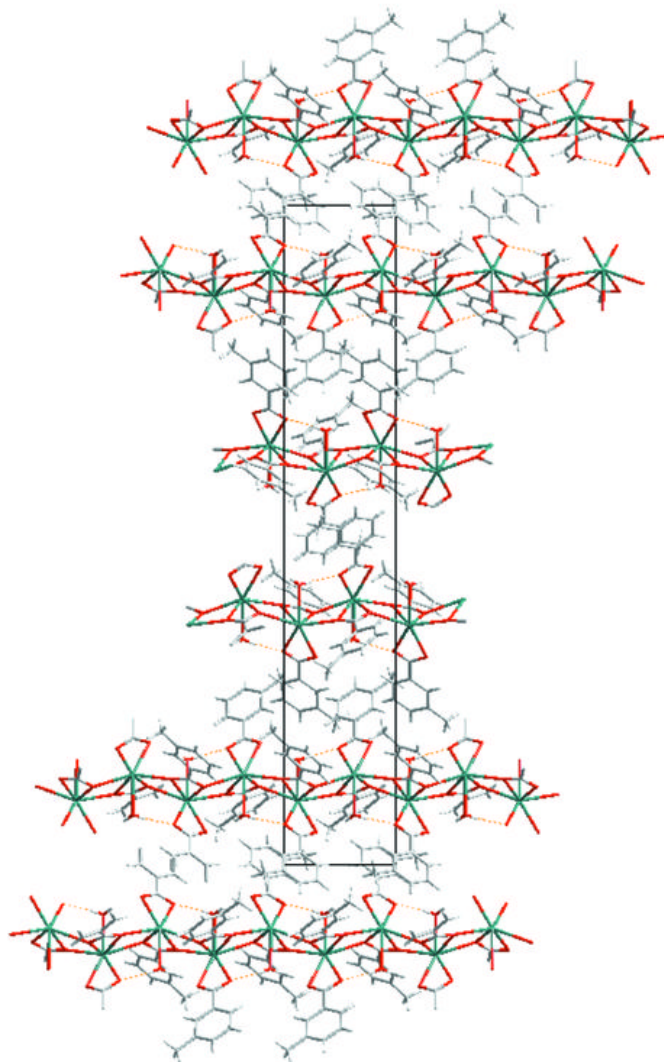


Fig. 4

