

Acta Crystallographica Section E

Structure Reports

Online

ISSN 1600-5368

Poly[di- μ_2 -chlorido(μ_2 -1,3-di-4-pyridyl-propane- $\kappa^2N:N'$)lead(II)]

Zhiyong Fu,* Dongpo Su and Desheng Song

School of Chemistry and Chemical Engineering, South China University of Technology, Guangzhou, People's Republic of China
Correspondence e-mail: zyfu@scut.edu.cn


Received 21 August 2009; accepted 7 September 2009

Key indicators: single-crystal X-ray study; $T = 298$ K; mean $\sigma(C-C) = 0.011$ Å; R factor = 0.033; wR factor = 0.077; data-to-parameter ratio = 14.6.

The title Pb^{II} coordination polymer, $[PbCl_2(C_{13}H_{14}N_2)]$, was prepared by the hydrothermal reaction of $PbCl_2$ with 4,4'-trimethylenedipyridine in a 1:1 ratio. It exhibits a two-dimensional layered structural motif consisting of $PbCl_2$ chains and the flexible bridged 4,4'-trimethylenedipyridine ligand. The connections result in a cavity of about 4×15 Å.

Related literature

For crystal engineering based upon transition metal coordination polymers, see: Abrahams *et al.* (1999). For applications of these metal-organic frameworks, see: Moulton & Zaworotko (2001); Natarajan & Mahata (2009). For networks with main group metals as connected nodes, see: Shi *et al.* (2002). For the related structure, $[PbCl_2(4,4'$ -bipy)] (bipy is bipyridine), see: Nordell *et al.* (2004).

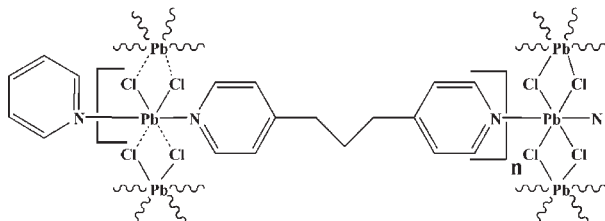

Experimental

Crystal data

$[PbCl_2(C_{13}H_{14}N_2)]$
 $M_r = 476.35$
Monoclinic, $P2_1/m$
 $a = 4.385$ (2) Å
 $b = 15.455$ (3) Å
 $c = 10.935$ (2) Å
 $\beta = 97.65$ (2)°

$V = 734.5$ (3) Å³
 $Z = 2$
Mo $K\alpha$ radiation
 $\mu = 11.84$ mm⁻¹
 $T = 298$ K
 $0.19 \times 0.15 \times 0.11$ mm

Data collection

Bruker SMART CCD diffractometer
Absorption correction: multi-scan (SADABS; Sheldrick, 1996)
 $T_{min} = 0.139$, $T_{max} = 0.277$

2401 measured reflections
1283 independent reflections
1109 reflections with $I > 2\sigma(I)$
 $R_{int} = 0.033$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.033$
 $wR(F^2) = 0.077$
 $S = 1.01$
1283 reflections

88 parameters
H-atom parameters constrained
 $\Delta\rho_{max} = 0.88$ e Å⁻³
 $\Delta\rho_{min} = -1.16$ e Å⁻³

Data collection: SMART (Bruker, 1996); cell refinement: SMART and SAINT (Bruker, 1996); data reduction: SHELXTL (Sheldrick, 2008); program(s) used to solve structure: SHELXS97 (Sheldrick, 2008); program(s) used to refine structure: SHELXL97 (Sheldrick, 2008); molecular graphics: SHELXTL; software used to prepare material for publication: SHELXTL.

The authors thank the NNSFC (grant No. 20701014) and the SRP program of the SCUT for financial support.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: PB2006).

References

- Abrahams, B. F., Egan, S. J. & Robson, R. (1999). *J. Am. Chem. Soc.* **121**, 3535–3536.
Bruker (1996). SMART and SAINT. Bruker AXS Inc., Madison, Wisconsin, USA.
Moulton, B. & Zaworotko, M. J. (2001). *Chem. Rev.* **101**, 1629–1658.
Natarajan, S. & Mahata, P. (2009). *Chem. Soc. Rev.* **38**, 2304–2318.
Nordell, K. J., Schultz, K. N., Higgins, K. A. & Smith, M. D. (2004). *Polyhedron*, **23**, 2161–2167.
Sheldrick, G. M. (1996). SADABS. University of Göttingen, Germany.
Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.
Shi, Y. J., Li, L. H., Li, Y. Z., Xu, Y., Chen, X. T., Xue, Z. & You, X. Z. (2002). *Inorg. Chem. Commun.* **5**, 1090–1094.

supplementary materials

Acta Cryst. (2009). E65, m1220 [doi:10.1107/S1600536809036150]

Poly[di- μ_2 -chlorido(μ_2 -1,3-di-4-pyridylpropane- $\kappa^2N:N'$)lead(II)]

Z. Fu, D. Su and D. Song

Comment

Crystal engineering based upon transition metal coordination polymers has made rapid progress (Abrahams *et al.*, 1999). These metal organic frameworks attracted much attention in the field of host guest chemistry (Natarajan *et al.*, 2009), which may find applications in catalysis, nonlinear optics, magnetism, molecular recognition and separation (Moulton *et al.*, 2001). By comparison, the networks with main group metals as connected nodes have not been well documented (Shi *et al.*, 2002). Recently, many lead halides based coordination polymers with nitrogen-containing ligand as bridge exhibit interesting physical properties and structural motifs (Nordell *et al.*, 2004). Different linkers, such as 4,4'-bipy, pyrazine and bipyridyl-based butadiene are introduced to the construction of lead halide organic-inorganic hybrid compounds. Here we report the hydrothermal synthesis and structural characterization of a new coordination complex based on PbCl_2 inorganic unit and 4,4'-trimethylenedipyridine. Hydrothermal reaction of PbCl_2 and 4,4'-trimethylenedipyridine with equimolar amounts afford block-like crystals. They were characterized by single-crystal X-ray structural analysis. Details of crystallographic data for the title compounds 1 is listed in Table 1. The structure of $\text{PbCl}_2(4,4'$ -trimethylenedipyridine) framework is a two-dimensional-layered motif constructed by the $[\text{PbCl}_2]_n$ chains and the flexible bridge 4,4'-trimethylenedipyridine ligand (Fig. 1). The crystal is monoclinic, space group $P2_1/m$, with the Pb, Cl1 and Cl2 atoms lying on a crystallographic mirror plane. Each lead metal center is six-coordinate geometry with four chloride ion on the square plane and two nitrogen donors at the axial direction. The bond distances of Pb—Cl range from 2.862 (6) Å to 2.982 (6) Å. And the bond distance of Pb—N is 2.667 (7) Å. These parameters are close to previous report (Nordell *et al.*, 2004). The bond angles of Cl—Pb—Cl at the square plane vary from 81.15 (17) to 97.21 (17)°. And the *trans* N1—Pb1—N1 bond angle is 166.1 (3)°. These value indicate that the lead center is situated in a distorted octahedral environment and the lone pair in Pb(II) is stereochemically active. As showed in figure 2, The $[\text{PbCl}_2]_n$ chains are linked into flat sheets by the 4,4'-trimethylenedipyridine bridges. The dimensions of the distorted square cavity are approximately 4*15 Å. The flexible of the spacers make the layer into an undulating structural motif. And the sheets stack along *a* axis at a distance of 4.69 Å.

Experimental

An aqueous mixture (10 ml) containing 4,4'-trimethylenedipyridine (0.1 g, 0.5 mmol), PbCl_2 (0.139 g, 0.5 mmol) was placed in a Parr Teflonlined stainless steel vessel (25 ml), and the vessel was sealed and heated to 403.15 K for 24 h. 0.08 g block-like crystals were obtained.

Refinement

H atoms were positioned geometrically and refined using a riding model, with C—H = 0.93–0.97 Å and with $U_{\text{iso}}(\text{H}) = 1.2$ (1.5 for methyl groups) times $U_{\text{eq}}(\text{C})$. The non-hydrogen atoms were refined anisotropically. 41 low-theta reflections were omitted from the data set.

Figures




Fig. 1. The molecular structure of (I), with atom labels and 50% probability displacement ellipsoids for non-H atoms.

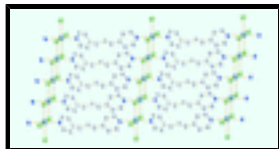


Fig. 2. The packing of (I), viewed down the *c* axis.

Poly[di- μ_2 -chlorido(μ_2 -1,3-di-4-pyridylpropane- $\kappa^2N:N'$)lead(II)]

Crystal data

[PbCl₂(C₁₃H₁₄N₂)]

$M_r = 476.35$

Monoclinic, $P2_1/m$

Hall symbol: -P2yb

$a = 4.385$ (2) Å

$b = 15.455$ (3) Å

$c = 10.935$ (2) Å

$\beta = 97.65$ (2)°

$V = 734.5$ (3) Å³

$Z = 2$

$F_{000} = 444$

$D_x = 2.155$ Mg m⁻³

Melting point: 533.15K K

Mo $K\alpha$ radiation, $\lambda = 0.71073$ Å

Cell parameters from 1283 reflections

$\theta = 2.6$ – 25.0 °

$\mu = 11.84$ mm⁻¹

$T = 298$ K

Block, yellow

$0.19 \times 0.15 \times 0.11$ mm

Data collection

Bruker SMART CCD
diffractometer

Radiation source: fine-focus sealed tube

Monochromator: graphite

$T = 298$ K

ω scans

Absorption correction: multi-scan
(SADABS; Sheldrick, 1996)

$T_{\min} = 0.139$, $T_{\max} = 0.277$

2401 measured reflections

1283 independent reflections

1109 reflections with $I > 2\sigma(I)$

$R_{\text{int}} = 0.033$

$\theta_{\max} = 25.0$ °

$\theta_{\min} = 2.6$ °

$h = -5 \rightarrow 5$

$k = -15 \rightarrow 18$

$l = -7 \rightarrow 12$

Refinement

Refinement on F^2

Least-squares matrix: full

$R[F^2 > 2\sigma(F^2)] = 0.033$

$wR(F^2) = 0.077$

Secondary atom site location: difference Fourier map

Hydrogen site location: inferred from neighbouring sites

H-atom parameters constrained

$w = 1/[\sigma^2(F_o^2) + (0.0359P)^2]$

where $P = (F_o^2 + 2F_c^2)/3$

$S = 1.01$	$(\Delta/\sigma)_{\max} < 0.001$
1283 reflections	$\Delta\rho_{\max} = 0.88 \text{ e } \text{\AA}^{-3}$
88 parameters	$\Delta\rho_{\min} = -1.16 \text{ e } \text{\AA}^{-3}$
Primary atom site location: structure-invariant direct methods	Extinction correction: none

Special details

Geometry. All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

Refinement. Refinement of F^2 against ALL reflections. The weighted R -factor wR and goodness of fit S are based on F^2 , conventional R -factors R are based on F , with F set to zero for negative F^2 . The threshold expression of $F^2 > \sigma(F^2)$ is used only for calculating R -factors(gt) *etc.* and is not relevant to the choice of reflections for refinement. R -factors based on F^2 are statistically about twice as large as those based on F , and R -factors based on ALL data will be even larger.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	x	y	z	$U_{\text{iso}}^*/U_{\text{eq}}$
Pb1	0.32077 (9)	0.7500	0.28349 (4)	0.03780 (17)
Cl2	0.7798 (10)	0.7500	0.1052 (3)	0.0748 (10)
Cl1	-0.1094 (10)	0.7500	0.4619 (3)	0.0719 (10)
C5	0.6217 (18)	0.4150 (5)	0.2292 (8)	0.0431 (19)
N1	0.3822 (16)	0.5787 (4)	0.2702 (7)	0.0482 (17)
C2	0.412 (2)	0.4554 (5)	0.1409 (8)	0.049 (2)
H2A	0.3481	0.4278	0.0662	0.059*
C3	0.574 (2)	0.5401 (5)	0.3555 (8)	0.057 (2)
H3A	0.6288	0.5684	0.4303	0.068*
C1	0.297 (2)	0.5358 (5)	0.1631 (8)	0.049 (2)
H1A	0.1573	0.5616	0.1026	0.059*
C6	0.770 (2)	0.3312 (5)	0.2033 (9)	0.055 (2)
H6A	0.9711	0.3283	0.2527	0.066*
H6B	0.8024	0.3302	0.1171	0.066*
C31	0.698 (2)	0.4595 (5)	0.3397 (9)	0.055 (2)
H3B	0.8335	0.4349	0.4030	0.066*
C7	0.584 (2)	0.2500	0.2302 (11)	0.040 (3)
H7A	0.3863	0.2500	0.1783	0.048*
H7C	0.5474	0.2500	0.3159	0.048*

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Pb1	0.0342 (2)	0.0274 (2)	0.0527 (3)	0.000	0.00873 (17)	0.000
Cl2	0.095 (3)	0.082 (2)	0.047 (2)	0.000	0.0061 (17)	0.000
Cl1	0.102 (3)	0.065 (2)	0.048 (2)	0.000	0.0045 (18)	0.000
C5	0.043 (5)	0.026 (4)	0.066 (6)	-0.005 (3)	0.027 (4)	0.002 (4)

supplementary materials

N1	0.057 (4)	0.027 (3)	0.062 (5)	0.006 (3)	0.016 (4)	0.006 (3)
C2	0.062 (5)	0.032 (4)	0.052 (5)	-0.003 (4)	0.008 (4)	-0.003 (4)
C3	0.081 (7)	0.032 (4)	0.056 (6)	0.002 (4)	0.003 (5)	-0.001 (4)
C1	0.053 (5)	0.032 (4)	0.059 (6)	-0.002 (4)	-0.002 (4)	0.009 (4)
C6	0.056 (5)	0.032 (4)	0.083 (7)	-0.002 (4)	0.029 (5)	0.004 (4)
C31	0.060 (6)	0.040 (4)	0.066 (6)	-0.007 (4)	0.005 (5)	0.006 (4)
C7	0.035 (6)	0.023 (5)	0.064 (7)	0.000	0.012 (5)	0.000

Geometric parameters (Å, °)

Pb1—N1 ⁱ	2.667 (7)	C2—C1	1.374 (10)
Pb1—N1	2.667 (7)	C2—H2A	0.9300
Pb1—C12 ⁱⁱ	2.862 (6)	C3—C31	1.379 (11)
Pb1—C11	2.887 (5)	C3—H3A	0.9300
Pb1—C11 ⁱⁱⁱ	2.957 (6)	C1—H1A	0.9300
Pb1—C12	2.982 (6)	C6—C7	1.548 (10)
C12—Pb1 ⁱⁱⁱ	2.862 (6)	C6—H6A	0.9700
C11—Pb1 ⁱⁱ	2.957 (6)	C6—H6B	0.9700
C5—C31	1.392 (12)	C31—H3B	0.9300
C5—C2	1.390 (12)	C7—C6 ^{iv}	1.548 (10)
C5—C6	1.494 (11)	C7—H7A	0.9700
N1—C3	1.313 (11)	C7—H7C	0.9700
N1—C1	1.354 (11)		
N1 ⁱ —Pb1—N1	166.1 (3)	C1—C2—H2A	119.8
N1 ⁱ —Pb1—C12 ⁱⁱ	92.49 (16)	C5—C2—H2A	119.8
N1—Pb1—C12 ⁱⁱ	92.49 (16)	N1—C3—C31	123.2 (8)
N1 ⁱ —Pb1—C11	96.69 (14)	N1—C3—H3A	118.4
N1—Pb1—C11	96.69 (14)	C31—C3—H3A	118.4
C12 ⁱⁱ —Pb1—C11	84.43 (17)	N1—C1—C2	122.1 (7)
N1 ⁱ —Pb1—C11 ⁱⁱⁱ	87.32 (16)	N1—C1—H1A	119.0
N1—Pb1—C11 ⁱⁱⁱ	87.32 (16)	C2—C1—H1A	119.0
C12 ⁱⁱ —Pb1—C11 ⁱⁱⁱ	178.36 (9)	C5—C6—C7	114.3 (7)
C11—Pb1—C11 ⁱⁱⁱ	97.21 (17)	C5—C6—H6A	108.7
N1 ⁱ —Pb1—C12	83.26 (14)	C7—C6—H6A	108.7
N1—Pb1—C12	83.26 (14)	C5—C6—H6B	108.7
C12 ⁱⁱ —Pb1—C12	97.21 (17)	C7—C6—H6B	108.7
C11—Pb1—C12	178.36 (11)	H6A—C6—H6B	107.6
C11 ⁱⁱⁱ —Pb1—C12	81.15 (17)	C3—C31—C5	120.1 (8)
Pb1 ⁱⁱⁱ —C12—Pb1	97.21 (17)	C3—C31—H3B	120.0
Pb1—C11—Pb1 ⁱⁱ	97.21 (17)	C5—C31—H3B	120.0
C31—C5—C2	116.2 (7)	C6—C7—C6 ^{iv}	108.3 (9)
C31—C5—C6	122.2 (8)	C6—C7—H7A	110.0
C2—C5—C6	121.5 (8)	C6 ^{iv} —C7—H7A	110.0
C3—N1—C1	117.9 (7)	C6—C7—H7C	110.0

C3—N1—Pb1	118.2 (6)	C6 ^{iv} —C7—H7C	110.0
C1—N1—Pb1	121.0 (5)	H7A—C7—H7C	108.4
C1—C2—C5	120.5 (8)		

Symmetry codes: (i) $x, -y+3/2, z$; (ii) $x-1, y, z$; (iii) $x+1, y, z$; (iv) $x, -y+1/2, z$.

Fig. 2

