

Acta Crystallographica Section E

Structure Reports

Online

ISSN 1600-5368

Poly[(μ_2 -4,4'-bipyridine- $\kappa^2N:N'$)bis-(μ_4 -cyclohexane-1,3-dicarboxylato- $\kappa^4O:O':O'':O'''$)dizinc(II)]

Mohd. Razali Rizal and Seik Weng Ng*

Department of Chemistry, University of Malaya, 50603 Kuala Lumpur, Malaysia

Correspondence e-mail: seikweng@um.edu.my


Received 31 August 2009; accepted 1 September 2009

 Key indicators: single-crystal X-ray study; $T = 100$ K; mean $\sigma(C-C) = 0.008$ Å; disorder in main residue; R factor = 0.050; wR factor = 0.123; data-to-parameter ratio = 11.8.

The cyclohexane-1,3-dicarboxylate dianion in the title three-dimensional coordination polymer, $[Zn_2(C_8H_{10}O_4)_2(C_{10}H_8N_2)]_n$, has one carboxylate group in an equatorial position and the other in an axial position of the cyclohexane ring, which adopts a chair conformation. The carboxylate groups function as bridges to two adjacent Zn^{II} atoms, generating a layer motif. Adjacent layers are linked through the 4,4'-bipyridine N -heterocycle, forming a three-dimensional network; the geometry of Zn^{II} is square-pyramidal with the N atom of the N -heterocycle occupying the apical position. The N -heterocycle lies about a center of inversion and is disordered in a 1:1 ratio with respect to the C atoms bearing H atoms.

Related literature

For the zinc cyclohexane-1,3-dicarboxylate adduct of 1,10-phenanthroline, see: Bailey *et al.* (2008).

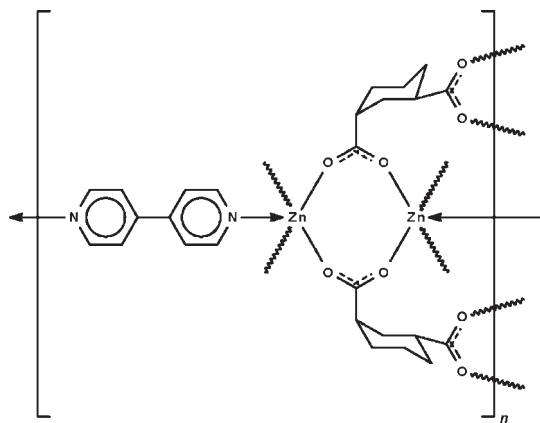

Experimental

Crystal data

 $[Zn_2(C_8H_{10}O_4)_2(C_{10}H_8N_2)]$
 $M_r = 313.64$

 Monoclinic, $C2/c$
 $a = 22.251$ (2) Å

 $b = 13.436$ (1) Å

 $c = 8.552$ (1) Å

 $\beta = 104.446$ (5)°

 $V = 2475.8$ (3) Å³
 $Z = 8$

 Mo $K\alpha$ radiation

 $\mu = 1.99$ mm⁻¹
 $T = 100$ K

 $0.12 \times 0.02 \times 0.02$ mm

Data collection

Bruker SMART APEX

diffractometer

Absorption correction: multi-scan

(SADABS; Sheldrick, 1996)

 $T_{min} = 0.557$, $T_{max} = 1.000$

8536 measured reflections

2175 independent reflections

 1407 reflections with $I > 2\sigma(I)$
 $R_{int} = 0.116$

Refinement

 $R[F^2 > 2\sigma(F^2)] = 0.050$
 $wR(F^2) = 0.123$
 $S = 0.99$

2175 reflections

184 parameters

36 restraints

H-atom parameters constrained

 $\Delta\rho_{max} = 0.77$ e Å⁻³
 $\Delta\rho_{min} = -0.65$ e Å⁻³

Data collection: *APEX2* (Bruker, 2007); cell refinement: *SAINT* (Bruker, 2007); data reduction: *SAINT* program(s) used to solve structure: *SHELXS97* (Sheldrick, 2008); program(s) used to refine structure: *SHELXL97* (Sheldrick, 2008); molecular graphics: *XSELL* (Sheldrick, 2008); software used to prepare material for publication: *pubCIF* (Westrip, 2009).

We thank the University of Malaya for supporting this study.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: TK2535).

References

- Bailey, A. J., Lee, C., Feller, R. K., Orton, J. B., Mellot-Draznieks, C., Slater, B., Harrison, W. T. A., Simonic, P., Navrotsky, A., Gossel, M. C. & Cheetham, A. K. (2008). *Angew. Chem. Int. Ed.* **47**, 8634–8637.
- Bruker (2007). *APEX2* and *SAINT*. Bruker AXS Inc., Madison, Wisconsin, USA.
- Sheldrick, G. M. (1996). *SADABS*. University of Göttingen, Germany.
- Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.
- Westrip, S. P. (2009). *pubCIF*. In preparation.

supplementary materials

Acta Cryst. (2009). E65, m1179 [doi:10.1107/S1600536809035168]

Poly[(μ_2 -4,4'-bipyridine- $\kappa^2N:N'$)bis(μ_4 -cyclohexane-1,3-dicarboxylato- $\kappa^4O:O':O'':O'''$)]dizinc(II)]

M. R. Rizal and S. W. Ng

Experimental

Zinc acetate (0.15 g, 0.76 mmol), cyclohexane-1,3-dicarboxylic acid (mixture of *cis*- and *trans*-isomers) (0.13 g, 0.76 mmol) and 4,4'-bipyridine (0.12 g, 0.76 mmol) along with water (18 ml) were heated in a 23-ml Teflon-lined stainless-steel Parr bomb. The bomb was heated at 403 K for 3 days. The bomb was cooled to room temperature at 5 K per hour. Tiny crystals were isolated from the solution.

Refinement

Hydrogen atoms were included in the refinement in the riding model approximation with C–H 0.95–1.00 Å, and with $U(H)$ $1.2U_{eq}(C)$. The 4,4'-bipyridine N-heterocycle is disordered about a center-of-inversion with respect to the carbon atoms bearing a hydrogen atom. As the disordered refined to nearly 50:50, the occupancy was fixed as 0.5. The distances of pairs of atoms were restrained to within 0.01 Å, and the pyridyl ring was restrained to near planarity. The displacement factors of the primed atoms were given those of the unprimed ones; the anisotropic behavior was restrained to be nearly isotropic.

Figures

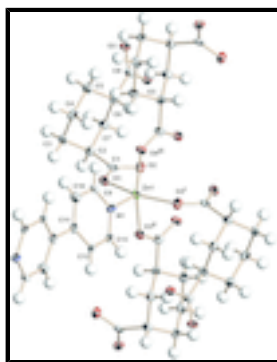


Fig. 1. 50% Probability displacement ellipsoid plot of the asymmetric unit of $Zn_2(C_{10}H_8N_2)(C_8H_{10}O_4)_2$ extended to show the coordination environment of the zinc center and a full molecule of 4,4'-bipyridine. Hydrogen atoms are drawn as spheres of arbitrary radii. Symmetry operations i: 0.5-x, 1.5-y, 1-z; ii: 0.5-x, 0.5+y, 0.5-z; iii: x, 1-y, 0.5+z.

Poly[(μ_2 -4,4'-bipyridine- $\kappa^2N:N'$)bis(μ_4 -cyclohexane- 1,3-dicarboxylato- $\kappa^4O:O':O'':O'''$)]dizinc(II)]

Crystal data

$[Zn_2(C_8H_{10}O_4)_2(C_{10}H_8N_2)]$

$M_r = 313.64$

Monoclinic, $C2/c$

Hall symbol: $-C 2yc$

$a = 22.251 (2) \text{ \AA}$

$b = 13.436 (1) \text{ \AA}$

$F_{000} = 1288$

$D_x = 1.683 \text{ Mg m}^{-3}$

Mo $K\alpha$ radiation, $\lambda = 0.71073 \text{ \AA}$

Cell parameters from 543 reflections

$\theta = 2.8\text{--}21.0^\circ$

$\mu = 1.99 \text{ mm}^{-1}$

supplementary materials

$c = 8.552 (1) \text{ \AA}$
 $\beta = 104.446 (5)^\circ$
 $V = 2475.8 (3) \text{ \AA}^3$
 $Z = 8$

$T = 100 \text{ K}$
Prism, colorless
 $0.12 \times 0.02 \times 0.02 \text{ mm}$

Data collection

Bruker SMART APEX
diffractometer
Radiation source: fine-focus sealed tube
Monochromator: graphite
 $T = 100 \text{ K}$
 ω scans
Absorption correction: Multi-scan
(SADABS; Sheldrick, 1996)
 $T_{\min} = 0.557, T_{\max} = 1.000$
8536 measured reflections

2175 independent reflections
1407 reflections with $I > 2\sigma(I)$
 $R_{\text{int}} = 0.116$
 $\theta_{\text{max}} = 25.0^\circ$
 $\theta_{\text{min}} = 1.8^\circ$
 $h = -26 \rightarrow 25$
 $k = -15 \rightarrow 15$
 $l = -10 \rightarrow 10$

Refinement

Refinement on F^2
Least-squares matrix: full
 $R[F^2 > 2\sigma(F^2)] = 0.050$
 $wR(F^2) = 0.123$
 $S = 0.99$
2175 reflections
184 parameters
36 restraints
Primary atom site location: structure-invariant direct methods

Secondary atom site location: difference Fourier map
Hydrogen site location: inferred from neighbouring sites
H-atom parameters constrained
 $w = 1/[\sigma^2(F_o^2) + (0.0478P)^2]$
where $P = (F_o^2 + 2F_c^2)/3$
 $(\Delta/\sigma)_{\text{max}} = 0.001$
 $\Delta\rho_{\text{max}} = 0.77 \text{ e \AA}^{-3}$
 $\Delta\rho_{\text{min}} = -0.65 \text{ e \AA}^{-3}$
Extinction correction: none

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	<i>x</i>	<i>y</i>	<i>z</i>	$U_{\text{iso}}^*/U_{\text{eq}}$	Occ. (<1)
Zn1	0.30423 (3)	0.80190 (5)	0.58500 (8)	0.0148 (2)	
O1	0.33841 (19)	0.7868 (3)	0.3855 (5)	0.0226 (10)	
O2	0.25270 (18)	0.7072 (3)	0.2612 (4)	0.0220 (10)	
O3	0.24532 (18)	0.4228 (3)	0.0174 (4)	0.0192 (9)	
O4	0.33149 (18)	0.3418 (3)	0.1412 (5)	0.0196 (10)	
N1	0.3745 (2)	0.8727 (3)	0.7432 (5)	0.0157 (11)	
C1	0.3081 (3)	0.7349 (4)	0.2723 (7)	0.0182 (14)	
C2	0.3373 (3)	0.7034 (4)	0.1370 (7)	0.0190 (13)	
H2	0.3281	0.7563	0.0521	0.023*	
C3	0.4082 (3)	0.6950 (4)	0.1978 (7)	0.0207 (13)	
H3A	0.4265	0.6834	0.1052	0.025*	
H3B	0.4252	0.7581	0.2503	0.025*	

C4	0.4259 (3)	0.6096 (4)	0.3182 (7)	0.0218 (14)	
H4A	0.4716	0.6040	0.3530	0.026*	
H4B	0.4104	0.6239	0.4148	0.026*	
C5	0.3985 (3)	0.5113 (4)	0.2433 (7)	0.0232 (15)	
H5A	0.4182	0.4929	0.1556	0.028*	
H5B	0.4080	0.4584	0.3263	0.028*	
C6	0.3287 (3)	0.5179 (4)	0.1755 (7)	0.0183 (14)	
H6	0.3108	0.5325	0.2693	0.022*	
C7	0.3106 (3)	0.6056 (4)	0.0586 (7)	0.0194 (14)	
H7A	0.3261	0.5935	-0.0386	0.023*	
H7B	0.2648	0.6107	0.0240	0.023*	
C8	0.3000 (3)	0.4193 (4)	0.1038 (7)	0.0180 (14)	
C9	0.4299 (6)	0.8277 (15)	0.8020 (17)	0.015 (3)	0.50
H9	0.4346	0.7607	0.7715	0.019*	0.50
C10	0.4800 (11)	0.8744 (6)	0.9043 (19)	0.022 (3)	0.50
H10	0.5181	0.8400	0.9432	0.027*	0.50
C9'	0.4219 (6)	0.8212 (16)	0.8385 (15)	0.015 (3)	0.50
H9'	0.4213	0.7506	0.8346	0.019*	0.50
C10'	0.4713 (10)	0.8691 (6)	0.942 (2)	0.022 (3)	0.50
H10'	0.5040	0.8311	1.0076	0.027*	0.50
C11	0.4734 (2)	0.9726 (4)	0.9490 (6)	0.0155 (13)	
C12	0.4164 (6)	1.0188 (15)	0.8894 (17)	0.016 (3)	0.50
H12	0.4102	1.0856	0.9184	0.019*	0.50
C13	0.3687 (11)	0.9669 (6)	0.7878 (19)	0.014 (2)	0.50
H13	0.3301	0.9996	0.7477	0.017*	0.50
C12'	0.4238 (6)	1.0236 (16)	0.8504 (16)	0.016 (3)	0.50
H12'	0.4230	1.0943	0.8524	0.019*	0.50
C13'	0.3758 (10)	0.9721 (6)	0.750 (2)	0.014 (2)	0.50
H13'	0.3425	1.0085	0.6828	0.017*	0.50

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Zn1	0.0119 (4)	0.0150 (4)	0.0150 (3)	-0.0020 (3)	-0.0011 (2)	-0.0008 (3)
O1	0.027 (2)	0.021 (2)	0.021 (2)	-0.0065 (19)	0.0087 (19)	-0.0056 (18)
O2	0.019 (2)	0.030 (3)	0.017 (2)	-0.002 (2)	0.0051 (18)	-0.0029 (18)
O3	0.011 (2)	0.018 (2)	0.023 (2)	0.0018 (18)	-0.0065 (19)	0.0021 (18)
O4	0.021 (3)	0.013 (2)	0.021 (2)	0.0026 (18)	-0.0026 (19)	-0.0014 (17)
N1	0.016 (3)	0.018 (3)	0.013 (2)	0.001 (2)	0.003 (2)	-0.003 (2)
C1	0.024 (4)	0.008 (3)	0.022 (3)	0.000 (2)	0.005 (3)	0.002 (2)
C2	0.023 (3)	0.017 (3)	0.016 (3)	0.000 (3)	0.004 (3)	-0.002 (3)
C3	0.017 (3)	0.020 (3)	0.025 (3)	-0.004 (3)	0.006 (3)	-0.005 (3)
C4	0.017 (4)	0.027 (4)	0.020 (3)	0.003 (3)	0.004 (3)	-0.005 (3)
C5	0.020 (4)	0.021 (3)	0.027 (4)	0.000 (3)	0.003 (3)	0.000 (3)
C6	0.015 (4)	0.017 (3)	0.021 (3)	-0.002 (3)	0.000 (3)	0.002 (3)
C7	0.024 (4)	0.019 (3)	0.014 (3)	-0.001 (3)	0.003 (3)	-0.003 (2)
C8	0.026 (4)	0.015 (3)	0.013 (3)	-0.001 (3)	0.005 (3)	0.001 (3)
C9	0.025 (5)	0.013 (4)	0.011 (6)	-0.001 (4)	0.008 (4)	0.005 (4)

supplementary materials

C10	0.018 (6)	0.022 (4)	0.022 (7)	0.000 (3)	-0.004 (4)	0.007 (3)
C9'	0.025 (5)	0.013 (4)	0.011 (6)	-0.001 (4)	0.008 (4)	0.005 (4)
C10'	0.018 (6)	0.022 (4)	0.022 (7)	0.000 (3)	-0.004 (4)	0.007 (3)
C11	0.010 (3)	0.021 (3)	0.013 (3)	-0.002 (3)	-0.001 (3)	-0.001 (2)
C12	0.015 (4)	0.017 (3)	0.017 (6)	-0.002 (3)	0.009 (4)	-0.006 (4)
C13	0.008 (5)	0.018 (3)	0.015 (7)	0.001 (3)	0.000 (4)	-0.002 (3)
C12'	0.015 (4)	0.017 (3)	0.017 (6)	-0.002 (3)	0.009 (4)	-0.006 (4)
C13'	0.008 (5)	0.018 (3)	0.015 (7)	0.001 (3)	0.000 (4)	-0.002 (3)

Geometric parameters (\AA , $^\circ$)

Zn1—O1	2.044 (4)	C4—H4B	0.9900
Zn1—O2 ⁱ	2.045 (4)	C5—C6	1.519 (8)
Zn1—O3 ⁱⁱ	2.034 (4)	C5—H5A	0.9900
Zn1—O4 ⁱⁱⁱ	2.044 (4)	C5—H5B	0.9900
Zn1—N1	2.031 (5)	C6—C8	1.532 (8)
Zn1—Zn1 ⁱ	2.8517 (13)	C6—C7	1.533 (7)
O1—C1	1.246 (7)	C6—H6	1.0000
O2—C1	1.267 (7)	C7—H7A	0.9900
O2—Zn1 ⁱ	2.045 (4)	C7—H7B	0.9900
O3—C8	1.257 (7)	C9—C10	1.384 (10)
O3—Zn1 ^{iv}	2.034 (4)	C9—H9	0.9500
O4—C8	1.252 (7)	C10—C11	1.392 (10)
O4—Zn1 ^v	2.044 (4)	C10—H10	0.9500
N1—C13'	1.338 (9)	C9'—C10'	1.385 (10)
N1—C13	1.338 (9)	C9'—H9'	0.9500
N1—C9'	1.351 (9)	C10'—C11	1.393 (10)
N1—C9	1.351 (9)	C10'—H10'	0.9500
C1—C2	1.522 (8)	C11—C12'	1.390 (10)
C2—C7	1.526 (7)	C11—C12	1.391 (10)
C2—C3	1.537 (8)	C11—C11 ^{vi}	1.478 (11)
C2—H2	1.0000	C12—C13	1.380 (10)
C3—C4	1.526 (8)	C12—H12	0.9500
C3—H3A	0.9900	C13—H13	0.9500
C3—H3B	0.9900	C12'—C13'	1.380 (10)
C4—C5	1.526 (8)	C12'—H12'	0.9500
C4—H4A	0.9900	C13'—H13'	0.9500
N1—Zn1—O3 ⁱⁱ	99.06 (17)	C6—C5—H5B	109.2
N1—Zn1—O2 ⁱ	95.55 (16)	C4—C5—H5B	109.2
O3 ⁱⁱ —Zn1—O2 ⁱ	88.19 (16)	H5A—C5—H5B	107.9
N1—Zn1—O1	102.59 (16)	C5—C6—C8	112.8 (5)
O3 ⁱⁱ —Zn1—O1	89.70 (15)	C5—C6—C7	111.8 (5)
O2 ⁱ —Zn1—O1	161.85 (15)	C8—C6—C7	112.9 (5)
N1—Zn1—O4 ⁱⁱⁱ	98.71 (17)	C5—C6—H6	106.3
O3 ⁱⁱ —Zn1—O4 ⁱⁱⁱ	162.21 (15)	C8—C6—H6	106.3
O2 ⁱ —Zn1—O4 ⁱⁱⁱ	89.29 (16)	C7—C6—H6	106.3

O1—Zn1—O4 ⁱⁱⁱ	87.23 (15)	C2—C7—C6	111.4 (5)
N1—Zn1—Zn1 ⁱ	169.00 (12)	C2—C7—H7A	109.3
O3 ⁱⁱ —Zn1—Zn1 ⁱ	82.66 (11)	C6—C7—H7A	109.3
O2 ⁱ —Zn1—Zn1 ⁱ	73.59 (11)	C2—C7—H7B	109.3
O1—Zn1—Zn1 ⁱ	88.25 (12)	C6—C7—H7B	109.3
O4 ⁱⁱⁱ —Zn1—Zn1 ⁱ	79.73 (11)	H7A—C7—H7B	108.0
C1—O1—Zn1	117.5 (4)	O4—C8—O3	125.4 (5)
C1—O2—Zn1 ⁱ	135.7 (4)	O4—C8—C6	117.8 (5)
C8—O3—Zn1 ^{iv}	124.3 (4)	O3—C8—C6	116.7 (5)
C8—O4—Zn1 ^v	127.7 (4)	N1—C9—C10	123 (2)
C13 ['] —N1—C9 [']	118.7 (15)	N1—C9—H9	118.4
C13—N1—C9 [']	115.4 (14)	C10—C9—H9	118.4
C13 ['] —N1—C9	115.0 (15)	C9—C10—C11	119 (2)
C13—N1—C9	117.4 (15)	C9—C10—H10	120.6
C13 ['] —N1—Zn1	120.0 (11)	C11—C10—H10	120.6
C13—N1—Zn1	121.4 (11)	N1—C9 ['] —C10 [']	122 (2)
C9 ['] —N1—Zn1	121.2 (11)	N1—C9 ['] —H9 [']	119.2
C9—N1—Zn1	121.2 (11)	C10 ['] —C9 ['] —H9 [']	119.2
O1—C1—O2	123.4 (5)	C9 ['] —C10 ['] —C11	120 (2)
O1—C1—C2	119.6 (5)	C9 ['] —C10 ['] —H10 [']	119.8
O2—C1—C2	116.9 (5)	C11—C10 ['] —H10 [']	119.8
C7—C2—C1	112.3 (5)	C12 ['] —C11—C10	115.0 (14)
C7—C2—C3	109.8 (5)	C12—C11—C10	118.1 (14)
C1—C2—C3	111.1 (5)	C12 ['] —C11—C10 [']	116.8 (14)
C7—C2—H2	107.8	C12—C11—C10 [']	114.3 (14)
C1—C2—H2	107.8	C12 ['] —C11—C11 ^{vi}	120.7 (12)
C3—C2—H2	107.8	C12—C11—C11 ^{vi}	121.1 (12)
C4—C3—C2	110.7 (5)	C10—C11—C11 ^{vi}	120.7 (12)
C4—C3—H3A	109.5	C10 ['] —C11—C11 ^{vi}	122.5 (11)
C2—C3—H3A	109.5	C13—C12—C11	120 (2)
C4—C3—H3B	109.5	C13—C12—H12	120.2
C2—C3—H3B	109.5	C11—C12—H12	120.2
H3A—C3—H3B	108.1	N1—C13—C12	123 (2)
C5—C4—C3	111.0 (5)	N1—C13—H13	118.5
C5—C4—H4A	109.4	C12—C13—H13	118.5
C3—C4—H4A	109.4	C13 ['] —C12 ['] —C11	120 (2)
C5—C4—H4B	109.4	C13 ['] —C12 ['] —H12 [']	119.8
C3—C4—H4B	109.4	C11—C12 ['] —H12 [']	119.8
H4A—C4—H4B	108.0	N1—C13 ['] —C12 [']	122 (2)
C6—C5—C4	111.9 (5)	N1—C13 ['] —H13 [']	118.9
C6—C5—H5A	109.2	C12 ['] —C13 ['] —H13 [']	118.9
C4—C5—H5A	109.2		
N1—Zn1—O1—C1	171.8 (4)	C3—C2—C7—C6	56.6 (6)
O3 ⁱⁱ —Zn1—O1—C1	-89.0 (4)	C5—C6—C7—C2	-54.5 (6)
O2 ⁱ —Zn1—O1—C1	-5.7 (7)	C8—C6—C7—C2	177.0 (5)

supplementary materials

O4 ⁱⁱⁱ —Zn1—O1—C1	73.5 (4)	Zn1 ^v —O4—C8—O3	-3.1 (8)
Zn1 ⁱ —Zn1—O1—C1	-6.3 (4)	Zn1 ^v —O4—C8—C6	173.7 (3)
O3 ⁱⁱ —Zn1—N1—C13'	-0.6 (6)	Zn1 ^{iv} —O3—C8—O4	-0.9 (8)
O2 ⁱ —Zn1—N1—C13'	-89.7 (6)	Zn1 ^{iv} —O3—C8—C6	-177.8 (3)
O1—Zn1—N1—C13'	91.1 (6)	C5—C6—C8—O4	16.7 (7)
O4 ⁱⁱⁱ —Zn1—N1—C13'	-179.8 (6)	C7—C6—C8—O4	144.6 (5)
Zn1 ⁱ —Zn1—N1—C13'	-98.8 (9)	C5—C6—C8—O3	-166.2 (5)
O3 ⁱⁱ —Zn1—N1—C13	19.4 (6)	C7—C6—C8—O3	-38.3 (7)
O2 ⁱ —Zn1—N1—C13	-69.6 (6)	C13' ⁱ —N1—C9—C10	19.0 (10)
O1—Zn1—N1—C13	111.2 (6)	C13—N1—C9—C10	-0.1 (3)
O4 ⁱⁱⁱ —Zn1—N1—C13	-159.8 (6)	Zn1—N1—C9—C10	177.0 (3)
Zn1 ⁱ —Zn1—N1—C13	-78.8 (10)	N1—C9—C10—C11	-0.2 (3)
O3 ⁱⁱ —Zn1—N1—C9'	-177.8 (6)	C13' ⁱ —N1—C9'—C10'	-0.1 (3)
O2 ⁱ —Zn1—N1—C9'	93.2 (6)	Zn1—N1—C9'—C10'	177.1 (3)
O1—Zn1—N1—C9'	-86.0 (6)	N1—C9'—C10'—C11	-0.3 (3)
O4 ⁱⁱⁱ —Zn1—N1—C9'	3.0 (6)	C9—C10—C11—C12'	-18.2 (11)
Zn1 ⁱ —Zn1—N1—C9'	84.0 (9)	C9—C10—C11—C12	0.6 (6)
O3 ⁱⁱ —Zn1—N1—C9	-157.6 (6)	C9—C10—C11—C10'	82 (6)
O2 ⁱ —Zn1—N1—C9	113.4 (6)	C9—C10—C11—C11 ^{vi}	-176.8 (5)
O1—Zn1—N1—C9	-65.9 (6)	C9'—C10'—C11—C12'	0.7 (6)
O4 ⁱⁱⁱ —Zn1—N1—C9	23.2 (6)	C9'—C10'—C11—C12	19.4 (10)
Zn1 ⁱ —Zn1—N1—C9	104.2 (9)	C9'—C10'—C11—C10	-87 (6)
Zn1—O1—C1—O2	13.7 (8)	C9'—C10'—C11—C11 ^{vi}	-177.0 (6)
Zn1—O1—C1—C2	-167.4 (4)	C10—C11—C12—C13	-0.6 (8)
Zn1 ⁱ —O2—C1—O1	-16.9 (9)	C10'—C11—C12—C13	-19.4 (12)
Zn1 ⁱ —O2—C1—C2	164.2 (4)	C11 ^{vi} —C11—C12—C13	176.7 (7)
O1—C1—C2—C7	152.2 (5)	C13' ⁱ —N1—C13—C12	-86 (7)
O2—C1—C2—C7	-28.9 (7)	C9'—N1—C13—C12	19.2 (12)
O1—C1—C2—C3	28.7 (7)	C9—N1—C13—C12	0.1 (7)
O2—C1—C2—C3	-152.3 (5)	Zn1—N1—C13—C12	-177.0 (5)
C7—C2—C3—C4	-58.1 (6)	C11—C12—C13—N1	0.3 (9)
C1—C2—C3—C4	66.7 (6)	C10'—C11—C12'—C13'	-0.8 (8)
C2—C3—C4—C5	57.2 (6)	C11 ^{vi} —C11—C12'—C13'	176.9 (6)
C3—C4—C5—C6	-54.6 (7)	C9'—N1—C13'—C12'	0.0 (7)
C4—C5—C6—C8	-178.4 (5)	Zn1—N1—C13'—C12'	-177.3 (5)
C4—C5—C6—C7	53.2 (6)	C11—C12'—C13'—N1	0.5 (9)
C1—C2—C7—C6	-67.6 (6)		

Symmetry codes: (i) $-x+1/2, -y+3/2, -z+1$; (ii) $-x+1/2, y+1/2, -z+1/2$; (iii) $x, -y+1, z+1/2$; (iv) $-x+1/2, y-1/2, -z+1/2$; (v) $x, -y+1, z-1/2$; (vi) $-x+1, -y+2, -z+2$.

Fig. 1

