

Acta Crystallographica Section E

Structure Reports

Online

ISSN 1600-5368

Poly[[aqua(μ -4,4'-bipyridine- κ^2 N:N')-(μ_3 -2-nitro-5-sulfonatobenzoato- κ^3 O¹:O^{1'}:O⁵)copper(II)] 4,4'-bipyridine hemisolvate]

Zheyu Zhang

Department of Chemistry, Baicheng Normal College, Baicheng 137000, People's Republic of China

Correspondence e-mail: chemzyzhang@yahoo.cn


Received 14 September 2009; accepted 28 September 2009

Key indicators: single-crystal X-ray study; $T = 293$ K; mean $\sigma(\text{C}-\text{C}) = 0.007$ Å; R factor = 0.065; wR factor = 0.135; data-to-parameter ratio = 12.9.

In the title compound, $[\text{Cu}(\text{C}_7\text{H}_3\text{NO}_7\text{S})(\text{C}_{10}\text{H}_8\text{N}_2)(\text{H}_2\text{O})] \cdot 0.5\text{C}_{10}\text{H}_8\text{N}_2$, the Cu^{II} atom is six-coordinated by two N atoms from two different bipyridine (bipy) ligands, one sulfonate O atom and two carboxylate O atoms from three 2-nitro-5-sulfonatobenzoate ligands and one water O atom in a distorted octahedral geometry. The bipy solvent molecule lies on an inversion center. The Cu^{II} atoms are linked by the bipy ligands, forming one-dimensional chains, which are connected by the 2-nitro-5-sulfonatobenzoate ligands into a two-dimensional layer-like network. The two-dimensional structure is extended by $\text{O}-\text{H}\cdots\text{O}$ and $\text{O}-\text{H}\cdots\text{N}$ hydrogen bonds into a three-dimensional supramolecular network.

Related literature

For general background to copper(II) sulfonate complexes, see: Du *et al.* (2009); Li *et al.* (2009); Liu *et al.* (2009); Sonnauer & Stock (2008); Sonnauer *et al.* (2009). For related structures, see: Dong *et al.* (2009).

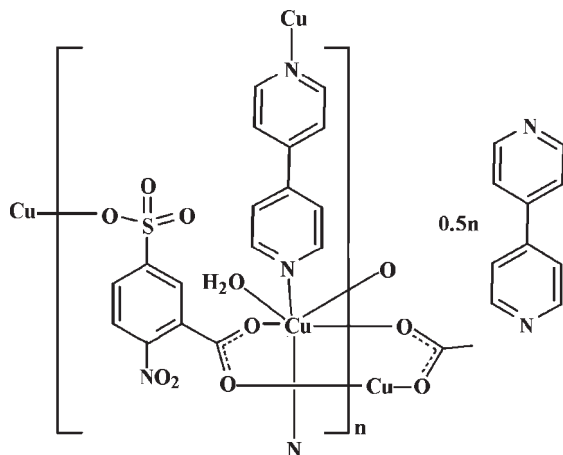

Experimental

Crystal data

$[\text{Cu}(\text{C}_7\text{H}_3\text{NO}_7\text{S})(\text{C}_{10}\text{H}_8\text{N}_2)(\text{H}_2\text{O})] \cdot 0.5\text{C}_{10}\text{H}_8\text{N}_2$
 $M_r = 561.00$
 Monoclinic, $P2_1/c$
 $a = 11.4549$ (17) Å
 $b = 11.0447$ (16) Å
 $c = 17.089$ (3) Å
 $\beta = 92.738$ (3)°
 $V = 2159.5$ (5) Å³
 $Z = 4$
 Mo $K\alpha$ radiation
 $\mu = 1.17$ mm⁻¹
 $T = 293$ K
 $0.23 \times 0.17 \times 0.14$ mm

Data collection

Bruker SMART APEX CCD diffractometer
 Absorption correction: multi-scan (SADABS; Bruker, 2001)
 $T_{\text{min}} = 0.767$, $T_{\text{max}} = 0.850$
 11892 measured reflections
 4260 independent reflections
 2560 reflections with $I > 2\sigma(I)$
 $R_{\text{int}} = 0.088$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.065$
 $wR(F^2) = 0.135$
 $S = 1.00$
 4260 reflections
 331 parameters
 H atoms treated by a mixture of independent and constrained refinement
 $\Delta\rho_{\text{max}} = 0.86$ e Å⁻³
 $\Delta\rho_{\text{min}} = -0.46$ e Å⁻³

Table 1

Selected bond lengths (Å).

Cu1—N2	1.986 (4)	Cu1—O4	1.969 (3)
Cu1—N3 ⁱ	2.004 (4)	Cu1—O5 ⁱⁱⁱ	2.299 (4)
Cu1—O2 ⁱⁱ	2.565 (4)	Cu1—O6	2.032 (4)

Symmetry codes: (i) $x, y + 1, z$; (ii) $-x + 1, y - \frac{1}{2}, -z + \frac{3}{2}$; (iii) $-x + 1, -y + 1, -z + 1$.

Table 2

Hydrogen-bond geometry (Å, °).

$D-\text{H}\cdots A$	$D-\text{H}$	$\text{H}\cdots A$	$D\cdots A$	$D-\text{H}\cdots A$
$\text{O6}-\text{H1A}\cdots\text{O1}^{\text{ii}}$	0.83 (5)	1.94 (5)	2.758 (5)	171 (6)
$\text{O6}-\text{H1B}\cdots\text{N4}^{\text{iv}}$	0.86 (5)	2.00 (5)	2.801 (6)	156 (5)

Symmetry codes: (ii) $-x + 1, y - \frac{1}{2}, -z + \frac{3}{2}$; (iv) $-x + 1, y + \frac{1}{2}, -z + \frac{3}{2}$.

Data collection: SMART (Bruker, 2007); cell refinement: SAINT (Bruker, 2007); data reduction: SAINT; program(s) used to solve structure: SHELXS97 (Sheldrick, 2008); program(s) used to refine structure: SHELXL97 (Sheldrick, 2008); molecular graphics: SHELXTL (Sheldrick, 2008) and DIAMOND (Brandenburg, 1999); software used to prepare material for publication: SHELXTL.

Baicheng Normal College is thanked for supporting this work.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: HY2230).

References

- Brandenburg, K. (1999). DIAMOND. Crystal Impact GbR, Bonn, Germany.
 Bruker (2001). SADABS. Bruker AXS Inc., Madison, Wisconsin, USA.
 Bruker (2007). SMART and SAINT. Bruker AXS Inc., Madison, Wisconsin, USA.
 Dong, H., Bi, W. & Zhu, H. (2009). Asian J. Chem. **21**, 5598–5602.
 Du, Z., Huang, J., Xie, Y. & Wen, H. (2009). J. Mol. Struct. **919**, 112–116.

Li, L., Xu, G. & Zhu, H.-B. (2009). *Acta Cryst.* **E65**, m476.

Liu, Y., Bi, Y., He, W., Wang, X., Liao, W. & Zhang, H. (2009). *J. Mol. Struct.* **919**, 235–238.

Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.

Sonnauer, A., Feyand, M. & Stock, N. (2009). *Cryst. Growth Des.* **9**, 586–592.

Sonnauer, A. & Stock, N. (2008). *Eur. J. Inorg. Chem.* pp. 5038–5045.

supplementary materials

Acta Cryst. (2009). E65, m1272-m1273 [doi:10.1107/S1600536809039294]

**Poly[[aqua(μ -4,4'-bipyridine- κ^2 N:N')(μ_3 -2-nitro-5-sulfonatobenzoato- κ^3 O¹:O^{1'}:O⁵)copper(II)]
4,4'-bipyridine hemisolvate]**

Z. Zhang

Comment

In recent years, the design and synthesis of copper(II) sulfonates have attracted great attention because of their flexible coordination modes, interesting inorganic-organic lamellar structures, selective and reversible guest inclusion properties, and their ability to intercalate guest molecules (Du *et al.*, 2009; Sonnauer *et al.*, 2009). It is noteworthy that some copper(II) sulfonate complexes with nitrogen-based secondary ligands, exhibiting different bonding modes dependent on the presence of secondary ligands, have been reported (Liu *et al.*, 2009; Sonnauer & Stock, 2008). It has also been demonstrated that the existence and changes of the secondary ligands can have a great effect on the structures of copper(II) sulfonates, often with surprising results (Li *et al.*, 2009). In this paper, we utilized 2-nitro-5-sulfobenzoic acid (H₂nsb) as an organic sulfonate ligand and 4,4'-bipyridine (bipy) as an N-donor ligand, providing a coordination compound, [Cu(nsb)(bipy)(H₂O)].0.5bipy, which is reported here.

In the title compound, the central Cu^{II} ion is six-coordinated by two N atoms from two different bipy ligands, one sulfonate O atom, two carboxylate O atoms from three nsb ligand and one water molecule in a distorted octahedral coordination geometry (Table 1). There are free bipy molecules in the structure, stabilized by hydrogen bonds (Fig. 1). The Cu—O distances are comparable to those found in other crystallographically characterized Cu^{II} complexes (Dong *et al.*, 2009). The Cu atoms are linked by the bipy ligands, forming an extended one-dimensional chain. These chains are further connected by the nsb ligands into a two-dimensional layer-like network. In addition, the existence of O—H \cdots O and O—H \cdots N hydrogen bonds (Table 2) extends the two-dimensional layer into a three-dimensional supramolecular architecture (Fig. 2).

Experimental

A mixture of Cu(CH₃CO₂)₂·2H₂O (0.040 g, 0.2 mmol), 2-nitro-5-sulfobenzoic acid (0.049 g, 0.2 mmol), 4,4'-bipyridine (0.039 g, 0.2 mmol), and H₂O (15 ml) was sealed in a 25 ml Teflon-lined stainless steel reactor, which was heated at 443 K for 72 h and then it was cooled to room temperature. Blue crystals of the title compound were collected.

Refinement

H atoms on C atoms were positioned geometrically and refined as riding atoms, with C—H = 0.93 Å and $U_{\text{iso}}(\text{H}) = 1.2U_{\text{eq}}(\text{C})$. The H atoms of the water molecule were located in a difference Fourier map and refined with a distance restraint of O—H = 0.85 (1) Å and with $U_{\text{iso}}(\text{H}) = 1.5U_{\text{eq}}(\text{O})$.

Figures

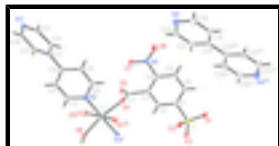


Fig. 1. The asymmetric unit of the title compound. Displacement ellipsoids are drawn at the 30% probability level. [Symmetry codes: (i) $x, 1+y, z$; (ii) $1-x, -0.5+y, 1.5-z$; (iii) $1-x, 1-y, 1-z$; (iv) $-x, 1-y, 2-z$.]

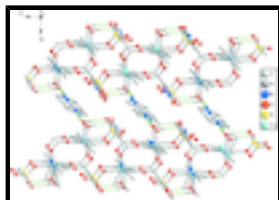


Fig. 2. View of the three-dimensional supramolecular network in the title compound. Dashed lines denote hydrogen bonds.

Poly[[aqua(μ -4,4'-bipyridine- $\kappa^2N:N'$)(μ_3 -2-nitro-5-sulfonatobenzoato- $\kappa^3O^1:O^1':O^5$)copper(II)] 4,4'-bipyridine hemisolvate]

Crystal data

$[\text{Cu}(\text{C}_7\text{H}_3\text{NO}_7\text{S})(\text{C}_{10}\text{H}_8\text{N}_2)(\text{H}_2\text{O})] \cdot 0.5\text{C}_{10}\text{H}_8\text{N}_2$

$M_r = 561.00$

Monoclinic, $P2_1/c$

Hall symbol: $-P\ 2ybc$

$a = 11.4549\ (17)\ \text{\AA}$

$b = 11.0447\ (16)\ \text{\AA}$

$c = 17.089\ (3)\ \text{\AA}$

$\beta = 92.738\ (3)^\circ$

$V = 2159.5\ (5)\ \text{\AA}^3$

$Z = 4$

$F_{000} = 1144$

$D_x = 1.725\ \text{Mg m}^{-3}$

Mo $K\alpha$ radiation, $\lambda = 0.71073\ \text{\AA}$

Cell parameters from 4260 reflections

$\theta = 1.8\text{--}26.0^\circ$

$\mu = 1.17\ \text{mm}^{-1}$

$T = 293\ \text{K}$

Block, blue

$0.23 \times 0.17 \times 0.14\ \text{mm}$

Data collection

Bruker SMART APEX CCD
diffractometer

Radiation source: fine-focus sealed tube

Monochromator: graphite

$T = 293\ \text{K}$

φ and ω scans

Absorption correction: multi-scan
(SADABS; Bruker, 2001)

$T_{\min} = 0.767$, $T_{\max} = 0.850$

11892 measured reflections

4260 independent reflections

2560 reflections with $I > 2\sigma(I)$

$R_{\text{int}} = 0.088$

$\theta_{\text{max}} = 26.0^\circ$

$\theta_{\text{min}} = 1.8^\circ$

$h = -14 \rightarrow 14$

$k = -13 \rightarrow 13$

$l = -21 \rightarrow 10$

Refinement

Refinement on F^2

Least-squares matrix: full

Secondary atom site location: difference Fourier map

Hydrogen site location: inferred from neighbouring sites

$$R[F^2 > 2\sigma(F^2)] = 0.065$$

$$wR(F^2) = 0.135$$

$$S = 1.00$$

4260 reflections

331 parameters

Primary atom site location: structure-invariant direct methods

H atoms treated by a mixture of independent and constrained refinement

$$w = 1/[\sigma^2(F_o^2) + (0.0455P)^2]$$

$$\text{where } P = (F_o^2 + 2F_c^2)/3$$

$$(\Delta/\sigma)_{\max} = 0.001$$

$$\Delta\rho_{\max} = 0.86 \text{ e } \text{Å}^{-3}$$

$$\Delta\rho_{\min} = -0.46 \text{ e } \text{Å}^{-3}$$

Extinction correction: none

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (Å^2)

	x	y	z	$U_{\text{iso}}^*/U_{\text{eq}}$
C1	0.2223 (4)	0.7923 (4)	0.6944 (3)	0.0215 (13)
C2	0.2994 (4)	0.7254 (4)	0.6511 (3)	0.0198 (12)
H2	0.3565	0.7656	0.6243	0.024*
C3	0.2929 (4)	0.5989 (5)	0.6472 (3)	0.0195 (12)
C4	0.2051 (5)	0.5449 (4)	0.6866 (3)	0.0224 (13)
C5	0.1244 (5)	0.6090 (5)	0.7293 (4)	0.0321 (15)
H5	0.0649	0.5692	0.7542	0.039*
C6	0.1356 (5)	0.7338 (5)	0.7335 (4)	0.0313 (15)
H6	0.0846	0.7786	0.7627	0.038*
C7	0.3842 (5)	0.5338 (4)	0.6006 (3)	0.0177 (12)
C8	0.5609 (4)	0.2511 (4)	0.6504 (3)	0.0229 (13)
H8	0.5129	0.2936	0.6831	0.027*
C9	0.5560 (4)	0.1262 (4)	0.6501 (3)	0.0237 (13)
H9	0.5067	0.0860	0.6831	0.028*
C10	0.6248 (5)	0.0607 (4)	0.6005 (3)	0.0183 (13)
C11	0.6982 (4)	0.1266 (4)	0.5532 (3)	0.0205 (13)
H11	0.7454	0.0869	0.5186	0.025*
C12	0.6997 (4)	0.2501 (4)	0.5582 (3)	0.0208 (13)
H12	0.7504	0.2924	0.5273	0.025*
C13	0.6233 (4)	-0.0732 (4)	0.5994 (3)	0.0191 (13)
C14	0.6096 (4)	-0.1390 (4)	0.6673 (3)	0.0207 (13)
H14	0.5960	-0.0992	0.7140	0.025*
C15	0.6162 (5)	-0.2632 (4)	0.6656 (3)	0.0241 (13)
H15	0.6098	-0.3057	0.7122	0.029*
C16	0.6431 (5)	-0.2628 (4)	0.5338 (3)	0.0248 (13)
H16	0.6541	-0.3054	0.4878	0.030*
C17	0.6397 (5)	-0.1375 (4)	0.5304 (3)	0.0236 (13)
H17	0.6482	-0.0971	0.4833	0.028*
C18	0.0395 (6)	0.2255 (6)	1.0226 (4)	0.052 (2)
H18	0.0316	0.1641	1.0593	0.063*
C19	0.0134 (6)	0.3431 (6)	1.0445 (4)	0.0483 (19)
H19	-0.0057	0.3597	1.0957	0.058*
C20	0.0160 (5)	0.4360 (5)	0.9900 (4)	0.0353 (16)
C21	0.0488 (5)	0.4042 (6)	0.9165 (4)	0.0408 (17)
H21	0.0509	0.4629	0.8776	0.049*

supplementary materials

C22	0.0790 (5)	0.2855 (6)	0.8995 (4)	0.0421 (17)
H22	0.1028	0.2677	0.8495	0.051*
N1	0.1916 (4)	0.4121 (4)	0.6833 (3)	0.0327 (13)
N2	0.6323 (4)	0.3136 (3)	0.6052 (3)	0.0212 (11)
N3	0.6313 (4)	-0.3253 (4)	0.5997 (3)	0.0194 (10)
N4	0.0754 (4)	0.1954 (5)	0.9520 (3)	0.0406 (14)
O1	0.1331 (3)	0.9957 (3)	0.7351 (2)	0.0321 (9)
O2	0.3416 (3)	0.9755 (3)	0.7461 (2)	0.0283 (10)
O3	0.2451 (4)	0.9910 (3)	0.6178 (2)	0.0373 (10)
O4	0.4740 (3)	0.5046 (3)	0.6409 (2)	0.0223 (8)
O5	0.3643 (3)	0.5231 (3)	0.5297 (2)	0.0277 (9)
O6	0.8116 (3)	0.4917 (4)	0.6061 (2)	0.0259 (9)
O7	0.2618 (3)	0.3519 (3)	0.6486 (3)	0.0376 (11)
O8	0.1112 (4)	0.3662 (4)	0.7165 (3)	0.0676 (17)
S1	0.23675 (13)	0.95326 (12)	0.69752 (9)	0.0243 (4)
Cu1	0.63413 (5)	0.49342 (5)	0.60435 (4)	0.0195 (2)
H1A	0.833 (5)	0.486 (5)	0.653 (3)	0.029*
H1B	0.843 (5)	0.543 (5)	0.576 (3)	0.029*

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
C1	0.025 (3)	0.019 (3)	0.021 (3)	0.002 (2)	-0.001 (3)	-0.003 (3)
C2	0.024 (3)	0.018 (3)	0.019 (3)	-0.002 (2)	0.004 (2)	0.001 (2)
C3	0.020 (3)	0.018 (3)	0.021 (3)	0.003 (2)	0.001 (3)	-0.002 (3)
C4	0.027 (3)	0.013 (3)	0.027 (4)	0.001 (2)	0.005 (3)	0.005 (2)
C5	0.027 (3)	0.029 (3)	0.042 (4)	-0.001 (3)	0.018 (3)	0.007 (3)
C6	0.032 (3)	0.026 (3)	0.037 (4)	0.009 (3)	0.013 (3)	0.001 (3)
C7	0.030 (3)	0.007 (3)	0.016 (3)	-0.005 (2)	0.006 (3)	0.001 (2)
C8	0.029 (3)	0.015 (3)	0.027 (3)	0.000 (2)	0.014 (3)	0.001 (3)
C9	0.030 (3)	0.014 (3)	0.028 (4)	-0.004 (2)	0.007 (3)	0.002 (3)
C10	0.029 (3)	0.005 (2)	0.020 (3)	0.002 (2)	-0.007 (3)	0.001 (2)
C11	0.028 (3)	0.011 (3)	0.024 (3)	-0.001 (2)	0.010 (3)	-0.004 (2)
C12	0.026 (3)	0.011 (3)	0.027 (3)	-0.001 (2)	0.007 (3)	0.004 (2)
C13	0.024 (3)	0.009 (3)	0.025 (4)	0.000 (2)	0.005 (3)	-0.002 (3)
C14	0.030 (3)	0.013 (3)	0.021 (3)	0.002 (2)	0.010 (3)	0.000 (2)
C15	0.032 (3)	0.016 (3)	0.025 (4)	-0.001 (2)	0.008 (3)	0.005 (3)
C16	0.040 (3)	0.014 (3)	0.022 (3)	0.003 (3)	0.011 (3)	-0.006 (3)
C17	0.035 (3)	0.015 (3)	0.021 (3)	-0.001 (3)	0.006 (3)	0.006 (3)
C18	0.068 (5)	0.043 (4)	0.048 (5)	0.014 (4)	0.020 (4)	0.011 (4)
C19	0.066 (5)	0.034 (4)	0.045 (5)	0.019 (4)	0.013 (4)	-0.004 (4)
C20	0.030 (4)	0.039 (4)	0.038 (4)	0.007 (3)	0.004 (3)	-0.004 (3)
C21	0.049 (4)	0.037 (4)	0.037 (4)	0.010 (3)	0.003 (4)	0.000 (3)
C22	0.047 (4)	0.043 (4)	0.037 (4)	0.007 (3)	0.004 (3)	-0.013 (4)
N1	0.033 (3)	0.025 (3)	0.041 (4)	-0.006 (2)	0.006 (3)	0.001 (3)
N2	0.029 (3)	0.011 (2)	0.024 (3)	0.002 (2)	0.005 (2)	-0.003 (2)
N3	0.022 (2)	0.011 (2)	0.026 (3)	-0.0013 (19)	0.005 (2)	0.001 (2)
N4	0.038 (3)	0.036 (3)	0.048 (4)	0.002 (2)	0.000 (3)	-0.003 (3)

O1	0.031 (2)	0.026 (2)	0.039 (2)	0.0052 (19)	0.0013 (19)	-0.006 (2)
O2	0.029 (2)	0.020 (2)	0.036 (3)	-0.0042 (16)	0.0006 (19)	-0.0048 (19)
O3	0.065 (3)	0.023 (2)	0.025 (2)	0.002 (2)	0.002 (2)	0.001 (2)
O4	0.0249 (19)	0.0142 (18)	0.028 (2)	0.0021 (17)	0.0053 (17)	0.0024 (19)
O5	0.045 (2)	0.017 (2)	0.021 (2)	0.0056 (17)	0.0079 (19)	-0.0030 (18)
O6	0.030 (2)	0.021 (2)	0.027 (2)	-0.0013 (18)	0.0064 (19)	0.006 (2)
O7	0.046 (3)	0.019 (2)	0.049 (3)	-0.005 (2)	0.019 (2)	-0.007 (2)
O8	0.066 (3)	0.035 (3)	0.106 (5)	-0.012 (2)	0.056 (3)	0.005 (3)
S1	0.0298 (8)	0.0166 (7)	0.0269 (9)	0.0041 (6)	0.0063 (7)	-0.0020 (6)
Cu1	0.0252 (3)	0.0066 (3)	0.0273 (4)	0.0008 (3)	0.0082 (3)	-0.0005 (3)

Geometric parameters (Å, °)

C1—C6	1.382 (7)	C15—H15	0.9300
C1—C2	1.391 (7)	C16—N3	1.334 (6)
C1—S1	1.787 (5)	C16—C17	1.385 (7)
C2—C3	1.401 (6)	C16—H16	0.9300
C2—H2	0.9300	C17—H17	0.9300
C3—C4	1.373 (7)	C18—N4	1.335 (8)
C3—C7	1.525 (7)	C18—C19	1.389 (9)
C4—C5	1.398 (7)	C18—H18	0.9300
C4—N1	1.475 (7)	C19—C20	1.386 (9)
C5—C6	1.386 (7)	C19—H19	0.9300
C5—H5	0.9300	C20—C21	1.375 (8)
C6—H6	0.9300	C20—C20 ⁱ	1.505 (11)
C7—O5	1.227 (6)	C21—C22	1.390 (8)
C7—O4	1.254 (6)	C21—H21	0.9300
C8—N2	1.341 (6)	C22—N4	1.342 (8)
C8—C9	1.381 (7)	C22—H22	0.9300
C8—H8	0.9300	N1—O8	1.216 (6)
C9—C10	1.388 (7)	N1—O7	1.219 (6)
C9—H9	0.9300	O1—S1	1.454 (4)
C10—C11	1.398 (7)	O2—S1	1.448 (4)
C10—C13	1.479 (6)	O3—S1	1.432 (4)
C11—C12	1.366 (6)	O6—H1A	0.83 (5)
C11—H11	0.9300	O6—H1B	0.86 (5)
C12—N2	1.339 (6)	Cu1—N2	1.986 (4)
C12—H12	0.9300	Cu1—N3 ⁱⁱ	2.004 (4)
C13—C14	1.384 (7)	Cu1—O2 ⁱⁱⁱ	2.565 (4)
C13—C17	1.397 (7)	Cu1—O4	1.969 (3)
C14—C15	1.374 (6)	Cu1—O5 ^{iv}	2.299 (4)
C14—H14	0.9300	Cu1—O6	2.032 (4)
C15—N3	1.337 (6)		
C6—C1—C2	119.9 (5)	N4—C18—C19	123.8 (7)
C6—C1—S1	121.2 (4)	N4—C18—H18	118.1
C2—C1—S1	118.9 (4)	C19—C18—H18	118.1
C1—C2—C3	121.4 (5)	C20—C19—C18	119.9 (7)
C1—C2—H2	119.3	C20—C19—H19	120.0

supplementary materials

C3—C2—H2	119.3	C18—C19—H19	120.0
C4—C3—C2	116.7 (5)	C21—C20—C19	116.2 (6)
C4—C3—C7	126.0 (5)	C21—C20—C20 ⁱ	121.8 (8)
C2—C3—C7	117.3 (5)	C19—C20—C20 ⁱ	122.0 (8)
C3—C4—C5	123.6 (5)	C20—C21—C22	120.9 (6)
C3—C4—N1	119.4 (5)	C20—C21—H21	119.5
C5—C4—N1	116.9 (5)	C22—C21—H21	119.5
C6—C5—C4	117.9 (5)	N4—C22—C21	122.9 (6)
C6—C5—H5	121.0	N4—C22—H22	118.6
C4—C5—H5	121.0	C21—C22—H22	118.6
C1—C6—C5	120.5 (5)	O8—N1—O7	122.2 (5)
C1—C6—H6	119.8	O8—N1—C4	118.4 (5)
C5—C6—H6	119.8	O7—N1—C4	119.4 (5)
O5—C7—O4	128.8 (5)	C12—N2—C8	117.4 (4)
O5—C7—C3	117.5 (5)	C12—N2—Cu1	120.8 (4)
O4—C7—C3	113.6 (5)	C8—N2—Cu1	121.7 (4)
N2—C8—C9	122.5 (5)	C16—N3—C15	117.9 (4)
N2—C8—H8	118.7	C16—N3—Cu1 ^v	123.2 (4)
C9—C8—H8	118.7	C15—N3—Cu1 ^v	118.8 (4)
C8—C9—C10	119.9 (5)	C18—N4—C22	116.2 (6)
C8—C9—H9	120.0	C7—O4—Cu1	126.4 (3)
C10—C9—H9	120.0	C7—O5—Cu1 ^{iv}	168.9 (4)
C9—C10—C11	117.2 (4)	Cu1—O6—H1A	105 (4)
C9—C10—C13	121.5 (5)	Cu1—O6—H1B	115 (4)
C11—C10—C13	121.4 (5)	H1A—O6—H1B	122 (5)
C12—C11—C10	119.3 (5)	O3—S1—O2	113.9 (2)
C12—C11—H11	120.4	O3—S1—O1	114.8 (2)
C10—C11—H11	120.4	O2—S1—O1	111.4 (2)
N2—C12—C11	123.7 (5)	O3—S1—C1	105.8 (3)
N2—C12—H12	118.1	O2—S1—C1	105.0 (2)
C11—C12—H12	118.1	O1—S1—C1	104.9 (2)
C14—C13—C17	117.7 (5)	O4—Cu1—N2	92.84 (16)
C14—C13—C10	121.1 (5)	O4—Cu1—N3 ⁱⁱ	86.36 (16)
C17—C13—C10	121.1 (5)	N2—Cu1—N3 ⁱⁱ	177.66 (18)
C15—C14—C13	119.9 (5)	O4—Cu1—O6	160.42 (16)
C15—C14—H14	120.1	N2—Cu1—O6	90.09 (17)
C13—C14—H14	120.1	N3 ⁱⁱ —Cu1—O6	91.39 (17)
N3—C15—C14	122.6 (5)	O4—Cu1—O5 ^{iv}	111.89 (14)
N3—C15—H15	118.7	N2—Cu1—O5 ^{iv}	85.92 (16)
C14—C15—H15	118.7	N3 ⁱⁱ —Cu1—O5 ^{iv}	92.34 (16)
N3—C16—C17	123.2 (5)	O6—Cu1—O5 ^{iv}	87.62 (15)
N3—C16—H16	118.4	O2 ⁱⁱⁱ —Cu1—N2	85.20 (17)
C17—C16—H16	118.4	O2 ⁱⁱⁱ —Cu1—N3 ⁱⁱ	96.74 (17)
C16—C17—C13	118.5 (5)	O2 ⁱⁱⁱ —Cu1—O4	75.35 (13)
C16—C17—H17	120.7	O2 ⁱⁱⁱ —Cu1—O5 ^{iv}	168.81 (12)

C13—C17—H17	120.7	O2 ⁱⁱⁱ —Cu1—O6	85.63 (13)
C6—C1—C2—C3	-1.2 (8)	C20 ⁱ —C20—C21—C22	179.5 (7)
S1—C1—C2—C3	179.4 (4)	C20—C21—C22—N4	1.7 (10)
C1—C2—C3—C4	1.4 (8)	C3—C4—N1—O8	-177.7 (6)
C1—C2—C3—C7	-177.9 (5)	C5—C4—N1—O8	0.9 (8)
C2—C3—C4—C5	0.1 (9)	C3—C4—N1—O7	3.5 (8)
C7—C3—C4—C5	179.2 (5)	C5—C4—N1—O7	-178.0 (5)
C2—C3—C4—N1	178.5 (5)	C11—C12—N2—C8	1.0 (8)
C7—C3—C4—N1	-2.3 (9)	C11—C12—N2—Cu1	-176.6 (4)
C3—C4—C5—C6	-1.7 (9)	C9—C8—N2—C12	0.5 (8)
N1—C4—C5—C6	179.8 (5)	C9—C8—N2—Cu1	178.1 (4)
C2—C1—C6—C5	-0.5 (9)	C17—C16—N3—C15	-0.4 (8)
S1—C1—C6—C5	178.9 (5)	C17—C16—N3—Cu1 ^v	179.2 (4)
C4—C5—C6—C1	1.9 (9)	C14—C15—N3—C16	1.6 (8)
C4—C3—C7—O5	95.3 (7)	C14—C15—N3—Cu1 ^v	-178.0 (4)
C2—C3—C7—O5	-85.6 (6)	C19—C18—N4—C22	-3.8 (10)
C4—C3—C7—O4	-88.7 (7)	C21—C22—N4—C18	0.7 (9)
C2—C3—C7—O4	90.4 (6)	O5—C7—O4—Cu1	26.7 (7)
N2—C8—C9—C10	-1.5 (9)	C3—C7—O4—Cu1	-148.7 (3)
C8—C9—C10—C11	0.9 (8)	O4—C7—O5—Cu1 ^{iv}	-29 (2)
C8—C9—C10—C13	179.0 (5)	C3—C7—O5—Cu1 ^{iv}	146.5 (15)
C9—C10—C11—C12	0.6 (8)	C6—C1—S1—O3	-130.7 (5)
C13—C10—C11—C12	-177.6 (5)	C2—C1—S1—O3	48.7 (5)
C10—C11—C12—N2	-1.6 (8)	C6—C1—S1—O2	108.6 (5)
C9—C10—C13—C14	-35.0 (8)	C2—C1—S1—O2	-72.0 (5)
C11—C10—C13—C14	143.0 (5)	C6—C1—S1—O1	-9.0 (5)
C9—C10—C13—C17	147.2 (5)	C2—C1—S1—O1	170.5 (4)
C11—C10—C13—C17	-34.7 (8)	C7—O4—Cu1—N2	-106.1 (4)
C17—C13—C14—C15	2.0 (8)	C7—O4—Cu1—N3 ⁱⁱ	71.7 (4)
C10—C13—C14—C15	-175.8 (5)	C7—O4—Cu1—O6	155.6 (5)
C13—C14—C15—N3	-2.5 (8)	C7—O4—Cu1—O5 ^{iv}	-19.4 (4)
N3—C16—C17—C13	0.1 (8)	C12—N2—Cu1—O4	153.9 (4)
C14—C13—C17—C16	-0.9 (8)	C8—N2—Cu1—O4	-23.6 (4)
C10—C13—C17—C16	176.9 (5)	C12—N2—Cu1—O6	-45.4 (4)
N4—C18—C19—C20	4.6 (11)	C8—N2—Cu1—O6	137.1 (4)
C18—C19—C20—C21	-2.0 (10)	C12—N2—Cu1—O5 ^{iv}	42.2 (4)
C18—C19—C20—C20 ⁱ	177.6 (7)	C8—N2—Cu1—O5 ^{iv}	-135.3 (4)
C19—C20—C21—C22	-0.9 (10)		

Symmetry codes: (i) $-x, -y+1, -z+2$; (ii) $x, y+1, z$; (iii) $-x+1, y-1/2, -z+3/2$; (iv) $-x+1, -y+1, -z+1$; (v) $x, y-1, z$.

Hydrogen-bond geometry ($\text{\AA}, ^\circ$)

$D-H\cdots A$	$D-H$	$H\cdots A$	$D\cdots A$	$D-H\cdots A$
O6—H1A \cdots O1 ⁱⁱⁱ	0.83 (5)	1.94 (5)	2.758 (5)	171 (6)
O6—H1B \cdots N4 ^{vi}	0.86 (5)	2.00 (5)	2.801 (6)	156 (5)

Symmetry codes: (iii) $-x+1, y-1/2, -z+3/2$; (vi) $-x+1, y+1/2, -z+3/2$.

Fig. 2

