

Acta Crystallographica Section E

Structure Reports

Online

ISSN 1600-5368

Dipotassium samarium(III) molybdate(VI) phosphate(V), $K_2Sm(MoO_4)(PO_4)$

Dan Zhao,^{a*} Feifei Li,^a Wendan Cheng^b and Hao Zhang^b

^aDepartment of Physics and Chemistry, Henan Polytechnic University, Jiaozuo, Henan 454000, People's Republic of China, and ^bState Key Laboratory of Structural Chemistry, Fujian Institute of Research on the Structure of Matter, Chinese Academy of Sciences, Fuzhou, Fujian, 350002, People's Republic of China
Correspondence e-mail: iamzd@hpu.edu.cn

Received 30 September 2009; accepted 12 October 2009

Key indicators: single-crystal X-ray study; $T = 298$ K; mean $\sigma(P-O) = 0.003$ Å; R factor = 0.014; wR factor = 0.079; data-to-parameter ratio = 16.0.

The title compound, $K_2Sm(MoO_4)(PO_4)$, has been prepared under atmospheric conditions using a high temperature solution growth (HTSG) method. The structure of $K_2Sm(MoO_4)(PO_4)$ is isotypic with other $A_2M(MoO_4)(PO_4)$ compounds, where $A = Na$ or K , and $M =$ trivalent rare earth cation. It can be described as being built up from two-dimensional anionic layers with composition $[Sm(MoO_4)(PO_4)]^{2-}$ that are stacked along the c axis and are interconnected by K^+ cations which are in an eightfold coordination by O atoms. The SmO_8 , MoO_4 and PO_4 polyhedra exhibit 2 symmetry.

Related literature

The structures and properties of other molybdate-phosphates with the general formula $A_2M(MoO_4)(PO_4)$, where $A = Na, K$; $M = Y, Bi, La-Nd, Sm-Lu$, have been reported by Ben Amara & Dabbabi (1987); Komissarova *et al.* (2006); Ryumin *et al.* (2007); Zatonvsky *et al.* (2006). For crystallographic background, see: Spek (2009).

Experimental

Crystal data

$K_2Sm(MoO_4)(PO_4)$
 $M_r = 483.46$
Orthorhombic, $Ibca$
 $a = 12.345$ (9) Å

$b = 7.004$ (5) Å
 $c = 19.733$ (12) Å
 $V = 1706$ (2) Å³
 $Z = 8$

Mo $K\alpha$ radiation
 $\mu = 9.46$ mm⁻¹

$T = 298$ K
 $0.15 \times 0.10 \times 0.05$ mm

Data collection

Rigaku Saturn 70 diffractometer
Absorption correction: multi-scan
(*CrystalClear*; Rigaku, 2000)
 $T_{min} = 0.742$, $T_{max} = 1.000$

3660 measured reflections
979 independent reflections
903 reflections with $I > 2\sigma(I)$
 $R_{int} = 0.022$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.014$
 $wR(F^2) = 0.079$
 $S = 1.01$
979 reflections

61 parameters
 $\Delta\rho_{max} = 0.85$ e Å⁻³
 $\Delta\rho_{min} = -0.99$ e Å⁻³

Table 1

Selected bond lengths (Å).

K1—O4 ⁱ	2.685 (3)	Sm1—O1 ⁱⁱ	2.339 (3)
K1—O2	2.695 (3)	Sm1—O3	2.399 (3)
K1—O2 ⁱⁱ	2.768 (3)	Sm1—O2	2.451 (3)
K1—O3 ⁱⁱ	2.991 (4)	Sm1—O1 ^{vi}	2.481 (3)
K1—O4	3.012 (4)	Mo1—O4	1.743 (3)
K1—O1 ⁱⁱⁱ	3.025 (3)	Mo1—O3	1.784 (3)
K1—O4 ^{iv}	3.184 (4)	P1—O2	1.533 (3)
K1—O3 ^v	3.191 (4)	P1—O1	1.549 (3)

Symmetry codes: (i) $-x + \frac{1}{2}, y, -z$; (ii) $-x + \frac{1}{2}, y - \frac{1}{2}, z$; (iii) $x, -y + 1, -z + \frac{1}{2}$; (iv) $-x + \frac{1}{2}, y + \frac{1}{2}, z$; (v) $x - \frac{1}{2}, -y + 1, z$; (vi) $x + \frac{1}{2}, y, -z + \frac{1}{2}$.

Data collection: *CrystalClear* (Rigaku, 2000); cell refinement: *CrystalClear*; data reduction: *CrystalClear*; program(s) used to solve structure: *SHELXS97* (Sheldrick, 2008); program(s) used to refine structure: *SHELXL97* (Sheldrick, 2008); molecular graphics: *SHELXTL* (Sheldrick, 2008) and *DIAMOND* (Brandenburg & Putz, 2005); software used to prepare material for publication: *SHELXTL*.

We thank Dr Yougui Huang and Qingxia Yao for fruitful discussions concerning the crystal structure and for help with graphics.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: WM2263).

References

- Ben Amara, M. & Dabbabi, M. (1987). *Acta Cryst.* **C43**, 616–618.
Brandenburg, K. & Putz, H. (2005). *DIAMOND*. Crystal Impact GbR, Bonn, Germany.
Komissarova, L. N., Ryumin, M. A., Bobylev, A. P., Zhizhin, M. G. & Danilov, V. P. (2006). *Russ. J. Inorg. Chem.* **51**, 397–403.
Rigaku (2000). *CrystalClear*. Rigaku Corporation, Tokyo, Japan.
Ryumin, M. A., Komissarova, L. N., Rusakov, D. A., Bobylev, A. P. & Zhizhin, M. G. (2007). *Russ. J. Inorg. Chem.* **52**, 717–724.
Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.
Spek, A. L. (2009). *Acta Cryst.* **D65**, 148–155.
Zatonvsky, I. V., Terebilenko, K. V., Slobodyanik, N. S., Baumer, V. N. & Shishkin, O. V. (2006). *J. Solid State Chem.* **179**, 3550–3555.

supporting information

Acta Cryst. (2009). E65, i78 [https://doi.org/10.1107/S1600536809041622]

Dipotassium samarium(III) molybdate(VI) phosphate(V), $K_2Sm(MoO_4)(PO_4)$ **Dan Zhao, Feifei Li, Wendan Cheng and Hao Zhang****S1. Comment**

In recent years, several complex molybdate-phosphates with the general formula $A_2M(MoO_4)(PO_4)$ ($A = Na, K; M = Y, Bi, La-Nd, Sm-Lu$) have been reported (Ben Amara & Dabbabi, 1987); Komissarova *et al.*, 2006; Ryumin *et al.*, 2007; Zatonvsky *et al.*, 2006). Herein, we present synthesis and crystal structure of the title compound, $K_2Sm(MoO_4)(PO_4)$.

X-ray analysis revealed that the compound $K_2Sm(MoO_4)(PO_4)$ crystallizes in the orthorhombic system with space group *Ibca* (Fig. 1). The asymmetric unit contains one K, one Sm, one Mo, one P and four O atoms. Each of the Mo and P atoms is tetrahedrally coordinated by four O atoms, forming nearly ideal MoO_4 and PO_4 tetrahedra with two types of Mo–O (1.743 (3) Å, 1.784 (3) Å) and P–O distances (1.533 (3) Å, 1.549 (3) Å), respectively. The Sm atom is surrounded by eight oxygen atoms in a distorted dodecahedral environment with the Sm–O bond distances in the range of 2.339 (3)–2.481 (3) Å. MoO_4 , PO_4 and SmO_8 polyhedra are interconnected *via* corner- or edge-sharing O atoms forming a two-dimensional anionic layer of overall composition $[Sm(MoO_4)(PO_4)]^{2-}$ extending parallel to the *ab*-plane, as shown in Fig. 2. Furthermore, the anionic framework delimits large cages in which the K^+ cations (coordination number 8) reside to ensure the cohesion of the structure and the neutrality of the compound, resulting in a three-dimensional framework structure.

S2. Experimental

Single crystals of $K_2Sm(MoO_4)(PO_4)$ were obtained by the high temperature solution growth (HTSG) reaction of K_2CO_3 (2.253 g, 16.3 mmol), Sm_2O_3 (0.569 g, 1.63 mmol), MoO_3 (0.939 g, 6.52 mmol) and $NH_4H_2PO_4$ (3.000 g, 26.1 mmol), with the molar ratio of 10:1:2:8 (K:Sm:Mo:P). The reaction mixture was thoroughly ground in an agate mortar and pressed into a pellet to ensure the best homogeneity and reactivity. The pellet was put into a platinum crucible and calcined at 673 K or 10 h to decompose the salts. Then the crucible was transferred to another furnace and heated at 1223 K for 48 h. Then the sample was cooled from 1173 K at a rate of 4 Kh^{-1} . After boiling for 24 h in water, a few prism-shaped colorless crystals were obtained in very low yield (<5%).

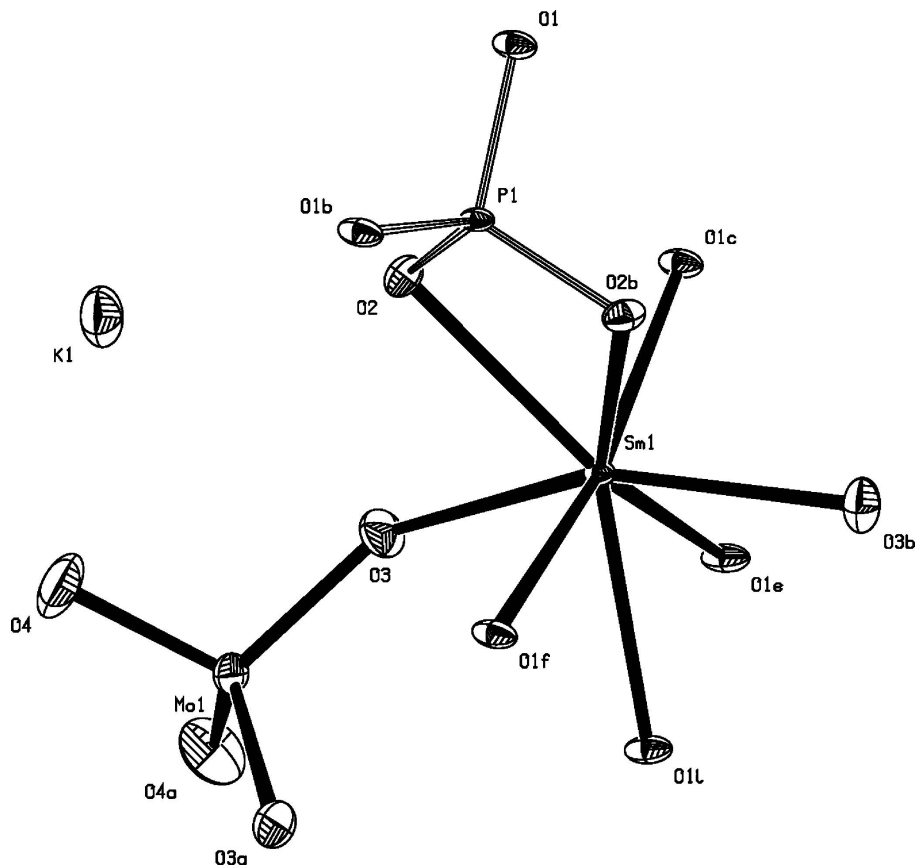


Figure 1

Part of the structure of the title compound, showing the labelling of the atoms. Displacement ellipsoids are drawn at the 50% probability level. [Symmetry codes: (a) $-X, 1/2 - Y, Z$ (b) $X, -Y, 1/2 - Z$ (c) $-X, 1/2 + Y, 1/2 - Z$ (e) $X, 1/2 + Y, -Z$ (f) $-X, Y, 1/2 + Z$ (l) $1/2 + X, Y, 1/2 - z$.]

Dipotassium samarium(III) molybdate(VI) phosphate(V)

Crystal data

$\text{K}_2\text{Sm}(\text{MoO}_4)(\text{PO}_4)$

$M_r = 483.46$

Orthorhombic, *Ibca*

Hall symbol: $-I\ 2b\ 2c$

$a = 12.345\ (9)\ \text{\AA}$

$b = 7.004\ (5)\ \text{\AA}$

$c = 19.733\ (12)\ \text{\AA}$

$V = 1706\ (2)\ \text{\AA}^3$

$Z = 8$

$F(000) = 1768$

$D_x = 3.764\ \text{Mg m}^{-3}$

Mo $K\alpha$ radiation, $\lambda = 0.71073\ \text{\AA}$

Cell parameters from 369 reflections

$\theta = 3.1\text{--}27.4^\circ$

$\mu = 9.46\ \text{mm}^{-1}$

$T = 298\ \text{K}$

Prism, colourless

$0.15 \times 0.10 \times 0.05\ \text{mm}$

Data collection

Rigaku Saturn 70
diffractometer

Radiation source: fine-focus sealed tube

Graphite monochromator

Detector resolution: $14.6306\ \text{pixels mm}^{-1}$

ω scans

Absorption correction: multi-scan

(*CrystalClear*; Rigaku, 2000)

$T_{\min} = 0.742, T_{\max} = 1.000$

3660 measured reflections

979 independent reflections

903 reflections with $I > 2\sigma(I)$

$R_{\text{int}} = 0.022$
 $\theta_{\text{max}} = 27.5^\circ$, $\theta_{\text{min}} = 2.1^\circ$
 $h = -15 \rightarrow 15$

$k = -9 \rightarrow 8$
 $l = -25 \rightarrow 25$

Refinement

Refinement on F^2
 Least-squares matrix: full
 $R[F^2 > 2\sigma(F^2)] = 0.014$
 $wR(F^2) = 0.079$
 $S = 1.01$
 979 reflections
 61 parameters
 0 restraints

Primary atom site location: structure-invariant
 direct methods
 Secondary atom site location: difference Fourier
 map
 $w = 1/[\sigma^2(F_o^2) + (0.063P)^2]$
 where $P = (F_o^2 + 2F_c^2)/3$
 $(\Delta/\sigma)_{\text{max}} < 0.001$
 $\Delta\rho_{\text{max}} = 0.85 \text{ e } \text{\AA}^{-3}$
 $\Delta\rho_{\text{min}} = -0.99 \text{ e } \text{\AA}^{-3}$

Special details

Geometry. All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

Refinement. Single crystal of $\text{K}_2\text{Sm}(\text{MoO}_4)(\text{PO}_4)$ with dimensions of 0.15 mm×0.10 mm×0.05 mm was selected for single-crystal X-ray diffraction determination. The diffraction data of $\text{K}_2\text{Sm}(\text{MoO}_4)(\text{PO}_4)$ were collected on a Rigaku Saturn70 CCD diffractometer with graphite-monochromated Mo—K α radiation ($\lambda = 0.71073 \text{ \AA}$). Intensity data were collected by the narrow frame method at 298 K. The data were corrected for Lorentz factor, polarization, air absorption and absorption due to variations in the path length through the detector faceplate. Absorption corrections based on Multi-scan technique were also applied (*CrystalClear*, ver. 1.3.5., Rigaku Corp., Woodlands, TX, 1999). The single-crystal refinement was performed with the program *SHELX97*. The spacegroup was determined to be *Ibca* based on systematic absences as well as E-value statistics. The structure was solved by the direct methods and the molybdenum and phosphorus atoms were revealed. Subsequent difference-Fourier syntheses by full-matrix least-squares fitting on F^2 allowed localization of potassium and all oxygen atoms. The final structure refinement performed by least-square methods with atomic coordinates and anisotropic thermal parameters resulted in satisfactory residuals. In addition, the final refined solutions obtained for were checked with the ADDSYM algorithm in the program *PLATON* (Spek, 2009) and no higher symmetries were found.

Refinement of F^2 against ALL reflections. The weighted R -factor wR and goodness of fit S are based on F^2 , conventional R -factors R are based on F , with F set to zero for negative F^2 . The threshold expression of $F^2 > \sigma(F^2)$ is used only for calculating R -factors(gt) etc. and is not relevant to the choice of reflections for refinement. R -factors based on F^2 are statistically about twice as large as those based on F , and R -factors based on ALL data will be even larger.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	x	y	z	$U_{\text{iso}}^*/U_{\text{eq}}$
K1	0.17099 (8)	0.28431 (16)	0.09418 (5)	0.0233 (3)
Sm1	0.42384 (2)	0.5000	0.2500	0.00627 (15)
Mo1	0.5000	0.2500	0.08208 (2)	0.01213 (17)
P1	0.17826 (12)	0.5000	0.2500	0.0066 (4)
O1	0.0995 (3)	0.6698 (4)	0.26009 (13)	0.0111 (6)
O2	0.2522 (3)	0.5240 (3)	0.18818 (14)	0.0113 (6)
O3	0.4690 (3)	0.4533 (5)	0.13294 (14)	0.0177 (6)
O4	0.3879 (3)	0.1914 (5)	0.03256 (15)	0.0292 (8)

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
K1	0.0327 (6)	0.0226 (5)	0.0147 (4)	-0.0016 (4)	-0.0042 (4)	-0.0018 (4)
Sm1	0.0049 (2)	0.0050 (2)	0.0090 (2)	0.000	0.000	0.00005 (8)
Mo1	0.0142 (3)	0.0153 (3)	0.0069 (3)	0.00155 (19)	0.000	0.000
P1	0.0041 (8)	0.0042 (9)	0.0115 (8)	0.000	0.000	0.0001 (4)
O1	0.0065 (13)	0.0058 (15)	0.0212 (13)	0.0000 (12)	-0.0006 (11)	-0.0018 (11)
O2	0.0085 (14)	0.0139 (14)	0.0116 (13)	-0.0026 (11)	-0.0010 (12)	0.0021 (10)
O3	0.0228 (18)	0.0192 (15)	0.0112 (13)	0.0032 (14)	0.0029 (12)	-0.0013 (12)
O4	0.032 (2)	0.033 (2)	0.0224 (15)	-0.0012 (16)	-0.0163 (15)	0.0016 (14)

Geometric parameters (\AA , $^\circ$)

K1—O4 ⁱ	2.685 (3)	Mo1—O4 ^{ix}	1.743 (3)
K1—O2	2.695 (3)	Mo1—O4	1.743 (3)
K1—O2 ⁱⁱ	2.768 (3)	Mo1—O3	1.784 (3)
K1—O3 ⁱⁱ	2.991 (4)	Mo1—O3 ^{ix}	1.784 (3)
K1—O4	3.012 (4)	P1—O2	1.533 (3)
K1—O1 ⁱⁱⁱ	3.025 (3)	P1—O2 ⁱⁱⁱ	1.533 (3)
K1—O4 ^{iv}	3.184 (4)	P1—O1 ⁱⁱⁱ	1.549 (3)
K1—O3 ^v	3.191 (4)	P1—O1	1.549 (3)
Sm1—O1 ⁱⁱ	2.339 (3)	O1—Sm1 ^{vi}	2.339 (3)
Sm1—O1 ^{vi}	2.339 (3)	O1—Sm1 ^x	2.481 (3)
Sm1—O3	2.399 (3)	O1—K1 ⁱⁱⁱ	3.025 (3)
Sm1—O3 ⁱⁱⁱ	2.399 (3)	O2—K1 ^{iv}	2.768 (3)
Sm1—O2	2.451 (3)	O3—K1 ^{iv}	2.991 (4)
Sm1—O2 ⁱⁱⁱ	2.451 (3)	O3—K1 ^{viii}	3.191 (4)
Sm1—O1 ^{vii}	2.481 (3)	O4—K1 ⁱ	2.685 (3)
Sm1—O1 ^{viii}	2.481 (3)	O4—K1 ⁱⁱ	3.184 (4)
O4 ⁱ —K1—O2	153.25 (10)	O3 ⁱⁱⁱ —Sm1—O1 ^{vii}	78.98 (10)
O4 ⁱ —K1—O2 ⁱⁱ	123.87 (11)	O2—Sm1—O1 ^{vii}	133.07 (9)
O2—K1—O2 ⁱⁱ	79.73 (9)	O2 ⁱⁱⁱ —Sm1—O1 ^{vii}	145.94 (9)
O4 ⁱ —K1—O3 ⁱⁱ	83.90 (10)	O1 ⁱⁱ —Sm1—O1 ^{viii}	68.11 (13)
O2—K1—O3 ⁱⁱ	121.45 (10)	O1 ^{vi} —Sm1—O1 ^{viii}	126.05 (8)
O2 ⁱⁱ —K1—O3 ⁱⁱ	61.05 (10)	O3—Sm1—O1 ^{viii}	78.98 (10)
O4 ⁱ —K1—O4	79.19 (11)	O3 ⁱⁱⁱ —Sm1—O1 ^{viii}	77.59 (10)
O2—K1—O4	94.69 (10)	O2—Sm1—O1 ^{viii}	145.94 (9)
O2 ⁱⁱ —K1—O4	79.85 (10)	O2 ⁱⁱⁱ —Sm1—O1 ^{viii}	133.07 (9)
O3 ⁱⁱ —K1—O4	116.70 (11)	O1 ^{vii} —Sm1—O1 ^{viii}	58.14 (15)
O4 ⁱ —K1—O1 ⁱⁱⁱ	146.34 (11)	O4 ^{ix} —Mo1—O4	111.8 (2)
O2—K1—O1 ⁱⁱⁱ	52.27 (9)	O4 ^{ix} —Mo1—O3	107.33 (15)
O2 ⁱⁱ —K1—O1 ⁱⁱⁱ	62.16 (9)	O4—Mo1—O3	109.46 (16)
O3 ⁱⁱ —K1—O1 ⁱⁱⁱ	70.78 (8)	O4 ^{ix} —Mo1—O3 ^{ix}	109.46 (16)
O4—K1—O1 ⁱⁱⁱ	131.75 (9)	O4—Mo1—O3 ^{ix}	107.33 (15)
O4 ⁱ —K1—O4 ^{iv}	78.43 (8)	O3—Mo1—O3 ^{ix}	111.5 (2)
O2—K1—O4 ^{iv}	77.88 (9)	O2—P1—O2 ⁱⁱⁱ	106.9 (3)

O2 ⁱⁱ —K1—O4 ^{iv}	157.51 (9)	O2—P1—O1 ⁱⁱⁱ	110.83 (15)
O3 ⁱⁱ —K1—O4 ^{iv}	131.29 (10)	O2 ⁱⁱⁱ —P1—O1 ⁱⁱⁱ	113.07 (14)
O4—K1—O4 ^{iv}	104.03 (10)	O2—P1—O1	113.08 (14)
O1 ⁱⁱⁱ —K1—O4 ^{iv}	101.61 (9)	O2 ⁱⁱⁱ —P1—O1	110.83 (15)
O4 ⁱ —K1—O3 ^v	98.70 (10)	O1 ⁱⁱⁱ —P1—O1	102.3 (3)
O2—K1—O3 ^v	76.53 (10)	P1—O1—Sm1 ^{vi}	145.66 (18)
O2 ⁱⁱ —K1—O3 ^v	119.10 (9)	P1—O1—Sm1 ^x	99.81 (16)
O3 ⁱⁱ —K1—O3 ^v	86.19 (11)	Sm1 ^{vi} —O1—Sm1 ^x	111.05 (13)
O4—K1—O3 ^v	156.35 (10)	P1—O1—K1 ⁱⁱⁱ	91.19 (13)
O1 ⁱⁱⁱ —K1—O3 ^v	58.87 (8)	Sm1 ^{vi} —O1—K1 ⁱⁱⁱ	90.67 (9)
O4 ^{iv} —K1—O3 ^v	52.93 (8)	Sm1 ^x —O1—K1 ⁱⁱⁱ	112.46 (9)
O1 ⁱⁱ —Sm1—O1 ^{vi}	165.83 (15)	P1—O2—Sm1	96.39 (15)
O1 ⁱⁱ —Sm1—O3	88.61 (10)	P1—O2—K1	104.95 (15)
O1 ^{vi} —Sm1—O3	94.68 (10)	Sm1—O2—K1	128.43 (12)
O1 ⁱⁱ —Sm1—O3 ⁱⁱⁱ	94.68 (10)	P1—O2—K1 ^{iv}	144.03 (15)
O1 ^{vi} —Sm1—O3 ⁱⁱⁱ	88.61 (10)	Sm1—O2—K1 ^{iv}	94.74 (11)
O3—Sm1—O3 ⁱⁱⁱ	153.13 (16)	K1—O2—K1 ^{iv}	94.39 (10)
O1 ⁱⁱ —Sm1—O2	90.20 (9)	Mo1—O3—Sm1	134.48 (17)
O1 ^{vi} —Sm1—O2	77.48 (9)	Mo1—O3—K1 ^{iv}	126.79 (14)
O3—Sm1—O2	74.39 (11)	Sm1—O3—K1 ^{iv}	90.36 (10)
O3 ⁱⁱⁱ —Sm1—O2	132.14 (11)	Mo1—O3—K1 ^{viii}	99.04 (13)
O1 ⁱⁱ —Sm1—O2 ⁱⁱⁱ	77.48 (9)	Sm1—O3—K1 ^{viii}	109.51 (11)
O1 ^{vi} —Sm1—O2 ⁱⁱⁱ	90.20 (9)	K1 ^{iv} —O3—K1 ^{viii}	86.78 (10)
O3—Sm1—O2 ⁱⁱⁱ	132.14 (11)	Mo1—O4—K1 ⁱ	132.86 (18)
O3 ⁱⁱⁱ —Sm1—O2 ⁱⁱⁱ	74.39 (11)	Mo1—O4—K1	115.37 (15)
O2—Sm1—O2 ⁱⁱⁱ	60.33 (15)	K1 ⁱ —O4—K1	94.75 (10)
O1 ⁱⁱ —Sm1—O1 ^{vii}	126.05 (8)	Mo1—O4—K1 ⁱⁱ	100.26 (13)
O1 ^{vi} —Sm1—O1 ^{vii}	68.11 (13)	K1 ⁱ —O4—K1 ⁱⁱ	120.73 (12)
O3—Sm1—O1 ^{vii}	77.59 (10)	K1—O4—K1 ⁱⁱ	80.58 (9)

Symmetry codes: (i) $-x+1/2, y, -z$; (ii) $-x+1/2, y-1/2, z$; (iii) $x, -y+1, -z+1/2$; (iv) $-x+1/2, y+1/2, z$; (v) $x-1/2, -y+1, z$; (vi) $-x+1/2, -y+3/2, -z+1/2$; (vii) $x+1/2, y, -z+1/2$; (viii) $x+1/2, -y+1, z$; (ix) $-x+1, -y+1/2, z$; (x) $x-1/2, y, -z+1/2$.