

Zn_{1.86}Cd_{0.14}(OH)VO₄

Tamara Đorđević,^{a*} Jovica Stojanović^b and Ljiljana Karanović^c

^aInstitut für Mineralogie und Kristallographie, Universität Wien-Geozentrum, Althanstrasse 14, A-1090 Vienna, Austria, ^bApplied Mineralogy Unit, Institute for Technology of Nuclear and Other Mineral Raw Materials, Franchet d'Épérey 86, PO Box 390, 11000 Belgrade, Serbia, and ^cLaboratory of Crystallography, Faculty of Mining and Geology, Đušina 7, 11000 Belgrade, Serbia
Correspondence e-mail: tamara.djordjevic@univie.ac.at

Received 25 October 2010; accepted 2 November 2010

Key indicators: single-crystal X-ray study; $T = 293$ K; mean $\sigma(V-O) = 0.002$ Å; disorder in main residue; R factor = 0.025; wR factor = 0.056; data-to-parameter ratio = 17.4.

The title compound, dizinc cadmium hydroxide tetraoxido-vanadate, Zn_{1.86}Cd_{0.14}(OH)VO₄, was prepared under low-temperature hydrothermal conditions. It is isostructural with Zn₂(OH)VO₄ and Cu₂(OH)VO₄. In the crystal structure, chains of edge-sharing [ZnO₆] octahedra are interconnected by VO₄ tetrahedra (site symmetries of both V atoms and their coordination polyhedra are *m*.) to form a three-dimensional [Zn(OH)VO₄]²⁻ framework with channels occupied by Zn and Zn/Cd cations adopting trigonal-bipyramidal and distorted octahedral coordinations, respectively. Zn_{1.86}-Cd_{0.14}(OH)VO₄ is topologically related to adamite-type phases, and descloizite- and tsumcorite-type structures.

Related literature

For isostructural compounds, see: Wang *et al.* (1998); Wu *et al.* (2003). For topologically related structures, see: Nandini & Vidyasagar (1998); Bachmann (1953); Qurashi & Barnes (1964). For structurally related compounds, see: Hawthorne & Faggiani (1979); Tillmanns & Gebert (1973). For bond-valence analysis, see: Brese & O'Keeffe (1991).

Experimental

Crystal data

Zn _{1.86} Cd _{0.14} (OH)VO ₄	$V = 795.8$ (3) Å ³
$M_r = 535.62$	$Z = 4$
Orthorhombic, <i>Pnma</i>	Mo $K\alpha$ radiation
$a = 14.702$ (3) Å	$\mu = 14.00$ mm ⁻¹
$b = 6.0511$ (12) Å	$T = 293$ K
$c = 8.9460$ (18) Å	$0.18 \times 0.03 \times 0.02$ mm

Data collection

Nonius KappaCCD diffractometer	5550 measured reflections
Absorption correction: multi-scan (Otwinowski & Minor, 1997; Otwinowski <i>et al.</i> , 2003)	1566 independent reflections
$T_{\min} = 0.187$, $T_{\max} = 0.767$	1377 reflections with $I > 2\sigma(I)$
	$R_{\text{int}} = 0.013$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.025$	2 restraints
$wR(F^2) = 0.056$	H-atom parameters constrained
$S = 1.17$	$\Delta\rho_{\text{max}} = 0.79$ e Å ⁻³
1566 reflections	$\Delta\rho_{\text{min}} = -0.91$ e Å ⁻³
90 parameters	

Table 1

Hydrogen-bond geometry (Å, °).

$D-H\cdots A$	$D-H$	$H\cdots A$	$D\cdots A$	$D-H\cdots A$
O7—H1 \cdots O4 ⁱ	0.89 (2)	2.45 (2)	3.176 (3)	139 (1)
O7—H1 \cdots O4 ⁱⁱ	0.89 (2)	2.45 (2)	3.176 (3)	139 (1)
O8—H2 \cdots O2	0.88 (2)	1.84 (2)	2.708 (4)	175 (9)

Symmetry codes: (i) $x + \frac{1}{2}, -y + \frac{1}{2}, -z + \frac{1}{2}$; (ii) $x + \frac{1}{2}, y, -z + \frac{1}{2}$.

Data collection: *COLLECT* (Nonius, 2002); cell refinement: *SCALEPACK* (Otwinowski & Minor, 1997); data reduction: *DENZO-SMN* (Otwinowski & Minor, 1997); program(s) used to solve structure: *SIR97* (Altomare *et al.*, 1999); program(s) used to refine structure: *SHELXL97* (Sheldrick, 2008) and *WinGX* (Farrugia, 1999); molecular graphics: *ATOMS* (Dowty, 2000); software used to prepare material for publication: *pubCIF* (Westrip, 2010).

The authors gratefully acknowledge financial support from the Austrian Science Foundation (FWF) (grant No. T300-N19), the Austrian Science Community (ÖFG) (grant No. MOEL 413) and the Ministry for Science and Technological Development of the Republic of Serbia (project Nos. 142030 and 19002).

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: BR2149).

References

- Altomare, A., Burla, M. C., Camalli, M., Cascarano, G. L., Giacovazzo, C., Guagliardi, A., Moliterni, A. G. G., Polidori, G. & Spagna, R. (1999). *J. Appl. Cryst.* **32**, 115–119.
- Bachmann, H. G. (1953). *Acta Cryst.* **6**, 102.
- Brese, N. E. & O'Keeffe, M. (1991). *Acta Cryst.* **B47**, 192–197.
- Dowty, E. (2000). *ATOMS for Windows*. Shape Software, Kingsport, Tennessee, USA.
- Farrugia, L. J. (1999). *J. Appl. Cryst.* **32**, 837–838.
- Hawthorne, F. C. & Faggiani, R. (1979). *Acta Cryst.* **B35**, 717–720.
- Nandini, R. & Vidyasagar, K. (1998). *J. Chem. Soc. Dalton Trans.* pp. 3013–3019.
- Nonius (2002). *COLLECT*. Nonius BV, Delft, The Netherlands.
- Otwinowski, Z., Borek, D., Majewski, W. & Minor, W. (2003). *Acta Cryst.* **A59**, 228–234.
- Otwinowski, Z. & Minor, W. (1997). *Methods in Enzymology*, Vol. 276, *Macromolecular Crystallography*, Part A, edited by C. W. Carter Jr & R. M. Sweet, pp. 307–326. New York: Academic Press.
- Qurashi, M. M. & Barnes, W. H. (1964). *Can. Mineral.* **8**, 23–29.
- Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.
- Tillmanns, E. & Gebert, W. (1973). *Acta Cryst.* **B29**, 2789–2794.
- Wang, X., Liu, L. & Jacobson, A. J. (1998). *Z. Anorg. Allg. Chem.* **624**, 1977–1981.
- Westrip, S. P. (2010). *J. Appl. Cryst.* **43**, 920–925.
- Wu, C. D., Lu, C. Z., Zhuang, H. H. & Huang, J. S. (2003). *Eur. J. Inorg. Chem.* pp. 2867–2871.

supporting information

Acta Cryst. (2010). E66, i79 [https://doi.org/10.1107/S1600536810044806]

Zn_{1.86}Cd_{0.14}(OH)VO₄**Tamara Đorđević, Jovica Stojanović and Ljiljana Karanović****S1. Comment**

The phases in *A–M–X–O–(H)* system often form such family of compounds showing rich structural chemistry with anionic frameworks built from *MO*₆ octahedra and *XO*₄ tetrahedra and *A*ⁿ⁺ ions as counter cations. There are many reports on divalent metal vanadates synthesized by high temperature solid state reactions. However, hydrothermal methods are proved to be effective for the synthesis of new vanadium compounds, including zinc vanadates (Wang *et al.*, 1998 and references therein). To keep the products of hydrothermal synthesis under control is often difficult because of the high sensitivity to the exact reaction conditions. However, hydrothermal syntheses often result in well developed single crystals. Here we report on the new zinc cadmium hydrogen vanadate, (Zn_{1.86}Cd_{0.14})(OH)VO₄. In its crystal structure [Zn₃O₆]_n octahedral chains are interconnected by VO₄ tetrahedra to form a [Zn₃(OH)VO₄] framework. The voids are filled by Zn1 and Zn2/Cd2 cations with trigonal bipyramidal and distorted octahedral coordination, respectively. The two distinct V atoms adopt tetrahedral coordination. VO₄ tetrahedra are distorted and both have site symmetry *m*. V—O bond lengths are in the ranges of 1.684 (3) to 1.729 (2) Å for V1 and 1.651 (3) to 1.789 (3) Å for V2. The Zn—O bond lengths vary from 1.958 (3) to 2.427 (2) Å. (Zn_{1.86}Cd_{0.14})(OH)VO₄ is isostructural with Zn₂(OH)VO₄ (Wang *et al.*, 1998) and Cu₂(OH)VO₄ (Wu *et al.*, 2003) and topologically related to ASbV₂O₈ (*A* = K, Rb, Tl or Cs) (Nandini & Vidyasagar, 1998), adamite-type phases (Zn₂(XO₄)(OH), X⁵⁺ = P, As, V) and the minerals descloizite PbZn(VO₄)(OH) (Bachmann, 1953; Qurashi & Barnes, 1964; Hawthorne & Faggiani, 1979) and tsumcorite PbZn₂(AsO₄)₂(H₂O) (Tillmanns & Gebert, 1973). In descloizite- and adamite-type structures the [ZnV₂O₉]-type chain is linked to four neighbours by sharing one column of tetrahedra with each neighbour. In the title compound the [Zn₃V₂O₉] chain is linked to three neighbours by sharing two columns tetrahedra with one neighbour and one column with each of the other two neighbours (see Figs. 4 and 5 in Wang *et al.*, 1998). If [ZnV₂O₉]-type chain shares two columns of tetrahedra with all neighbours, a two-dimensional layer instead of three-dimensional framework are formed. Such case is found in mineral tsumcorite, where [ZnAs₂O₉] chain is linked by sharing two of AsO₄ tetrahedra with each of its two neighbours thus forming a layered structure eighbor and one column with each of the other two neighbours (see Fig. 6 in Wang *et al.*, 1998). Bond-valence summations for all atoms, calculated using the parameters of Brese & O'Keeffe (1991), give 2.00 v.u. (valence units) for Zn1, 2.00 (1.22/0.78) v.u. for Zn2/Cd2, 2.07 v.u. for Zn3, 5.11 v.u. for V1, 4.90 for V2. For O atoms bond-valence summations are 1.94 v.u. (O1), 1.88 v.u. (O2), 1.99 v.u. (O3), 1.94 v.u. (O4), 1.96 v.u. (O5), 1.90 (O6), 1.32 v.u. (O7) and 1.38 v.u. (O8). Taking into account that the O7 and O8 atoms are the single donors of strong hydrogen bonds toward O4 (H2 forms a bifurcated hydrogen bond to two O4 atoms) and O2, respectively, the bond valences are well balanced.

S2. Experimental

Single crystals of (Zn_{1.86}Cd_{0.14})(OH)VO₄ were obtained as reaction products from mixtures of Cd(OH)₂ (Alfa Products), 2ZnO.2CO₃.4H₂O (Alfa Products), and V₂O₅ (Fluka Chemika 94710, 98%). The mixture was transferred into Teflon vessel and filled to approximately 70% of their inner volume with distilled water (pH of the mixture was 6). Finally it

was enclosed into stainless steel autoclave. The mixture was heated under heating regime with three steps: the autoclaves were heated from 293.15 to 473.15 K (4 h), held at 473.15 K for 192 h, and finally cooled to room temperature within 175 h. At the end of the reaction the pH of the solvent was 6. The reaction products were filtered and washed thoroughly with distilled water. $(\text{Zn}_{1.86}\text{Cd}_{0.14})(\text{OH})\text{VO}_4$ crystallized as transparent colourless needle-like crystals (yield *ca* 65%) and uninvestigated powder (yield *ca* 35%). All crystals are up to 0.2 mm in length.

Qualitative chemical analyses were performed using a Jeol JSM-6400LV scanning electron microscope (SEM) connected with a LINK energy-dispersive X-ray analysis (EDX) unit confirmed the presence of Zn, Cd and V.

S3. Refinement

Studies of several single crystals of $(\text{Zn}_{1.86}\text{Cd}_{0.14})(\text{OH})\text{VO}_4$ all revealed orthorhombic unit cell. A sample exhibiting sharp reflection spots was chosen for data collection. The crystal structure was refined starting from the atomic coordinates of $\text{Zn}_2(\text{OH})\text{VO}_4$ (Wang *et al.*, 1998) using standard procedures. The space-group symmetry $Pnma$ was indicated by systematic absences and intensity statistics, and was confirmed by the structure refinement. Substitutional disorder was apparent and the occupancies of Zn^{2+} and Cd^{2+} were refined keeping the occupancy sum of $\text{Zn}2+\text{Cd}2$ fixed at 2.0 atoms per unit cell to satisfy the charge balance. The atomic coordinates and displacement parameters of Zn2 and Cd2 were kept equal. Occupancy of 72.7 and 27.3% for Zn2 and Cd2, respectively, were obtained. Anisotropic displacement parameters were allowed to vary for all non-H atoms. The H atoms were located from difference Fourier map and refined as riding atoms, with restraints on the O—H bond distance of 0.82 (2) Å and $U_{\text{iso}}(\text{H})$ values at $1.2U_{\text{eq}}(\text{O})$.

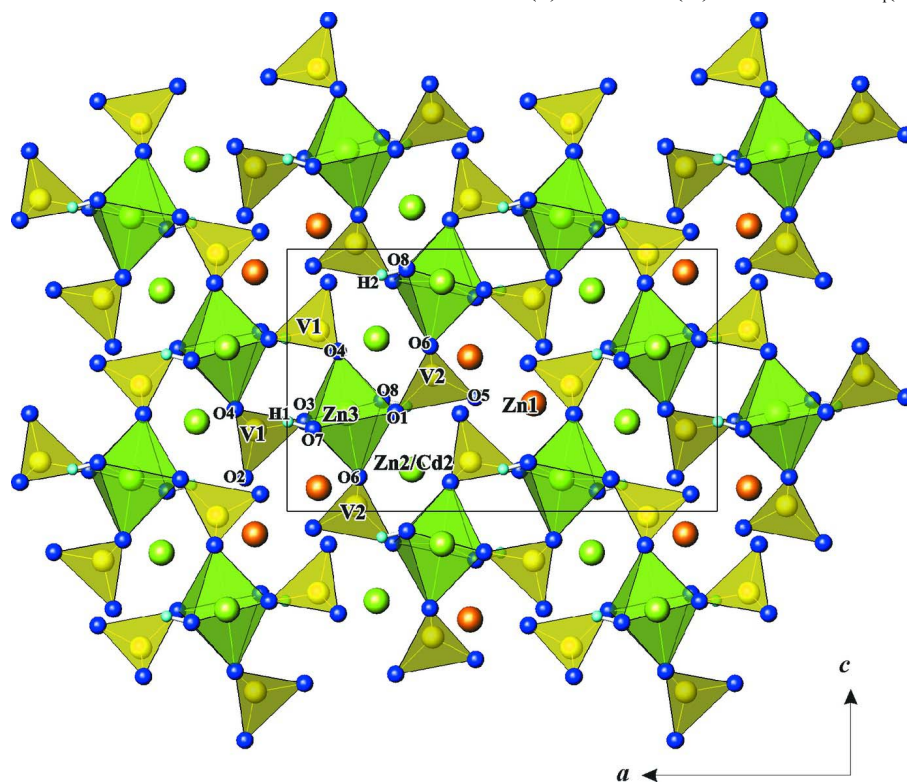


Figure 1

Polyhedral view of the structure of $\text{Zn}_{1.86}\text{Cd}_{0.14}(\text{OH})\text{VO}_4$ along [010].

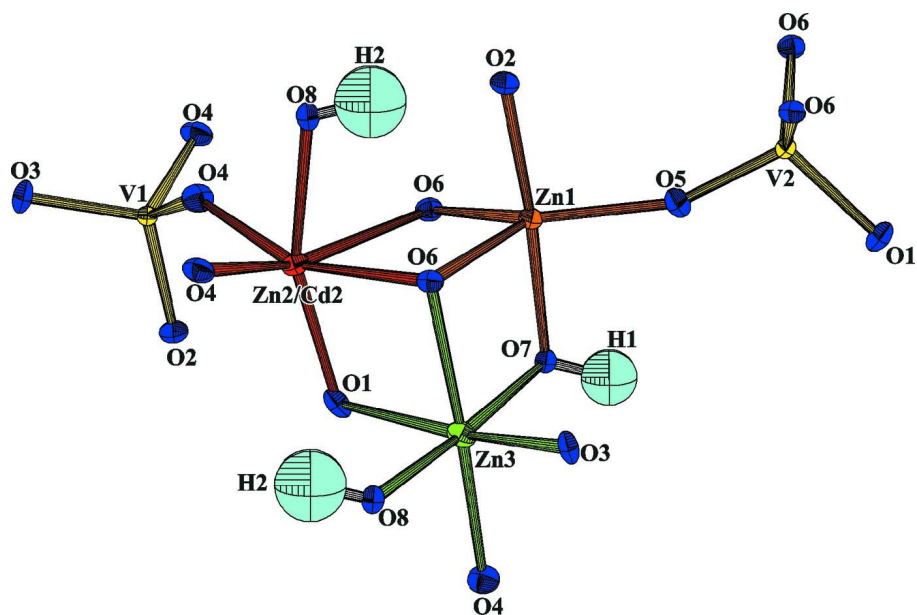


Figure 2

The local coordination of V, Zn and Cd atoms with atomic displacement ellipsoids at 50% probability.

dizinc cadmium hydroxide tetraoxidovanadate

Crystal data

$\text{Zn}_{1.86}\text{Cd}_{0.14}(\text{OH})\text{VO}_4$

$M_r = 535.62$

Orthorhombic, *Pnma*

Hall symbol: -P 2ac 2n

$a = 14.702$ (3) Å

$b = 6.0511$ (12) Å

$c = 8.9460$ (18) Å

$V = 795.8$ (3) Å³

$Z = 4$

$F(000) = 1010$

$D_x = 4.470$ Mg m⁻³

Mo $K\alpha$ radiation, $\lambda = 0.71073$ Å

Cell parameters from 1706 reflections

$\theta = 0.4\text{--}32.6^\circ$

$\mu = 14.00$ mm⁻¹

$T = 293$ K

Prismatic, colourless

$0.18 \times 0.03 \times 0.02$ mm

Data collection

Nonius KappaCCD

diffractometer

Radiation source: fine-focus sealed tube

Graphite monochromator

φ and ω scans

Absorption correction: multi-scan

(Otwinowski & Minor, 1997; Otwinowski *et al.*, 2003)

$T_{\min} = 0.187$, $T_{\max} = 0.767$

5550 measured reflections

1566 independent reflections

1377 reflections with $I > 2\sigma(I)$

$R_{\text{int}} = 0.013$

$\theta_{\max} = 32.6^\circ$, $\theta_{\min} = 2.8^\circ$

$h = -22 \rightarrow 22$

$k = -9 \rightarrow 9$

$l = -13 \rightarrow 13$

Refinement

Refinement on F^2

Least-squares matrix: full

$R[F^2 > 2\sigma(F^2)] = 0.025$

$wR(F^2) = 0.056$

$S = 1.17$

1566 reflections

90 parameters

2 restraints

Primary atom site location: structure-invariant

direct methods

Secondary atom site location: difference Fourier

map

Hydrogen site location: difference Fourier map
 H-atom parameters constrained
 $w = 1/[\sigma^2(F_o^2) + (0.0223P)^2 + 1.9948P]$
 where $P = (F_o^2 + 2F_c^2)/3$
 $(\Delta/\sigma)_{\max} < 0.001$

$\Delta\rho_{\max} = 0.79 \text{ e } \text{\AA}^{-3}$
 $\Delta\rho_{\min} = -0.91 \text{ e } \text{\AA}^{-3}$
 Extinction correction: *SHELXL97* (Sheldrick,
 2008), $F_c^* = kFc[1 + 0.001x Fc^2 \lambda^3 / \sin(2\theta)]^{-1/4}$
 Extinction coefficient: 0.00065 (16)

Special details

Geometry. All esds (except the esd in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell esds are taken into account individually in the estimation of esds in distances, angles and torsion angles; correlations between esds in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell esds is used for estimating esds involving l.s. planes.

Refinement. Refinement of F^2 against ALL reflections. The weighted R-factor wR and goodness of fit S are based on F^2 , conventional R-factors R are based on F, with F set to zero for negative F^2 . The threshold expression of $F^2 > 2\text{sigma}(F^2)$ is used only for calculating R-factors(gt) etc. and is not relevant to the choice of reflections for refinement. R-factors based on F^2 are statistically about twice as large as those based on F, and R-factors based on ALL data will be even larger.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	x	y	z	$U_{\text{iso}}^*/U_{\text{eq}}$	Occ. (<1)
Zn1	0.42606 (3)	0.2500	0.41189 (5)	0.01136 (10)	
Zn2	0.20888 (3)	0.2500	0.34164 (4)	0.01276 (13)	0.726 (5)
Cd2	0.20888 (3)	0.2500	0.34164 (4)	0.01276 (13)	0.274 (5)
Zn3	0.36089 (2)	-0.00355 (5)	0.12498 (3)	0.01342 (9)	
V1	0.42663 (4)	0.2500	0.81152 (7)	0.00849 (12)	
V2	0.16102 (4)	0.2500	-0.02047 (7)	0.00833 (12)	
O1	0.24703 (19)	0.2500	0.1209 (3)	0.0133 (5)	
O2	0.4029 (2)	0.2500	0.6273 (3)	0.0158 (5)	
O3	0.45895 (18)	-0.2500	0.1564 (3)	0.0139 (5)	
O4	0.11984 (14)	-0.0146 (3)	0.3903 (2)	0.0162 (4)	
O5	0.56142 (19)	0.2500	0.4353 (3)	0.0172 (6)	
O6	0.33279 (13)	-0.0120 (3)	0.37011 (19)	0.0122 (3)	
O7	0.43897 (17)	0.2500	0.1853 (3)	0.0101 (5)	
H1	0.4931	0.2500	0.1629	0.012*	
O8	0.22122 (18)	0.2500	0.5759 (3)	0.0114 (5)	
H2	0.2752	0.2500	0.5989	0.014*	

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Zn1	0.01098 (19)	0.0146 (2)	0.00853 (19)	0.000	-0.00083 (14)	0.000
Zn2	0.0144 (2)	0.0143 (2)	0.00956 (19)	0.000	0.00227 (13)	0.000
Cd2	0.0144 (2)	0.0143 (2)	0.00956 (19)	0.000	0.00227 (13)	0.000
Zn3	0.01645 (15)	0.00951 (14)	0.01431 (16)	-0.00237 (11)	-0.00186 (10)	-0.00122 (10)
V1	0.0081 (3)	0.0099 (3)	0.0074 (2)	0.000	0.00004 (19)	0.000
V2	0.0081 (2)	0.0086 (2)	0.0084 (3)	0.000	-0.00083 (19)	0.000
O1	0.0140 (12)	0.0087 (11)	0.0172 (13)	0.000	-0.0071 (10)	0.000
O2	0.0162 (13)	0.0224 (14)	0.0088 (12)	0.000	-0.0011 (10)	0.000
O3	0.0082 (11)	0.0116 (11)	0.0220 (13)	0.000	-0.0041 (10)	0.000
O4	0.0202 (9)	0.0152 (9)	0.0131 (9)	-0.0040 (8)	-0.0016 (7)	-0.0030 (7)
O5	0.0124 (12)	0.0234 (14)	0.0158 (13)	0.000	-0.0033 (10)	0.000

O6	0.0146 (8)	0.0116 (8)	0.0102 (8)	-0.0010 (7)	0.0000 (6)	-0.0006 (6)
O7	0.0085 (11)	0.0098 (11)	0.0118 (11)	0.000	0.0005 (9)	0.000
O8	0.0092 (11)	0.0088 (11)	0.0160 (12)	0.000	-0.0008 (9)	0.000

Geometric parameters (Å, °)

Zn1—O2	1.957 (3)	Zn3—O4 ⁱⁱ	2.1214 (19)
Zn1—O5	2.001 (3)	Zn3—O6	2.2321 (18)
Zn1—O7	2.036 (3)	Zn3—O1	2.271 (2)
Zn1—O6	2.1291 (19)	V1—O2	1.685 (3)
Zn1—O6 ⁱ	2.1291 (19)	V1—O3 ⁱⁱⁱ	1.706 (3)
Zn2—O1	2.053 (3)	V1—O4 ^{iv}	1.7299 (19)
Zn2—O4	2.113 (2)	V1—O4 ^v	1.730 (2)
Zn2—O4 ⁱ	2.113 (2)	V2—O5 ^{vi}	1.650 (3)
Zn2—O6 ⁱ	2.428 (2)	V2—O6 ⁱⁱ	1.7439 (19)
Zn2—O6	2.428 (2)	V2—O6 ^{vii}	1.7439 (19)
Zn3—O8 ⁱⁱ	1.9683 (17)	V2—O1	1.788 (3)
Zn3—O3	2.0931 (19)		
O2—Zn1—O5	94.01 (12)	O8 ⁱⁱ —Zn3—O4 ⁱⁱ	84.27 (9)
O2—Zn1—O7	175.32 (12)	O3—Zn3—O4 ⁱⁱ	94.46 (10)
O5—Zn1—O7	90.67 (11)	O8 ⁱⁱ —Zn3—O6	95.08 (9)
O2—Zn1—O6	93.48 (8)	O3—Zn3—O6	88.82 (10)
O5—Zn1—O6	131.22 (5)	O4 ⁱⁱ —Zn3—O6	176.58 (8)
O7—Zn1—O6	83.41 (7)	O8 ⁱⁱ —Zn3—O1	93.22 (8)
O2—Zn1—O6 ⁱ	93.48 (8)	O3—Zn3—O1	172.38 (10)
O5—Zn1—O6 ⁱ	131.22 (5)	O4 ⁱⁱ —Zn3—O1	92.72 (9)
O7—Zn1—O6 ⁱ	83.41 (7)	O6—Zn3—O1	83.96 (9)
O6—Zn1—O6 ⁱ	96.24 (10)	O2—V1—O3 ⁱⁱⁱ	111.65 (15)
O1—Zn2—O4	111.55 (7)	O2—V1—O4 ^{iv}	108.46 (8)
O1—Zn2—O4 ⁱ	111.55 (7)	O3 ⁱⁱⁱ —V1—O4 ^{iv}	108.71 (9)
O4—Zn2—O4 ⁱ	98.51 (11)	O2—V1—O4 ^v	108.46 (8)
O1—Zn2—O6 ⁱ	84.03 (7)	O3 ⁱⁱⁱ —V1—O4 ^v	108.71 (9)
O4—Zn2—O6 ⁱ	159.66 (7)	O4 ^{iv} —V1—O4 ^v	110.86 (14)
O4 ⁱ —Zn2—O6 ⁱ	87.05 (7)	O5 ^{vi} —V2—O6 ⁱⁱ	107.78 (8)
O1—Zn2—O6	84.03 (7)	O5 ^{vi} —V2—O6 ^{vii}	107.78 (8)
O4—Zn2—O6	87.05 (7)	O6 ⁱⁱ —V2—O6 ^{vii}	111.37 (12)
O4 ⁱ —Zn2—O6	159.66 (7)	O5 ^{vi} —V2—O1	107.51 (14)
O6 ⁱ —Zn2—O6	81.51 (9)	O6 ⁱⁱ —V2—O1	111.10 (8)
O8 ⁱⁱ —Zn3—O3	84.98 (8)	O6 ^{vii} —V2—O1	111.10 (8)

Symmetry codes: (i) $x, -y+1/2, z$; (ii) $-x+1/2, -y, z-1/2$; (iii) $-x+1, -y, -z+1$; (iv) $-x+1/2, y+1/2, z+1/2$; (v) $-x+1/2, -y, z+1/2$; (vi) $x-1/2, y, -z+1/2$; (vii) $-x+1/2, y+1/2, z-1/2$.

Hydrogen-bond geometry (Å, °)

$D-H\cdots A$	$D-H$	$H\cdots A$	$D\cdots A$	$D-H\cdots A$
O7—H1 \cdots O4 ^{viii}	0.89 (2)	2.45 (2)	3.176 (3)	139 (1)

O7—H1...O4 ^{ix}	0.89 (2)	2.45 (2)	3.176 (3)	139 (1)
O8—H2...O2	0.88 (2)	1.84 (2)	2.708 (4)	175 (9)

Symmetry codes: (viii) $x+1/2, -y+1/2, -z+1/2$; (ix) $x+1/2, y, -z+1/2$.