

Acta Crystallographica Section E

Structure Reports

Online

ISSN 1600-5368

Silver(I) diaquanickel(II) catena-borodiphosphate(V) hydrate, (Ag_{0.57}Ni_{0.22})Ni(H₂O)₂[BP₂O₈]·0.67H₂O

Hafid Zouihri,^{a,b} Mohamed Saadi,^b Boujemaa Jaber^{a*} and Lahcen El Ammari^b

^aCentre National pour la Recherche Scientifique et Technique, Division UATRS, Angle Allal AlFassi et Avenue des FAR, Hay Ryad, BP 8027, Rabat, Morocco, and

^bLaboratoire de Chimie du Solide Appliquée, Faculté des Sciences, Université

Mohammed V-Agdal, Avenue Ibn Batouta, BP 1014, Rabat, Morocco

Correspondence e-mail: b_jaber50@yahoo.com

Received 15 July 2011; accepted 21 July 2011

Key indicators: single-crystal X-ray study; $T = 296$ K; mean $\sigma(\text{O}-\text{B}) = 0.003$ Å; disorder in main residue; R factor = 0.028; wR factor = 0.071; data-to-parameter ratio = 26.5.

The structure framework of the title compound, (Ag_{0.57}Ni_{0.22})Ni(H₂O)₂[BP₂O₈]·0.67H₂O, is the same as that of its recently published counterpart AgMg(H₂O)₂[BP₂O₈]·H₂O. In the title structure, the Ag, Ni, B and one O atom are located on special positions (sites symmetry 2). The structure consists of infinite borophosphate helical [BP₂O₈]³⁻ ribbons, built up from alternate BO₄ and PO₄ tetrahedra arranged around the 6₅ screw axes. The vertex-sharing BO₄ and PO₄ tetrahedra form a spiral ribbon of four-membered rings in which BO₄ and PO₄ groups alternate. The ribbons are connected through slightly distorted NiO₄(H₂O)₂ octahedra, four O atoms of which belong to the phosphate groups. The resulting three-dimensional framework is characterized by hexagonal channels running along [001]. However, the main difference between the structures of these two compounds lies in the filling ratio of Wyckoff positions 6*a* and 6*b* in the tunnels. Indeed, in this work, the refinement of the occupancy rate of sites 6*a* and 6*b* shows that the first is occupied by water at 67% and the second is partially occupied by 56.6% of Ag and 21.6% of Ni. In the AgMg(H₂O)₂[BP₂O₈]·H₂O structure, these two sites are completely occupied by H₂O and Ag⁺, respectively. The title structure is stabilized by O—H...O hydrogen bonds between water molecules and O atoms that are part of the helices.

Related literature

For the isotypic Mg analogue, see: Zouihri *et al.* (2011); Menezes *et al.* (2008). For other borophosphates, see: Kniep *et al.* (1998); Ewald *et al.* (2007); Lin *et al.* (2008). For bond valence calculations see: Brown & Altermatt (1985).

Experimental

Crystal data

(Ag_{0.57}Ni_{0.22})Ni(H₂O)₂[BP₂O₈]·0.67H₂O
 $V = 1208.28$ (18) Å³
 $Z = 6$
 $M_r = 381.35$
 Hexagonal, $P6_522$
 $a = 9.3848$ (6) Å
 $c = 15.8411$ (18) Å
 Mo $K\alpha$ radiation
 $\mu = 4.69$ mm⁻¹
 $T = 296$ K
 $0.18 \times 0.12 \times 0.11$ mm

Data collection

Bruker APEXII CCD detector
 diffractometer
 Absorption correction: multi-scan (SADABS; Sheldrick, 1999)
 $T_{\min} = 0.705$, $T_{\max} = 0.741$
 16974 measured reflections
 2043 independent reflections
 1912 reflections with $I > 2\sigma(I)$
 $R_{\text{int}} = 0.037$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.028$
 $wR(F^2) = 0.071$
 $S = 1.08$
 2043 reflections
 77 parameters
 1 restraint
 H-atom parameters constrained
 $\Delta\rho_{\text{max}} = 1.23$ e Å⁻³
 $\Delta\rho_{\text{min}} = -0.59$ e Å⁻³
 Absolute structure: Flack (1983),
 779 Friedel pairs
 Flack parameter: 0.006 (15)

Table 1

Hydrogen-bond geometry (Å, °).

$D-H\cdots A$	$D-H$	$H\cdots A$	$D\cdots A$	$D-H\cdots A$
O5—H5A...O4 ⁱ	0.86	1.90	2.728 (2)	161
O5—H5B...O2	0.86	1.95	2.762 (2)	156
O6—H6A...O3 ⁱⁱ	0.89	2.18	2.819 (5)	128

Symmetry codes: (i) $-x + y, -x + 1, z + \frac{1}{3}$; (ii) $x, x - y + 2, -z + \frac{1}{6}$.

Data collection: APEX2 (Bruker, 2005); cell refinement: SAINT (Bruker, 2005); data reduction: SAINT; program(s) used to solve structure: SHELXS97 (Sheldrick, 2008); program(s) used to refine structure: SHELXL97 (Sheldrick, 2008); molecular graphics: ORTEP-3 for Windows (Farrugia, 1997) and DIAMOND (Brandenburg, 2006); software used to prepare material for publication: WinGX (Farrugia, 1999).

The authors thank the Unit of Support for Technical and Scientific Research (UATRS, CNRST) for the X-ray measurements.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: BR2172).

References

- Brandenburg, K. (2006). DIAMOND. Crystal Impact GbR, Bonn, Germany.
 Brown, I. D. & Altermatt, D. (1985). *Acta Cryst.* **B41**, 244–247.
 Bruker (2005). APEX2 and SAINT. Bruker AXS Inc., Madison, Wisconsin, USA.
 Ewald, B., Huang, Y.-X. & Kniep, R. (2007). *Z. Anorg. Allg. Chem.* **633**, 1517–1540.
 Farrugia, L. J. (1997). *J. Appl. Cryst.* **30**, 565.
 Farrugia, L. J. (1999). *J. Appl. Cryst.* **32**, 837–838.
 Flack, H. D. (1983). *Acta Cryst.* **A39**, 876–881.
 Kniep, R., Engelhardt, H. & Hauf, C. (1998). *Chem. Mater.* **10**, 2930–2934.
 Lin, J.-R., Huang, Y.-X., Wu, Y.-H. & Zhou, Y. (2008). *Acta Cryst.* **E64**, i39–i40.
 Menezes, P. W., Hoffmann, S., Prots, Y. & Kniep, R. (2008). *Z. Kristallogr.* **223**, 333–334.
 Sheldrick, G. M. (1999). SADABS. University of Göttingen, Germany.
 Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.
 Zouihri, H., Saadi, M., Jaber, B. & El Ammari, L. (2011). *Acta Cryst.* **E67**, i39.

supporting information

Acta Cryst. (2011). E67, i44 [doi:10.1107/S160053681102962X]

Silver(I) diaquanickel(II) catena-borodiphosphate(V) hydrate, (Ag_{0.57}Ni_{0.22})Ni(H₂O)₂[BP₂O₈]·0.67H₂O

Hafid Zouihri, Mohamed Saadi, Boujemaa Jaber and Lahcen El Ammari

S1. Comment

A large group of borophosphates is known with a molar ratio of B:P = 1:2 and helical structure type, which consist of loop branched chain anions built from tetrahedral BO₄ and PO₄ units (Kniep *et al.*, 1998; Ewald *et al.*, 2007; Lin *et al.* 2008).

The aim of this work is the synthesis and the crystal structure of a new borophosphate-hydrate (Ag_{0.57}Ni_{0.22})Ni(H₂O)₂[BP₂O₈]·0.67(H₂O), which is isotypic with analogue nickel borophosphates A(I)M(H₂O)₂[BP₂O₈]·H₂O (A(I)=Li, Na, K, NH₄⁺; M(II)=Mg, Mn, Fe, Co, Ni, Cu, Zn, Cd) (Zouihri *et al.*, 2011; Menezes *et al.*, 2008).

The anionic partial structure of the title compound contains one-dimensional infinite helices, [BP₂O₈]³⁻, which are wound around 6₅ axis. It is built up from alternate borate (BO₄) and phosphate (PO₄) tetrahedra, forming a spiral ribbon. The Ni²⁺ cation is six fold coordinated by four oxygen atoms originating from four phosphate groups and two water molecules as shown in Fig.1. The ribbons are interconnected through slightly distorted NiO₄(H₂O)₂ octahedra. The resulting 3-D framework shows hexagonal tunnels running along c direction where water molecules are located (Fig.2).

The +I, +II, +III and +V oxidation states of the Ag, Ni, B and P atoms were confirmed by bond valence sum calculations (Brown & Altermatt, 1985). The calculated values for the Ag⁺, Ni^{II+}, B^{III+} and P^{V+} ions are as expected, *viz.* 1.06, 1.89, 3.06 and 4.97, respectively.

The main difference between the structure of this compound and that of his counterpart AgMg(H₂O)₂[BP₂O₈]·H₂O lies in the filling ratio of the Wyckoff positions 6a and 6b in tunnels. Indeed, in this work, the refinement of the occupancy rate of the following sites (symmetry 2) 6a (x, 0, 0) and 6b (x, 2x, 3/4) (space group P6₅22) shows that the first is occupied by water at 67% and the second is partially occupied by 56.6% of Ag⁺ and 21.6% of Ni²⁺ for a total of 78%. While in the case of AgMg(H₂O)₂[BP₂O₈]·H₂O structure these two sites are completely occupied by H₂O and Ag⁺ respectively.

The structure is stabilized by O—H···O hydrogen bonds between water molecules and O atoms that are part of the helices (Fig.1 and Table 1).

S2. Experimental

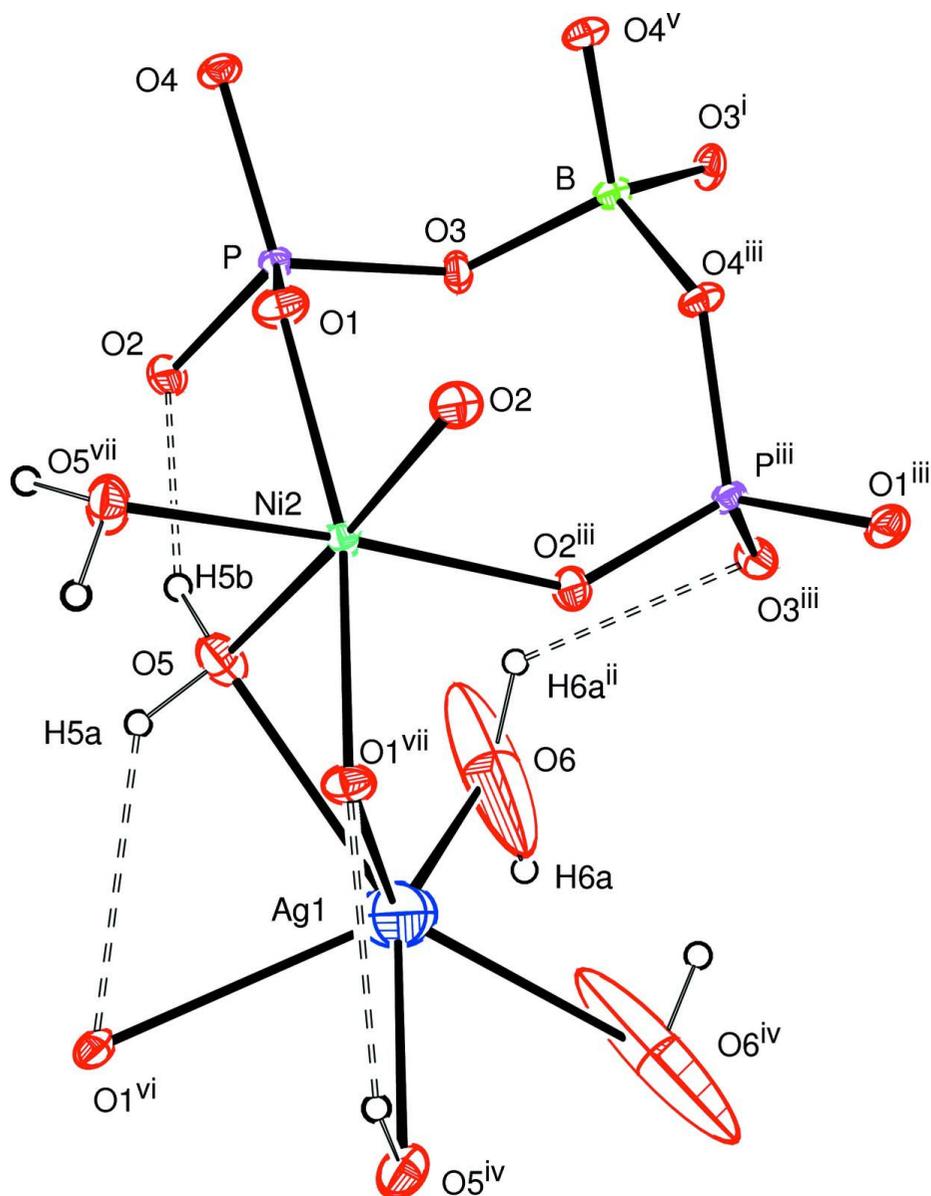
The compound was hydrothermally synthesized at 453 K for 7 days in a 25 ml Teflon-lined steel autoclave from the mixture of NiCO₃, H₃BO₃, H₃PO₄ (85%), AgNO₃ and 5 mL of distilled water in the molar ratio of 1:4:6:1:165. The brilliant colourless octahedral crystals were recovered and washed with hot water, then dried in air.

Except for boron and hydrogen the presence of the elements were additionally confirmed by EDAX measurements.

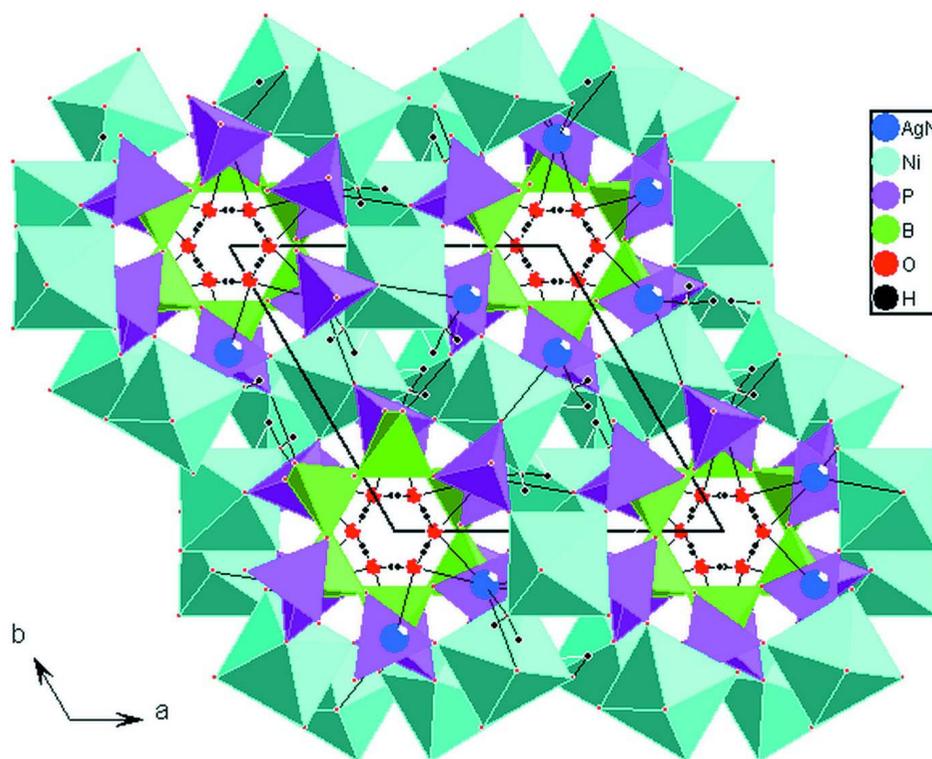
S3. Refinement

The refinement with the sites of Ag and O6 fully occupied led to $R = 0.06$, $R_w = 0.20$ and two peaks in the Fourier difference map $+4.7$ and -3.4 at 0.18 \AA from Ni and at 0.35 \AA from Ag respectively. While the refinement of the occupancy rate of Ag(0.350 (2)) and O6(0.34 (1)) leads to $R = 0.027$, $R_w = 0.07$ and two peaks $+1.21$ and -0.66 at 0.65 \AA and 0.52 \AA from Ag. In the final refinement cycles, the occupancy of O6 was fixed to 0.667. However, the large atomic displacement parameter for this atom indicate disorder or atomic movement along the partially empty tunnel.

The electrical neutrality of the molecule led us to put some nickel in the site of Ag. The refinement of this model leads to the ratio Ag/Ni about 0.47. In the site occupied by a mixture of Ag^+ and Ni^{2+} , the cations are constrained to have the same positional and displacement parameters and the sum of the occupancy rate is restrained to fit the charge balance. The highest peak and the minimum peak in the difference map are at 0.66 \AA and 0.52 \AA respectively from Ag1 atom. The O-bound H atoms were initially located in a difference map and refined with O—H distance restraints of 0.86 (1). In the last cycles they were refined in the riding model approximation with $U_{\text{iso}}(\text{H})$ set to $1.5U_{\text{eq}}(\text{O})$. The 779 Friedel opposite reflections are not merged.


Figure 1

Partial plot of $(\text{Ag}_{0.57}\text{Ni}_{0.22})\text{Ni}(\text{H}_2\text{O})_2[\text{BP}_2\text{O}_8] \cdot 0.67(\text{H}_2\text{O})$ crystal structure showing polyhedra linkage. Displacement ellipsoids are drawn at the 50% probability level. Symmetry codes: (i) $-y + 1, -x + 1, -z + 13/6$; (ii) $y - 1, -x + y, z + 1/6$; (iii) $y - 1, x, -z + 5/3$; (iv) $x, x - y + 1, -z + 11/6$; (v) $-x + y - 1, y, -z + 3/2$; (vi) $-x, -x + y, -z + 4/3$; (vii) $y, x + 1, -z + 5/3$; (viii) $x - y + 1, -y + 2, -z + 2$.

**Figure 2**

Projection view of the $(\text{Ag}_{0.57}\text{Ni}_{0.22})\text{Ni}(\text{H}_2\text{O})_2[\text{BP}_2\text{O}_8]\cdot 0.67(\text{H}_2\text{O})$ framework structure showing tunnel running along c direction where water molecules are located.

Silver diaquanickel(II) catena-borodiphosphate(V) hydrate

Crystal data

$(\text{Ag}_{0.57}\text{Ni}_{0.22})\text{Ni}(\text{H}_2\text{O})_2[\text{BP}_2\text{O}_8]\cdot 0.67\text{H}_2\text{O}$

$M_r = 381.35$

Hexagonal, $P6_322$

Hall symbol: $P\ 65\ 2\ (0\ 0\ 1)$

$a = 9.3848\ (6)\ \text{\AA}$

$c = 15.8411\ (18)\ \text{\AA}$

$V = 1208.28\ (18)\ \text{\AA}^3$

$Z = 6$

$F(000) = 1118$

$D_x = 3.145\ \text{Mg m}^{-3}$

Mo $K\alpha$ radiation, $\lambda = 0.71073\ \text{\AA}$

Cell parameters from 1912 reflections

$\theta = 3.6\text{--}36.9^\circ$

$\mu = 4.69\ \text{mm}^{-1}$

$T = 296\ \text{K}$

Prism, colourless

$0.18 \times 0.12 \times 0.11\ \text{mm}$

Data collection

Bruker APEXII CCD detector
diffractometer

Radiation source: fine-focus sealed tube

Graphite monochromator

ω and φ scans

Absorption correction: multi-scan

(*SADABS*; Sheldrick, 1999)

$T_{\min} = 0.705$, $T_{\max} = 0.741$

16974 measured reflections

2043 independent reflections

1912 reflections with $I > 2\sigma(I)$

$R_{\text{int}} = 0.037$

$\theta_{\max} = 36.9^\circ$, $\theta_{\min} = 3.6^\circ$

$h = -14 \rightarrow 15$

$k = -13 \rightarrow 15$

$l = -25 \rightarrow 26$

Refinement

Refinement on F^2	Secondary atom site location: difference Fourier map
Least-squares matrix: full	Hydrogen site location: difference Fourier map
$R[F^2 > 2\sigma(F^2)] = 0.028$	H-atom parameters constrained
$wR(F^2) = 0.071$	$w = 1/[\sigma^2(F_o^2) + (0.043P)^2 + 0.3826P]$
$S = 1.08$	where $P = (F_o^2 + 2F_c^2)/3$
2043 reflections	$(\Delta/\sigma)_{\max} = 0.001$
77 parameters	$\Delta\rho_{\max} = 1.23 \text{ e } \text{\AA}^{-3}$
1 restraint	$\Delta\rho_{\min} = -0.59 \text{ e } \text{\AA}^{-3}$
Primary atom site location: structure-invariant direct methods	Absolute structure: Flack (1983), 777 Friedel pairs
	Absolute structure parameter: 0.006 (15)

Special details

Geometry. All s.u.'s (except the s.u. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell s.u.'s are taken into account individually in the estimation of s.u.'s in distances, angles and torsion angles; correlations between s.u.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell s.u.'s is used for estimating s.u.'s involving l.s. planes.

Refinement. Refinement of F^2 against all reflections. The weighted R -factor wR and goodness of fit S are based on F^2 , conventional R -factors R are based on F , with F set to zero for negative F^2 . The threshold expression of $F^2 > 2\sigma(F^2)$ is used only for calculating R -factors(gt) etc. and is not relevant to the choice of reflections for refinement. R -factors based on F^2 are statistically about twice as large as those based on F , and R -factors based on all data will be even larger.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	x	y	z	$U_{\text{iso}}^*/U_{\text{eq}}$	Occ. (<1)
Ag1	0.18588 (3)	0.81412 (3)	1.0833	0.03293 (14)	0.567 (2)
Ni1	0.18588 (3)	0.81412 (3)	1.0833	0.03293 (14)	0.2167 (12)
Ni2	0.10776 (4)	0.553882 (19)	0.9167	0.00726 (7)	
P	0.17053 (5)	0.78027 (5)	0.75196 (3)	0.00600 (8)	
B	-0.15242 (15)	0.6952 (3)	0.7500	0.0068 (4)	
O1	0.13668 (19)	0.61873 (17)	0.79010 (8)	0.0111 (2)	
O2	0.31964 (17)	0.93224 (18)	0.78587 (8)	0.0111 (2)	
O3	0.02186 (17)	0.80809 (17)	0.76714 (8)	0.0088 (2)	
O4	0.18247 (16)	0.76331 (16)	0.65399 (8)	0.0084 (2)	
O5	0.29029 (19)	0.79869 (19)	0.94467 (10)	0.0150 (3)	
H5A	0.3751	0.8066	0.9698	0.022*	
H5B	0.3290	0.8571	0.8997	0.022*	
O6	0.1235 (7)	1.0000	1.0000	0.135 (5)	0.67
H6A	0.1238	1.0524	1.0471	0.203*	0.67

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Ag1	0.0385 (2)	0.0385 (2)	0.0261 (2)	0.0225 (2)	-0.00270 (16)	-0.00270 (16)
Ni1	0.0385 (2)	0.0385 (2)	0.0261 (2)	0.0225 (2)	-0.00270 (16)	-0.00270 (16)
Ni2	0.00732 (13)	0.00740 (10)	0.00704 (11)	0.00366 (6)	0.000	0.00101 (9)
P	0.00595 (16)	0.00698 (16)	0.00472 (14)	0.00296 (13)	0.00006 (13)	0.00092 (13)
B	0.0085 (7)	0.0070 (9)	0.0046 (8)	0.0035 (4)	0.0006 (7)	0.000

O1	0.0162 (6)	0.0098 (5)	0.0080 (5)	0.0069 (5)	0.0009 (4)	0.0024 (4)
O2	0.0068 (5)	0.0109 (6)	0.0104 (5)	0.0004 (4)	-0.0005 (4)	-0.0007 (4)
O3	0.0053 (5)	0.0102 (5)	0.0107 (5)	0.0037 (4)	-0.0001 (4)	-0.0022 (4)
O4	0.0111 (5)	0.0107 (5)	0.0051 (4)	0.0066 (5)	0.0010 (4)	0.0016 (4)
O5	0.0112 (6)	0.0138 (6)	0.0159 (6)	0.0033 (5)	-0.0028 (5)	0.0037 (5)
O6	0.045 (2)	0.112 (7)	0.271 (12)	0.056 (3)	-0.077 (4)	-0.154 (8)

Geometric parameters (Å, °)

Ag1—O5	2.4389 (17)	Ni2—O5	2.1152 (16)
Ag1—O5 ⁱ	2.4389 (17)	Ni2—O5 ⁱⁱ	2.1152 (16)
Ag1—O6	2.480 (4)	P—O1	1.5108 (14)
Ag1—O6 ⁱ	2.480 (4)	P—O2	1.5117 (15)
Ag1—O1 ⁱⁱ	2.6569 (15)	P—O3	1.5611 (14)
Ag1—O1 ⁱⁱⁱ	2.6569 (15)	P—O4	1.5698 (13)
Ni2—O2 ^{iv}	2.0610 (14)	B—O3 ^{vi}	1.462 (2)
Ni2—O2 ^v	2.0610 (14)	B—O3	1.462 (2)
Ni2—O1 ⁱⁱ	2.0733 (13)	B—O4 ^{vii}	1.477 (2)
Ni2—O1	2.0733 (13)	B—O4 ^{iv}	1.477 (2)
O5—Ag1—O5 ⁱ	132.92 (8)	O2 ^v —Ni2—O5 ⁱⁱ	88.46 (7)
O5—Ag1—O6	78.79 (10)	O1 ⁱⁱ —Ni2—O5 ⁱⁱ	88.16 (6)
O5 ⁱ —Ag1—O6	147.60 (8)	O1—Ni2—O5 ⁱⁱ	82.71 (6)
O5—Ag1—O6 ⁱ	147.60 (8)	O5—Ni2—O5 ⁱⁱ	90.93 (10)
O5 ⁱ —Ag1—O6 ⁱ	78.79 (10)	O1—P—O2	115.82 (8)
O6—Ag1—O6 ⁱ	71.1 (2)	O1—P—O3	110.43 (8)
O2 ^{iv} —Ni2—O2 ^v	92.40 (9)	O2—P—O3	105.70 (8)
O2 ^{iv} —Ni2—O1 ⁱⁱ	87.94 (5)	O1—P—O4	106.47 (7)
O2 ^v —Ni2—O1 ⁱⁱ	101.12 (6)	O2—P—O4	111.57 (8)
O2 ^{iv} —Ni2—O1	101.12 (6)	O3—P—O4	106.52 (7)
O2 ^v —Ni2—O1	87.94 (5)	O3 ^{vi} —B—O3	102.25 (19)
O1 ⁱⁱ —Ni2—O1	166.98 (9)	O3 ^{vi} —B—O4 ^{vii}	112.61 (8)
O2 ^{iv} —Ni2—O5	88.46 (7)	O3—B—O4 ^{vii}	113.91 (7)
O2 ^v —Ni2—O5	176.10 (6)	O3 ^{vi} —B—O4 ^{iv}	113.91 (7)
O1 ⁱⁱ —Ni2—O5	82.71 (6)	O3—B—O4 ^{iv}	112.61 (8)
O1—Ni2—O5	88.16 (6)	O4 ^{vii} —B—O4 ^{iv}	102.02 (18)
O2 ^{iv} —Ni2—O5 ⁱⁱ	176.10 (6)		

Symmetry codes: (i) $-y+1, -x+1, -z+13/6$; (ii) $x, x-y+1, -z+11/6$; (iii) $-x+y, -x+1, z+1/3$; (iv) $y-1, -x+y, z+1/6$; (v) $y-1, x, -z+5/3$; (vi) $-x+y-1, y, -z+3/2$; (vii) $-x, -x+y, -z+4/3$.

Hydrogen-bond geometry (Å, °)

<i>D</i> —H \cdots <i>A</i>	<i>D</i> —H	H \cdots <i>A</i>	<i>D</i> \cdots <i>A</i>	<i>D</i> —H \cdots <i>A</i>
O5—H5A \cdots O4 ⁱⁱⁱ	0.86	1.90	2.728 (2)	161
O5—H5B \cdots O2	0.86	1.95	2.762 (2)	156
O6—H6A \cdots O3 ^{viii}	0.89	2.18	2.819 (5)	128

Symmetry codes: (iii) $-x+y, -x+1, z+1/3$; (viii) $x, x-y+2, -z+11/6$.