

Acta Crystallographica Section E

Structure Reports

Online

ISSN 1600-5368

Trisodium scandium bis(orthoborate)

Jinzhong Fang,^a Xinyuan Zhang,^{b,c} Jiyong Yao,^b Guochun Zhang^{b*} and Kunpeng Wang^a

^aNational Center for Materials Service Safety, University of Science and Technology Beijing, Beijing 100083, People's Republic of China, ^bKey Laboratory of Functional Crystal and Laser Technology, Technical Institute of Physics and Chemistry, Chinese Academy of Sciences, Beijing 100190, People's Republic of China, and ^cGraduate University of Chinese Academy of Sciences, Beijing 100049, People's Republic of China

Correspondence e-mail: gc Zhang@mail.ipc.ac.cn

Received 30 December 2011; accepted 5 April 2012

Key indicators: single-crystal X-ray study; $T = 153$ K; mean $\sigma(\text{B}-\text{O}) = 0.002$ Å; R factor = 0.027; wR factor = 0.067; data-to-parameter ratio = 14.6.

Single crystals of trisodium scandium bis(orthoborate), $\text{Na}_3\text{Sc}(\text{BO}_3)_2$, have been obtained by spontaneous crystallization from an $\text{Na}_2\text{O}-\text{Sc}_2\text{O}_3-\text{B}_2\text{O}_3$ melt. The crystal structure features a three-dimensional framework composed of planar $[\text{BO}_3]^{3-}$ groups and distorted ScO_6 octahedra with Na atoms in the cavities. The Sc atom occupies a special position (Wyckoff position $2b$, site symmetry $\bar{1}$) and of the two Na atoms, one occupies a special position (Wyckoff position $2c$, site symmetry $\bar{1}$).

Related literature

For $\text{Na}_3\text{Sc}_2(\text{BO}_3)_3$, see: Zhang *et al.* (2006) and for NaScB_2O_5 , see: Becker & Held (2001). For similar structures, see: Cai *et al.* (2011). The program *STRUCTURE TIDY* (Gelato & Parthé, 1987) was used to standardize the structural data.

Experimental

Crystal data

 $\text{Na}_3\text{Sc}(\text{BO}_3)_2$ $M_r = 231.55$

Monoclinic, $P2_1/c$
 $a = 5.0739$ (10) Å
 $b = 8.9930$ (18) Å
 $c = 7.029$ (2) Å
 $\beta = 123.60$ (2)°
 $V = 267.14$ (11) Å³

$Z = 2$
 Mo $K\alpha$ radiation
 $\mu = 1.58$ mm⁻¹
 $T = 153$ K
 $0.27 \times 0.14 \times 0.09$ mm

Data collection

Rigaku Saturn724+ diffractometer
 Absorption correction: multi-scan
 (*ABSCOR*; Higashi, 1995)
 $T_{\min} = 0.824$, $T_{\max} = 1$

3029 measured reflections
 847 independent reflections
 760 reflections with $I > 2\sigma(I)$
 $R_{\text{int}} = 0.026$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.027$
 $wR(F^2) = 0.067$
 $S = 1.22$
 847 reflections

58 parameters
 $\Delta\rho_{\text{max}} = 0.35$ e Å⁻³
 $\Delta\rho_{\text{min}} = -0.62$ e Å⁻³

Data collection: *CrystalClear* (Rigaku, 2008); cell refinement: *CrystalClear*; data reduction: *CrystalClear*; program(s) used to solve structure: *SHELXS97* (Sheldrick, 2008); program(s) used to refine structure: *SHELXL97* (Sheldrick, 2008); molecular graphics: *DIAMOND* (Brandenburg, 2006); software used to prepare material for publication: *SHELXL97*.

The authors thank Professor Kaibei Yu, of the State Key Laboratory of Explosion Science and Technology of Beijing Institute of Technology, for collecting the single-crystal X-ray diffraction data. This work was supported financially by the National Natural Science Foundation of China (Nos. 91022026 and 51132005) and the Beijing Natural Science Foundation (No. 2102044).

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: FI2123).

References

- Becker, P. & Held, P. (2001). *Z. Kristallogr. New Cryst. Struct.* **216**, 35.
 Brandenburg, K. (2006). *DIAMOND*. Crystal Impact GbR, Bonn, Germany.
 Cai, G. M., Tao, X. M., Su, L. M., Zheng, F., Yi, D. Q., Chen, X. L. & Jin, Z. P. (2011). *J. Solid State Chem.* **184**, 115–122.
 Gelato, L. M. & Parthé, E. (1987). *J. Appl. Cryst.* **20**, 139–143.
 Higashi, T. (1995). *ABSCOR*. Rigaku Corporation, Tokyo, Japan.
 Rigaku (2008). *CrystalClear*. Rigaku Corporation, Tokyo, Japan.
 Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.
 Zhang, Y., Ye, N. & Keszler, D. A. (2006). *Acta Cryst.* **E62**, i266–i268.

supporting information

Acta Cryst. (2012). E68, i36 [doi:10.1107/S1600536812015061]

Trisodium scandium bis(orthoborate)

Jinzhi Fang, Xinyuan Zhang, Jiyong Yao, Guochun Zhang and Kunpeng Wang

S1. Comment

In efforts to identify new borates as optical materials or catalysts, investigations have been carried out in the Na₂O—Sc₂O₃—B₂O₃ system, in which, two phases are already known, *viz.* Na₃Sc₂(BO₃)₃ (Zhang *et al.*, 2006) and NaScB₂O₅ (Becker & Held, 2001). Here, we report a new compound, Na₃Sc(BO₃)₂.

The fundamental building units of the title compounds are triangular [BO₃]³⁻ groups and irregular ScO₆ octahedra. Each [BO₃]³⁻ group connects to three ScO₆ octahedra, and each ScO₆ octahedron are connected to six [BO₃]³⁻ groups by corner sharing, thereby constructing a three-dimensional framework whose cavities are filled with Na⁺ cations. Sc occupies a special position (Wyckoff position 2b, site symmetry -1), of the two Na atoms, one occupies a special positions (Wyckoff position 2c, site symmetry -1). Na₂ occupies a general position. The B—O bond lengths range from 1.3708 (17) to 1.3802 (19) Å, and the mean O—B—O bond angles are equal to 120 (12)° which indicates that the [BO₃]³⁻ groups are almost planar. The Sc³⁺ cation is six-coordinated by oxygen atoms to form a distorted ScO₆ octahedron with Sc—O bond lengths ranging from 2.0765 (11) to 2.1285 (11) Å. The Na atoms appear in two crystallographically different environments. The Na1 and Na2 atoms are six- and eight-coordinated by oxygen atoms, respectively. The Na—O bond lengths range from 2.3448 (12) to 2.8515 (15) Å. These abovementioned values are normal in borates such as Na₃Sc₂(BO₃)₃ and NaScB₂O₅.

The structure of the title compound is closely related to Li₃Sc(BO₃)₃ (Cai *et al.*, 2011) which is crystallized in the same space group. The crystal structure of Li₃Sc(BO₃)₃ could also be characterized as a three-dimensional framework constructed by planar [BO₃]³⁻ groups and irregular ScO₆ octahedra. Both Na and Li atoms occupy two crystallographically independent sites, but Li atoms are four-coordinated by oxygen atoms due to their small ionic radii.

S2. Experimental

The composition of the mixture for crystal growth was 10:1:10 of Na₂CO₃ (analytically pure), Sc₂O₃ (analytically pure), and B₂O₃ (analytically pure). This mixture was heated in a platinum crucible to 1373 K, held at this temperature for several hours, and then the transparent melt was cooled slowly from 1373 K to 1223 K at 3 K h⁻¹. Upon further cooling to room temperature, block shaped colorless crystals were obtained.

S3. Refinement

The structure was solved with the direct methods program *SHELXS97* and refined with the least-squares program *SHELXL97* of the *SHELXTL*.PC suite of programs. The final refinement included anisotropic displacement parameters and a secondary extinction correction. The program *STRUCTURE TIDY* (Gelato & Parthé, 1987) was then employed to standardize the atomic coordinates.

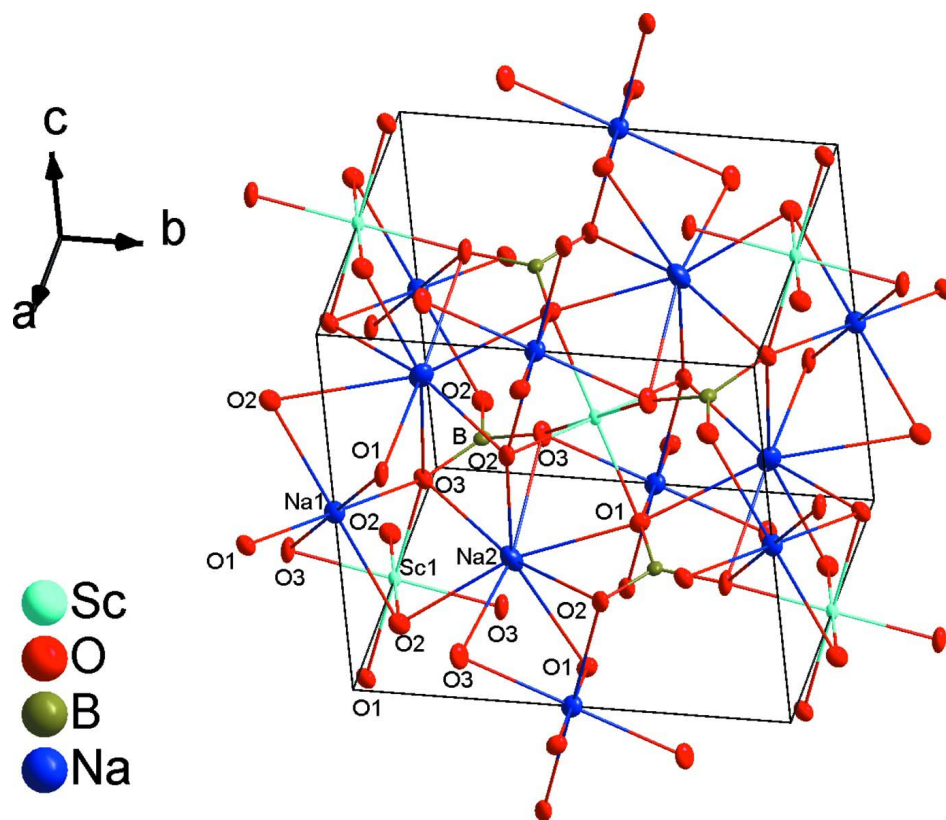
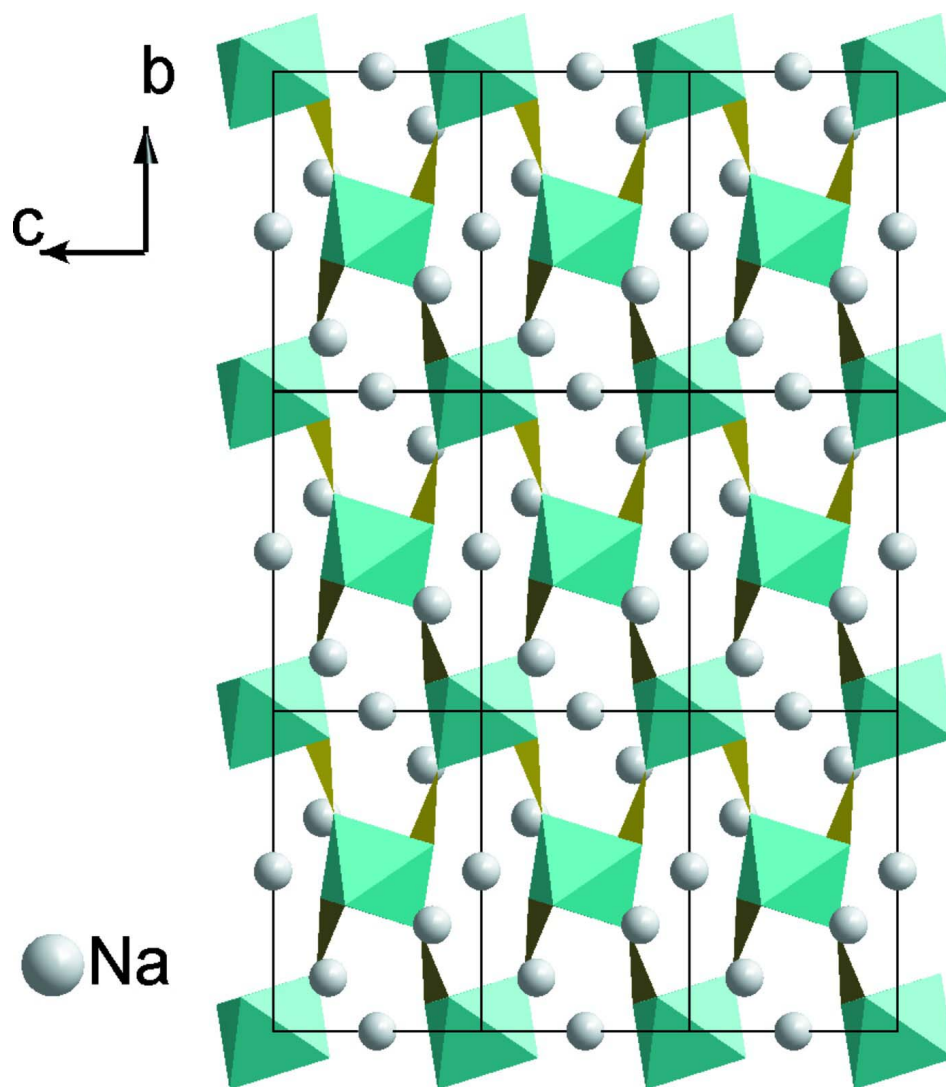


Figure 1

The structure of $\text{Na}_3\text{Sc}(\text{BO}_3)_2$ with displacement ellipsoids drawn at the 80% probability level.

**Figure 2**

The structure of $\text{Na}_3\text{Sc}(\text{BO}_3)_2$ given in the polyhedral description. $[\text{ScO}_6]$ octahedra are aqua, and $[\text{BO}_3]$ units are dark yellow.

Trisodium scandium bis(orthoborate)

Crystal data

$\text{Na}_3\text{Sc}(\text{BO}_3)_2$

$M_r = 231.55$

Monoclinic, $P2_1/c$

Hall symbol: $-P\ 2_1/c$

$a = 5.0739$ (10) Å

$b = 8.9930$ (18) Å

$c = 7.029$ (2) Å

$\beta = 123.60$ (2)°

$V = 267.14$ (11) Å³

$Z = 2$

$F(000) = 224$

$D_x = 2.879$ Mg m⁻³

Mo $K\alpha$ radiation, $\lambda = 0.71073$ Å

Cell parameters from 2093 reflections

$\theta = 3.6\text{--}31.0^\circ$

$\mu = 1.58$ mm⁻¹

$T = 153$ K

Prism, colourless

$0.27 \times 0.14 \times 0.09$ mm

Data collection

Rigaku Saturn724+ diffractometer	3029 measured reflections
Radiation source: fine-focus sealed tube	847 independent reflections
Graphite monochromator	760 reflections with $I > 2\sigma(I)$
Detector resolution: 28.5714 pixels mm ⁻¹	$R_{\text{int}} = 0.026$
ω scans	$\theta_{\text{max}} = 30.9^\circ$, $\theta_{\text{min}} = 4.2^\circ$
Absorption correction: multi-scan (<i>ABSCOR</i> ; Higashi, 1995)	$h = -7 \rightarrow 6$
$T_{\text{min}} = 0.824$, $T_{\text{max}} = 1.000$	$k = -13 \rightarrow 13$
	$l = -10 \rightarrow 8$

Refinement

Refinement on F^2	Primary atom site location: structure-invariant direct methods
Least-squares matrix: full	Secondary atom site location: difference Fourier map
$R[F^2 > 2\sigma(F^2)] = 0.027$	$w = 1/[\sigma^2(F_o^2) + (0.030P)^2]$
$wR(F^2) = 0.067$	where $P = (F_o^2 + 2F_c^2)/3$
$S = 1.22$	$(\Delta/\sigma)_{\text{max}} < 0.001$
847 reflections	$\Delta\rho_{\text{max}} = 0.35 \text{ e } \text{\AA}^{-3}$
58 parameters	$\Delta\rho_{\text{min}} = -0.62 \text{ e } \text{\AA}^{-3}$
0 restraints	

Special details

Geometry. All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

Refinement. Refinement of F^2 against ALL reflections. The weighted R -factor wR and goodness of fit S are based on F^2 , conventional R -factors R are based on F , with F set to zero for negative F^2 . The threshold expression of $F^2 > \sigma(F^2)$ is used only for calculating R -factors(gt) etc. and is not relevant to the choice of reflections for refinement. R -factors based on F^2 are statistically about twice as large as those based on F , and R -factors based on ALL data will be even larger.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	x	y	z	$U_{\text{iso}}^*/U_{\text{eq}}$
Sc1	0.5000	0.0000	0.0000	0.00372 (11)
O1	0.4755 (2)	0.08396 (12)	0.27296 (17)	0.0073 (2)
O2	-0.0650 (2)	0.10637 (11)	0.15507 (18)	0.0076 (2)
O3	0.2676 (2)	0.31781 (12)	0.29120 (18)	0.0086 (2)
B1	0.2264 (4)	0.16821 (18)	0.2386 (2)	0.0052 (3)
Na1	1.0000	0.0000	0.5000	0.00806 (18)
Na2	0.73774 (13)	0.33234 (8)	0.23583 (10)	0.01153 (16)

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Sc1	0.00282 (19)	0.00312 (18)	0.00441 (18)	-0.00007 (12)	0.00150 (14)	-0.00011 (12)
O1	0.0057 (5)	0.0083 (5)	0.0072 (5)	0.0011 (4)	0.0030 (4)	-0.0006 (4)
O2	0.0054 (5)	0.0077 (5)	0.0087 (5)	-0.0022 (4)	0.0033 (4)	-0.0023 (4)
O3	0.0084 (5)	0.0047 (5)	0.0104 (5)	-0.0016 (4)	0.0038 (4)	-0.0021 (4)
B1	0.0066 (7)	0.0054 (7)	0.0039 (7)	-0.0007 (5)	0.0032 (6)	-0.0007 (5)
Na1	0.0061 (4)	0.0092 (4)	0.0065 (4)	0.0002 (3)	0.0020 (3)	-0.0004 (3)

Na2	0.0100 (3)	0.0111 (3)	0.0143 (3)	0.0014 (2)	0.0072 (3)	-0.0017 (2)
-----	------------	------------	------------	------------	------------	-------------

Geometric parameters (Å, °)

Sc1—O2 ⁱ	2.0765 (11)	O3—Na2	2.6242 (12)
Sc1—O2 ⁱⁱ	2.0765 (11)	O3—Na2 ^{vii}	3.0050 (15)
Sc1—O3 ⁱⁱⁱ	2.0769 (11)	B1—Na2 ^{viii}	2.8761 (17)
Sc1—O3 ^{iv}	2.0769 (11)	B1—Na2 ^{vii}	2.9851 (19)
Sc1—O1	2.1285 (11)	B1—Na2 ^{ix}	2.9897 (19)
Sc1—O1 ^v	2.1285 (11)	B1—Na2	2.9945 (17)
Sc1—Na1 ^{vi}	2.9866 (11)	B1—Na2 ^{iv}	3.0253 (19)
Sc1—Na1	2.9866 (11)	B1—Na1 ^{viii}	3.0528 (16)
Sc1—Na2 ^{iv}	3.1073 (8)	Na1—O1 ^{xi}	2.3448 (12)
Sc1—Na2 ⁱⁱⁱ	3.1073 (8)	Na1—O3 ^{iv}	2.3752 (12)
Sc1—Na2 ^v	3.3049 (9)	Na1—O3 ^{xii}	2.3752 (12)
Sc1—Na2	3.3049 (9)	Na1—O2 ^{xiii}	2.4529 (12)
O1—B1	1.3758 (17)	Na1—O2 ⁱⁱ	2.4529 (12)
O1—Na1	2.3448 (12)	Na1—Sc1 ^{xiv}	2.9866 (11)
O1—Na2 ^{iv}	2.4942 (13)	Na1—Na2 ^{vii}	3.0386 (8)
O1—Na2	2.6855 (12)	Na1—Na2 ^{xv}	3.0386 (8)
O1—Na2 ^{vii}	2.8515 (15)	Na1—B1 ^{xiii}	3.0528 (16)
O2—B1	1.3708 (17)	Na1—B1 ⁱⁱ	3.0528 (16)
O2—Sc1 ^{viii}	2.0765 (11)	Na2—O2 ⁱⁱ	2.4662 (12)
O2—Na1 ^{viii}	2.4529 (12)	Na2—O1 ^x	2.4942 (13)
O2—Na2 ^{viii}	2.4662 (12)	Na2—O3 ⁱⁱ	2.4976 (12)
O2—Na2 ^{ix}	2.5933 (14)	Na2—O2 ^{xii}	2.5933 (14)
O2—Na2 ^{iv}	2.8301 (13)	Na2—O2 ^x	2.8301 (13)
O3—B1	1.3802 (19)	Na2—O1 ⁱⁱⁱ	2.8515 (15)
O3—Sc1 ^x	2.0769 (11)	Na2—B1 ⁱⁱ	2.8761 (17)
O3—Na1 ^x	2.3752 (12)	Na2—B1 ⁱⁱⁱ	2.985 (2)
O3—Na2 ^{viii}	2.4976 (12)	Na2—B1 ^{xii}	2.990 (2)
O2 ⁱ —Sc1—O2 ⁱⁱ	180.00 (5)	O1—B1—Na1 ^{viii}	103.69 (9)
O2 ⁱ —Sc1—O3 ⁱⁱⁱ	88.26 (4)	O3—B1—Na1 ^{viii}	111.93 (9)
O2 ⁱⁱ —Sc1—O3 ⁱⁱⁱ	91.74 (4)	Na2 ^{viii} —B1—Na1 ^{viii}	69.41 (4)
O2 ⁱ —Sc1—O3 ^{iv}	91.74 (4)	Na2 ^{vii} —B1—Na1 ^{viii}	70.56 (4)
O2 ⁱⁱ —Sc1—O3 ^{iv}	88.26 (4)	Na2 ^{ix} —B1—Na1 ^{viii}	111.63 (5)
O3 ⁱⁱⁱ —Sc1—O3 ^{iv}	180.00 (4)	Na2—B1—Na1 ^{viii}	149.78 (6)
O2 ⁱ —Sc1—O1	93.52 (4)	Na2 ^{iv} —B1—Na1 ^{viii}	59.99 (3)
O2 ⁱⁱ —Sc1—O1	86.48 (4)	O1—Na1—O1 ^{xi}	180.0
O3 ⁱⁱⁱ —Sc1—O1	93.65 (4)	O1—Na1—O3 ^{iv}	75.13 (4)
O3 ^{iv} —Sc1—O1	86.35 (4)	O1 ^{xi} —Na1—O3 ^{iv}	104.87 (4)
O2 ⁱ —Sc1—O1 ^v	86.48 (4)	O1—Na1—O3 ^{xii}	104.87 (4)
O2 ⁱⁱ —Sc1—O1 ^v	93.52 (4)	O1 ^{xi} —Na1—O3 ^{xii}	75.13 (4)
O3 ⁱⁱⁱ —Sc1—O1 ^v	86.35 (4)	O3 ^{iv} —Na1—O3 ^{xii}	180.0
O3 ^{iv} —Sc1—O1 ^v	93.65 (4)	O1—Na1—O2 ^{xiii}	106.23 (4)
O1—Sc1—O1 ^v	180.00 (2)	O1 ^{xi} —Na1—O2 ^{xiii}	73.77 (4)
O2 ⁱ —Sc1—Na1 ^{vi}	54.43 (3)	O3 ^{iv} —Na1—O2 ^{xiii}	106.43 (4)

O2 ⁱⁱ —Sc1—Na1 ^{vi}	125.57 (3)	O3 ^{xii} —Na1—O2 ^{xiii}	73.57 (4)
O3 ⁱⁱⁱ —Sc1—Na1 ^{vi}	52.27 (3)	O1—Na1—O2 ⁱⁱ	73.77 (4)
O3 ^{iv} —Sc1—Na1 ^{vi}	127.73 (3)	O1 ^{xi} —Na1—O2 ⁱⁱ	106.23 (4)
O1—Sc1—Na1 ^{vi}	128.72 (3)	O3 ^{iv} —Na1—O2 ⁱⁱ	73.57 (4)
O1 ^v —Sc1—Na1 ^{vi}	51.28 (3)	O3 ^{xii} —Na1—O2 ⁱⁱ	106.43 (4)
O2 ⁱ —Sc1—Na1	125.57 (3)	O2 ^{xiii} —Na1—O2 ⁱⁱ	180.0
O2 ⁱⁱ —Sc1—Na1	54.43 (3)	O1—Na1—Sc1 ^{xiv}	134.91 (3)
O3 ⁱⁱⁱ —Sc1—Na1	127.73 (3)	O1 ^{xi} —Na1—Sc1 ^{xiv}	45.09 (3)
O3 ^{iv} —Sc1—Na1	52.27 (3)	O3 ^{iv} —Na1—Sc1 ^{xiv}	136.25 (3)
O1—Sc1—Na1	51.28 (3)	O3 ^{xii} —Na1—Sc1 ^{xiv}	43.75 (3)
O1 ^v —Sc1—Na1	128.72 (3)	O2 ^{xiii} —Na1—Sc1 ^{xiv}	43.52 (3)
Na1 ^{vi} —Sc1—Na1	180.0	O2 ⁱⁱ —Na1—Sc1 ^{xiv}	136.48 (3)
O2 ⁱ —Sc1—Na2 ^{iv}	55.86 (4)	O1—Na1—Sc1	45.09 (3)
O2 ⁱⁱ —Sc1—Na2 ^{iv}	124.14 (3)	O1 ^{xi} —Na1—Sc1	134.91 (3)
O3 ⁱⁱⁱ —Sc1—Na2 ^{iv}	123.28 (3)	O3 ^{iv} —Na1—Sc1	43.75 (3)
O3 ^{iv} —Sc1—Na2 ^{iv}	56.72 (3)	O3 ^{xii} —Na1—Sc1	136.25 (3)
O1—Sc1—Na2 ^{iv}	52.98 (3)	O2 ^{xiii} —Na1—Sc1	136.48 (3)
O1 ^v —Sc1—Na2 ^{iv}	127.02 (3)	O2 ⁱⁱ —Na1—Sc1	43.52 (3)
Na1 ^{vi} —Sc1—Na2 ^{iv}	110.20 (2)	Sc1 ^{xiv} —Na1—Sc1	180.0
Na1—Sc1—Na2 ^{iv}	69.80 (2)	O1—Na1—Na2 ^{vii}	62.41 (3)
O2 ⁱ —Sc1—Na2 ⁱⁱⁱ	124.14 (4)	O1 ^{xi} —Na1—Na2 ^{vii}	117.59 (3)
O2 ⁱⁱ —Sc1—Na2 ⁱⁱⁱ	55.86 (4)	O3 ^{iv} —Na1—Na2 ^{vii}	126.75 (3)
O3 ⁱⁱⁱ —Sc1—Na2 ⁱⁱⁱ	56.72 (3)	O3 ^{xii} —Na1—Na2 ^{vii}	53.25 (3)
O3 ^{iv} —Sc1—Na2 ⁱⁱⁱ	123.28 (3)	O2 ^{xiii} —Na1—Na2 ^{vii}	60.94 (3)
O1—Sc1—Na2 ⁱⁱⁱ	127.02 (3)	O2 ⁱⁱ —Na1—Na2 ^{vii}	119.06 (3)
O1 ^v —Sc1—Na2 ⁱⁱⁱ	52.98 (3)	Sc1 ^{xiv} —Na1—Na2 ^{vii}	72.62 (2)
Na1 ^{vi} —Sc1—Na2 ⁱⁱⁱ	69.80 (2)	Sc1—Na1—Na2 ^{vii}	107.38 (2)
Na1—Sc1—Na2 ⁱⁱⁱ	110.20 (2)	O1—Na1—Na2 ^{xv}	117.59 (3)
Na2 ^{iv} —Sc1—Na2 ⁱⁱⁱ	180.00 (3)	O1 ^{xi} —Na1—Na2 ^{xv}	62.41 (3)
O2 ⁱ —Sc1—Na2 ^v	48.18 (3)	O3 ^{iv} —Na1—Na2 ^{xv}	53.25 (3)
O2 ⁱⁱ —Sc1—Na2 ^v	131.82 (3)	O3 ^{xii} —Na1—Na2 ^{xv}	126.75 (3)
O3 ⁱⁱⁱ —Sc1—Na2 ^v	116.88 (4)	O2 ^{xiii} —Na1—Na2 ^{xv}	119.06 (3)
O3 ^{iv} —Sc1—Na2 ^v	63.12 (4)	O2 ⁱⁱ —Na1—Na2 ^{xv}	60.94 (3)
O1—Sc1—Na2 ^v	125.86 (3)	Sc1 ^{xiv} —Na1—Na2 ^{xv}	107.38 (2)
O1 ^v —Sc1—Na2 ^v	54.14 (3)	Sc1—Na1—Na2 ^{xv}	72.62 (2)
Na1 ^{vi} —Sc1—Na2 ^v	64.735 (14)	Na2 ^{vii} —Na1—Na2 ^{xv}	180.0
Na1—Sc1—Na2 ^v	115.265 (14)	O1—Na1—B1 ^{xiii}	84.60 (4)
Na2 ^{iv} —Sc1—Na2 ^v	72.919 (18)	O1 ^{xi} —Na1—B1 ^{xiii}	95.40 (4)
Na2 ⁱⁱⁱ —Sc1—Na2 ^v	107.081 (18)	O3 ^{iv} —Na1—B1 ^{xiii}	87.18 (4)
O2 ⁱ —Sc1—Na2	131.82 (3)	O3 ^{xii} —Na1—B1 ^{xiii}	92.82 (4)
O2 ⁱⁱ —Sc1—Na2	48.18 (3)	O2 ^{xiii} —Na1—B1 ^{xiii}	26.03 (4)
O3 ⁱⁱⁱ —Sc1—Na2	63.12 (4)	O2 ⁱⁱ —Na1—B1 ^{xiii}	153.97 (4)
O3 ^{iv} —Sc1—Na2	116.88 (4)	Sc1 ^{xiv} —Na1—B1 ^{xiii}	69.47 (3)
O1—Sc1—Na2	54.14 (3)	Sc1—Na1—B1 ^{xiii}	110.53 (3)
O1 ^v —Sc1—Na2	125.86 (3)	Na2 ^{vii} —Na1—B1 ^{xiii}	59.56 (4)
Na1 ^{vi} —Sc1—Na2	115.265 (14)	Na2 ^{xv} —Na1—B1 ^{xiii}	120.44 (4)
Na1—Sc1—Na2	64.735 (14)	O1—Na1—B1 ⁱⁱ	95.40 (4)
Na2 ^{iv} —Sc1—Na2	107.081 (18)	O1 ^{xi} —Na1—B1 ⁱⁱ	84.60 (4)

Na2 ⁱⁱⁱ —Sc1—Na2	72.919 (18)	O3 ^{iv} —Na1—B1 ⁱⁱ	92.82 (4)
Na2 ^v —Sc1—Na2	180.00 (2)	O3 ^{xii} —Na1—B1 ⁱⁱ	87.18 (4)
B1—O1—Sc1	122.92 (9)	O2 ^{xiii} —Na1—B1 ⁱⁱ	153.97 (4)
B1—O1—Na1	152.05 (9)	O2 ⁱⁱ —Na1—B1 ⁱⁱ	26.03 (4)
Sc1—O1—Na1	83.62 (4)	Sc1 ^{xiv} —Na1—B1 ⁱⁱ	110.53 (3)
B1—O1—Na2 ^{iv}	98.70 (8)	Sc1—Na1—B1 ⁱⁱ	69.47 (3)
Sc1—O1—Na2 ^{iv}	84.07 (4)	Na2 ^{vii} —Na1—B1 ⁱⁱ	120.44 (4)
Na1—O1—Na2 ^{iv}	92.19 (4)	Na2 ^{xv} —Na1—B1 ⁱⁱ	59.56 (4)
B1—O1—Na2	88.93 (8)	B1 ^{xiii} —Na1—B1 ⁱⁱ	180.0
Sc1—O1—Na2	85.89 (4)	O2 ⁱⁱ —Na2—O1 ^x	165.38 (4)
Na1—O1—Na2	84.11 (4)	O2 ⁱⁱ —Na2—O3 ⁱⁱ	56.90 (4)
Na2 ^{iv} —O1—Na2	169.63 (5)	O1 ^x —Na2—O3 ⁱⁱ	117.78 (4)
B1—O1—Na2 ^{vii}	81.85 (8)	O2 ⁱⁱ —Na2—O2 ^{xii}	119.08 (4)
Sc1—O1—Na2 ^{vii}	154.03 (5)	O1 ^x —Na2—O2 ^{xii}	74.02 (4)
Na1—O1—Na2 ^{vii}	70.81 (4)	O3 ⁱⁱ —Na2—O2 ^{xii}	97.40 (4)
Na2 ^{iv} —O1—Na2 ^{vii}	100.94 (4)	O2 ⁱⁱ —Na2—O3	120.74 (4)
Na2—O1—Na2 ^{vii}	87.01 (4)	O1 ^x —Na2—O3	68.37 (4)
B1—O2—Sc1 ^{viii}	173.15 (9)	O3 ⁱⁱ —Na2—O3	164.30 (6)
B1—O2—Na1 ^{viii}	102.22 (8)	O2 ^{xii} —Na2—O3	69.69 (4)
Sc1 ^{viii} —O2—Na1 ^{viii}	82.05 (4)	O2 ⁱⁱ —Na2—O1	67.85 (4)
B1—O2—Na2 ^{viii}	92.64 (8)	O1 ^x —Na2—O1	121.70 (2)
Sc1 ^{viii} —O2—Na2 ^{viii}	92.96 (4)	O3 ⁱⁱ —Na2—O1	119.33 (4)
Na1 ^{viii} —O2—Na2 ^{viii}	86.77 (4)	O2 ^{xii} —Na2—O1	88.09 (4)
B1—O2—Na2 ^{ix}	92.69 (8)	O3—Na2—O1	53.44 (3)
Sc1 ^{viii} —O2—Na2 ^{ix}	82.63 (4)	O2 ⁱⁱ —Na2—O2 ^x	121.86 (2)
Na1 ^{viii} —O2—Na2 ^{ix}	164.22 (5)	O1 ^x —Na2—O2 ^x	53.00 (4)
Na2 ^{viii} —O2—Na2 ^{ix}	97.81 (4)	O3 ⁱⁱ —Na2—O2 ^x	65.40 (4)
B1—O2—Na2 ^{iv}	84.56 (8)	O2 ^{xii} —Na2—O2 ^x	72.99 (4)
Sc1 ^{viii} —O2—Na2 ^{iv}	92.00 (4)	O3—Na2—O2 ^x	116.64 (4)
Na1 ^{viii} —O2—Na2 ^{iv}	69.81 (3)	O1—Na2—O2 ^x	161.07 (4)
Na2 ^{viii} —O2—Na2 ^{iv}	155.11 (4)	O2 ⁱⁱ —Na2—O1 ⁱⁱⁱ	86.99 (4)
Na2 ^{ix} —O2—Na2 ^{iv}	107.01 (4)	O1 ^x —Na2—O1 ⁱⁱⁱ	79.06 (4)
B1—O3—Sc1 ^x	154.28 (10)	O3 ⁱⁱ —Na2—O1 ⁱⁱⁱ	88.51 (4)
B1—O3—Na1 ^x	120.79 (9)	O2 ^{xii} —Na2—O1 ⁱⁱⁱ	152.06 (5)
Sc1 ^x —O3—Na1 ^x	83.98 (4)	O3—Na2—O1 ⁱⁱⁱ	107.09 (4)
B1—O3—Na2 ^{viii}	91.07 (8)	O1—Na2—O1 ⁱⁱⁱ	112.77 (4)
Sc1 ^x —O3—Na2 ^{viii}	102.13 (4)	O2 ^x —Na2—O1 ⁱⁱⁱ	84.99 (4)
Na1 ^x —O3—Na2 ^{viii}	77.11 (4)	O2 ⁱⁱ —Na2—B1 ⁱⁱ	28.43 (4)
B1—O3—Na2	91.39 (8)	O1 ^x —Na2—B1 ⁱⁱ	145.72 (5)
Sc1 ^x —O3—Na2	81.85 (4)	O3 ⁱⁱ —Na2—B1 ⁱⁱ	28.67 (4)
Na1 ^x —O3—Na2	88.33 (4)	O2 ^{xii} —Na2—B1 ⁱⁱ	108.19 (5)
Na2 ^{viii} —O3—Na2	164.30 (6)	O3—Na2—B1 ⁱⁱ	145.52 (5)
B1—O3—Na2 ^{vii}	75.88 (8)	O1—Na2—B1 ⁱⁱ	92.52 (5)
Sc1 ^x —O3—Na2 ^{vii}	78.82 (4)	O2 ^x —Na2—B1 ⁱⁱ	94.05 (4)
Na1 ^x —O3—Na2 ^{vii}	162.26 (5)	O1 ⁱⁱⁱ —Na2—B1 ⁱⁱ	89.96 (4)
Na2 ^{viii} —O3—Na2 ^{vii}	110.62 (5)	O2 ⁱⁱ —Na2—B1 ⁱⁱⁱ	85.97 (4)
Na2—O3—Na2 ^{vii}	85.01 (4)	O1 ^x —Na2—B1 ⁱⁱⁱ	83.59 (4)
O2—B1—O1	121.35 (13)	O3 ⁱⁱ —Na2—B1 ⁱⁱⁱ	110.22 (5)

O2—B1—O3	118.55 (12)	O2 ^{xii} —Na2—B1 ⁱⁱⁱ	150.41 (4)
O1—B1—O3	120.10 (12)	O3—Na2—B1 ⁱⁱⁱ	84.32 (5)
O2—B1—Na2 ^{viii}	58.93 (7)	O1—Na2—B1 ⁱⁱⁱ	87.48 (4)
O1—B1—Na2 ^{viii}	171.39 (10)	O2 ^x —Na2—B1 ⁱⁱⁱ	108.55 (4)
O3—B1—Na2 ^{viii}	60.25 (7)	O1 ⁱⁱⁱ —Na2—B1 ⁱⁱⁱ	27.14 (4)
O2—B1—Na2 ^{vii}	122.23 (9)	B1 ⁱⁱ —Na2—B1 ⁱⁱⁱ	101.22 (5)
O1—B1—Na2 ^{vii}	71.01 (8)	O2 ⁱⁱ —Na2—B1 ^{xii}	95.39 (4)
O3—B1—Na2 ^{vii}	77.48 (8)	O1 ^x —Na2—B1 ^{xii}	95.47 (4)
Na2 ^{viii} —B1—Na2 ^{vii}	101.32 (5)	O3 ⁱⁱ —Na2—B1 ^{xii}	72.47 (5)
O2—B1—Na2 ^{ix}	60.05 (7)	O2 ^{xii} —Na2—B1 ^{xii}	27.26 (4)
O1—B1—Na2 ^{ix}	106.68 (9)	O3—Na2—B1 ^{xii}	92.97 (5)
O3—B1—Na2 ^{ix}	102.82 (9)	O1—Na2—B1 ^{xii}	90.87 (4)
Na2 ^{viii} —B1—Na2 ^{ix}	81.08 (5)	O2 ^x —Na2—B1 ^{xii}	72.71 (4)
Na2 ^{vii} —B1—Na2 ^{ix}	177.30 (6)	O1 ⁱⁱⁱ —Na2—B1 ^{xii}	155.12 (4)
O2—B1—Na2	158.47 (10)	B1 ⁱⁱ —Na2—B1 ^{xii}	80.99 (5)
O1—B1—Na2	63.72 (7)	B1 ⁱⁱⁱ —Na2—B1 ^{xii}	177.30 (6)
O3—B1—Na2	61.17 (7)	O2 ⁱⁱ —Na2—B1	93.37 (5)
Na2 ^{viii} —B1—Na2	119.59 (6)	O1 ^x —Na2—B1	94.69 (4)
Na2 ^{vii} —B1—Na2	79.25 (4)	O3 ⁱⁱ —Na2—B1	146.62 (5)
Na2 ^{ix} —B1—Na2	98.50 (5)	O2 ^{xii} —Na2—B1	83.59 (4)
O2—B1—Na2 ^{iv}	68.63 (8)	O3—Na2—B1	27.44 (4)
O1—B1—Na2 ^{iv}	54.58 (7)	O1—Na2—B1	27.35 (4)
O3—B1—Na2 ^{iv}	164.17 (10)	O2 ^x —Na2—B1	143.91 (4)
Na2 ^{viii} —B1—Na2 ^{iv}	122.42 (5)	O1 ⁱⁱⁱ —Na2—B1	106.18 (4)
Na2 ^{vii} —B1—Na2 ^{iv}	86.79 (4)	B1 ⁱⁱ —Na2—B1	119.59 (6)
Na2 ^{ix} —B1—Na2 ^{iv}	92.97 (5)	B1 ⁱⁱⁱ —Na2—B1	79.16 (5)
Na2—B1—Na2 ^{iv}	117.94 (5)	B1 ^{xii} —Na2—B1	98.41 (5)
O2—B1—Na1 ^{viii}	51.75 (7)		

Symmetry codes: (i) $-x, -y, -z$; (ii) $x+1, y, z$; (iii) $x, -y+1/2, z-1/2$; (iv) $-x+1, y-1/2, -z+1/2$; (v) $-x+1, -y, -z$; (vi) $x-1, y, z-1$; (vii) $x, -y+1/2, z+1/2$; (viii) $x-1, y, z$; (ix) $x-1, -y+1/2, z-1/2$; (x) $-x+1, y+1/2, -z+1/2$; (xi) $-x+2, -y, -z+1$; (xii) $x+1, -y+1/2, z+1/2$; (xiii) $-x+1, -y, -z+1$; (xiv) $x+1, y, z+1$; (xv) $-x+2, y-1/2, -z+1/2$.