

NASICON-related $\text{Na}_{3.4}\text{Mn}_{0.4}\text{Fe}_{1.6}(\text{PO}_4)_3$

Michael M. Yatskin,^{a*} Nataliya Yu. Strutynska,^a
Vyacheslav N. Baumer,^b Ivan V. Ogorodnyk^a and
Nikolay S. Slobodyanik^a

^aDepartment of Inorganic Chemistry, Taras Shevchenko National University, 64 Volodymyrska str., 01601 Kyiv, Ukraine, and ^bSTC "Institute for Single Crystals", NAS of Ukraine, 60 Lenin ave., 61001 Kharkiv, Ukraine
Correspondence e-mail: yats_13@ukr.net

Received 31 May 2012; accepted 18 June 2012

Key indicators: single-crystal X-ray study; $T = 293$ K; mean $\sigma(\text{P}-\text{O}) = 0.002$ Å; disorder in main residue; R factor = 0.028; wR factor = 0.072; data-to-parameter ratio = 19.2.

The solid solution, sodium [iron(III)/manganese(II)] tris-(orthophosphate), $\text{Na}_{3.4}\text{Mn}_{0.4}\text{Fe}_{1.6}(\text{PO}_4)_3$, was obtained using a flux method. Its crystal structure is related to that of NASICON-type compounds. The $[(\text{Mn}/\text{Fe})_2(\text{PO}_4)_3]$ framework is built up from an $(\text{Mn}/\text{Fe})\text{O}_6$ octahedron (site symmetry $\bar{3}$), with a mixed Mn/Fe occupancy, and a PO_4 tetrahedron (site symmetry $\bar{2}$). The Na^+ cations are distributed over two partially occupied sites in the cavities of the framework. One Na^+ cation (site symmetry $\bar{3}$) is surrounded by six O atoms, whereas the other Na^+ cation (site symmetry $\bar{2}$) is surrounded by eight O atoms.

Related literature

For applications and properties of NASICON-related compounds, see: Goodenough *et al.* (1976); Shimizu & Ushijima (2000); Verissimo *et al.* (1997); Mariappan *et al.* (2005); Arbi *et al.* (2002); Moreno-Real *et al.* (2002). For details of structural relationships with other compounds, see: γ - $\text{Na}_3\text{Fe}_2(\text{PO}_4)_3$ (Masquelier *et al.*, 2000); $\text{Na}_4\text{Fe}_2(\text{PO}_4)_3$ (Hatert, 2009); $\text{Na}_4\text{MgFe}(\text{PO}_4)_3$ (Strutynska *et al.*, 2012); $\text{Na}_4\text{NiFe}(\text{PO}_4)_3$ (Essehli *et al.*, 2011).

Experimental

Crystal data

$\text{Na}_{3.4}\text{Mn}_{0.4}\text{Fe}_{1.6}(\text{PO}_4)_3$	$Z = 6$
$M_r = 474.41$	Mo $K\alpha$ radiation
Trigonal, $R\bar{3}c$	$\mu = 3.59$ mm ⁻¹
$a = 8.8694$ (2) Å	$T = 293$ K
$c = 21.6074$ (7) Å	$0.10 \times 0.10 \times 0.08$ mm
$V = 1472.05$ (7) Å ³	

Data collection

Oxford Diffraction Xcalibur-3 diffractometer	8867 measured reflections
Absorption correction: multi-scan (Blessing, 1995)	728 independent reflections
$T_{\min} = 0.721$, $T_{\max} = 0.795$	658 reflections with $I > 2\sigma(I)$
	$R_{\text{int}} = 0.033$

Refinement

$R[F^2 > 2\sigma(F^2)] = 0.028$	38 parameters
$wR(F^2) = 0.072$	2 restraints
$S = 1.23$	$\Delta\rho_{\max} = 0.66$ e Å ⁻³
728 reflections	$\Delta\rho_{\min} = -0.39$ e Å ⁻³

Table 1

Selected bond lengths (Å).

Na1—O2	2.4546 (15)	Fe1—O1	1.9962 (16)
Na2—O2 ⁱ	2.4505 (16)	Fe1—O2	2.1053 (15)
Na2—O2 ⁱⁱ	2.472 (2)	P1—O1	1.5244 (16)
Na2—O1 ⁱ	2.587 (2)	P1—O2 ⁱⁱ	1.5346 (15)
Na2—O1 ⁱⁱⁱ	2.921 (2)		

Symmetry codes: (i) $y + \frac{2}{3}, -x + y + \frac{1}{3}, -z + \frac{1}{3}$; (ii) $-x + y + \frac{1}{3}, y - \frac{1}{3}, z + \frac{1}{6}$; (iii) $y + 1, x, -z + \frac{1}{2}$.

Data collection: *CrysAlis CCD* (Oxford Diffraction, 2006); cell refinement: *CrysAlis CCD*; data reduction: *CrysAlis RED* (Oxford Diffraction, 2006); program(s) used to solve structure: *SHELXS97* (Sheldrick, 2008); program(s) used to refine structure: *SHELXL97* (Sheldrick, 2008); molecular graphics: *DIAMOND* (Brandenburg, 1999); software used to prepare material for publication: *WinGX* (Farrugia, 1999) and *enCIFer* (Allen *et al.*, 2004).

The authors are grateful to Dr. Igor V. Zlatovskiy from Department of Inorganic Chemistry, Taras Shevchenko National University, Kiev, Ukraine, for valuable comments and support.

Supplementary data and figures for this paper are available from the IUCr electronic archives (Reference: WM2642).

References

- Allen, F. H., Johnson, O., Shields, G. P., Smith, B. R. & Towler, M. (2004). *J. Appl. Cryst.* **37**, 335–338.
- Arbi, K., Mandal, S., Rojo, J. M. & Sanz, J. (2002). *Chem. Mater.* **14**, 1091–1097.
- Blessing, R. H. (1995). *Acta Cryst.* **A51**, 33–38.
- Brandenburg, K. (1999). *DIAMOND*. University of Bonn, Germany.
- Essehli, R., Bali, B. E., Benmokhtar, S., Bouziane, K., Manoun, B., Abdalslam, M. A. & Ehrenberg, H. (2011). *J. Alloys Compd.* **509**, 1163–1171.
- Farrugia, L. J. (1999). *J. Appl. Cryst.* **32**, 837–838.
- Goodenough, J. B., Hong, H. Y. P. & Kafalas, J. A. (1976). *Mater. Res. Bull.* **11**, 203–220.
- Hatert, F. (2009). *Acta Cryst.* **E65**, i30.
- Mariappan, C. R., Govindaraj, G. & Roling, B. (2005). *Solid State Ionics*, **176**, 723–729.
- Masquelier, C., Wurm, C., Rodríguez-Carvajal, J., Gaubicher, J. & Nazar, L. (2000). *Chem. Mater.* **12**, 525–532.
- Moreno-Real, L., Maldonado-Manso, P., Leon-Reina, L., Losilla, E. R., Mouahid, F. E., Zahir, M. & Sanz, J. (2002). *J. Mater. Chem.* **12**, 3681–3687.
- Oxford Diffraction (2006). *CrysAlis CCD* and *CrysAlis RED*. Oxford Diffraction Ltd, Abingdon, England.
- Sheldrick, G. M. (2008). *Acta Cryst.* **A64**, 112–122.
- Shimizu, Y. & Ushijima, T. (2000). *Solid State Ionics*, **132**, 143–148.
- Strutynska, N. Yu., Zlatovskiy, I. V., Yatskin, M. M., Slobodyanik, N. S. & Ogorodnyk, I. V. (2012). *Inorg. Mater.* **48**, 402–406.
- Verissimo, C., Garrido, F. M. S., Alves, O. L., Calle, P., Martínez-Juárez, A., Iglesias, J. E. & Rojo, J. M. (1997). *Solid State Ionics*, **100**, 127–134.

supporting information

Acta Cryst. (2012). E68, i55 [https://doi.org/10.1107/S1600536812027584]

NASICON-related $\text{Na}_{3.4}\text{Mn}_{0.4}\text{Fe}_{1.6}(\text{PO}_4)_3$

Michael M. Yatskin, Nataliya Yu. Strutynska, Vyacheslav N. Baumer, Ivan V. Ogorodnyk and Nikolay S. Slobodyanik

S1. Comment

NASICON-type compounds possess high ionic conductivity, chemical stability and attract great interest for application in solid-state electrochemical devices (Goodenough *et al.*, 1976; Shimizu & Ushijima, 2000; Verissimo *et al.*, 1997; Mariappan *et al.*, 2005; Arbi *et al.*, 2002; Moreno-Real *et al.*, 2002).

Herein, the structure of $\text{Na}_{3.4}\text{Mn}_{0.4}\text{Fe}_{1.6}(\text{PO}_4)_3$, (I), is reported. Compound (I) can be considered as a solid solution of $\gamma\text{-Na}_3\text{Fe}_2(\text{PO}_4)_3$ (Masquelier *et al.*, 2000) and belongs to the NASICON structure type.

There are two Na sites (Wyckoff positions *6b* and *18e*), one mixed occupied Mn/Fe site (*12c*), one P site (*18e*) and two O sites (*36f*) in the asymmetric unit of (I) (Fig. 1). The basic building block of the structure is the $[(\text{Mn}/\text{Fe})_2(\text{PO}_4)_3]$ unit, which consists of two $(\text{Mn}/\text{Fe})\text{O}_6$ polyhedra interlinked by three bridging PO_4 -tetrahedra (Fig. 2). These fragments alternate with NaIO_6 -polyhedra along $[001]$ forming ribbons, which in turn are interconnected by PO_4 -tetrahedra forming a three-dimensional framework (Fig. 2). The distances $M\text{—O}$ in the $(\text{Mn}/\text{Fe})\text{O}_6$ octahedra vary from 1.9962 (16) to 2.1053 (15) Å and are similar to that in isotypic structures (*e.g.* 1.956 (2)–2.048 (2) Å in $\gamma\text{-Na}_3\text{Fe}_2(\text{PO}_4)_3$ (Masquelier *et al.*, 2000); 2.010 (6)–2.130 (6) Å in $\text{Na}_4\text{Fe}_2(\text{PO}_4)_3$ (Hatert, 2009); 1.926 (5)–2.037 (6) Å in $\text{Na}_4\text{MgFe}(\text{PO}_4)_3$ (Strutynska *et al.*, 2012); 1.955 (3)–2.050 (3) Å in $\text{Na}_4\text{NiFe}(\text{PO}_4)_3$ (Essehli *et al.*, 2011)). The P atom has an almost regular tetrahedral coordination, the P—O distances in the PO_4 tetrahedra being in the range 1.5244 (16)–1.5346 (15) Å, as is typically observed in NASICON-type phosphates. Two types of sodium atoms occupy the cavities of the framework. The Na1 atoms (s.o.f. = 0.848 (5)) lie on a threefold roto-inversion axis and are surrounded by six O2 atoms in a distance of 2.4546 (15) Å. The Na2 (s.o.f. = 0.853 (5)) coordination environment is formed by eight oxygen atoms with four pairs of equal contacts ($d(\text{Na}2\text{—O}) = 2.4505$ (16)– 2.921 (2) Å, using a cut-off distance of 3.1 Å).

S2. Experimental

The title compound was obtained during investigation of the melting system $\text{Na}_2\text{O—P}_2\text{O}_5\text{—Fe}_2\text{O}_3\text{—MnO}$. A mixture of NaPO_3 (12.24 g), Na_2CO_3 (1.908 g), Fe_2O_3 (2.4 g) and $\text{MnCO}_3\text{Mn}(\text{OH})_2$ (3.8 g) was ground in an agate mortar, placed in a platinum crucible and heated up to 1273 K. The melt was kept at this temperature for 3 h. After that, the temperature was cooled down to 973 K at a rate of 10 K/h. The light-violet crystals of (I) were recovered using hot water. The chemical composition of single-crystal was verified using EDX analysis. Analysis found: Na 16.62, Mn 2.14, Fe 7.93, P 14.94 and O 58.37 at%, while $\text{Na}_{3.4}\text{Mn}_{0.4}\text{Fe}_{1.6}(\text{PO}_4)_3$ requires Na 16.67, Mn 1.96, Fe 7.84, P 14.70 and O 58.82 at%.

S3. Refinement

For refinement of the Fe/Mn ratio and the Na-content, SUMP instructions in *SHELXL* (Sheldrick, 2008) were employed, assuming full occupancy of the (Fe/Mn) site and an average charge of the (Fe/Mn) and Na sites of +9. The refined composition is close to that determined by EDX measurements. The highest remaining peak in the final difference

Fourier map is 0.76 Å from P1 and the deepest hole is 1.09 Å from the same atom.

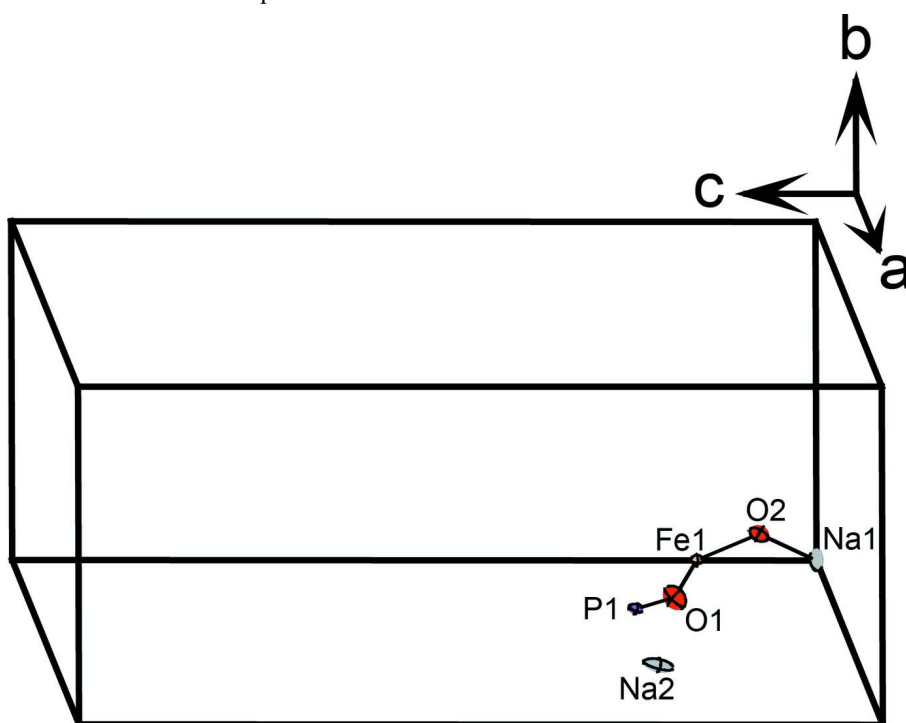


Figure 1

The asymmetric unit of (I), showing displacement ellipsoids at the 50% probability level.

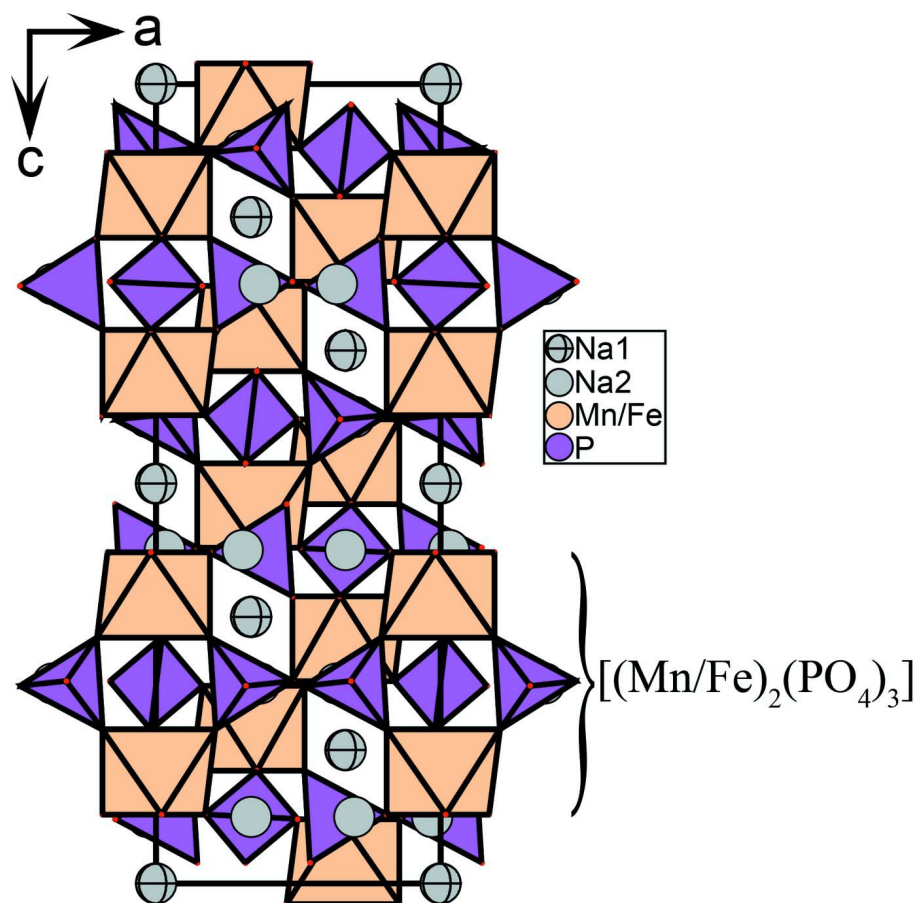


Figure 2

Elementary fragments and three-dimensional framework in the title compound.

[iron(III)/manganese(II)] tris(orthophosphate)

Crystal data

$\text{Na}_{3.4}\text{Mn}_{0.4}\text{Fe}_{1.6}(\text{PO}_4)_3$

$M_r = 474.41$

Trigonal, $R\bar{3}c$

Hall symbol: $-\text{R } 3\ 2''\ c$

$a = 8.8694\ (2)\ \text{\AA}$

$c = 21.6074\ (7)\ \text{\AA}$

$V = 1472.05\ (7)\ \text{\AA}^3$

$Z = 6$

$F(000) = 1380$

$D_x = 3.212\ \text{Mg m}^{-3}$

Mo $K\alpha$ radiation, $\lambda = 0.71073\ \text{\AA}$

Cell parameters from 8867 reflections

$\theta = 3.3\text{--}35.0^\circ$

$\mu = 3.59\ \text{mm}^{-1}$

$T = 293\ \text{K}$

Prism, light-violet

$0.10 \times 0.10 \times 0.08\ \text{mm}$

Data collection

Oxford Diffraction Xcalibur-3
diffractometer

Radiation source: fine-focus sealed tube

Graphite monochromator

φ and ω scans

Absorption correction: multi-scan
(Blessing, 1995)

$T_{\min} = 0.721$, $T_{\max} = 0.795$

8867 measured reflections

728 independent reflections

658 reflections with $I > 2\sigma(I)$

$R_{\text{int}} = 0.033$

$\theta_{\max} = 35.0^\circ$, $\theta_{\min} = 3.3^\circ$

$h = -14 \rightarrow 14$

$k = -13 \rightarrow 14$

$l = -34 \rightarrow 34$

Refinement

Refinement on F^2
 Least-squares matrix: full
 $R[F^2 > 2\sigma(F^2)] = 0.028$
 $wR(F^2) = 0.072$
 $S = 1.23$
 728 reflections
 38 parameters
 2 restraints

Primary atom site location: structure-invariant
 direct methods
 Secondary atom site location: difference Fourier
 map
 $w = 1/[\sigma^2(F_o^2) + (0.0324P)^2 + 3.4282P]$
 where $P = (F_o^2 + 2F_c^2)/3$
 $(\Delta/\sigma)_{\max} = 0.064$
 $\Delta\rho_{\max} = 0.66 \text{ e } \text{\AA}^{-3}$
 $\Delta\rho_{\min} = -0.39 \text{ e } \text{\AA}^{-3}$

Special details

Geometry. All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

Refinement. Refinement of F^2 against ALL reflections. The weighted R -factor wR and goodness of fit S are based on F^2 , conventional R -factors R are based on F , with F set to zero for negative F^2 . The threshold expression of $F^2 > \sigma(F^2)$ is used only for calculating R -factors(gt) *etc.* and is not relevant to the choice of reflections for refinement. R -factors based on F^2 are statistically about twice as large as those based on F , and R -factors based on ALL data will be even larger.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	<i>x</i>	<i>y</i>	<i>z</i>	$U_{\text{iso}}^*/U_{\text{eq}}$	Occ. (<1)
Na1	0	0	0	0.0322 (8)	0.848 (5)
Na2	0.63677 (18)	0	0.25	0.0356 (6)	0.853 (5)
Fe1	0	0	0.149480 (18)	0.01045 (11)	0.7991 (12)
Mn1	0	0	0.149480 (18)	0.01045 (11)	0.2009 (12)
P1	0.29637 (7)	0	0.25	0.01144 (13)	
O1	0.1887 (2)	-0.0197 (3)	0.19242 (8)	0.0346 (4)	
O2	0.18883 (19)	0.17055 (18)	0.08615 (7)	0.0214 (3)	

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Na1	0.0421 (11)	0.0421 (11)	0.0124 (10)	0.0211 (6)	0	0
Na2	0.0206 (6)	0.0151 (7)	0.0694 (14)	0.0075 (3)	0.0068 (4)	0.0136 (7)
Fe1	0.01042 (13)	0.01042 (13)	0.01049 (17)	0.00521 (7)	0	0
Mn1	0.01042 (13)	0.01042 (13)	0.01049 (17)	0.00521 (7)	0	0
P1	0.01059 (19)	0.0092 (2)	0.0141 (2)	0.00459 (12)	0.00093 (9)	0.00185 (18)
O1	0.0270 (8)	0.0404 (10)	0.0327 (8)	0.0142 (7)	-0.0155 (7)	0.0016 (7)
O2	0.0157 (6)	0.0139 (6)	0.0274 (7)	0.0021 (5)	-0.0002 (5)	0.0021 (5)

Geometric parameters (\AA , $^\circ$)

Na1—O2 ⁱ	2.4546 (15)	Na2—O1 ^x	2.921 (2)
Na1—O2	2.4546 (15)	Na2—O1 ^{xi}	2.921 (2)
Na1—O2 ⁱⁱ	2.4546 (15)	Fe1—O1 ⁱⁱ	1.9962 (16)
Na1—O2 ⁱⁱⁱ	2.4546 (15)	Fe1—O1 ⁱⁱⁱ	1.9962 (16)
Na1—O2 ^{iv}	2.4546 (15)	Fe1—O1	1.9962 (16)

Na1—O2 ^v	2.4546 (15)	Fe1—O2 ⁱⁱ	2.1053 (15)
Na2—O2 ^{vi}	2.4505 (16)	Fe1—O2 ⁱⁱⁱ	2.1053 (15)
Na2—O2 ^{vii}	2.4505 (16)	Fe1—O2	2.1053 (15)
Na2—O2 ^{viii}	2.472 (2)	P1—O1	1.5244 (16)
Na2—O2 ^{ix}	2.472 (2)	P1—O1 ^{xii}	1.5244 (16)
Na2—O1 ^{vii}	2.587 (2)	P1—O2 ^{ix}	1.5346 (15)
Na2—O1 ^{vi}	2.587 (2)	P1—O2 ^{viii}	1.5346 (15)
O2 ⁱ —Na1—O2	180.00 (5)	O1 ^{vii} —Na2—O1 ^{xi}	109.85 (7)
O2 ⁱ —Na1—O2 ⁱⁱ	111.27 (5)	O1 ^{vi} —Na2—O1 ^{xi}	86.08 (4)
O2—Na1—O2 ⁱⁱ	68.73 (5)	O1 ^x —Na2—O1 ^{xi}	81.67 (9)
O2 ⁱ —Na1—O2 ⁱⁱⁱ	111.27 (5)	O1 ⁱⁱ —Fe1—O1 ⁱⁱⁱ	100.14 (7)
O2—Na1—O2 ⁱⁱⁱ	68.73 (5)	O1 ⁱⁱ —Fe1—O1	100.14 (7)
O2 ⁱⁱ —Na1—O2 ⁱⁱⁱ	68.73 (5)	O1 ⁱⁱⁱ —Fe1—O1	100.14 (7)
O2 ⁱ —Na1—O2 ^{iv}	68.73 (5)	O1 ⁱⁱ —Fe1—O2 ⁱⁱ	87.95 (7)
O2—Na1—O2 ^{iv}	111.27 (5)	O1 ⁱⁱⁱ —Fe1—O2 ⁱⁱ	167.15 (7)
O2 ⁱⁱ —Na1—O2 ^{iv}	111.27 (5)	O1—Fe1—O2 ⁱⁱ	88.10 (7)
O2 ⁱⁱⁱ —Na1—O2 ^{iv}	180.00 (8)	O1 ⁱⁱ —Fe1—O2 ⁱⁱⁱ	88.10 (7)
O2 ⁱ —Na1—O2 ^v	68.73 (5)	O1 ⁱⁱⁱ —Fe1—O2 ⁱⁱⁱ	87.95 (7)
O2—Na1—O2 ^v	111.27 (5)	O1—Fe1—O2 ⁱⁱⁱ	167.15 (7)
O2 ⁱⁱ —Na1—O2 ^v	180.00 (9)	O2 ⁱⁱ —Fe1—O2 ⁱⁱⁱ	82.32 (6)
O2 ⁱⁱⁱ —Na1—O2 ^v	111.27 (5)	O1 ⁱⁱ —Fe1—O2	167.15 (7)
O2 ^{iv} —Na1—O2 ^v	68.73 (5)	O1 ⁱⁱⁱ —Fe1—O2	88.10 (7)
O2 ^{vi} —Na2—O2 ^{vii}	162.12 (10)	O1—Fe1—O2	87.95 (7)
O2 ^{vi} —Na2—O2 ^{viii}	129.35 (6)	O2 ⁱⁱ —Fe1—O2	82.32 (6)
O2 ^{vii} —Na2—O2 ^{viii}	68.52 (7)	O2 ⁱⁱⁱ —Fe1—O2	82.32 (6)
O2 ^{vi} —Na2—O2 ^{ix}	68.52 (7)	O1—P1—O1 ^{xii}	110.62 (16)
O2 ^{vii} —Na2—O2 ^{ix}	129.35 (6)	O1—P1—O2 ^{ix}	112.19 (10)
O2 ^{viii} —Na2—O2 ^{ix}	60.85 (8)	O1 ^{xii} —P1—O2 ^{ix}	106.30 (9)
O2 ^{vi} —Na2—O1 ^{vii}	114.64 (5)	O1—P1—O2 ^{viii}	106.30 (9)
O2 ^{vii} —Na2—O1 ^{vii}	68.83 (5)	O1 ^{xii} —P1—O2 ^{viii}	112.19 (10)
O2 ^{viii} —Na2—O1 ^{vii}	68.62 (6)	O2 ^{ix} —P1—O2 ^{viii}	109.33 (12)
O2 ^{ix} —Na2—O1 ^{vii}	93.19 (7)	P1—O1—Fe1	150.92 (13)
O2 ^{vi} —Na2—O1 ^{vi}	68.83 (5)	P1—O1—Na2 ^{xiii}	120.86 (11)
O2 ^{vii} —Na2—O1 ^{vi}	114.64 (5)	Fe1—O1—Na2 ^{xiii}	86.63 (6)
O2 ^{viii} —Na2—O1 ^{vi}	93.19 (7)	P1—O1—Na2 ^{xiv}	76.78 (7)
O2 ^{ix} —Na2—O1 ^{vi}	68.62 (6)	Fe1—O1—Na2 ^{xiv}	102.77 (7)
O1 ^{vii} —Na2—O1 ^{vi}	159.36 (11)	Na2 ^{xiii} —O1—Na2 ^{xiv}	112.45 (8)
O2 ^{vi} —Na2—O1 ^x	53.35 (5)	P1 ^{ix} —O2—Fe1	141.73 (9)
O2 ^{vii} —Na2—O1 ^x	111.21 (7)	P1 ^{ix} —O2—Na2 ^{xiii}	93.51 (8)
O2 ^{viii} —Na2—O1 ^x	153.24 (6)	Fe1—O2—Na2 ^{xiii}	87.96 (6)
O2 ^{ix} —Na2—O1 ^x	114.32 (5)	P1 ^{ix} —O2—Na1	128.40 (8)
O1 ^{vii} —Na2—O1 ^x	86.07 (4)	Fe1—O2—Na1	89.86 (5)
O1 ^{vi} —Na2—O1 ^x	109.85 (7)	Na2 ^{xiii} —O2—Na1	86.38 (5)
O2 ^{vi} —Na2—O1 ^{xi}	111.22 (7)	P1 ^{ix} —O2—Na2 ^{ix}	94.91 (7)
O2 ^{vii} —Na2—O1 ^{xi}	53.35 (5)	Fe1—O2—Na2 ^{ix}	87.39 (6)

$O2^{viii}-Na2-O1^{xi}$	114.32 (5)	$Na2^{xiii}-O2-Na2^{ix}$	171.00 (7)
$O2^{ix}-Na2-O1^{xi}$	153.24 (6)	$Na1-O2-Na2^{ix}$	85.91 (5)

Symmetry codes: (i) $-x, -y, -z$; (ii) $-x+y, -x, z$; (iii) $-y, x-y, z$; (iv) $y, -x+y, -z$; (v) $x-y, x, -z$; (vi) $y+2/3, -x+y+1/3, -z+1/3$; (vii) $x+1/3, x-y-1/3, z+1/6$; (viii) $-x+y+1/3, y-1/3, z+1/6$; (ix) $-x+2/3, -y+1/3, -z+1/3$; (x) $y+1, x, -z+1/2$; (xi) $-x+y+1, -x, z$; (xii) $x-y, -y, -z+1/2$; (xiii) $x-y-1/3, x-2/3, -z+1/3$; (xiv) $-y, x-y-1, z$.